

Mesoporous bioactive glasses (MBGs) in cancer therapy: Full of hope and promise

Original

Mesoporous bioactive glasses (MBGs) in cancer therapy: Full of hope and promise / Kargozar, S.; Mozafari, M.; Hamzehlou, S.; Kim, H. -W.; Baino, F.. - In: MATERIALS LETTERS. - ISSN 0167-577X. - ELETTRONICO. - 251:(2019), pp. 241-246. [10.1016/j.matlet.2019.05.019]

Availability:

This version is available at: 11583/2743281 since: 2019-07-24T10:19:17Z

Publisher:

Elsevier B.V.

Published

DOI:10.1016/j.matlet.2019.05.019

Terms of use:

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

Publisher copyright

Elsevier postprint/Author's Accepted Manuscript

© 2019. This manuscript version is made available under the CC-BY-NC-ND 4.0 license
<http://creativecommons.org/licenses/by-nc-nd/4.0/>. The final authenticated version is available online at:
<http://dx.doi.org/10.1016/j.matlet.2019.05.019>

(Article begins on next page)

Mesoporous Bioactive Glasses (MBGs) in Cancer Therapy: Full of Hope and Promise

Saeid Kargozar^{1,*}, Masoud Mozafari^{2,3,4}, Sepideh Hamzehlou⁵, Hae-Won Kim^{6,7,8}, Francesco Baino^{9,*}

1. Tissue Engineering Research Group (TERG), Department of Anatomy and Cell Biology, School of Medicine, Mashhad University of Medical Sciences, 917794-8564 Mashhad, Iran
2. Bioengineering Research Group, Nanotechnology and Advanced Materials Department, Materials and Energy Research Center (MERC), P.O. Box 4777-141 55, Tehran, Iran
3. Cellular and Molecular Research Center, Iran University of Medical Sciences, Tehran, Iran
4. Department of Tissue Engineering & Regenerative Medicine, Faculty of Advanced Technologies in Medicine, Iran University of Medical Sciences (IUMS), Tehran, Iran
5. Department of Medical Genetics, School of Medicine, Tehran University of Medical Sciences, 14155-6447 Tehran, Iran
6. Institute of Tissue Regeneration Engineering (ITREN), Dankook University, Cheonan, Republic of Korea
7. Department of Nanobiomedical Science & BK21 PLUS NBM Global Research Center for Regenerative Medicine, Dankook University, Cheonan, Republic of Korea
8. Department of Biomaterials Science, School of Dentistry, Dankook University, Cheonan, Republic of Korea
9. Institute of Materials Physics and Engineering, Applied Science and Technology Department, Politecnico di Torino, Corso Duca degli Abruzzi 24, 10129 Torino, Italy

* Correspondence: kargozarsaeid@gmail.com (S.K.); francesco.baino@polito.it (F.B.);

Tel.: +98-513-800-2343 (S.K.); +39-011-090-4668 (F.B.)

Abstract

Implementing novel approaches for cancer therapy are under continuous progress, and bioactive glasses (BGs) and glass-ceramics show excellent potential in this regard. Although these materials have been mostly used as magnetic substances in hyperthermia approach, some of their subsets, i.e., mesoporous bioactive glasses (MBGs), have been recently proposed not only as magnetic materials but also as drug delivery systems for advanced treatment of bone cancer. Different types of MBGs including granular particles and three-dimensional (3D) scaffolds can be applied for cancer therapy. Based on the results obtained from *in vitro* studies, MBGs seem to have a bright future in the therapeutic strategies to combat cancer; however, their application in this field is still in its beginning, and more research needs to reveal all pros and cons of this newly proposed approach.

Keywords: Biomaterials; Porous materials; Bioactive glasses; Magnetic materials; Cancer therapy; Drug delivery.

1- Introduction

Cancer is among the deadliest diseases of humans, and its prevalence is continuously increasing over the globe. Up to now, a few approaches have been proposed and used for treating cancerous tissues and specifically the metastases, such as chemotherapy, radiotherapy, and hyperthermia [1]. In comparison to the first two approaches, the use of hyperthermia, i.e., increasing the temperature above 40°C in the diseased site to kill the cancer cells, exhibits some merits such as the lack of using chemicals and hazardous radiations [2].

Magnetic bioactive glasses (BGs) belong to the bioceramics superfamily and have been recently proposed for cancer treatment (Figure 1) [3]. BGs were firstly developed for the repair and regeneration of bone defects [4-8] and then, interestingly, were gradually found useful in contact with soft tissues, too (e.g., healing of skin wounds, muscle and nerve repair, cardiac tissue engineering) [9-13]. After being exposed to an external alternating magnetic field, a magnetic BG can act as an anticancer substance via the hyperthermic effect and exhibits a bone regenerative capability, thus eliciting a multifunctional action. Bioactivity is also useful to reduce the risk of material displacement (through bone-bonding) when the glass is implanted in the diseased bone [14]. Stimulation of apoptotic pathways in cancer cells by using some specific formulations of BGs (e.g., vanadium- or lanthanum-doped silicate glasses) has also been reported [15, 16]. It is worth mentioning that some types of non-bioactive glasses are clinically being used for the treatment of specific cancers via a different therapeutic action: for example, ⁹⁰Y-doped SiO₂-Al₂O₃ radioactive glass insoluble microspheres, commercialized as Theresphere[®] (Nordion; Ottawa, Ontario, Canada), are systemically administrated for the treatment of unresectable hepatocellular carcinoma and metastatic colorectal cancer (mCRC) [17, 18].

More recently, the use of mesoporous bioactive glasses (MBGs) has also been proposed and applied in hyperthermia and photothermal therapy (PPT) for cancer treatment [19]. These materials, having a porous structure with a highly controllable arrangement and diameters (2 to 50 nm), are recognized as excellent platforms for anti-cancer drug loading and release [20, 21]. Moreover, it is feasible to incorporate some specific elements, for example iron (Fe), into the structure of MBGs to give them magnetic properties and thus improve their anti-tumor effects. As angiogenesis is crucial for the proliferation and metastatic spread of cancer cells, developing novel formulations of MBGs with the ability to suppress new blood vessel formation, regulated via releasing anti-angiogenic ions or delivering anti-angiogenic drugs and chemicals, could be of great importance for designing new therapeutic approaches against cancer.

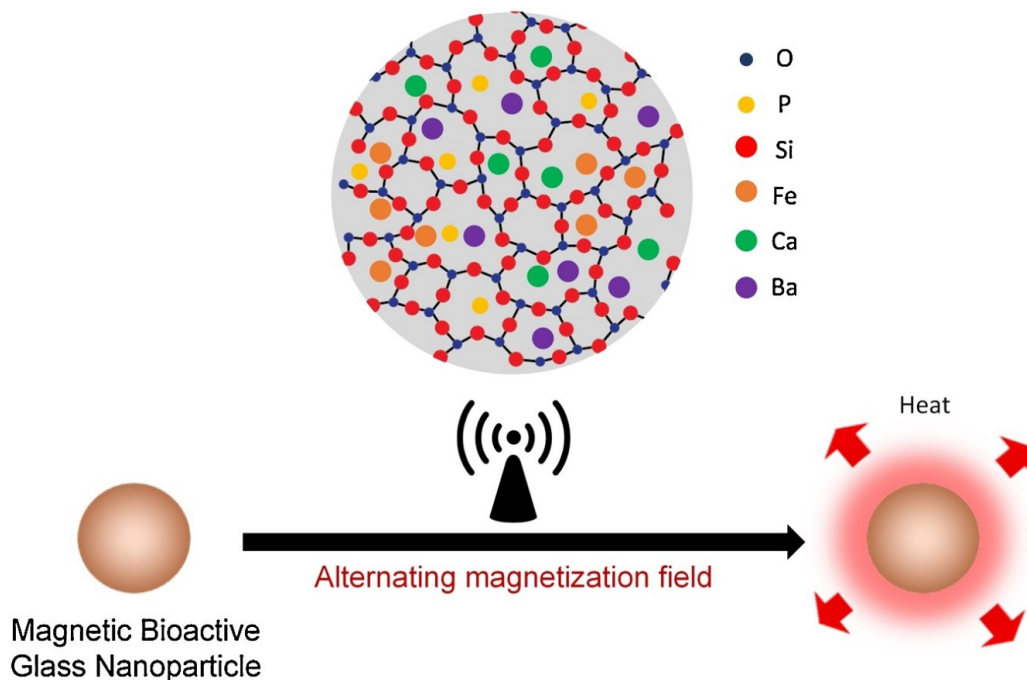


Figure 1. Schematic representation of magnetic BGs developed for hyperthermia therapy of cancer. Reproduced from [14].

The potential of glass-ceramics for cancer therapy has been recently reviewed by Miola et al. [22]; thus, the primary goal of the present study is to evaluate the applicability of MBGs in the treatment of cancer along with the challenges related to their use.

2. MBGs as vehicles for anticancer strategies

The sol-gel process caused a revolution in preparing a new generation of materials, i.e., mesoporous substances with a highly-ordered porous structure at the nanoscale. In 2004 and later in 2006, two scientific groups could take benefit of this technique along with the principles of supramolecular chemistry for developing MBGs for the first time [23, 24]. Since then, the ability of these materials for loading and releasing various drugs (e.g., anti-cancer agents) in a controlled and targeted manner has continuously attracted increasing interest [25]. Based on the current literature, it is apparent that MBGs, in the form of fine powders and scaffolds, are used to fill bone defects and cavities caused by cancers. Furthermore, the incorporation of MBGs into polymeric matrices to prepare composites is an additional strategy to expand the range of their applications [26-28]. The currently-proposed approaches for imparting anti-cancer activities to MBGs include loading of anti-tumor chemicals and drugs (e.g., Imatinib and doxorubicin) [29, 30], incorporation of anti-tumor transition metals (e.g., terbium) [31] into their structure, and the photothermal therapy (PTT) [32].

In regards to drug delivery, MBGs have been widely proved to be valuable release platforms in bone regenerative strategies, where they can elicit a multifunctional action (inherent excellent bioactivity and local therapeutic action of the drug) [33]. The same properties can be exploited in the context of bone cancer treatment to perform local chemotherapy. It has been shown that some

parameters can control the final output of this strategy, including the variation in the pH of the microenvironment, the initial concentration of the loaded drug, and the degradation rate of MBGs [30]. For instance, Shoaib et al. could successfully load an anti-cancer drug, imatinib, into MBGs at a concentration of 1 mg/mL with the efficiency of 77.59%. Their study showed that the release kinetics were indeed controlled by changing the pH (from 4.4 to 10.4) and the initial drug concentration (0.2 –1 mg/mL) so that the maximum cumulative imatinib release of 81% happened during 250 h at the pH of 4.4. In another study, Wang et al. reported doxorubicin-loaded terbium-containing MBGs as promising materials for the treatment of bone tissue lesions [31]. The experimental data clarified that the release of doxorubicin from the MBGs followed a Fickian diffusion mechanism according to the Higuchi model. Similar to the study carried out by Shoaib et al., the authors concluded that the delivery of the doxorubicin from MBGs could be controlled by changing pH and drug concentration.

Targeted therapy is one of the main goals of scientists working on cancer to reduce the side effects of drugs and to improve the efficient killing of tumor cells [34]. This strategy has been proposed for targeted drug delivery from MBGs: for example, Lin and coworkers functionalized the glass particles with folate groups, the receptors of which are highly overexpressed on the surface of the cells of many tumor types [35, 36].

The incorporation of anti-cancer metals into the glass structure is another clever approach to create anti-cancer properties. Some members of lanthanides (e.g., terbium (Tb) and holmium (Ho)) have been recognized as radiopharmaceuticals and are currently used for cancer therapy [37]. For instance, the radionuclide samarium (^{153}Sm) is extensively used as ^{153}Sm -ethylenediaminetetramethylphosphonic acid (^{153}Sm -EDTMP) for stabilizing pain in patients with metastatic bone lesions [38].

Christie et al. also incorporated radioactive yttrium in BGs to prepare radionuclide vectors for cancer treatment [39]. The authors described that a combination of high surface reactivity with a slow release of yttrium is desirable for BGs used in cancer therapy. The release mechanism of yttrium from the glass was reported to be controlled by the coordination environment of yttrium ions and their clustering behavior. As adding yttrium to the BGs leads to a significant decrease in the network connectivity (NC), the glass showed less durability associated with a faster release of ionic species such as yttrium. At present, there is a paucity of reports on MBGs doped with radioactive anti-cancer elements; other options apart from Tb- and Sm-doped MBGs [26, 31] deserve to be considered in future studies.

Photothermal therapy (PTT) is a non-invasive therapeutic technique for the treatment of solid tumors. In this approach, the laser beam (wavelength in the second near-infrared window (NIR-II, 1000-1400 nm)) applied to the target tissue is converted into heat and creates localized thermal damage in the tumor region via surface plasmon resonance of plasmonic materials [40]. In order to utilize this technology for the treatment of bone tumors, Chang et al. recently synthesized copper (Cu)-doped MBGs that possessed both photothermal effects and bone-forming capability [19]. Their results showed that PTT and chemotherapy could be simultaneously achieved using Cu-doped MBGs, and this combination is an excellent approach to enhance the efficacy of tumor therapy.

3. Cancer treatment by using MBG-induced hyperthermia

Treatment of bone cancer by magnetic hyperthermia involves the use of implantable materials to generate heat in the diseased site under the application of an external alternating magnetic field [41]. Malignant cells are selectively killed if exposed to temperatures within 41-47 °C due to their intrinsic microenvironment including low pH, whereas normal cells can

survive at even higher temperatures [42]. Tumors are prone to be more efficiently heated compared to surrounding healthy tissues as their vascular network is poorly structured and cannot dissipate heat efficiently.

While being mostly used as contrast agents for diagnostics, magnetic nanoparticles have been recently applied for the treatment of cancer by hyperthermia. Sadhukha et al. [43] reported that magnetic hyperthermic effect transduced by superparamagnetic iron oxide nanoparticles (SPIONs) could significantly reduce or even eliminate cancer stem cell populations. Aminosilane-coated magnetite nanoparticles (NanoTherm, MagForce, Germany) have been approved by the European Medicines Agency (EMA) for clinical use in selected patients suffering from glioblastoma, a lethal brain tumor with limited therapeutic options [44]. An aqueous dispersion of SPIONs is injected into the tumor site and, once the nanoparticles are safely transferred, an alternating magnetic field is applied to generate heat and delivering a localized treatment.

Unlike SPIONs, BGs typically exhibit a non-magnetic behavior unless magnetic phases, e.g., magnetite (F_3O_4), are somehow embedded in the glass network. Introducing Fe in the sol-gel synthesis is relatively easy, whereas it can be tricky in melt-derived glasses and glass-ceramics. Li et al. [45] first prepared magnetic SiO_2 -CaO- P_2O_5 MBGs by introducing iron nitrate in the sol; as a result, MBG powders containing a homogeneous dispersion of F_3O_4 nanoparticles was obtained. The presence of this nanophase did not suppress the textural properties (specific surface area $>250\text{ m}^2/\text{g}$, mesopore size within 3.4-3.8 nm), the apatite-forming ability and sustained drug (ibuprofen) release capacity of Fe-doped MBGs, but imparted superparamagnetic properties to the materials, the saturation magnetization of which was found to increase with increasing amounts of Fe species.

Hierarchical Fe-doped MBG scaffolds containing F_3O_4 superparamagnetic nanoparticles were often fabricated by using a co-templating method, in which surfactant molecules (Pluronic P123) act as meso-structure directing agents and a polyurethane open-cell sponge generates the macroporous (200-500 μm) 3D architecture [3, 46] (Figure. 2a). These scaffolds were sintered in air and suffered from high brittleness (compressive strength ~ 50 kPa); therefore, production of MBG-based composites was thought as a valuable strategy to improve the mechanical properties. Zhu et al. [47] prepared superparamagnetic Fe-doped MBG scaffolds by the co-templating approach described above but performed the thermal treatment of calcination under argon atmosphere, thereby inducing carbonization of the polymeric skeleton. As a result, composite scaffolds with a carbon core coated by a MBG layer were obtained, and the compressive strength was significantly higher than that of the scaffolds calcined in air (>0.3 vs. 0.05 MPa). More recently, the same research group used 3D printing to fabricate Fe-doped MBG/polycaprolactone composite scaffolds showing the potential tri-functionality of enhanced osteogenic activity (due to bioactivity), local anticancer delivery of doxorubicin and magnetic hyperthermia [48].

Magnetic bioactive composites comprising 58S sol-gel glass and different amounts of melt-derived $\text{SiO}_2\text{-CaO-Fe}_2\text{O}_3$ glass-ceramics were found capable of inducing *in vitro* effective hyperthermia on human osteosarcoma (Saos-2) cells with reduction of cell proliferation and viability [49].

Fe-doped MBGs based on the quaternary $\text{SiO}_2\text{-CaO-Na}_2\text{O-P}_2\text{O}_5$ system were used to prepare multiscale porous scaffolds by using P123 block copolymer as a mesopore former and poly(methyl methacrylate) (PMMA) colloidal crystals to generate the macropores (Figure. 2b) [50]. Interestingly, the transition from paramagnetic to ferromagnetic behavior was observed when the scaffolds are calcined in the argon atmosphere, associated to the formation of

maghemite (γ - Fe_2O_3) nanoparticles (diameter <100 nm) [51]. Calcination in a non-oxidizing atmosphere was also reported to be the key for inducing the nucleation of magnetic phases (Fe_3O_4 and/or γ - Fe_2O_3) in macro-mesoporous bioactive glass-ceramic scaffolds produced by sol-gel foaming [52, 53] (Figures. 2c and d).

Very interestingly, a recent study revealed that other elements apart from Fe can play a role in imparting magnetic properties to MBGs. Koohkan et al. [54] investigated the bioactive and magnetic properties of SiO_2 -CaO- P_2O_5 MBGs doped with Fe, Cu or co-doped with both, and showed that the addition of Cu to the MBG composition resulted in better entrance of Fe_2O_3 into the glass structure and, accordingly, better formation of Fe_3O_4 after calcination and higher saturation magnetization (Figure 3). These materials also exhibited other attractive features due to the local release of Cu^{2+} ions, such as antibacterial behavior and stimulation of angiogenesis, along with good biocompatibility with mesenchymal stem cells.

The existing set of studies about the use of MBGs for hyperthermic treatment of bone cancer is limited to *in vitro* assays, but the results are overall promising and motivate further research in animal models. Some key points to be considered will be the optimal material dosage for obtaining a therapeutic effect *in vivo*, the duration and the parameters of the clinical treatment to apply (e.g., frequency and amplitude of the alternating magnetic field).

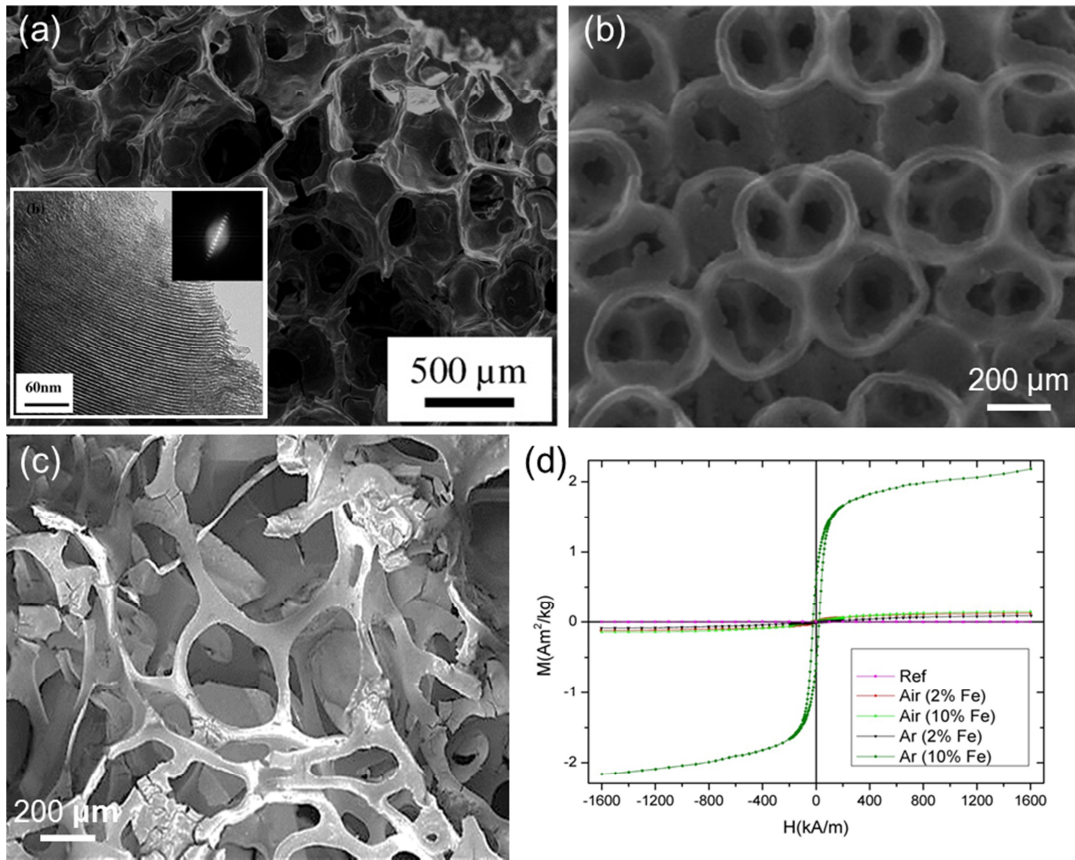


Figure 2. Magnetic hierarchical MBG scaffolds produced by different methods: (a) sponge replication (the TEM inset shows the mesoporous structure) (images reproduced from [3]), (b) use of PMMA crystals as macropore-forming agents (image reproduced from [35]), (c) sol-gel foaming (image reproduced from [38]); (d) influence of the calcination atmosphere (argon vs. air) on the magnetic properties of sol-gel Fe-doped MBG foams (images reproduced from [37]).

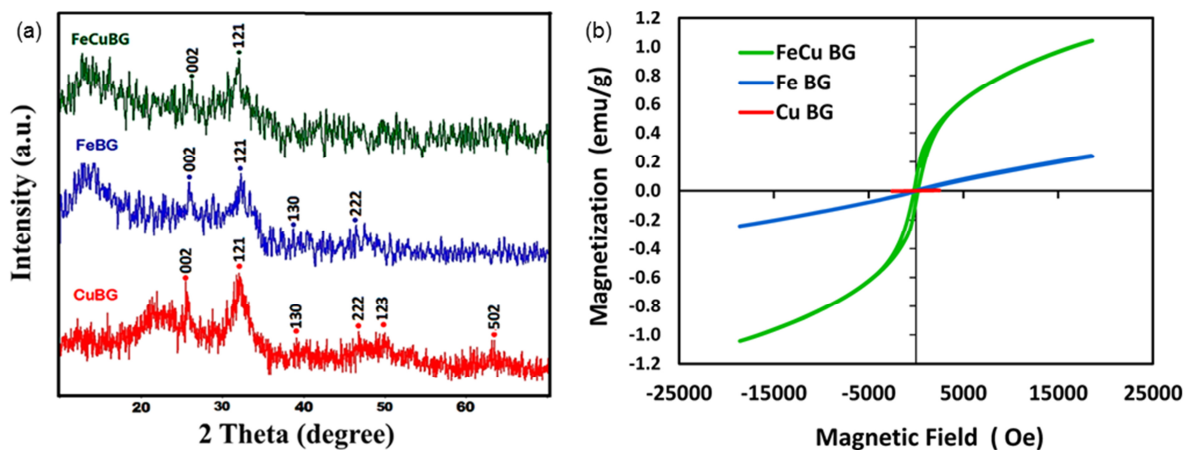


Figure 3. Fe-, Cu- and Fe/Cu-doped MBGs: evidence of (a) *in vitro* bioactive properties (the XRD patterns show the major diffraction peaks of hydroxyapatite after soaking in SBF) and (b) magnetic behavior. Images reproduced from [39].

4. Summary and outlook

Magnetic hyperthermia is a powerful technique for combating against cancerous cells, and its efficacy has generally been well recognized through *in vitro* and *in vivo* experiments.

At present, SPIONs are a promising clinical option to treat cancer via hyperthermia. High interest is also emerging towards the development of multifunctional SPION-based systems formed by a magnetite core functioning as a contrast agent, a biocompatible coating and a therapeutic outer layer targeted with active genes, drug compounds or special biomarkers [55, 56]. However, the toxicity associated with the non-degradable SPION core is still a matter of debate, including problems related to biodistribution, local accumulation and the long-term fate of the nanoparticles *in vivo* [57].

The use of magnetic BGs in the form of thermoseeds [14] could potentially overcome the limitations mentioned above as the solubility of these materials in the biological environment can

be tuned depending on the composition and structure, and the ionic dissolution products from glasses can be metabolized and excreted through physiological paths [58].

Apart from being non-toxic and highly biocompatible, MBGs can allow scientists to move a step forward and develop novel therapeutic strategies that were unthinkable or very difficult to develop with “conventional” melt-derived BGs. In fact, MBGs show great promise for anti-cancer applications due to their unique properties including the easiness of being doped with anti-cancer and magnetic ions (e.g., samarium [26] and iron [59], respectively) as well as of being loaded with anti-tumor chemicals (e.g., Imatinib and doxorubicin) [29, 30] that will be locally released in a controlled way. Moreover, recent studies suggest that some defined formulations of MBGs, e.g., Cu-containing MBGs, can be used in a newly developed strategy for cancer therapy based on PTT, in which not only the thermal ablation of cancer cells upon NIR laser irradiation is achieved, but the release of chemotherapeutic drug can be modulated by the photothermal effect [19].

From the authors' point of view, it should be underlined that the inhibition of angiogenesis via developing specific formulations of MBGs can also be beneficial in cancer therapy as tumor cells need new blood vessels to supply oxygen, nutrients and the removal of waste products as well as to guarantee their growth and proliferation in the body [60, 61]. In this regard, loading and delivery of various anti-angiogenic molecules (e.g., some types of small interfering RNA (siRNAs)) and chemicals (e.g., Sunitinib (anti-VEGFR drug)) by MBGs may be a wise strategy for the inhibition of the growth and progression of cancerous cells. This strategy has already been successfully performed using mesoporous silicate nanoparticles (MSNs) both *in vitro* and *in vivo* [62]; however, there is no report on the use of MBGs for the same purpose in the existing literature.

In brief, this work witnesses that the use of special types of MBGs for cancer therapy is in its beginning and numerous fascinating opportunities deserve further investigation in the future. Although relatively few studies have been focused on this specific application of MBGs, the preliminary results are highly promising and can be attractive for scientists working in this hot research field across materials science and medicine. However, plenty of questions on the usability of these materials for reliable cancer therapy still remain (e.g., optimal dosage of ions and drugs to embed in MBGs, the fate of MBGs *in vivo*, long-term side effects), which should be addressed through performing well-organized *in vitro* and *in vivo* studies. It is expected that interdisciplinary research and effective collaborations between materials scientists, chemists, biologists, and clinicians can potentially overcome all the obstacles on the way of magnetic and multifunctional MBGs and make this novel therapeutic approach as a feasible option in the near future.

References

- [1] J. Cassidy, D. Bissett, R.A.S. OBE, M. Payne, G. Morris-Stiff, Oxford handbook of oncology, OUP Oxford 2015.
- [2] S. Cappelletti, P. Daria, G. Sani, M. Aromataro, Caffeine: cognitive and physical performance enhancer or psychoactive drug?, *Current neuropharmacology* 13(1) (2015) 71-88.
- [3] C. Wu, W. Fan, Y. Zhu, M. Gelinsky, J. Chang, G. Cuniberti, V. Albrecht, T. Friis, Y. Xiao, Multifunctional magnetic mesoporous bioactive glass scaffolds with a hierarchical pore structure, *Acta biomaterialia* 7(10) (2011) 3563-3572.
- [4] S. Kargozar, N. Lotfibakhshaiesh, J. Ai, A. Samadikuchaksaraie, R.G. Hill, P.A. Shah, P.B. Milan, M. Mozafari, M. Fathi, M.T. Joghataei, Synthesis, physico-chemical and biological characterization of strontium and cobalt substituted bioactive glasses for bone tissue engineering, *Journal of Non-Crystalline Solids* 449 (2016) 133-140.
- [5] D.-Y. Zhu, B. Lu, J.-H. Yin, Q.-F. Ke, H. Xu, C.-Q. Zhang, Y.-P. Guo, Y.-S. Gao, Gadolinium-doped bioglass scaffolds promote osteogenic differentiation of hBMSC via the Akt/GSK3 β pathway and facilitate bone repair *in vivo*, *International journal of nanomedicine* 14 (2019) 1085-1100.
- [6] U. Patel, L. Macri-Pellizzeri, K.M.Z. Hossain, B.E. Scammell, D.M. Grant, C.A. Scotchford, A.C. Hannon, A.R. Kennedy, E.R. Barney, I. Ahmed, *In vitro* cellular testing of Strontium/Calcium substituted phosphate glass discs and microspheres shows potential for bone regeneration, *Journal of tissue engineering and regenerative medicine* (2019).

- [7] J.R. Jones, Review of bioactive glass: from Hench to hybrids, *Acta biomaterialia* 9(1) (2013) 4457-4486.
- [8] A.A. El-Rashidy, J.A. Roether, L. Harhaus, U. Kneser, A.R. Boccaccini, Regenerating bone with bioactive glass scaffolds: A review of in vivo studies in bone defect models, *Acta biomaterialia* 62 (2017) 1-28.
- [9] S. Kargozar, S. Hamzehlou, F. Baino, Can bioactive glasses be useful to accelerate the healing of epithelial tissues?, *Materials Science and Engineering: C* 97 (2019) 1009-1020.
- [10] S. Marza, K. Magyari, S. Bogdan, M. Moldovan, C. Pestean, A. Nagy, F. Tabaran, E. Licarete, S. Suarasan, A. Dreanca, Skin wound regeneration with bioactive glass-gold nanoparticles ointment, *Biomedical Materials* (2019).
- [11] S. Kargozar, S. Hamzehlou, F. Baino, Potential of Bioactive Glasses for Cardiac and Pulmonary Tissue Engineering, *Materials* 10(12) (2017) 1429.
- [12] F. Baino, G. Novajra, V. Miguez-Pacheco, A.R. Boccaccini, C. Vitale-Brovarone, Bioactive glasses: special applications outside the skeletal system, *Journal of Non-Crystalline Solids* 432 (2016) 15-30.
- [13] P. Balasubramanian, T. Büttner, V.M. Pacheco, A.R. Boccaccini, Boron-containing bioactive glasses in bone and soft tissue engineering, *Journal of the European Ceramic Society* 38(3) (2018) 855-869.
- [14] A. Yazdanpanah, F. Moztarzadeh, Synthesis and characterization of Barium-Iron containing magnetic bioactive glasses: The effect of magnetic component on structure and in vitro bioactivity, *Colloids and Surfaces B: Biointerfaces* (2018).
- [15] N. Kilcup, S. Gaynard, U. Werner-Zwanziger, E. Tonkopi, J. Hayes, D. Boyd, Stimulation of apoptotic pathways in liver cancer cells: An alternative perspective on the biocompatibility and the utility of biomedical glasses, *Journal of biomaterials applications* 30(10) (2016) 1445-1459.
- [16] N. Kilcup, U. Werner-Zwanziger, E. Tonkopi, D. Boyd, Unanticipated stabilization of zinc-silicate glasses by addition of lanthanum: Implications for therapeutic inorganic ion delivery systems, *Journal of Non-Crystalline Solids* 429 (2015) 83-92.
- [17] J. Edeline, M. Gilibert, E. Garin, E. Boucher, J.-L. Raoul, Yttrium-90 microsphere radioembolization for hepatocellular carcinoma, *Liver Cancer* 4(1) (2015) 16-25.
- [18] A.M. Abbott, R. Kim, S.E. Hoffe, B. Arslan, B. Biebel, J. Choi, G. El-Haddad, B. Kis, J. Sweeney, K.L. Meredith, Outcomes of Therasphere radioembolization for colorectal metastases, *Clinical colorectal cancer* 14(3) (2015) 146-153.
- [19] L. Chang, Y. Liu, C. Wu, Copper-Doped Mesoporous Bioactive Glass for Photothermal Enhanced Chemotherapy, *Journal of Biomedical Nanotechnology* 14(4) (2018) 786-794.
- [20] S. Kargozar, M. Mozafari, Nanotechnology and Nanomedicine: Start small, think big, *Materials Today: Proceedings* 5(7, Part 3) (2018) 15492-15500.
- [21] F. Baino, S. Hamzehlou, S. Kargozar, Bioactive Glasses: Where Are We and Where Are We Going?, *Journal of Functional Biomaterials* 9(1) (2018) 25.
- [22] M. Miola, Y. Pakzad, S. Banijamali, S. Kargozar, C. Vitale-Brovarone, A. Yazdanpanah, O. Bretcanu, A. Ramedani, E. Vernè, M. Mozafari, Glass-ceramics for cancer treatment: So close, or yet so far?, *Acta Biomaterialia* 83 (2019) 55-70.
- [23] A. López-Noriega, D. Arcos, I. Izquierdo-Barba, Y. Sakamoto, O. Terasaki, M. Vallet-Regí, Ordered mesoporous bioactive glasses for bone tissue regeneration, *Chemistry of materials* 18(13) (2006) 3137-3144.
- [24] X. Yan, C. Yu, X. Zhou, J. Tang, D. Zhao, Highly ordered mesoporous bioactive glasses with superior in vitro bone-forming bioactivities, *Angewandte Chemie International Edition* 43(44) (2004) 5980-5984.
- [25] W. Xia, J. Chang, Well-ordered mesoporous bioactive glasses (MBG): a promising bioactive drug delivery system, *Journal of Controlled Release* 110(3) (2006) 522-530.

- [26] Y. Zhang, X. Wang, Y. Su, D. Chen, W. Zhong, A doxorubicin delivery system: samarium/mesoporous bioactive glass/alginate composite microspheres, *Materials Science and Engineering: C* 67 (2016) 205-213.
- [27] M. Shoaib, M.S. ur Rahman, A. Saeed, M.M. Naseer, Mesoporous bioactive glass-polyurethane nanocomposites as reservoirs for sustained drug delivery, *Colloids and Surfaces B: Biointerfaces* 172 (2018) 806-811.
- [28] S. Kargozar, M. Mozafari, R.G. Hill, P. Brouki Milan, M. Taghi Joghataei, S. Hamzehlou, F. Baino, Synergistic combination of bioactive glasses and polymers for enhanced bone tissue regeneration, *Materials Today: Proceedings* 5(7, Part 3) (2018) 15532-15539.
- [29] M. Shoaib, A. Saeed, M.S.U. Rahman, M.M. Naseer, Mesoporous nano-bioglass designed for the release of imatinib and in vitro inhibitory effects on cancer cells, *Materials Science and Engineering: C* 77 (2017) 725-730.
- [30] C. Wu, W. Fan, J. Chang, Functional mesoporous bioactive glass nanospheres: synthesis, high loading efficiency, controllable delivery of doxorubicin and inhibitory effect on bone cancer cells, *Journal of Materials Chemistry B* 1(21) (2013) 2710-2718.
- [31] X. Wang, Y. Zhang, C. Lin, W. Zhong, Sol-gel derived terbium-containing mesoporous bioactive glasses nanospheres: In vitro hydroxyapatite formation and drug delivery, *Colloids and Surfaces B: Biointerfaces* 160 (2017) 406-415.
- [32] R.K. Singh, K.D. Patel, C. Mahapatra, M.S. Kang, H.-W. Kim, C-Dot Generated Bioactive Organosilica Nanospheres in Theranostics: Multicolor Luminescent and Photothermal Properties Combined with Drug Delivery Capacity, *ACS applied materials & interfaces* 8(37) (2016) 24433-24444.
- [33] S. Kargozar, M. Montazerian, S. Hamzehlou, H.-W. Kim, F. Baino, Mesoporous bioactive glasses: Promising platforms for antibacterial strategies, *Acta Biomaterialia* 81 (2018) 1-19.
- [34] C. Sawyers, Targeted cancer therapy, *Nature* 432(7015) (2004) 294.
- [35] S.-Y. Chen, P.-F. Chou, W.-K. Chan, H.-M. Lin, Preparation and characterization of mesoporous bioactive glass from agricultural waste rice husk for targeted anticancer drug delivery, *Ceramics International* 43(2) (2017) 2239-2245.
- [36] H.-M. Lin, H.-Y. Lin, M.-H. Chan, Preparation, characterization, and in vitro evaluation of folate-modified mesoporous bioactive glass for targeted anticancer drug carriers, *Journal of Materials Chemistry B* 1(44) (2013) 6147-6156.
- [37] R.D. Teo, J. Termini, H.B. Gray, Lanthanides: Applications in Cancer Diagnosis and Therapy: Miniperspective, *Journal of medicinal chemistry* 59(13) (2016) 6012-6024.
- [38] L. Correa-González, C.A. de Murphy, P. Pichardo-Romero, M. Pedraza-López, C. Moreno-García, L. Correa-Hernández, ¹⁵³Sm-EDTMP for pain relief of bone metastases from prostate and breast cancer and other malignancies, *Archives of medical research* 45(4) (2014) 301-308.
- [39] J.K. Christie, J. Malik, A. Tilocca, Bioactive glasses as potential radioisotope vectors for in situ cancer therapy: investigating the structural effects of yttrium, *Physical Chemistry Chemical Physics* 13(39) (2011) 17749-17755.
- [40] X. Huang, P.K. Jain, I.H. El-Sayed, M.A. El-Sayed, Plasmonic photothermal therapy (PPTT) using gold nanoparticles, *Lasers in medical science* 23(3) (2008) 217.
- [41] E.A. Perigo, G. Hemery, O. Sandre, D. Ortega, E. Garaio, F. Plazaola, F.J. Teran, Fundamentals and advances in magnetic hyperthermia, *Applied Physics Reviews* 2(4) (2015) 041302.
- [42] M. Idrees, A.Z. Jebakumar, A review on potential benefits of hyperthermia in the treatment of cancer, *Acta Biomed. Sci* 1 (2014) 98-104.
- [43] T. Sadhukha, L. Niu, T.S. Wiedmann, J. Panyam, Effective elimination of cancer stem cells by magnetic hyperthermia, *Molecular pharmaceuticals* 10(4) (2013) 1432-1441.
- [44] K. Maier-Hauff, F. Ulrich, D. Nestler, H. Niehoff, P. Wust, B. Thiesen, H. Orawa, V. Budach, A. Jordan, Efficacy and safety of intratumoral thermotherapy using magnetic iron-oxide nanoparticles combined

- with external beam radiotherapy on patients with recurrent glioblastoma multiforme, *Journal of neuro-oncology* 103(2) (2011) 317-324.
- [45] X. Li, X. Wang, Z. Hua, J. Shi, One-pot synthesis of magnetic and mesoporous bioactive glass composites and their sustained drug release property, *Acta Materialia* 56(13) (2008) 3260-3265.
- [46] Y. Zhu, F. Shang, B. Li, Y. Dong, Y. Liu, M.R. Lohe, N. Hanagata, S. Kaskel, Magnetic mesoporous bioactive glass scaffolds: preparation, physicochemistry and biological properties, *Journal of Materials Chemistry B* 1(9) (2013) 1279-1288.
- [47] M. Zhu, J. Zhang, Y. Zhou, Y. Liu, X. He, C. Tao, Y. Zhu, Preparation and characterization of magnetic mesoporous bioactive glass/carbon composite scaffolds, *Journal of Chemistry* 2013 (2013).
- [48] J. Zhang, S. Zhao, M. Zhu, Y. Zhu, Y. Zhang, Z. Liu, C. Zhang, 3D-printed magnetic Fe₃O₄/MBG/PCL composite scaffolds with multifunctionality of bone regeneration, local anticancer drug delivery and hyperthermia, *Journal of Materials Chemistry B* 2(43) (2014) 7583-7595.
- [49] M. Alcaide, C. Ramírez-Santillán, M.J. Feito, M. de la Concepción Matesanz, E. Ruiz-Hernández, D. Arcos, M. Vallet-Regí, M.T. Portolés, In vitro evaluation of glass-glass ceramic thermoseed-induced hyperthermia on human osteosarcoma cell line, *Journal of Biomedical Materials Research Part A* 100(1) (2012) 64-71.
- [50] T. Charoensuk, C. Sirisathitkul, U. Boonyang, I.J. Macha, J. Santos, D. Grossin, B. Ben-Nissan, In vitro bioactivity and stem cells attachment of three-dimensionally ordered macroporous bioactive glass incorporating iron oxides, *Journal of Non-Crystalline Solids* 452 (2016) 62-73.
- [51] T. Charoensuk, C. Sirisathitkul, W. Tangwatanakul, S. Pinitsoontorn, U. Boonyang, Magnetic phase transitions in macro/mesoporous bioactive glass by ferric nitrate addition in sol-gel synthesis, *J. Ceram. Sci. Tech* 7 (2016) 139-144.
- [52] F. Baino, E. Fiume, M. Miola, F. Leone, B. Onida, F. Laviano, R. Gerbaldo, E. Verné, Fe-doped sol-gel glasses and glass-ceramics for magnetic hyperthermia, *Materials* 11(1) (2018) 173.
- [53] F. Baino, E. Fiume, M. Miola, F. Leone, B. Onida, E. Verné, Fe-doped bioactive glass-derived scaffolds produced by sol-gel foaming, *Materials Letters* 235 (2019) 207-211.
- [54] R. Koohkan, T. Hooshmand, D. Mohebbi-Kalhari, M. Tahriri, M.T. Marefati, Synthesis, Characterization, and in Vitro Biological Evaluation of Copper-Containing Magnetic Bioactive Glasses for Hyperthermia in Bone Defect Treatment, *ACS Biomaterials Science & Engineering* 4(5) (2018) 1797-1811.
- [55] F.M. Kievit, M. Zhang, Surface engineering of iron oxide nanoparticles for targeted cancer therapy, *Accounts of chemical research* 44(10) (2011) 853-862.
- [56] M.V. Yigit, A. Moore, Z. Medarova, Magnetic nanoparticles for cancer diagnosis and therapy, *Pharmaceutical research* 29(5) (2012) 1180-1188.
- [57] O.L. Gobbo, K. Sjaastad, M.W. Radomski, Y. Volkov, A. Prina-Mello, Magnetic nanoparticles in cancer theranostics, *Theranostics* 5(11) (2015) 1249-1263.
- [58] A. Hoppe, N.S. Güldal, A.R. Boccaccini, A review of the biological response to ionic dissolution products from bioactive glasses and glass-ceramics, *Biomaterials* 32(11) (2011) 2757-2774.
- [59] Y. Zhang, Y. Liu, M. Li, S. Lu, J. Wang, The effect of iron incorporation on the in vitro bioactivity and drug release of mesoporous bioactive glasses, *Ceramics International* 39(6) (2013) 6591-6598.
- [60] M. Momeny, H. Yousefi, H. Eyvani, F. Moghaddaskho, A. Salehi, F. Esmaeili, Z. Alishahi, F. Barghi, S. Vaezijoze, S. Shamsaiegahkani, G. Zarrinrad, G. Sankanian, Z. Sabourinejad, S. Hamzehlou, D. Bashash, E.S. Aboutorabi, P. Ghaffari, A.R. Dehpour, S.M. Tavangar, J. Tavakkoly-Bazzaz, K. Alimoghaddam, A. Ghavamzadeh, S.H. Ghaffari, Blockade of nuclear factor- κ B (NF- κ B) pathway inhibits growth and induces apoptosis in chemoresistant ovarian carcinoma cells, *The International Journal of Biochemistry & Cell Biology* 99 (2018) 1-9.
- [61] N. Nishida, H. Yano, T. Nishida, T. Kamura, M. Kojiro, Angiogenesis in cancer, *Vascular health and risk management* 2(3) (2006) 213-219.

[62] S. Goel, F. Chen, H. Hong, H.F. Valdovinos, R. Hernandez, S. Shi, T.E. Barnhart, W. Cai, VEGF121-Conjugated Mesoporous Silica Nanoparticle: A Tumor Targeted Drug Delivery System, *ACS Applied Materials & Interfaces* 6(23) (2014) 21677-21685.