

Joining of SiC, alumina, and mullite by the Refractory Metal—Wrap pressureless process

*Original*

Joining of SiC, alumina, and mullite by the Refractory Metal—Wrap pressureless process / Gianchandani, P.K., Casalegno, V., De la Pierre des Ambrois, S., Salvo, M., De Aloysio, G., Laghi, L., Ferraris, M.. - In: INTERNATIONAL JOURNAL OF APPLIED CERAMIC TECHNOLOGY. - ISSN 1546-542X. - (2020). [10.1111/ijac.13477]

*Availability:*

This version is available at: 11583/2791832 since: 2020-02-12T14:42:03Z

*Publisher:*

Wiley

*Published*

DOI:10.1111/ijac.13477

*Terms of use:*

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

*Publisher copyright*

(Article begins on next page)

## Joining of SiC, alumina and mullite by the Refractory Metal (RM) – Wrap pressure-less process

Journal:	<i>International Journal of Applied Ceramic Technology</i>
Manuscript ID	ACT-5573.R1
Manuscript Type:	Article
Date Submitted by the Author:	n/a
Complete List of Authors:	Gianchandani, Pardeep; Mehran University of Engineering and Technology CASALEGNO, VALENTINA; Politecnico di Torino, The Department of APPLIED SCIENCE AND TECHNOLOGY De la Pierre des Ambrois, Stefano; Politecnico di Torino, The Department of APPLIED SCIENCE AND TECHNOLOGY Salvo, Milena; Politecnico di Torino, The Department of APPLIED SCIENCE AND TECHNOLOGY Aloysio, Giulia ; CERTIMAC Laghi, Luca ; CERTIMAC Ferraris, Monica; Politecnico di Torino, The Department of APPLIED SCIENCE AND TECHNOLOGY
Keywords:	joints/joining, ceramic matrix composites, thermal analysis, silicon carbide, alumina
Author-supplied Keyword: If there is one additional keyword you would like to include that was not on the list, please add it below::	Pressure-less joining

SCHOLARONE™  
 Manuscripts

## Joining of SiC, alumina and mullite by the Refractory Metal (RM) – Wrap pressure-less process

Pardeep Kumar Gianchandani(1), Valentina Casalegno (2), Stefano De la Pierre des Ambrois (2), Milena Salvo (2), Giulia De Aloysio (3), Luca Laghi(3), Monica Ferraris (2)

(1) Mehran University of Engineering and Technology Jamshoro, Sindh, Pakistan.

(2) Department of Applied Science and Technology, Politecnico di Torino, Italy.

(3) CERTIMAC, Faenza (RA), Italy

### Abstract

The aim of this work is to discuss the suitability of the joining process called “RM-Wrap” (RM= Refractory Metals, i.e. Mo, Nb, Ta, Zr) as a pressure-less and tailorable technique to join several different ceramics such as SiC, alumina and mullite ( $3Al_2O_3 \cdot 2SiO_2$ ). In the RM-Wrap joining technique the refractory metal foil is used as a wrap containing one or more silicon foils. It is performed at 1450 °C, under flowing argon, and the resulting joining materials are in-situ formed composites made of refractory metal disilicides ( $MoSi_2$ ,  $NbSi_2$ ,  $TaSi_2$  or  $ZrSi_2$ ) embedded in a silicon rich matrix; their coefficient of thermal expansion has been calculated and the Laser Flash Method was used to measure the thermal diffusivity of one of them ( $MoSi_2/Si$ ) in 25-1000 °C range, then to calculate its thermal conductivity. All the obtained joints are uniform, continuous and crack free. Some preliminary oxidation tests were carried out on all joints at 1100 °C, 6 hours in air, giving unchanged morphology of the interface and the joining materials itself; the joint strength of RM-Wrap joined SiC was measured at room temperature using three different mechanical tests: (i) single lap (SL), (ii) single lap off-set (SLO) and (iii) torsion on hourglass shaped samples (THG) (on Mo-wrap joined SiC).

### Keywords

RM-wrap, Pressure-less joining, SiC, alumina, mullite, shear tests, thermal properties

### Introduction

SiC, alumina and mullite are stable materials for high temperature applications, with a unique combination of properties such as lightweight, high temperature stability and chemical inertness. More and more they are used in components for energy production, defense, space and many other high-performance applications

1  
2  
3 and have great potential to replace conventional materials such as metals and superalloys in many  
4 applications.<sup>1,2</sup>  
5

6  
7 However, the joining of ceramics to themselves or to other materials remains a critical issue. The  
8 manufacturing of net-shape and ready to use ceramic components for advanced design solutions require  
9 large and complex parts, which can be built by joining and integrating discrete units of similar or dissimilar  
10 ceramics.<sup>3-5</sup>  
11  
12

13  
14 Many joining techniques have been developed so far to join similar and dissimilar ceramics, among them:  
15 Liquid Silicon Infiltration (LSI)<sup>6</sup>, Affordable Robust Ceramic Joining (ARCJoint TM)<sup>7</sup>, Nano-Infiltration and  
16 Transient Eutectic Phase (NITE)<sup>8,9</sup>, Spark Plasma Sintering (SPS)<sup>10,11</sup>, Laser<sup>12</sup> or Microwave- Assisted Joining<sup>13</sup>,  
17 Solid State Displacement Reactions (SSDR)<sup>14</sup>, Transient-Liquid-Phase Bonding (TLPB)<sup>15</sup>, brazing and glass-  
18 ceramic based joints<sup>16,3</sup> are prominent.  
19  
20  
21  
22  
23  
24

25  
26 The "RM-Wrap" (RM= Refractory Metals, i.e. Mo, Nb, Ta, Zr) is a novel brazing technique where the refractory  
27 metal, shaped as a wrap, is used to contain one or more silicon foils. It is a pressure-less joining process  
28 performed at 1450 °C, in an inert environment (argon flow).<sup>17-19</sup> The wrap is necessary to prevent the too  
29 fast spreading of molten silicon and its leaking outside the joined region during the joining process. The  
30 joining materials are in-situ formed composites made of refractory metals disilicides (MoSi<sub>2</sub>, NbSi<sub>2</sub>, TaSi<sub>2</sub> or  
31 ZrSi<sub>2</sub>) embedded in a silicon-rich matrix. Disilicides have high melting temperature and good oxidation  
32 resistance at elevated temperature, making them a suitable choice to join ceramics.  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42

43 The conventional manufacturing routes for disilicides are time consuming and prone to contamination and  
44 oxidation.<sup>20,21</sup> On the contrary, the RM-Wrap process is quick, free from undesired phases and has excellent  
45 reproducibility and versatility<sup>18</sup> the quantity of each metal can be modified and more than one refractory  
46 metal can be used in the same wrap.  
47  
48  
49  
50

51  
52 Metal disilicides are characterized by a wide range of interesting properties, a few of them are highlighted  
53 here. Mo-disilicides (MoSi<sub>2</sub>, Mo<sub>5</sub>Si<sub>3</sub> and Mo<sub>3</sub>Si)<sup>22</sup> are characterized by melting points above 2000 °C and  
54 excellent oxidation and corrosion resistance at elevated temperature due to development of a thin protective  
55 coating of SiO<sub>2</sub>.<sup>23</sup> The Nb-Si phase diagram is similar to the Si-Mo one, where three (Nb<sub>5</sub>Si<sub>3</sub>, Nb<sub>3</sub>Si and NbSi<sub>2</sub>)  
56 compounds can be formed<sup>24</sup>: NbSi<sub>2</sub> exhibits higher shear strength, hardness and oxidation resistance.<sup>25</sup> The  
57  
58  
59  
60

1  
2  
3 Ta-Si phase diagram shows the formation of four intermetallics: TaSi<sub>2</sub>, Ta<sub>5</sub>Si<sub>3</sub>, Ta<sub>2</sub>Si, and Ta<sub>3</sub>Si. Among them,  
4  
5 TaSi<sub>2</sub> has the best oxidation resistance due to the formation of a protective SiO<sub>2</sub> layer on its surface. <sup>26</sup> The  
6  
7 Zr-Si phase diagram shows the formation of several phases and intermetallics (ZrSi<sub>2</sub>, Zr<sub>5</sub>Si<sub>4</sub>, Zr<sub>3</sub>Si<sub>2</sub>, Zr<sub>2</sub>Si, Zr<sub>3</sub>Si)  
8  
9 and an eutectic at 1370°C. <sup>27</sup>  
10  
11

12  
13 An original joining technique called “RM-Wrap” was developed in our previous studies <sup>17-19</sup> as an alternative  
14  
15 to obtain refractory-metals disilicide-based joints. The RM-Wrap technology has been effectively used to join  
16  
17 C/SiC, SiC/SiC and SiC foam sandwich structures; in the present work this joining technique was successfully  
18  
19 used to join different materials, namely SiC, alumina and mullite. To assess the reliability of the RM-Wrap  
20  
21 process, joined SiC samples have been mechanically tested at room temperature using three different  
22  
23 mechanical tests (single lap, SL, single lap off-set, SLO, and torsion on hourglass shaped samples, THG);  
24  
25 moreover, oxidation tests on SiC joints were carried out at 1100 °C, 6 hours in air, as a preliminary test to  
26  
27 investigate the suitability of these joints in working conditions. Furthermore, one of the RM-wrap joining  
28  
29 material (MoSi<sub>2</sub>/Si) has been characterised by means of the laser flash method: the thermal diffusivity has  
30  
31 been measured to calculate the thermal conductivity and specific heat of the joining material in 25-1000 °C  
32  
33 range.  
34  
35  
36  
37

### 38 **Experimental**

39  
40 Materials to be joined, i.e. SiC (density 3.1 g/cm<sup>3</sup>, supplied by Bettini S.p.A, Italy; 98,5% purity), Al<sub>2</sub>O<sub>3</sub> (density  
41  
42 3.8 g/cm<sup>3</sup>, 99,5% purity, supplied by Accuratus, USA) and mullite (density 2.8 g/cm<sup>3</sup>, supplied by Accuratus,  
43  
44 USA) were cut to 10 mm x 10 mm x (3 to 5) mm, polished to 800 micron by grit paper, sonicated in ethanol,  
45  
46 dried in air, then joined with the RM-Wrap technique.  
47  
48  
49

50  
51 The “RM-Wrap” technique consists in wrapping one Si foil (525±25 µm thick Virginia Semiconductor Electron-  
52  
53 MEC s.r.l. Italy, 99.95% Si) in a refractory metal (Mo, Nb, Ta or Zr) (25.4 µm thick, Alfa Aesar Germany, 99.95%)  
54  
55 foil folded as a wrap.  
56  
57

58  
59 The optimized heating conditions were found to be 1450 °C, heating rate of 1000 °C/h, dwell of 5 minutes,  
60  
natural cooling to room temperature under flowing argon (Carbolite, Gero, Germany), as reported in <sup>2</sup> for

1  
2  
3 Mo-Wrap. The joint thickness ranges withing 200-250  $\mu\text{m}$ , measured *ex-post* joining. Compositions ranging  
4  
5 between about 30-70 wt % Mo, Nb, Ta or Zr (balance to 100% with Si) have been tested to optimize each  
6  
7 joining process.  
8  
9

10 Preliminary oxidation tests on joints **obtained using Mo, Nb and Ta wrap** were performed at 1100°C, 6 hours  
11  
12 in air (with 10 °C/min heating rate and cooling in air), then their polished cross-sections were analysed.

13  
14 Each joint morphology was analysed by FESEM, (QUANTA INSPECT 200, Zeiss SUPRATM 40™) equipped with  
15  
16 Energy Dispersive Spectroscopy (EDS, EDAX PV 9900™).  
17  
18

19  
20 The coefficient of thermal expansion (CTE) for the RM-wrap joining materials was calculated by the rule of  
21  
22 mixture, according to their composition. **The wrap joining material is composed by silicon and metal**  
23  
24 **disilicides; the used compositions range between 30-70wt% for refractory metals (balance to 100% with Si).**  
25  
26 **According to the joining material composition, the relative phase diagram and the density of the different**  
27  
28 **phases, we calculated the fraction volume of the 2 phases (metal disilicide and silicon).**  
29  
30  
31

32  
33 One **MoSi<sub>2</sub>/Si** pellet of about 11.6 mm diameter and 2.6 mm thickness was prepared by grinding and sintering  
34  
35 the same Si and Mo used to obtain the Mo-wrap joints, in the same quantity and with the same thermal  
36  
37 treatment used to obtain the joints; the pellet density (3.24 g/cm<sup>3</sup>) was measured by Archimede's method.

38  
39 The Laser Flash Method (LFA 467 HT ® Hyper Flash NETZSCH9) was used in order to evaluate the thermal  
40  
41 properties of the MoSi<sub>2</sub>/Si pellet between 25-1000 °C with 200 °C temperature steps at a heating rate of 4  
42  
43 °C·min<sup>-1</sup>, under flowing Ar, mass flow 50 ml·min<sup>-1</sup>. A specific SiC ring was designed, in order to minimize the  
44  
45 backlash between the sample and the sample holder (12.7 mm diameter). This technique allows the direct  
46  
47 determination of the thermal diffusivity and, through the Software Proteus®, the indirect determination of  
48  
49 the specific heat and of the thermal conductivity, when the sample's density is known. The specific heat of  
50  
51 the sample was determined by comparing its temperature increase with the reference material one (Poco  
52  
53 Graphite Serial Nr. 21517) used to calculate the absorbed energy.<sup>28,29</sup> The thermal diffusivity is determined  
54  
55 by a mathematical analysis of the measured temperature increase/time function, as explained by Parker et  
56  
57  
58  
59  
60

1  
2  
3 al. <sup>30</sup> After measuring the thermal diffusivity ( $\alpha$ ), it is possible to evaluate the thermal conductivity ( $\lambda$ ) as  
4  
5 shown in Eq. 1.

$$\alpha(T)\rho(T)c_p(T) = \lambda(T) \quad (1)$$

6  
7  
8  
9  
10 Where  $c_p$  is the specific heat and  $\rho$  is the bulk density of the sample.

11  
12  
13 The joints were tested by single lap (SL) shear test in compression, according to <sup>31</sup> on five samples. The  
14 commercial Scotch-Weld DP490 epoxy adhesive was used to attach the specimens to the aluminium fixtures  
15 and cured for 45 min at 90 °C. The joined specimen size was 10 mm x 10 mm x (3 to 5) mm. Furthermore, the  
16 single lap off-set (SLO) (adapted from ASTM-D905-08 <sup>32</sup>) was also used to measure the joint strength of RM-  
17 Wrap joined SiC with specimen size of 5 mm x 10 mm x 5 mm (3 mm offset); with this configuration, no  
18 adhesive was necessary. The mechanical tests were performed at room temperature with a compression  
19 machine (SINTEC D/10) with a cross-head speed of 0.5 mm/min. Mo-Wrap joined SiC samples were also  
20 tested by torsion: SiC hourglass shaped samples with a circular joined area of 4 mm or 5 mm in diameter  
21 (referred to as THG-4 and THG-5, respectively) were joined one by one or machined (by Morise Ltd. Japan)  
22 to obtain THG-4 and THG-5 hourglasses from a joined 35 mm x 8 mm x 4 mm specimen. A custom-made  
23 torsional testing machine developed at Politecnico di Torino (Italy) was used to test the SiC joints in torsion.

24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

~~The X-Ray Diffraction (XRD) analysis was carried out on the fracture surfaces of each joined sample after mechanical test (X'Pert Phillips diffractometer, with Cu K $\alpha$  radiation, and the XRD spectra were analyzed by using X'Pert High Score Plus software).~~

## Results and discussion

Following the success of RM-Wrap in joining SiC-based composites and foams<sup>17-19</sup>, its scope has been extended to another refractory metal (Zr) and to other substrates (silicon carbide, alumina and mullite).

1  
2  
3 The use of silicon has the dual function of providing the liquid phase necessary to wet the faying surfaces and  
4 to form the disilicides by reacting with the refractory metal. In all the cases, the joining materials were in-situ  
5 formed composites made of disilicides homogenously dispersed in a Si rich matrix. The presence of free (un-  
6 reacted) Mo, Nb, Ta or Zr must be avoided because of their poor oxidation resistance. Likewise, the presence  
7 of free silicon may be not desirable for some applications, but a certain amount of silicon was necessary to  
8 achieve a good wettability and crack-free continuous joints. In this work, the amount of free, unreacted  
9 silicon was minimized by gradually reducing its amount inside each wrap, but always trying to avoid the  
10 presence of unreacted refractory metal. The best compromise was obtained with 65-68 wt.% Si + 32-35 wt.%  
11 Mo, 67-69 wt.% Si + 31-33 wt.% Nb, 50-51 wt.% Si + 49-50 wt.% Ta and 71wt.% Si + 29 wt.% Zr (Si-Zr eutectic  
12 composition), respectively. A higher amount of the refractory metal resulted in an insufficient amount of  
13 silicon matrix, thus leading to discontinuous joints.

14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28 The RM-Wrap SiC-SiC joint microstructures are shown in Figure 1 (Mo-Wrap), Figure 2 (Nb-Wrap) and Figure  
29 3 (Ta-Wrap): the round shaped disilicides particles are uniformly embedded in the Si rich matrix, which shows  
30 an excellent wettability on Mo at temperature above its melting point<sup>34</sup> and can easily infiltrate and hinder  
31 the formation of pores between MoSi<sub>2</sub> particles. Likewise, all the joining material/SiC interfaces are  
32 continuous, and no cracks are visible within the joint area, thus indicating that the CTE mismatch between  
33 RM silicides/Si and SiC did not affect the integrity of the joint. The joints showed an excellent wettability on  
34 SiC surfaces and continuous and robust interfaces (Figure 1-3).

35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45 As expected, the Zr-wrap joining material (Figure 4) is characterized by a typical eutectic microstructure with  
46 needle-shaped ZrSi<sub>2</sub> and Si phases, evidenced in the Si-Zr phase diagram in Figure 5. Recently, Naikade M. et  
47 al.<sup>35</sup> has shown that Si<sub>0.92</sub>Zr<sub>0.08</sub> eutectic alloy has good wettability on SiC and slower spreading in  
48 comparison with the instantaneous spreading of the pure molten silicon. The same results were obtained  
49 with the Zr-wrap, with all the joining material well confined in the joined region.

50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
The interaction of silicon carbide with refractory metals results in the formation of carbide(s) and silicide  
compounds, if they are more thermodynamically stable than SiC; reactions are extensive at temperature  
above 1000°C, as reported in<sup>36</sup> and the kinetics for solid state diffusion is normally fast enough at T above

1  
2  
3 1200°C.<sup>37</sup> In case of Nb/SiC interface, it has been reported that the typical reaction layer sequence is  
4 SiC/Nb<sub>x</sub>Si<sub>y</sub>C/NbC<sub>z</sub>/NbO/Nb<sup>38</sup>; in fact, not only silicon and carbon can be detected on the SiC surface, but also  
5 a thin layer of SiO<sub>2</sub>. These reaction layers (carbides and silicides) have been found also by other authors at  
6 the Ta/SiC, Mo/SiC, Zr/SiC interfaces.<sup>39,40</sup> Nevertheless, the data reported in literature refer to temperature  
7 comparable with that used in our joining process (1450°C), but the solid-state diffusive reaction at SiC/RM  
8 interface involved dwelling time from few hours to hundreds of hours.<sup>40,41</sup> Moreover, the absence of applied  
9 pressure during the “refractory metal (RM) – wrap” joining process does not foster the diffusive process at  
10 the interface. Furthermore, the presence of Si at the interface can hinder the formation of carbides; for  
11 instance, in case of Mo, it has been reported<sup>42</sup> that Si diffuses towards Mo faster than C, thus leading to  
12 silicides formation.  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25

26 In conclusion, the formation of a distinct layer of RM-carbide layer (i.e. MC<sub>x</sub> or MSi<sub>y</sub>C<sub>z</sub>) was not observed up  
27 to now in our joined samples, but it cannot be ruled out that, immediately adjacent to SiC, a nano-layer of  
28 carbide exists.  
29  
30  
31  
32

33 In order to evaluate their oxidation resistance and thermal stability, SiC joined by Mo-, Nb- and Ta-Wraps  
34 were tested at 1100 °C for 6 hours in air; this thermal treatment simulates possible operating conditions for  
35 SiC-based components in aerospace<sup>43</sup> and the creep of the silicon matrix advises against their use at higher  
36 temperatures. The FESEM analysis of the cross-sections of the joints after the oxidation tests is shown in  
37 Figure 1(d) (Mo-Wrap), Figure 2(c) (Nb-Wrap) and Figure 3 (c) (Ta-Wrap).  
38  
39  
40  
41  
42  
43  
44

45 All the joints were apparently not affected by this preliminary heat treatment, since no cracks, debonding or  
46 formation of new phases (i.e. SiO<sub>2</sub><sup>44</sup>) were observed. Actually, it was reported that MoSi<sub>2</sub> forms gaseous  
47 oxidation products and silica at 1100 °C, but none of them have been detected in this work. It is possible that  
48 a negligible silica layer was polished away during sample preparation. It must be underlined that the oxidation  
49 of MoSi<sub>2</sub> is a very complex process. In the temperature range of 375° to 600°C, MoO<sub>3</sub> whiskers and SiO<sub>2</sub>  
50 clusters will form, causing the disintegration of bulk MoSi<sub>2</sub> (pesteing). At higher temperatures, MoO<sub>3</sub> is  
51 volatile.<sup>45,46</sup> However, none of these reactions were observed during Mo-wrap joining.  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 Mo-Wrap was successful and for the first time used to join oxide-based ceramics: alumina-to-alumina (Figure  
4 6 a) and mullite to SiC joints (Figure 6 b).

5  
6  
7  
8 The coefficient of thermal expansion (CTE) for the RM-wrap joining materials ( $\text{MoSi}_2/\text{Si}$ ,  $\text{NbSi}_2/\text{Si}$ ,  $\text{TaSi}_2/\text{Si}$ ,  
9 and  $\text{ZrSi}_2/\text{Si}$ ), calculated by the rule of mixture according to their composition <sup>47</sup> and the RM-wrap  
10 compositions ( as volume ratio between RM silicides and silicon) are summarized in Table 1, also showing  
11 those of the joined materials for comparison purposes: except Ta-wrap, all the other wraps range at about  
12  $3.9 - 4.5 \times 10^{-6} \text{ }^\circ\text{C}^{-1}$ , making them suitable joining materials for SiC-carbide based materials. Ta-wrap, with a  
13 CTE of about  $6.3 \times 10^{-6} \text{ }^\circ\text{C}^{-1}$  may offer interesting opportunities for alumina-to-mullite or alumina-to-SiC joints,  
14 given its intermediate value: research is ongoing on this respect.

15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
Despite of the CTE mismatch with alumina, no cracks in the joining material or debonding at the joining  
material/alumina and joining material/mullite interfaces were observed (Figure 6) . There might be several  
possible uses of this joining technology for alumina-based components and these mullite-to-SiC joints could  
be used to obtain thermal barrier coatings in various high temperature applications.

In order to calculate the thermal diffusivity of the sample, the Cape-Lehman model was used<sup>48</sup>, which  
consider a two-dimensional heat flow and the heat loss to evaluate the radiation effect above 500 °C.  
Moreover, the convection from the test sample to the ambient gas flow was taken into account. The thermal  
diffusivity of the  $\text{MoSi}_2/\text{Si}$  pellet ranges between 38 mm<sup>2</sup>/s at room temperature and 8 mm<sup>2</sup>/s at 1000°C, as  
shown in Figure 7 (a). The decrease *versus* temperature increase is most likely due to phonon scattering  
enhancement at higher temperatures. The standard deviation of the thermal diffusivity values for each  
temperature point is in the order of magnitude of 0.1 mm<sup>2</sup>/s.

The specific heat of the  $\text{MoSi}_2/\text{Si}$  pellet was measured by using a reference sample (i.e. Poco Graphite Serial  
Nr. 21517): it ranges between 0.63 J/gK at room temperature and 0.89 J/gK at 1000°C as shown in Figure 7  
(b). Finally, the thermal conductivity of the  $\text{MoSi}_2/\text{Si}$  pellet was calculated and varies between 77 W/mK at  
RT and 24W/(mK) at 1000 °C, Figure 7 (c). The thermal conductivity values of the  $\text{MoSi}_2/\text{Si}$  pellet is higher

1  
2  
3 than those available in the literature for the  $\text{MoSi}_2$ <sup>49,50</sup>, most likely due to the contribution of the silicon  
4  
5 matrix.

6  
7  
8 The mechanical strength of the RM-Wrap SiC joints was measured at room temperature using three different  
9  
10 tests: (i) single lap (SL), (ii) single lap off-set (SLO) and (iii) torsion on hourglass shaped samples (THG). It is  
11  
12 worth mentioning that all the SiC joints did not break during the single lap tests (SL, SLO): the specimen were  
13  
14 detached from the aluminium fixtures during the SL test, or SiC crushed during SLO tests. As a consequence,  
15  
16 it was not possible to measure their joint strength by means of these lap tests.

17  
18  
19  
20 As previously reported<sup>51</sup>, lap shear tests (SL and SLO) are useful for comparative purposes, i.e. when the  
21  
22 joining strength of a similar set of samples is to be compared. Moreover, the results in case of brittle materials  
23  
24 are strongly related to the size and the shape of joined samples and fixtures. Both SL and SLO has been found  
25  
26 inappropriate for measuring the RM-Wrap joint strength of SiC-based samples: even though the specimens  
27  
28 mostly failed in the fixtures rather than in the joining seam, this behaviour might be due to a high stress  
29  
30 concentration close to the joined region, rather than a high mechanical strength of the joint. Due to this  
31  
32 uncertainty, SL and SLO tests were replaced by torsion test.

33  
34  
35  
36 The torsion test can properly measure the shear strength of brittle joined materials, but the shear strength  
37  
38 can only be calculated when the failure starts and propagates inside the joining material. If this is not the  
39  
40 case, then either the test method is not correctly done, or the substrate and joint strength are similar. A  
41  
42 custom-made torsional testing machine built at Politecnico di Torino in 2006 was used to test the different  
43  
44 joints in torsion: details and comparison with other tests can be found in<sup>33</sup>.

45  
46  
47  
48 In this work, SiC hourglasses of two different sizes (4 and 5 mm in diameter) were joined by Mo-Wrap, and  
49  
50 named as THG-4 and THG-5 respectively. The fractured surfaces after torsion test are shown in Figure 8 (b,c):  
51  
52 the fracture initiates and propagates inside the SiC substrates, as evidenced in particular in Figure 8(c): the  
53  
54 hourglass is partially crushed after torsion and some SiC parts are missing, leaving an irregular shape (see  
55  
56 "SiC surface" with red arrows in Figure 8(c)). This can be due to a certain misalignment of hourglasses joined  
57  
58 one by one by Mo-wrap, thus giving to mixed mode loads together with torsion one. To obtain a reliable  
59  
60

1  
2  
3 shear value with torsion, the joints must be perfectly aligned: a few micrometres lateral shift in sample  
4  
5 position may result in mixed shear along with bending load, thus unreliable results ranging between 21-32  
6  
7 MPa.  
8

9  
10 ~~In order to understand if this fracture behaviour under torsion was due to a sample misalignment during the~~  
11 ~~joining process or to the similar mechanical strength of both~~, some joined SiC tiles (Figure 9 a) were prepared,  
12  
13 machined to obtain hourglasses (Figure 9 b) and then tested in torsion. In this case the fracture propagated  
14  
15 inside the joined area only (Figure 9 c, d), probably initiated by a macroscopic defect induced in the joined  
16  
17 region by machining; ~~the machining of a brittle joining material such as a RM-disilicide reinforced silicon~~  
18  
19 ~~matrix composite, may induce significant defects (cracks, disilicides detachment from the silicon matrix, etc..)~~  
20  
21 ~~on the external region of the joint, thus affecting the mechanical strength of the joints.~~  
22  
23  
24  
25

26 However, the obtained values of  $14 \pm 5$  MPa, with a partially cohesive/adhesive fracture (Figure 9 c, d) is at  
27  
28 the moment the only pure shear strength result available for these joints at room temperature. Further tests  
29  
30 are ongoing to completely characterize the mechanical strengths of them by other mechanical tests and at  
31  
32 higher temperature.  
33  
34

35  
36 ~~The X-ray diffraction analysis on fracture surfaces after mechanical tests, confirmed the formation of RM~~  
37  
38 ~~disilicides and silicon as the only phases, as already reported in<sup>1</sup> for RM-Wrap joined C/SiC.~~  
39  
40  
41  
42  
43  
44

## 45 Conclusions

46  
47 A pressure-less tailorable joining technique named "RM-Wrap" (Refractory metals = RM, i.e. Mo, Nb, Ta, Zr)  
48  
49 was successfully used to join SiC, alumina and mullite. Morphological analyses showed continuous, crack free  
50  
51 and well bonded interfaces with a joining microstructure consisting of *in-situ* formed composites made of a  
52  
53 silicon rich matrix with disilicides of molybdenum ( $\text{MoSi}_2$  in case of Mo-Wrap), niobium ( $\text{NbSi}_2$  in case of Nb-  
54  
55 Wrap), tantalum ( $\text{TaSi}_2$  in case of Ta-Wrap) and zirconium ( $\text{ZrSi}_2$  in case of Zr-wrap). Thermal and oxidation  
56  
57 stability of SiC joints were carried out at 1100 °C for 6 hours. FESEM analysis before and after this thermal  
58  
59 ageing showed unaffected joint interfaces and microstructure. CTE have been calculated for all RM-wraps  
60

1  
2  
3 and thermal diffusivity, thermal conductivity and specific heat have been measured or calculated for  
4  
5 MoSi<sub>2</sub>/Si.  
6  
7

8 SiC joints were mechanically tested in three different modes SL in compression, SLO in compression and  
9  
10 torsion on hourglass shaped samples: a shear strength of  $14 \pm 5$  MPa was measured at room temperature by  
11  
12 torsion on Mo-wrap joined SiC hourglass samples, only when obtained by machining from a joined tile.  
13  
14

15 For the first time, refractory metal disilicides based materials have been exploited in joining of SiC, alumina  
16  
17 and mullite. It can be concluded that RM-Wrap joining offers many attractive advantages and its scope can  
18  
19 be further extended: a summary of all RM-wrap joints obtained until now is shown in Figure 10.  
20  
21

## 22 23 24 **Acknowledgements**

25  
26 **The research leading to these results has received funding from the European Union's Horizon 2020 research**  
27  
28 **and innovation programme under grant agreement No 721045- Project "NEXTOWER" advanced materials**  
29  
30 **solutions for next-generation high efficiency concentrated solar power (CSP) tower systems.**  
31  
32

## 33 34 35 **References**

- 36  
37  
38  
39 [1] Boch P, Chartier T. Alumina, mullite and spinel, zirconia (Ch 6). In: Boch P, Niepce J-C, editors.  
40  
41 Ceramic Materials: Processes, Properties and Applications. ISTE Publication; 2007.  
42  
43 [2] Torrecillas R, Calderón J M, Moya J S, Reece M J, Davies C K L , Olagnon C, Fantozzi G. Suitability of  
44  
45 mullite for high temperature applications, J Eur Ceram Soc. 1999; 19: 2519-2527.  
46  
47 [3] Bansal N P, Lamon J. Ceramic Matrix Composites: Materials, Modeling and Technology. John Wiley  
48  
49 & Sons; 014.  
50  
51 [4] Ferraris M. Joining and Machining of CMCs. In: Beaumont P W R, Zweben C H, editors.  
52  
53 Comprehensive Composite Materials II. Elsevier, Oxford. 2018; 293-307.  
54  
55 [5] Singh M, Kondo N, Asthana R. Chapter 12 - Manufacturing of Ceramic Components using Robust  
56  
57 Integration Technologies, Green and Sustainable Manufacturing of Advanced Material. Elsevier,  
58  
59 Oxford. 2016; 295-308.  
60

- 1  
2  
3 [6] Krenkel W, Henke T, Mason N. In-situ joined CMC components. Key Engineering Materials, Trans  
4 Tech Publ. 1997; 313-320.  
5  
6  
7 [7] Singh M. A reaction forming method for joining of silicon carbide-based ceramics. Scripta Mater.  
8 1997; 37[8]: 1151-1154.  
9  
10  
11 [8] Katoh Y, Kohyama A, Nozawa T, Sato M. SiC/SiC composites through transient eutectic-phase route  
12 for fusion applications. J Nucl Mat. 2004; 329: 587-59.  
13  
14  
15 [9] Shimoda K, Hinoki T, Kohyama A. Effect of additive content on transient liquid phase sintering in SiC  
16 nanopowder infiltrated SiCf/SiC composites. Compos Sci Technol. 2011; 71(5): 609-615.  
17  
18  
19 [10] Fan J, Chen L, Bai S, Shi X. Joining of Mo to CoSb<sub>3</sub> by spark plasma sintering by inserting a Ti  
20 interlayer. Mater Lett. 2004; 58 (30) :3876-3878.  
21  
22  
23 [11] Rizzo S, Grasso S, Salvo M, Casalegno V, Reece M J, Ferraris M. Joining of C/SiC composites by spark  
24 plasma sintering technique. J Eur Cer Soc. 2014; 34 (4): 903-913.  
25  
26  
27 [12] Lippmann W, Knorr J, Wolf R, Rasper R, Exner H, Reinecke A M, Nieher M, Schreiber R. Laser  
28 joining of silicon carbide—a new technology for ultra-high temperature resistant joints. Nucl Eng  
29 Des. 2004; 231 (29): 151-161.  
30  
31  
32 [13] Aravindan S, Krishnamurthy R. Microwave Joining of Al<sub>2</sub>O<sub>3</sub>-ZrO<sub>2</sub> Composites. 1999. Paper  
33 presented at: 23<sup>rd</sup> Annual Conference on Composites, Advanced Ceramics, Materials, and  
34 Structures: B: Ceramic Engineering and Science Proceedings. Wiley Online Library. 1999; 71-78.  
35  
36  
37 [14] Radhakrishnan R, Bhaduri S, Henager Jr C, Brimhall J. Synthesis of Ti<sub>3</sub>SiC<sub>2</sub>S/SiC and TiSi<sub>2</sub>/SiC  
38 composites using displacement reactions in the Ti-Si-C system. Scripta Mater. 1996; 34 (12).  
39  
40  
41 [15] MacDonald W, Eagar T. Transient liquid phase bonding. Annu Rev Mater Res. 1992; 22 (1): 23-46.  
42  
43  
44 [16] Ferraris M, Salvo M, Isola C, Appendino Montorsi M, Kohyama A. Glass-ceramic joining and coating  
45 of SiC/SiC for fusion applications. J Nucl Mat. 1998; 258-263 (PART 2 B): 1546-1550.  
46  
47  
48 [17] Gianchandani P K, Casalegno V, Salvo M, Ferraris M, Dlouhý I. Refractory Metal, RM – Wrap: a  
49 tailorable, pressure-less joining technology. Ceram Int. 2019; 45(4): 4824-4834.  
50  
51  
52 [18] Gianchandani P K, Casalegno V, Smeacetto F, Ferraris M. Pressure-less joining of C/SiC and SiC/SiC  
53 by a MoSi<sub>2</sub>/Si composite. Int J Appl Ceram Tec. 2017; 14 (3): 305-312.  
54  
55  
56  
57  
58  
59  
60

- 1  
2  
3 [19] Gianchandani P K, Casalegno V, Salvo M, Bianchi G, Ortona A, Ferraris M. SiC foam sandwich  
4 structures obtained by Mo-wrap joining. *Mater Lett.* 2018; 221: 240-243.  
5  
6  
7 [20] Prasad N E, Wanhill R. *Aerospace Materials and Material Technologies.* Springer, Singapore; 2017.  
8  
9  
10 [21] Wiltner B, Klöden T, Weißgärber T, Hutsch, Kieback B, Reaction temperatures within Mo–Si powder  
11 mixtures and their influencing factors. *Int J Refract Met H.* 2013; 37: 73-81.  
12  
13  
14 [22] Okamoto H, Mo-Si (Molybdenum-Silicon). *J Phase Equilib Diff.* 2011; 32 (2) : 176-176.  
15  
16  
17 [23] Cherniack G B, Elliot A G. High-Temperature Behavior of MoSi<sub>2</sub> and Mo<sub>5</sub>Si<sub>3</sub>. *J Am Cer Soc.* 1964; 47  
18 (3): 136-141.  
19  
20  
21 [24] Schlesinger M E, Okamoto H, Gokhale A B, Abbaschian R. The Nb-Si (Niobium-Silicon) system. *J*  
22 *Phase Equilib.* 1993; 14 (4): 502-509.  
23  
24  
25 [25] Todai M, Hagihara K, Kishida K, Inui H, Nakano T. Microstructure and fracture toughness in boron  
26 added NbSi<sub>2</sub>(C40)/MoSi<sub>2</sub>(C11b) duplex crystals *Scripta Mater.* 2016; 113 [Supplement C] 236-240.  
27  
28  
29 [26] Yeh C L, Wang H J. A comparative study on combustion synthesis of Ta–Si compounds.  
30 *Intermetallics.* 2007; 15 (10) : 1277-1284.  
31  
32  
33  
34 [27] Okamoto H. The Si-Zr (Silicon-Zirconium) system. *J Phase Equilib.* 1990; 11 (5): 513-519.  
35  
36  
37 [28] ASTM E 1461-13, Standard test method for thermal diffusivity by the flash method, 2013.  
38  
39 [29] ASTM E 2585-09, Standard practice for thermal diffusivity by the laser flash, 2009.  
40  
41 [30] Parker W, Jenkins R, Butler C, Abbott G. Flash method of determining thermal diffusivity, heat  
42 capacity, and thermal conductivity. *J Appl Phys.* 1961; 32 (9): 1679-1684.  
43  
44  
45 [31] Ferraris M, Ventrella A, Salvo M, Avalle M, Pavia F, Martin E. Comparison of shear strength tests on  
46 AV119 epoxy-joined carbon/carbon composites. *Compos Part B-Eng.* 2010; 41 (2): 182-191.  
47  
48  
49 [32] ASTM D905-D908, Standard Test Method for Strength Properties of Adhesive Bonds in Shear by  
50 Compression Loading. 2013; ASTM Int., West Conshohocken, PA USA  
51  
52  
53  
54 [33] Ferraris M, Salvo M, Rizzo S, Casalegno V, Han S, Ventrella A, Hinoki T, Katoh Y. Torsional shear  
55 strength of silicon carbide components pressurelessly joined by a glass-ceramic. *Int J Appl Ceram*  
56 *Tec.* 2012; 9 (4): 786-794.  
57  
58  
59  
60

- 1  
2  
3 [34]Zhang Y, Ni W, Li Y. Effect of siliconizing temperature on microstructure and phase constitution of  
4  
5 Mo–MoSi<sub>2</sub> functionally graded materials. *Ceram Int.* 2018; 44[10]: 11166-11171.  
6  
7 [35]Naikade M, Fankhänel B, Weber L, Ortona A, Stelter M, Graule T. Studying the wettability of Si and  
8  
9 eutectic Si-Zr alloy on carbon and silicon carbide by sessile drop experiments. *J Eur Cer Soc.* 2019;  
10  
11 39 (4): 735-742.  
12  
13 [36] Chou T C, Joshi A. High temperature interfacial reactions of SiC with metals, *J Vac Sci Technol A.*  
14  
15 1991; 9: 1525.  
16  
17 [37] Cockeram, B.V.,The diffusion bonding of silicon carbide and boron carbide using refractory metals,  
18  
19 ASM Materials Solution 99: International Conference on Joining of Advanced and Specialty Metals  
20  
21 and Advances in Surface Engineering; Cincinnati, OH (United States); 1999, 31(1) , 42 (1).  
22  
23 [38] Yaney D L, Joshi A. Reaction between niobium and silicon carbide at 1373 K J. *Mater. Res.* 1990; 5  
24  
25 (10) .  
26  
27 [39] Burkyna A L, Strashinskaya L V, Evtushok T M. Investigation of the interaction of silicon carbide with  
28  
29 refractory metals and oxides *Fiziko-Khimicheskaya Mekhanika Materialov.* 1968; 4 (3) : 301-305.  
30  
31 [40] Bhanumurthy K, Schmid-Fetzer R. Interface reaction between silicon carbide and metals (Ni, Cr, Pd,  
32  
33 Zr) *Compos: Part A* . 2001; 32: 569–574.  
34  
35 [41] Joshi A, Hu SH, Wadsworth J. Interfacial reaction of refractory metals niobium and tantalum with  
36  
37 ceramics silicon carbide and alumina, *Mat. Res. Soc. Symp.* 1990; 170.  
38  
39 [42]Martinelli A, Drew R. Microstructural development during diffusion bonding of a silicon carbide to  
40  
41 molybdenum. *Mat Sci Eng A.* 1995; 191:239–247.  
42  
43 [43]Triantou K I, Mergia K, Perez B, Florez S, Stefan A, Ban C, Pelin G, Ionescu G, Zuber C, Fischer W  
44  
45 P P , BarcenaJ . Thermal shock performance of carbon-bonded carbon fiber composite and ceramic  
46  
47 matrix composite joints for thermal protection re-entry applications. *Compos Part B-Eng.* 2017; 111:  
48  
49 270-278.  
50  
51 [44] Zhu Y T, Stan M, Conzone S D, Butt D P. Thermal oxidation kinetics of MoSi<sub>2</sub>-based powders. *J Am*  
52  
53 *Ceram Soc.* 1999; 82 (10): 2785-2790.  
54  
55  
56  
57  
58  
59  
60

- 1  
2  
3 [45] Sheikh S, Bijaksana M K, Motallebzadeh A, Shafeie S, Lozinko A, Gan L , Tsao T K , Klement U,  
4  
5 Canadinc D, Murakami H, Guo S. Accelerated oxidation in ductile refractory high-entropy alloys,  
6  
7 Intermetallics. 2018; 97:58-66.  
8  
9  
10 [46] Chou T C, Nieh T G. Mechanism of MoSi<sub>2</sub> pest during low temperature oxidation. J Mater Res. 2016;  
11  
12 8 (1) : 214-226.  
13  
14 [47] Bruck H A, Rabin B H. Evaluation of Rule-of-Mixtures Predictions of Thermal Expansion in Powder-  
15  
16 Processed Ni–Al<sub>2</sub>O<sub>3</sub> Composites. J Am Ceram Soc. 1999; 82 (10): 2927-2930.  
17  
18 [48] Cape J, Lehman G. Temperature and finite pulse-time effects in the flash method for measuring  
19  
20 thermal diffusivity. J Appl Phys. 1963; 34 (7): 1909-1913.  
21  
22 [49] Bose S, Hecht R J. Thermal properties of MoSi<sub>2</sub> and SiC whisker-reinforced MoSi<sub>2</sub>. J Mater Sci. 1992;  
23  
24 27 (10): 2749-2752.  
25  
26 [50] Mohamad, Ohishi Y, Muta H, Kurosaki K, Yamanaka S. Thermal and Mechanical Properties of α-  
27  
28 MoSi<sub>2</sub> as a High-Temperature Material. Phys Status Solidi (b), 2018. 255(4): 1700448.  
29  
30 [51] Ventrella A, Salvo M, Avalle M, Ferraris M. Comparison of shear strength tests on AV119 epoxy-  
31  
32 joined ceramics (2010) J Mat Sci 45 (16), pp. 4401-4405.  
33  
34 [52] Ferraris M, Salvo M, Rizzo S, Casalegno V, Han S, Ventrella A, Hinoki T, Katoh Y. Torsional shear  
35  
36 strength of silicon carbide components pressurelessly joined by a glass-ceramic. Int J Appl Ceram  
37  
38 Tec. 2012; 9 (4): 786-794.  
39  
40 [53] Engstrom I, Lönnberg T B. Thermal expansion studies of the group IV-VII transition-metal disilicides,  
41  
42 J Appl Phys. 1988; 63: 4476.  
43  
44 [54] [http://www.bettinitextile.it/ENG/2\\_Materials\\_05.htm](http://www.bettinitextile.it/ENG/2_Materials_05.htm)  
45  
46  
47  
48  
49 [55] MatWeb Material Property data, 2019. <http://www.matweb.com/search/PropertySearch.aspx>.  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

	CTE [ $10^{-6} \text{ }^{\circ}\text{C}^{-1}$ ]	% vol $\text{MSi}_2/\text{Si}$
<b>MoSi<sub>2</sub>/Si</b>	3.9	33.8/66.2
<b>NbSi<sub>2</sub>/Si</b>	3.9	29.4/70.6
<b>TaSi<sub>2</sub>/Si</b>	6.3	61.2/38.8
<b>ZrSi<sub>2</sub>/Si</b>	4.5	34.2/65.8
<b>SiC</b>	3.8 <sup>54</sup>	
<b>Al<sub>2</sub>O<sub>3</sub></b>	5.5 <sup>55</sup>	
<b>Mullite</b>	5.0 <sup>55</sup>	
<b>Silicon</b>	2.5 <sup>55</sup>	
<b>MoSi<sub>2</sub></b>	6.8 <sup>53</sup>	
<b>NbSi<sub>2</sub></b>	7.3 <sup>53</sup>	
<b>TaSi<sub>2</sub></b>	8.7 <sup>53</sup>	
<b>ZrSi<sub>2</sub></b>	8.3 <sup>53</sup>	

**Table and Figure captions:**

**Table 1** Coefficient of thermal expansion for the RM-wrap joining materials, calculated according to their composition, (those of the joined materials and silicides for comparison purposes); CTE values at room T, except for SiC (comprised between RT and 400°C)

**Figure 1** SEM Cross-section of SiC joined by Mo-Wrap (a, b), higher magnification of the interface between MoSi<sub>2</sub>/Si and SiC (c); after oxidation test: 1100 °C, 6 hours, in air (d) arrows show the interface between SiC and the *in situ* formed joining material.

**Figure 2** SEM cross section of SiC joined by Nb-Wrap (a, b) and after oxidation test (c): 1100 °C, 6 hours, in air, particular of the interface between *in situ* formed NbSi<sub>2</sub>/Si composite and SiC

**Figure 3** SEM cross section of SiC joined by Ta-Wrap (a, b) and after oxidation test (c): 1100 °C, 6 hours, in air, particular of the interface between *in situ* formed NbSi<sub>2</sub>/Si composite and SiC

**Figure 4** SEM cross section of SiC joined by Zr-Wrap; the joining material shows a typical eutectic microstructure with needle-shaped Si-Zr phase within the Si matrix

**Figure 5** Silicon-zirconium phase diagram with indicated the composition used for the Zr-wrap joint.


**Figure 6** SEM cross-section of alumina (a) and of SiC joined to mullite by Mo-Wrap (b)

**Figure 7** Thermal diffusivity (a) measured by Laser Flash Method and calculated specific heat (b) and thermal conductivity (c) versus temperature for a MoSi<sub>2</sub>/Si pellet of about 11.6 mm diameter, 2.6 mm thickness


**Figure 8** Torsion test on Mo-Wrap joined SiC hourglass (a), fracture surfaces after test at room temperature (b, c)

**Figure 9** Mo-Wrap joined SiC tiles (35 mm x 5 mm x 4 mm) (a), machined to obtain hourglasses (b), fracture surfaces after test at room temperature (c, d)

**Figure 10** Summary of Wrap technology options for joining of ceramics and CMCs; RM= Refractory Metals. In the case of CMC, *coated* or *uncoated* means with or without the CVD (Chemical Vapour Deposition) SiC coating usually deposited on these materials.

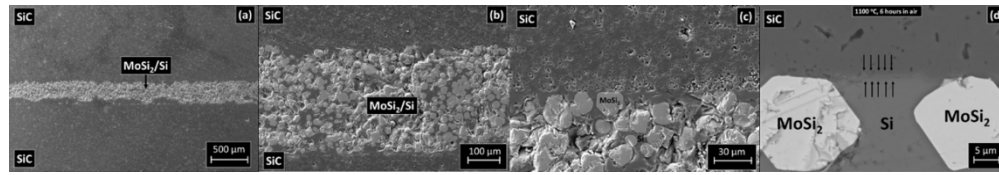


SEM Cross-section of SiC joined by Mo-Wrap (a,b), higher magnification of the interface between MoSi<sub>2</sub>/Si and SiC (c); after oxidation test: 1100 °C, 6 hours, in air (d) arrows show the interface between SiC and the in situ formed joining material.

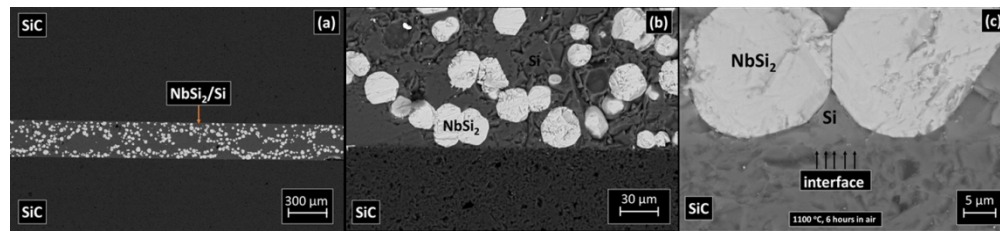


SEM cross section of SiC joined by Nb-Wrap (a, b) and after oxidation test (c): 1100 °C, 6 hours, in air, particular of the interface between in situ formed NbSi<sub>2</sub>/Si composite and SiC


1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

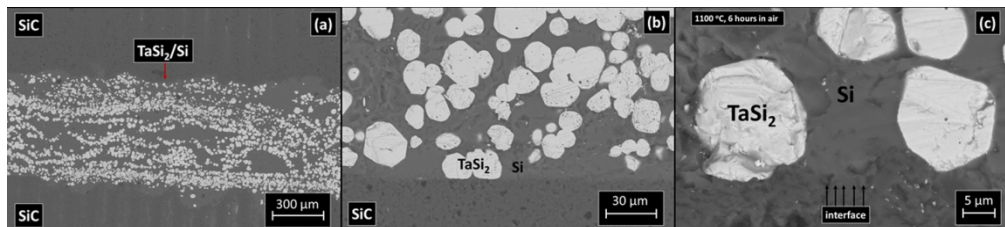


SEM cross section of SiC joined by Ta-Wrap (a, b) and after oxidation test (c) : 1100 °C, 6 hours, in air, particular of the interface between in situ formed TaSi<sub>2</sub>/Si composite and SiC

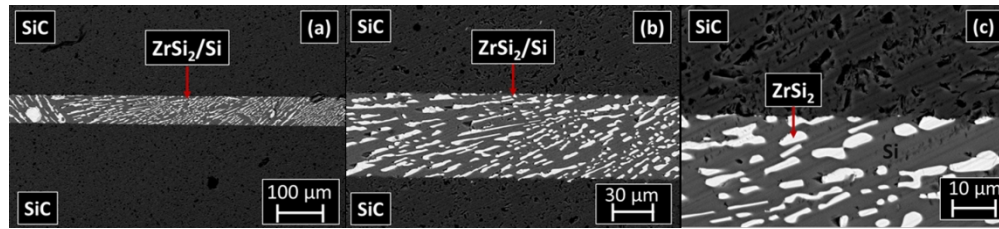


SEM cross section of SiC joined by Zr-Wrap; the joining material shows a typical eutectic microstructure with needle-shaped Si-Zr phase within the Si matrix

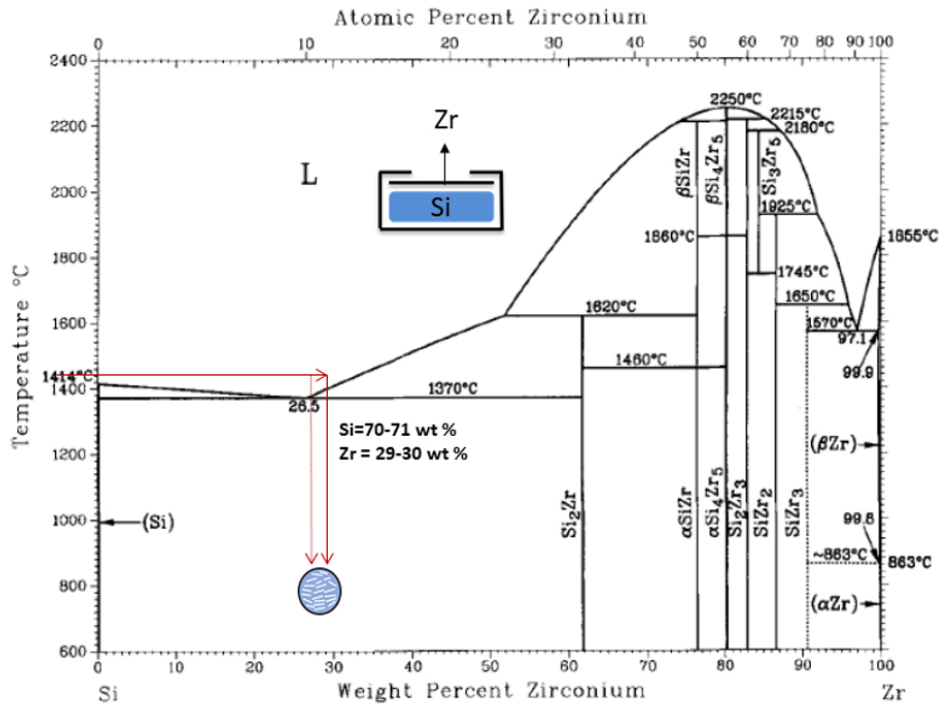


Silicon-zirconium phase diagram with indicated the composition used for the Zr-wrap joint.

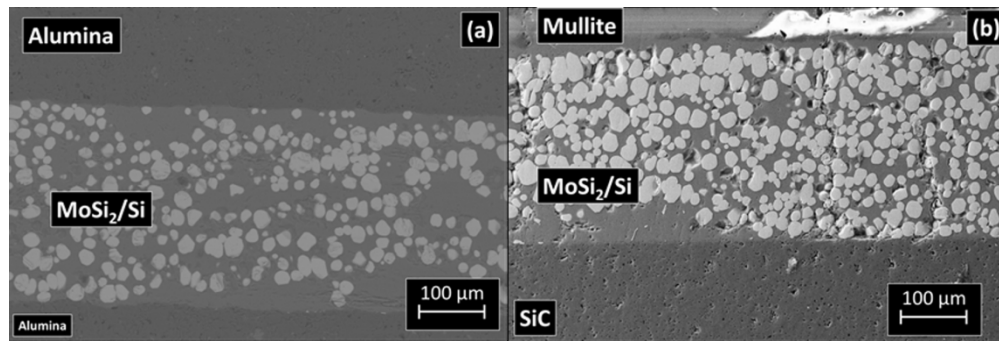

SEM cross-section of alumina (a) and of SiC joined to mullite by Mo-Wrap (b)

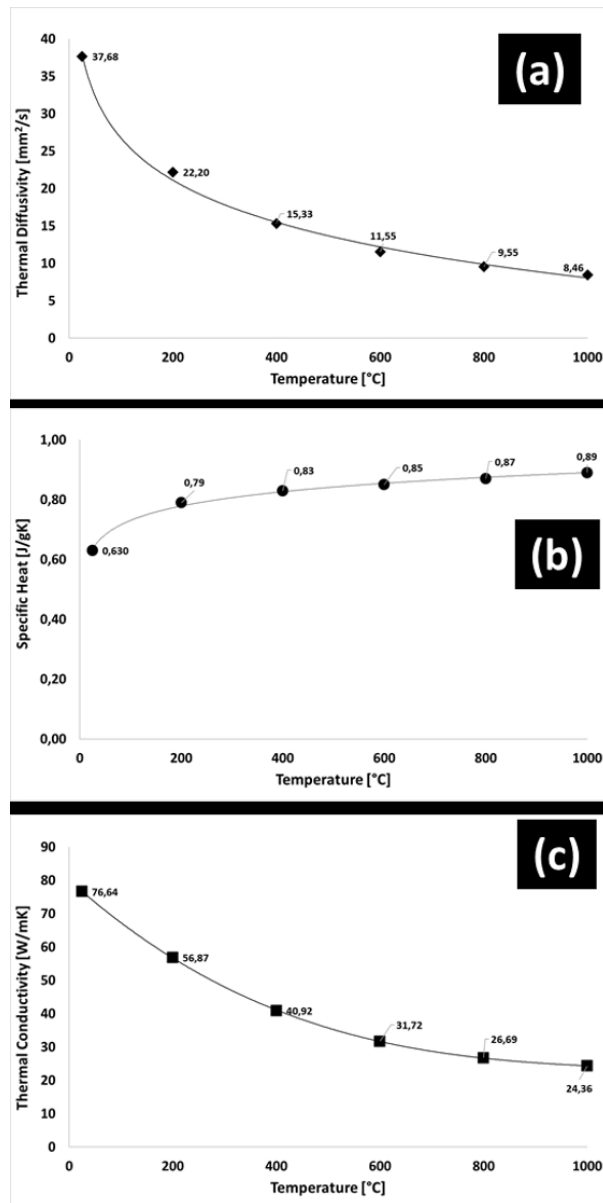


Thermal diffusivity (a) measured by Laser Flash Method and calculated specific heat (b) and thermal conductivity (c) versus temperature for a  $\text{MoSi}_2/\text{Si}$  pellet of about 11.6 mm diameter, 2.6 mm thickness

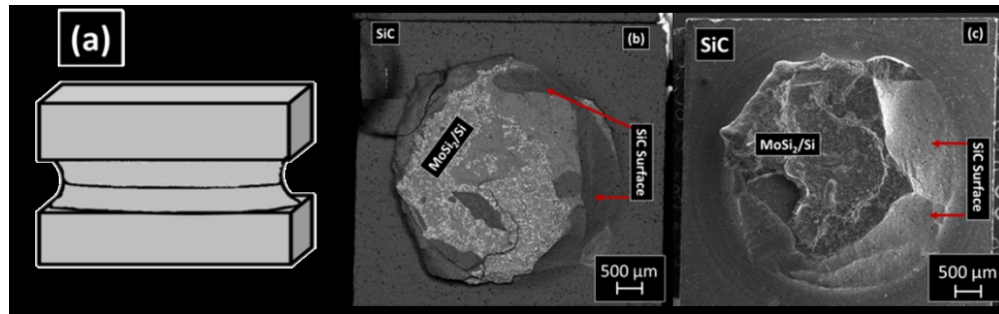


Torsion test on Mo-Wrap joined SiC hourglass (a), fracture surfaces after test at room temperature (b,c)

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

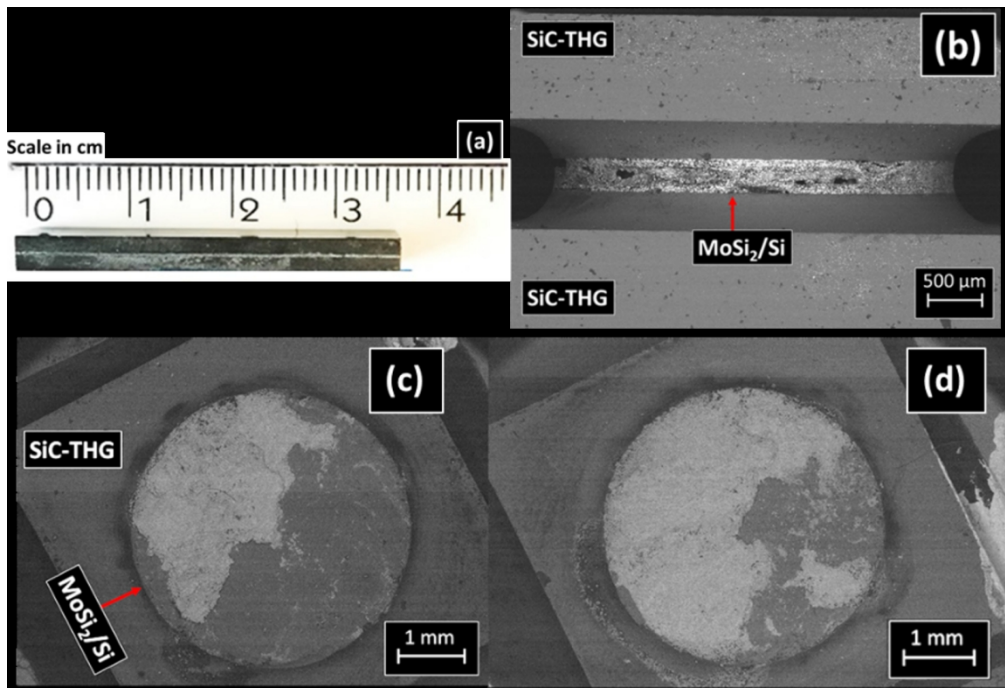

Mo-Wrap joined SiC tiles (35 mm x 5 mm x 4 mm) (a), machined to obtain hourglasses (b), fracture surfaces after test at room temperature (c, d)

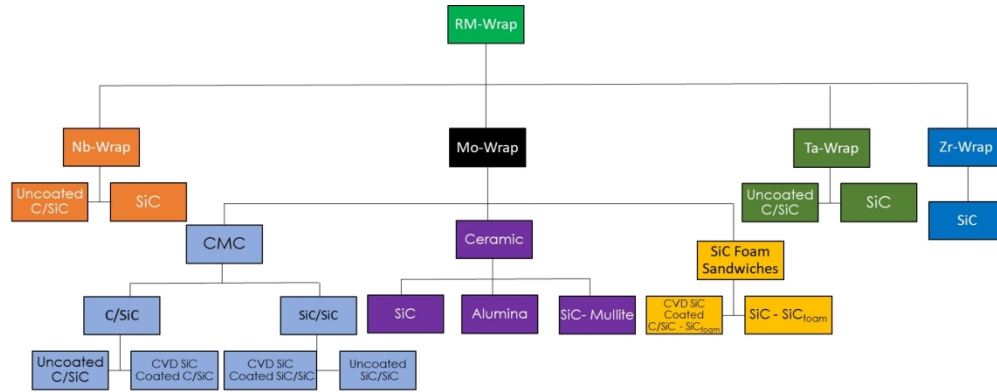

Summary of Wrap technology options for joining of ceramics and CMCs; RM= Refractory Metals. In the case of CMC, coated or uncoated means with or without the CVD (Chemical Vapour Deposition) SiC coating usually deposited on these materials.

336x131mm (149 x 149 DPI)