

Analysis of multiple protein detection methods in human osteoporotic bone  
extracellular matrix: From literature to practice

*Original*

Analysis of multiple protein detection methods in human osteoporotic bone  
extracellular matrix: From literature to practice / Licini, Caterina; Montalbano, Giorgia; Ciapetti, Gabriela; Cerqueni,  
Giorgia; VITALE BROVARONE, Chiara; Mattioli-Belmonte, Monica. - In: BONE. - ISSN 8756-3282. - ELETTRONICO. -  
137:115363(2020). [10.1016/j.bone.2020.115363]

*Availability:*

This version is available at: 11583/2844051 since: 2020-09-04T09:47:50Z

*Publisher:*

Elsevier

*Published*


DOI:10.1016/j.bone.2020.115363

*Terms of use:*

This article is made available under terms and conditions as specified in the corresponding bibliographic description in  
the repository

*Publisher copyright*

(Article begins on next page)



## Full Length Article

# Analysis of multiple protein detection methods in human osteoporotic bone extracellular matrix: From literature to practice



Caterina Licini<sup>a,b</sup>, Giorgia Montalbano<sup>a</sup>, Gabriela Ciapetti<sup>c</sup>, Giorgia Cerqueni<sup>b</sup>, Chiara Vitale-Brovarone<sup>a,\*</sup>, Monica Mattioli-Belmonte<sup>b</sup>

<sup>a</sup> Department of Applied Science and Technology, Politecnico di Torino, Corso Duca degli Abruzzi 24, 10129 Torino, Italy

<sup>b</sup> Department of Clinical and Molecular Sciences (DISCLIMO), Università Politecnica delle Marche, Via Tronto 10/A, 60126 Ancona, Italy

<sup>c</sup> Laboratorio di Fisiopatologia Ortopedica e Medicina Rigenerativa, Istituto Ortopedico Rizzoli, IRCCS, Via di Barbiano 1/10, 40136 Bologna, Italy

## ARTICLE INFO

## Keywords:

Bone ECM  
Protein detection  
Osteoporosis  
Protein extraction  
Proteomics

## ABSTRACT

The punctual analysis of bone Extracellular Matrix (ECM) proteins represents a pivotal point for medical research in bone diseases like osteoporosis. Studies in this field, historically done to appreciate bone biology, were mainly conducted on animal samples and, up to today, only a few studies on protein detection in human bone are present. The challenges in bone ECM protein extraction and quantitation protocols are related to both the separation of proteins from the mineral content (i.e. hydroxyapatite) and the difficulty of avoiding protein denaturation during the extraction processes. The aim of the present work was to define appropriate protocol(s) for bone ECM protein extraction that could be applied to investigate both normal and pathological conditions. We compared and optimised some of the most used protocols present in the literature, modifying the protein precipitation method, the buffer used for resuspension and/or the volume of reagent used. Bradford and BCA assays and Western Blotting were used to evaluate the variations in the total protein recovery and the amount of selected proteins (Type I Collagen, TGF- $\beta$ , IGF-1, Decorin, Osteopontin, Bone Sialoprotein-2 and Osteocalcin). Collectively, we were capable to draw-up two single-extract protocols with optimal recovery and ideal protein content, that can be used for a detailed analysis of ECM proteins in pathological bone samples. Time-consuming multi-extract procedures, optimised in their precipitation methods, are however crucial for a precise detection of specific proteins, like osteocalcin. As the matter of fact, also the demineralization processes, commonly suggested and performed in several protocols, could hinder an accurate protein detection, thus inherently affecting the study of a pathological bone ECM. This study represents a starting point for the definition of appropriate strategies in the study of bone extracellular matrix proteins involved in the onset and maintenance of bone diseases, as well as a tool for the development of customized scaffolds capable to modulate a proper feedback loop in bone remodelling, altered in case of diseases like osteoporosis.

## 1. Introduction

Bone is composed of 2 phases: approximately 75% wt. inorganic and 25% wt. organic. The inorganic phase contains water and mineral, whereby the main component is hydroxyapatite (HA) constituted by crystalline nanoplatelets containing  $\text{Ca}^{2+}$  and  $\text{PO}_4^{3-}$ . The organic phase comprises cells and molecules of the extracellular matrix (ECM). Type I Collagen is the most abundant protein, constituting about 90% of bone ECM, whereas non-collagenous proteins (NCPs) represent the remaining part [1]. These latter molecules are different in function and chemical feature, and can be grouped in growth factors - like

Transforming Growth Factor-beta (TGF- $\beta$ ) and Insulin-like Growth Factor 1 (IGF-1), glycoproteins - such as Osteopontin (OPN) and Bone Sialoprotein 2 (BSP-2), proteoglycans - like Decorin (DCN), and  $\gamma$ -carboxyglutamic acid-containing proteins - such as Osteocalcin (OCN) [2–7].

The ECM proteins exert an important role in normal bone metabolism and their unbalance could result in bone diseases like osteoporosis. Therefore, the accurate analysis of bone ECM protein content could represent a pivotal point for medical research in this field [8,9]. In the past, the studies that were considered central to the understanding of bone biology were mainly conducted on animals [10–12]. Currently,

*Abbreviations:* HA, hydroxyapatite; ECM, extracellular matrix; NCPs, non-collagenous proteins; Col1a1, Collagen 1 alpha 1 chain; Col1a2, Collagen 1 alpha 2 chain; TGF- $\beta$ , Transforming Growth Factor beta; IGF-1, Insulin-like Growth Factor 1; OPN, Osteopontin; BSP-2, Bone Sialoprotein 2; DCN, Decorin; OCN, Osteocalcin

\* Corresponding author at: Politecnico di Torino, Corso Duca degli Abruzzi 24, 10129 Torino, Italy.

E-mail address: [chiara.vitale@polito.it](mailto:chiara.vitale@polito.it) (C. Vitale-Brovarone).

<https://doi.org/10.1016/j.bone.2020.115363>

Received 24 January 2020; Received in revised form 2 April 2020; Accepted 7 April 2020

Available online 13 April 2020

8756-3282/ © 2020 The Authors. Published by Elsevier Inc. This is an open access article under the CC BY-NC-ND license

(<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

few studies on protein detection in human bone have been published [13,14].

Protein extraction from bone ECM and the consequent analysis are challenging processes, and some issues, such as the separation of proteins from the HA nanocrystals and the ability to prevent their denaturation during the extraction processes, have not been completely solved [15–17]. Another issue that should be addressed is the complete removal of all soft tissues and cells, in order to avoid inaccurate results [18].

The study of proteins from decellularized ECM makes difficult the normalization of Western Blotting results, as the usual normalization process based on the expression of endogenous proteins from the cytoskeleton or cytoplasm (i.e. Actin, Tubulin, or GAPDH) is not appropriate in the decellularized matrix analysis [19].

A variety of reagents with different functions has been employed for protein extraction from the bone tissue. Reagents, such as ethylenediaminetetraacetic acid (EDTA) and hydrochloric acid (HCl), have been used to demineralize bone and recover proteins strictly bonded to HA [20–22]. Solutions containing guanidine hydrochloride (GuHCl) [10,20,21], ammonium phosphate and ammonium bicarbonate [9], glycerol [13,23], or surfactants and detergents, like Triton X-100 and sodium dodecyl sulphate (SDS) [13,23] have also been applied to extract and solubilize proteins from bone ECM.

The aim of this study was to define appropriate protocol(s) for bone ECM protein extraction that correctly analyse the bone protein content and could be applied to investigate a pathological condition such as osteoporosis. We, therefore, compared some of the most used protocols present in the literature in order to obtain 8 different proteins (Col1a1, Col1a2, TGF- $\beta$ , IGF-1, DCN, OPN, BSP-2, OCN) that are implicated in osteoporosis onset and its management [24]. Changes in the protein precipitation method, the buffer used for resuspension and/or the volume of reagents used were tested to evaluate the impact on the total protein recovery and the amount of the selected proteins. Bradford and BCA assays and Western Blotting were performed to estimate the efficiency of each protocol.

## 2. Materials and methods

### 2.1. Sample preparation

Bone samples were obtained from one osteoporotic humeral head [25] discarded during prosthetic replacement of the shoulder prosthesis surgery carried out at Istituto Ortopedico Rizzoli. In accordance with the Local Ethical Committee guidelines and with the 1964 Helsinki declaration, informed consent was obtained. The patient was aware that the tissue used for the study represented a discard from the surgical procedure and voluntarily participated in the study (freedom from coercion or undue influence, real or imagined). The humeral head was mechanically deprived of the majority of the soft tissue, washed in PBS 1 $\times$ , dried and stored at  $-80^{\circ}\text{C}$  until use. Sample treatments were summarized in Fig. 1. Briefly, the bone was broken using a hammer and chisel and 1 g of the sample was collected for each protocol, except for protocol 5 where 100 mg of bone were used. The same starting weight for each sample was used to reduce variations that could influence the protein quantification. To degrease and remove the remaining soft tissues and cells, each sample was immersed in a saline solution at pH 7.2 (0.05 M NaCl, 0.02 M  $\text{NaH}_2\text{PO}_4$ , 0.03 M  $\text{Na}_2\text{HPO}_4$ ) with protease inhibitors, sonicated in ultrasonic bath for 1 min (min) and interposed with 1 min in ice, for 5 cycles overall (modified from [18]).

Samples were then powdered in liquid nitrogen by mortar and pestle and the same weight of powder (i.e. 850 mg) was aliquoted in tubes.

### 2.2. Protein extraction

The obtained bone powder was suspended in solutions for each

extraction protocol and processed as described below. Each protocol was tested thrice. All incubation and centrifugation steps during protein extraction were performed at  $4^{\circ}\text{C}$  where not otherwise specified. Samples were resuspended in the same volume of the final solution. To determine protein concentration, the Bradford and BCA based Lowry assays were performed [26].

#### 2.2.1. Protocol 1 (P1): G-E extracts protocol

G-E extracts protocol was modified from Termine 1980 [18] (Table 1) (Fig. 2). The bone powder was suspended in a G solution, constituted of 4 M Guanidine Hydrochloride (GuHCl) in 0.05 M Tris pH 7.4 and protease inhibitors (all from Sigma-Aldrich), and incubated for 72 h. The solution was then centrifuged at 800g for 20 min and the supernatant collected (G extract), whereas pellet was resuspended in an E solution containing 0.5 M EDTA (Sigma-Aldrich) in 4 M GuHCl and 0.05 M Tris pH 7.4 with protease inhibitors, and incubated for 72 h. This E extract was then centrifuged at 12,000g for 40 min and the supernatant was collected. Proteins in the G extract were obtained by Acetone precipitation, while proteins in E extract were harvested by Acetone or Trichloroacetic acid and sonication (TCA/sonication) precipitations, as described below. After precipitation, 7 M Urea (Sigma-Aldrich) or distilled water ( $\text{H}_2\text{O}$ ) were used as buffers for resuspending. From P1 the following final extracts were obtained: 1G, 1E1, 1E2 and 1E3 (Table 1) (Fig. 2).

#### 2.2.2. Protocol 2 (P2): G1-E-G2 extracts protocol

Protocol 2 was applied according to Goldberg 1988 et al. [27], who have modified the protocol from Termine 1980 et al. [18], to obtain three extracts (Table 1) (Fig. 2). The bone powder was incubated with the G solution for 48 h and then centrifuged at 1000g per 15 min. The supernatant was saved as G1 extract and the pellet was washed twice with 0.05 M Tris-HCl pH 7.4, before incubation with an E solution (0.5 M EDTA in 0.05 M Tris-HCl pH 7.4 containing protease inhibitors) for 48 h. This solution was then centrifuged, and the supernatant stored as E extract. The E pellet was suspended again in the G solution for further 48 h and, after centrifugation, the supernatant was collected as G2 extract. Proteins in the G1, E, and G2 extracts were obtained with Acetone or TCA/sonication precipitations, as described below, or concentrated by Amicon Ultra-4. The buffer used after precipitation and during concentration was 7 M Urea. From P2 it was possible to obtain the extracts 2G1, 2G2, 2E and 2G3 (Table 1) (Fig. 2).

#### 2.2.3. Protocol 3(P3): HCl-SDS extracts protocol

HCl-SDS protocol was modified from Buckley 2010 and Craig 2002 [22,28] (Table 1) (Fig. 2). The bone powder samples were treated overnight with 5 or 20 ml of 0.6 M HCl at room temperature and then centrifuged at 7200g for 20 min. The supernatant was collected and the remaining pellet washed with  $\text{H}_2\text{O}$  and centrifuged thrice as above mentioned. The final pellet was then resuspended in 2% SDS (Sigma-Aldrich) for 48 h at room temperature. Proteins in HCl and SDS solutions were precipitated with TCA/sonication and EtOH precipitations respectively, as described below. Proteins from TCA/sonication precipitation were resuspended in 7 M Urea, while proteins from EtOH precipitation were resuspended in 2% SDS. From P3, the extracts 5-HCl, 20-HCl, 5-SDS, and 20-SDS were obtained (Table 1) (Fig. 2).

#### 2.2.4. Protocol 4 (P4): NaOH-EDTA protocol

Protocol 4 was modified from Singh 2011 et al. [29] (Table 1) (Fig. 2). We performed this protocol to determine whether the EDTA solution, used in most protocols for collagen recovery, could hamper protein content, thus reducing their correct analysis and quantification. The bone powder was incubated in 0.1 M NaOH overnight and centrifuged at 3200g for 20 min and discarding the supernatant containing NCPs. The pellet was washed twice with  $\text{H}_2\text{O}$  and then resuspended in 0.5 M EDTA pH 8 containing protease inhibitors for 72 h. The sample was centrifuged as described above and the supernatant was collected.

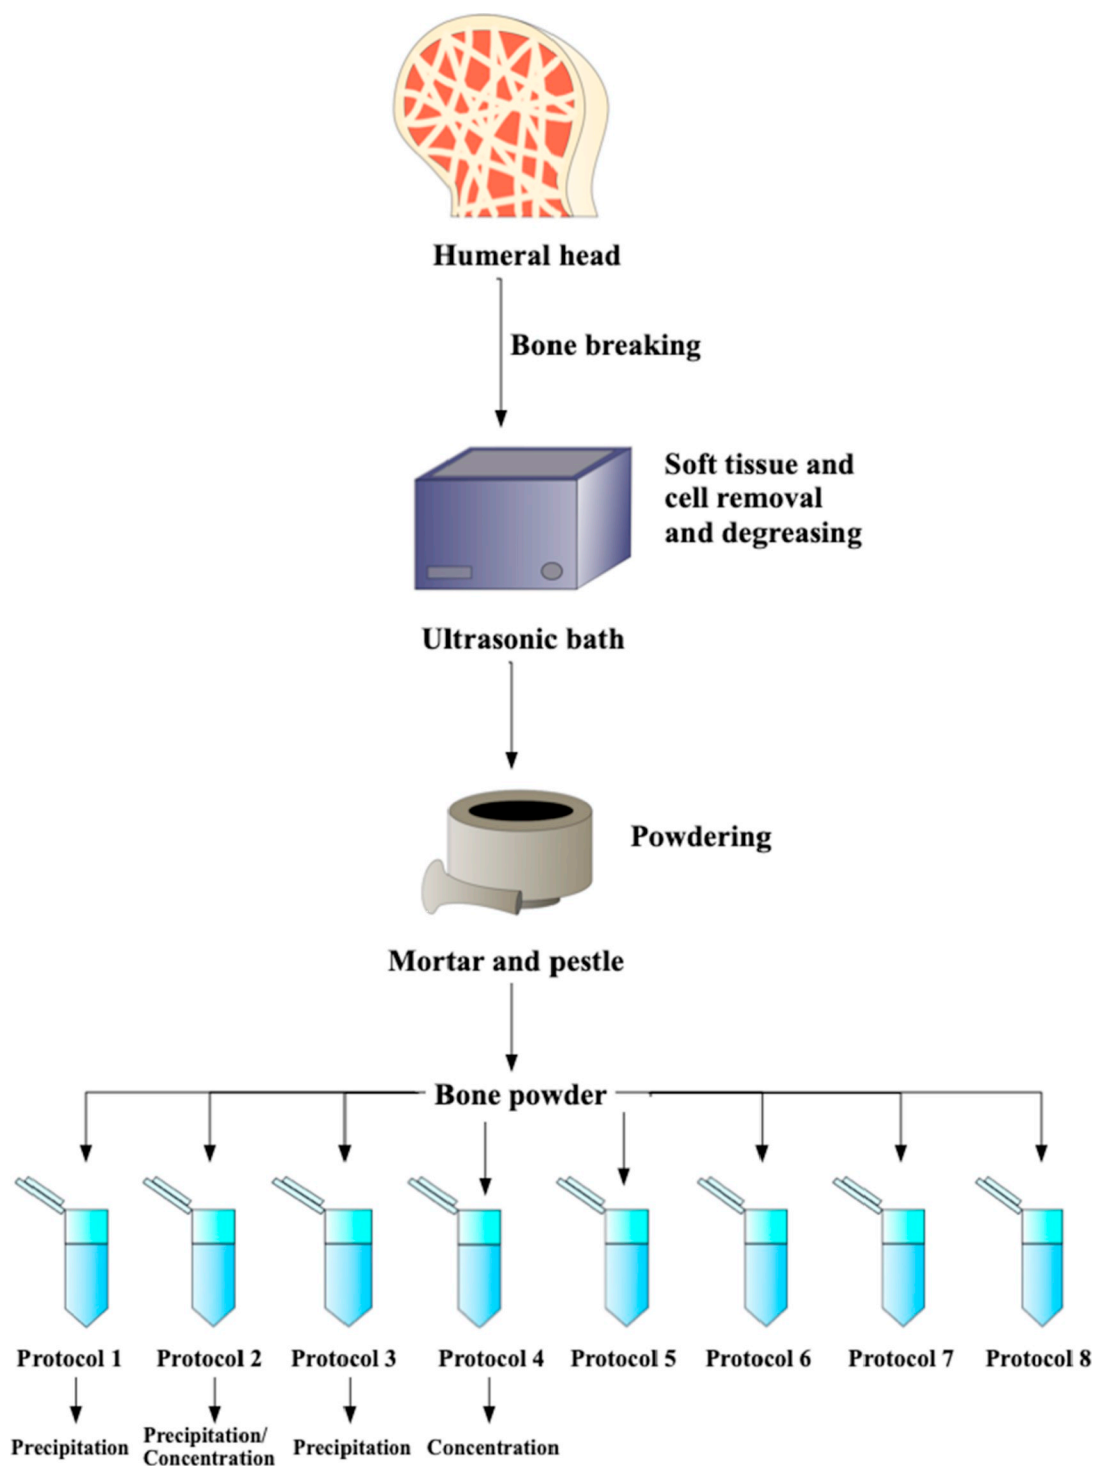


Fig. 1. Representative drawing of stages of the protocols: bone breaking, removal of soft tissues and cells, bone powdering, and processing by different protocols. The first 4 protocols need precipitation and/or concentration methods to obtain protein extracts.

Two consecutive incubations with the EDTA solution were performed. EDTA solution extracts were then concentrated by Amicon Ultra 4 progressively changing the initial buffer with 7 M Urea (Table 1) (Fig. 2). From P4, the extracts 1-EDTA and 2-EDTA were obtained (Table 1) (Fig. 2).

#### 2.2.5. Protocol 5 (P5): TRIzol reagent protocol

TRIzol protocol was conducted according to the manufacturer's instruction (Table 1) (Fig. 3). Briefly, the bone powder (100 mg) was dissolved in 1 ml TRIzol reagent and chloroform (Sigma-Aldrich). After

2–3 min incubation at room temperature, the solution was centrifuged at 12,000g for 15 min and the aqueous phase containing RNA discarded. Absolute ethanol was then incorporated, incubated at room temperature and centrifuged at 2000g for 20 min, to obtain the protein phase as supernatant. To precipitate proteins, isopropanol was added, and the solution was centrifuged at 12,000g for 10 min. The obtained pellets were washed with 0.3 M GuHCl in 95% Ethanol, then centrifuged at 7500g for 5 min after incubation and the supernatant was discarded. This step was repeated for 3 times, before incubating with 100% Ethanol for 20 min, centrifuging at 7500g for 5 min and

**Table 1**  
Protocols for protein extraction.

Protocols		Starting solutions		Precipitation/concentration method	Final buffer	Final extracts	Days	Ref
N°	Definition	N°	Acronyms					
P1	G-E	2	G	Acetone precipitation	H <sub>2</sub> Od	1G	7	Termine 1980
			E	Acetone precipitation	Urea 7 M	1E1		
				Acetone precipitation	H <sub>2</sub> Od	1E2		
				TCA/sonication precipitation	Urea 7 M	1E3		
P2	G1-E-G2	3	G1	TCA/sonication precipitation	Urea 7 M	2G1	7	Goldberg 1988 et al
				Acetone precipitation	Urea 7 M	2G2		
			E	Amicon Ultra 4-MWCO1000	Urea 7 M	2E		
			G2	TCA/sonication precipitation	Urea 7 M	2G3		
P3	HCl-SDS	2	5	TCA/sonication precipitation	Urea 7 M	5-HCl	8	Craig 2002; Buckley 2010
				EtOH precipitation	2% SDS	5-SDS		
			20	TCA/sonication precipitation	Urea 7 M	20-HCl		
				EtOH precipitation	2% SDS	20-SDS		
P4	NaOH-EDTA	1	EDTA	Amicon Ultra 4-MWCO1000	Urea 7 M	1-EDTA	8	Singh 2011 et al
				Amicon Ultra 4-MWCO1000	Urea 7 M	2-EDTA		
P5	TRLzol reagent	1	T	N.A.	1% SDS	T	1	N.A.
P6	NET-Triton buffer	1	N	N.A.	N.A.	N	3	Wang 2014
P7	High concentration phosphate buffer	1	HCP	N.A.	N.A.	HCP	3	Cleland et al. 2015
P8	Tris-SDS buffer	1	TS	N.A.	N.A.	TS	3	Lyon 2016

N.A. = not applicable.

discarding the supernatant. In the end, the pellet was resuspended in 200  $\mu$ l of 1% SDS, the solution was centrifuged at 10000g for 10 min to remove insoluble materials and the supernatant stored at  $-80^{\circ}\text{C}$  until use. From P5, T extract was obtained (Table 1) (Fig. 3).

#### 2.2.6. Protocol 6 (P6): NET-Triton buffer protocol

NET-Triton buffer protocol was modified from Wang 2014 [13] (Table 1) (Fig. 3). The bone powder was incorporated in the NET-Triton buffer (0,01 M Tris-HCl 7.4, 1 mM EDTA, 0,1 M NaCl, 1% Triton X-100, 10% glycerol, 0,1% SDS, 0,5% sodium deoxycholate and protease inhibitors) and the solution was homogenized by Ultra-Turrax T8 (IKA-WERKE, Lille, France) for 1 min in ice interposed by 1 min of rest, for 4 cycles overall. The sample was centrifuged at 14,000g for 10 min to remove debris and the supernatant was collected at  $-80^{\circ}\text{C}$  until use. From P6, N extract was obtained (Table 1) (Fig. 3).

#### 2.2.7. Protocol 7 (P7): high concentration phosphate buffer protocol

High Concentration Phosphate protocol was modified from Cleland et al. 2015 [9] (Table 1) (Fig. 3). Concisely, the bone powder was dissolved in an HCP solution pH 8 and incubated at  $75^{\circ}\text{C}$  for 24 h. The HCP solution contained 400 mM ammonium phosphate dibasic, 200 mM ammonium bicarbonate and 4 M GuHCl. The samples were then centrifuged at 14,000g for 30 min to precipitate insoluble materials and the supernatant was collected and stored at  $-80^{\circ}\text{C}$ . From P7, the HCP extract was obtained (Table 1) (Fig. 3).

#### 2.2.8. Protocol 8 (P8): Tris-SDS buffer protocol

Tris-SDS buffer protocol was modified from Lyon 2016 [23] (Table 1) (Fig. 3). The lysis buffer contained 1.2 M Tris-acetate pH 6.8, 1% SDS, 0.5% glycerol, 1% 100 mM EDTA and Protease Inhibitors (Sigma-Aldrich), 10 mM  $\beta$ -glycerophosphate, 1 mM sodium orthovanadate and 50 mM dithiothreitol (DTT) were added immediately before use. The solution containing bone powder was homogenized by Ultra-Turrax T8 for 1 min in ice interposed by 1 min of rest, for 4 cycles overall, and frozen at  $-80^{\circ}\text{C}$  overnight. The sample was then centrifuged at 14,000g for 10 min to remove mineral matrix debris and the supernatant was collected at  $-80^{\circ}\text{C}$  until use. From P8, TS extract was obtained (Table 1) (Fig. 3).

### 2.3. Precipitation methods

All passages for TCA/sonication or Acetone precipitation were

performed at  $4^{\circ}\text{C}$  where not otherwise specified [30]. Briefly, for TCA/sonication precipitation protocol, 1 volume of 20% TCA was added to 1 volume of protein solution and incubated at  $-20^{\circ}\text{C}$  for 1 h. The solution was centrifuged at 15,000g for 15 min and the supernatant was removed. Ice-cold acetone containing 20 mM DTT was added to the pellet, incubating at  $-20^{\circ}\text{C}$  for 1 h and vortexing every 20 min, and then the solution was centrifuged at 13,000g for 15 min. The supernatant was discarded, and the pellet was air-dried before resuspending in the selected buffer and sonicating for 10 s for 6 cycles overall. For Acetone precipitation protocol, 4 volumes of ice-cold acetone containing 20 mM DTT were added to 1 volume of protein solution. The solution was vortexed and incubated at  $-20^{\circ}\text{C}$  for 1 h. The supernatant was discarded after centrifuging at 15,000g for 15 min, and the pellet was air-dried before resuspending in the selected buffer.

Ethanol precipitation was performed as previously described by Rajalingam 2009 and all the passages were performed at  $4^{\circ}\text{C}$  where not otherwise specified [31]. Concisely, 5 volumes of 100% ethanol were added to 1 volume of protein and incubated overnight at  $-20^{\circ}\text{C}$ . The solution was centrifuged at 7000g for 20 min, the supernatant was wasted, and the pellet washed with 5 ml of ice-cold acetone and incubated for 20 min at  $-20^{\circ}\text{C}$ . The centrifugation was performed at 7000g for 20 min, the supernatant was discarded, and the pellet was resuspended in the selected buffer after air drying.

### 2.4. Western Blotting

Western Blotting was performed on the extracts obtained from three different reps of the above-mentioned protocols. All protein samples (50  $\mu$ g of protein for each sample) were prepared using NuPAGE™ LDS Sample Buffer according to manufacturer's instruction, fractionated in NuPAGE™ 4–12% Bis-Tris Protein Gels and electrophoretically transferred to PVDF membranes (Millipore).

Membranes were incubated with 5% milk in Tris-Buffered Saline with 0.1% Tween 20 (TBS-T) to block non-specific sites and then with primary antibodies in TBS-T at  $4^{\circ}\text{C}$  overnight.

After washes with TBS-T, the membranes were incubated with secondary antibody anti-mouse conjugated with horseradish peroxidase or secondary antibody anti-rabbit conjugated with horseradish peroxidase. Detection of antibody binding was performed with Pierce ECL Western Blotting Substrate and images were acquired with Alliance Mini HD9 (Uvitec, Cambridge, UK). Densitometric analysis was performed with ImageJ software (<https://imagej.nih.gov/ij/download>).

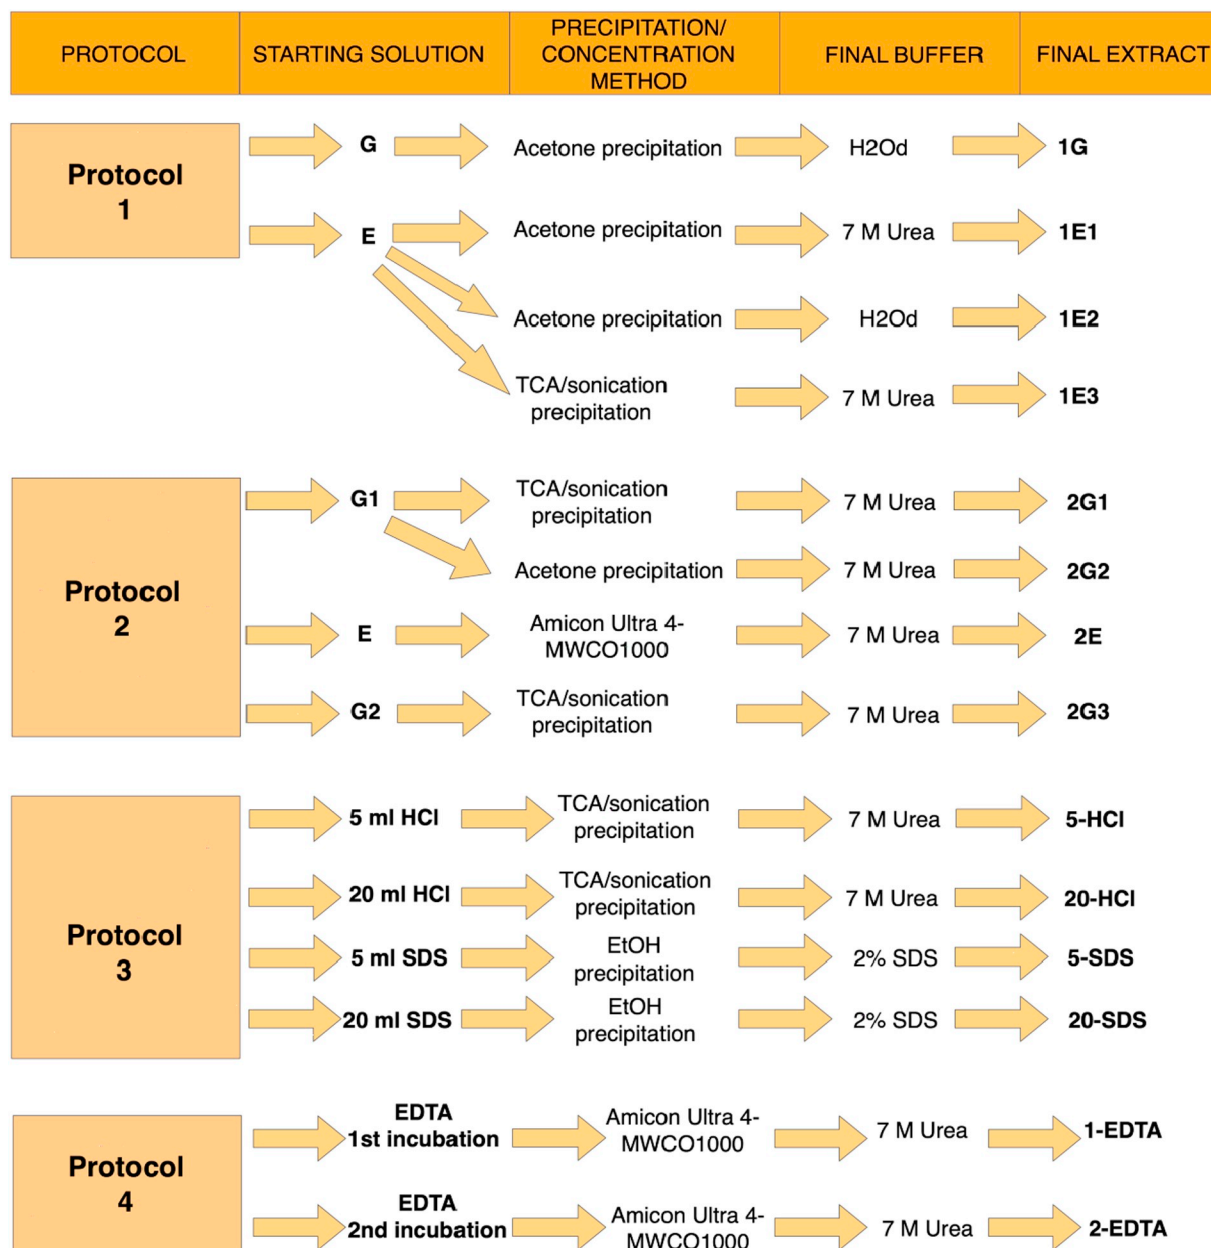


Fig. 2. Schematic drawing of the steps of the multi-extract protocols (P1–P4). For each step of the protocols, starting work solutions, precipitation and/or concentration methods, final buffers employed for resuspension after precipitation or concentration and final extracts obtained are indicated.

html). No membrane was stripped between antibody incubations to avoid protein loss.

## 2.5. Key resources table

ANTIBODIES				
REAGENT	ANTIBODY	DILUTION	CATALOG	SOURCE
<i>Human Col1a1</i>	Mouse monoclonal	1:250	SC-293182	Santa Cruz Biotechnology
<i>Human Col1a2</i>	Rabbit polyclonal	1:1000	14695-1-AP	Proteintech
<i>Human Decorin</i>	Rabbit polyclonal	1:1000	Ab-175404	Abcam
<i>Human Osteocalcin</i>	Mouse monoclonal	1:200	SC-365797	Santa Cruz Biotechnology
<i>Human Osteopontin</i>	Mouse monoclonal	1:200	SC-73631	Santa Cruz Biotechnology

<i>Human Transforming Growth Factor-<math>\beta</math></i>	Mouse monoclonal	1:2000	GTX21279	Genetex
<i>Human Insulin-like Growth Factor-1</i>	Mouse monoclonal	1:250	SC-74116	Santa Cruz Biotechnology
<i>Human Bone Sialoprotein-2</i>	Mouse monoclonal	1:200	SC-73630	Santa Cruz Biotechnology
<i>Secondary antibody conjugated with horseradish peroxidase</i>	Anti-mouse	1:15000	A190-116P	Bethyl Laboratories
<i>Secondary antibody conjugated with horseradish peroxidase</i>	Anti-rabbit	1:5000	SC-2004	Santa Cruz Biotechnology
CHEMICALS				
<i>Protease inhibitors</i>	N/A	N/A	S8820	Sigma-Aldrich
<i>TRIzol reagent</i>	N/A	N/A	15596018	Invitrogen
<i>Dithiothreitol (DTT)</i>	N/A	N/A	NP0009	Invitrogen
<i>Bradford reagent</i>	N/A	N/A	B6916	Sigma-Aldrich

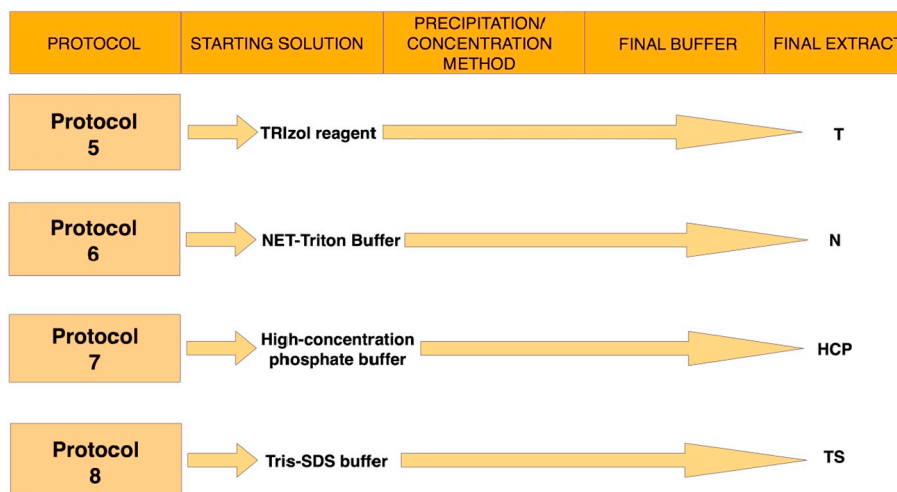


Fig. 3. Schematic drawing of steps of the single-extract protocols (P5–P8). For each step of the protocols, starting work solutions and final extracts obtained are indicated. In this drawing, we have underlined that precipitation or concentration methods and buffer for resuspension were not used.

<i>NuPAGE™ LDS Sample Buffer (4X)</i>	N/A	N/A	NP0007	Invitrogen
<i>NuPAGE™ 4-12% Bis-Tris Protein Gels</i>	N/A	N/A	NP0322BOX	Invitrogen
<i>Pierce ECL Western Blotting Substrate</i>	N/A	N/A	32106	Thermo Scientific
<b>DEVICES</b>				
<i>Amicon Ultra 4</i>	N/A	N/A	MWCO10000	Merck Millipore
<i>Ultra-Turrax T8</i>	N/A	N/A	Z404519	IKA-WERKE

### 3. Results

#### 3.1. Macroscopic observations

Macroscopically, some solutions showed insoluble residues after protein extraction. The TS and N extracts, obtained from P8 and P6 respectively, exhibited a filamentous residue during the homogenization phase. The 1E2 extract, obtained in P1 from the resuspension in H<sub>2</sub>O after acetone precipitation, contained a copious amount of white residue, whereas the 1E3 extract from P1 gained in the same protocol after the resuspension in 7 M Urea after the TCA/sonication precipitation contained only a little insoluble white deposit.

#### 3.2. Total protein amounts

Table 2 summarized the total protein recovery from each extract, comparing Bradford and BCA assays. The highest protein recovery detected by Bradford assay was in P5 and P2: the protein concentration of the T extract (P5) was 3.450 µg/µl from 100 mg of bone, while the 2G1 extract (P2) contained 15.613 µg/µl from 1 g of bone. A good protein recovery was also detected in the HCP extract from P7 (11.774 µg/µl), the 2G2 extract from P2 (9.625 µg/µl), and the N extract from P6 (8.239 µg/µl).

Further differences were found treating the same extract with different precipitation methods (i.e. 2G1 vs 2G2 extracts) and/or different buffer (i.e. 1E1 vs. 1E2 extracts from P1) or using a different volume of extraction solution (5-HCl vs 20-HCl extracts from P3; 5-SDS vs. 20-SDS extracts from P3). The highest protein content was detected in the T (P5) and the 2G1 (P2) extracts also by BCA assay; overall, this assay showed a lower protein recovery than Bradford one: the protein concentration for the T extract was 1.076 µg/µl from 100 mg of bone and for the 2G1 extract was 1.950 µg/µl. A good protein recovery was observed also in the P extract from P7 (1.540 µg/µl), in the 2G2 extract

Table 2

Total protein recovery.

N°	Protocols	Definition	Final extracts	Concentration (µg/µl)	
				Bradford assay	BCA assay
P1	G-E		1G	1.452	0.909
			1E1	1.732	0.280
			1E2	1.024	0.259
P2	G1-E-G2		1E3	1.166	–
			2G1	15.613	1.950
			2G2	9.625	1.460
P3	HCl-SDS		2E	1.392	0.335
			2G3	3.951	0.232
			5-HCl	0.913	0.492
P4	NaOH-EDTA		5-SDS	2.454	0.267
			20-HCl	0.514	0.447
			20-SDS	3.623	0.088
P5 <sup>a</sup>	TRizol reagent		1-EDTA	2.200	0.933
			2-EDTA	3.539	0.964
P6	NET-Triton buffer		T	3.45	1.076
P7	High concentration phosphate buffer		N	8.239	0.935
P8	Tris-SDS buffer		HCP	11.774	1.540
			TS	3.348	1.015

<sup>a</sup> Starting from 100 mg of bone.

from P2 (1.460 µg/µl) and in the TS extract from P8 (1.015 µg/µl). We found differences in protein recovery comparing the same extract with different precipitation methods (i.e. 2G1 vs 2G2 extracts from P2) or using a different volume of extraction solution (5-SDS vs 20-SDS from P3). No proteins were detected in 1E3 extract (P1).

#### 3.3. Protein staining analysis

Results of the densitometric analysis are summarized in Fig. 4. Detailed information are available as Supplementary files (Figs. 1S–4S and Table 1S).

Only TS (P8) and T (P5) extracts showed staining for all the examined proteins. The T extract revealed the best staining for TGF-β at 25 and 50 kDa, DCN at 40 kDa, OPN at 55 kDa and BSP-2 at 55 and 80 kDa. The TS extract showed the highest intensity for Col1a1 at 140 kDa, IGF-1 at 7.6 kDa, OPN at 25 and 66 kDa and a similar intensity to the T extract for BSP-2 at 55 kDa. Furthermore, the N extract (P6) exhibited the highest amount of Col1a1 at 90 kDa, TGF-β at 12.5 kDa and BSP-2 at 35 kDa but did not show signals for Col1a2 and IGF-1

		P1				P2				P3				P4		P5	P6	P7	P8
		1G	1E1	1E2	1E3	2G1	2G2	2E	2G3	5-HCl	20-HCl	5-SDS	20-SDS	1-EDTA	2-EDTA	T	N	HCP	TS
Col1a1	140 kDa	-	-	-	-	-	-	-	-	-	-	-	-	-	-	+++ ++	+++ +	-	+++ ++
	90 kDa	-	-	-	-	-	-	-	-	-	-	-	-	-	-	+/-	+	-	+/-
Col1a2	120 kDa	-	++	++	++	-	-	++	+++	+++ +	-	+	+	+++	+++ ++	+/-	-	+	+++
TGF-beta	50 kDa	-	-	-	-	-	-	-	-	-	-	-	-	-	-	+++ ++	-	-	+++
	25 kDa	-	-	-	-	-	-	-	-	-	-	-	-	-	-	+++ ++	-	-	+++ ++
	12 kDa	-	-	-	-	-	-	-	-	++	-	+++ +	+++	-	-	+++ ++	-	-	+++ ++
IGF-1	22 kDa	-	+	-	-	-	-	+	-	-	-	+++ ++	++	-	-	-	-	-	-
	7 kDa	-	-	-	-	-	-	-	-	-	-	-	-	-	-	++	-	-	+++
Decorin	120 kDa	-	-	-	-	-	-	-	-	+++ +	+++	-	-	-	-	++	+/-	-	+
	40 kDa	-	-	-	-	-	-	-	-	++	+	+++	+	-	-	+++	+/-	-	++
Osteopontin	66 kDa	-	-	-	-	-	-	-	-	+/-	-	-	-	-	-	+++ +	-	-	+++ +
	44 kDa	-	-	-	-	-	-	-	-	-	-	-	-	-	-	+++ ++	-	-	+/-
	25 kDa	-	++	+	+	-	-	+	-	-	-	-	-	-	-	+++ ++	-	-	+++ ++
Bone Sialoprotein-2	80 kDa	-	-	-	-	-	-	-	-	-	-	-	-	-	-	+++ ++	-	-	+++ ++
	55 kDa	-	-	-	-	-	-	-	-	-	-	-	-	-	-	+++ +	-	-	+++ +
	33 kDa	-	-	-	-	-	-	-	-	-	-	-	-	-	-	+++ +	-	-	+++ +
Osteocalcin	6 kDa	+++ ++	+++ +	++	++	+++ ++	+++ +	-	-	+/-	+	+/-	+/-	-	-	+/-	+/-	+/-	+/-

Fig. 4. Schematic drawing to resume the results of densitometric analysis for protein expression of each extract (I: intensity/mm3). -: no staining; +/-:  $I < 10^6$ ; +:  $10^6 < I < 2.5 \times 10^6$ ; ++:  $2.5 \times 10^6 < I < 5 \times 10^6$ ; +++:  $5 \times 10^6 < I < 8 \times 10^6$ ; ++++:  $8 \times 10^6 < I < 1.2 \times 10^7$ ; +++++:  $I > 1.3 \times 10^7$ .

proteins. Col1a2, TGF-beta, IGF-1, DCN, and OCN were identified in the 5-SDS and 20-SDS extracts (P3). The 5-SDS extract showed also the highest staining for IGF-1 at 22 kDa. The 5-HCl extract (P3) exhibited staining for Col1a2, TGF-beta, OPN, OCN and the highest content of DCN at 120 kDa, whereas the 20-HCl (P3) showed only the presence of DCN and OCN. The 1E1, 1E2 and 1E3 extracts (P1) contained Col1a2 and OPN in similar amounts, but the 1E1 extract contained also IGF-1 and showed staining for OCN 4-fold more than 1E2 and 1E3. The 2E

extract permitted the collection of Col1a2, IGF-1, and OPN. The remaining extracts showed staining only for one protein: among these, the 2G1 extract (P2) showed the highest staining for OCN and the 2-EDTA one for Col1a2.

#### 4. Discussion

Protein extraction from bone ECM is a complicated process

influenced by several variables, such as the use of different reagents, the concentration methods and the resuspension buffers, which could hamper the accurate quantitation of many proteins involved in bone biology and pathologies.

In this study, we compared different protocols from published literature to identify the best method for the extraction of bone ECM proteins in a pathological condition (i.e. osteoporosis). Since the imbalance between bone resorption and formation affects the bone ECM protein content [8], the modification of current protocols in terms of total protein recovery and collection of peculiar proteins involved in osteoporosis could represent a valid tool in the study and/or management of this pathology.

The normalization of Western Blotting results was one of the main issues to address because the usual analysis of endogenous proteins cannot be useful in the examination of a decellularized bone ECM.

Therefore, in order to reduce variations that could influence the protein quantification, arrangements like the use of only one humeral head to obtain different samples (each protocol was tested thrice), the same starting weight and final volume of resuspension, an equal protein amount loaded in Western Blotting gels, and no membrane stripping were taken [32,33].

To load the same protein amount we performed Bradford and BCA assays. Matching the same extract, we found a higher protein quantitation with Bradford assay. In bone ECM, Type I Collagen usually represents 90% of the total protein content, and its chains contain arginine and lysine that preferentially bound to Coomassie in the Bradford assay [26,34,35]. The remaining 10% of bone ECM proteins is constituted by 180–200 NCPs [34,35]. Osteocalcin, the most abundant among them, and TGF- $\beta$  are primarily revealed by BCA assay, whereas IGF-1, DCN, OPN and BSP-2 are preferentially identified by Bradford assay. Considering the protein detection amount and the affinity for the most proteins of interest, Bradford assay was the best for our aim.

Other useful arrangements to reduce influence in protein quantification, save for the suggested above, could be the use of Ponceau or Coomassie normalization for protein loading/transfer measure and the positive control loading for the analysed proteins [36,37].

Protocols P5, P6, P7 and P8, which are single-extract protocols, provide the proteins in a single extract without using precipitation and/or concentration methods and do not require > 3 days. The T extract from P5 showed both the higher total protein recovery and the detection of all proteins of interest, providing the best-tested ones. Also, P6 showed good results in terms of protein content, allowing the collection of most of the selected proteins. On the contrary, although the total protein recovery from P7 was high, the HCP extract contained only Type I Collagen and OCN. Additionally, the TS extract from P8 exhibited similar staining results obtained with P5, but with a 10-fold lower total protein concentration than the latter.

In the T (P5) and TS extracts (P8), that resulted as the best-tested protocols, Type I Collagen was the protein with the highest expression, but OCN staining was very low compared to all the other detected NCPs.

With the multi-step protocols, we obtained several extracts capable to provide different proteins according to their chemical and physical features. With the use of GuHCl buffers for the first step of P1 and P2, we expected to collect proteins from unmineralized tissue and osteoid layer, like proteoglycans and part of Type I Collagen, in the corresponding extracts (1G, 2G1 and 2G2) [18,20]. Nonetheless, the extracts were positive only for OCN which is strictly related to mineralized tissue [38], showing a high content of this protein.

Demineralizing solutions were employed in the first step (as in P3) or after (as in P1, P2 and P4). The extracts including EDTA or HCl contained OCN and other proteins associated with HA, like OPN and Type I Collagen, as expected [18,20,27,38–40]. Interestingly, we also observed the expression of growth factors (i.e. TGF- $\beta$  and IGF-1) and proteoglycans (i.e. DCN). In the EDTA and HCl extracts derived from demineralizing solutions, we obtained a notable protein amount and

variety, as observed also by Schroeter et al. [17]. Furthermore, in P3, the SDS extract, collected after the demineralizing step with HCl solution, exhibited only a low amount of Type I Collagen. Some protocols for protein extraction from bone, especially those employed for collagen collection, use a first demineralizing step on samples before the effective extraction procedures [41,42]. Our data suggest that the initial decalcification step causes loss of proteins, affecting the final protein recovery, and therefore should be avoided.

Lately, from the third step of P2, we recovered the residue Type I Collagen in the 2G3 extract, as expected [27].

Although each multi-step protocol provides two or more solutions for the obtainment of specific extracts, no tested protocol was per se useful to collect all the 8 proteins of interest. Additionally, these multi-step methods require more days and longer period of incubations than the single-extract ones, thus they are not time-efficient. With these protocols (from P1 to P4), just a few extracts exhibited a good protein recovery with a good or high expression of few proteins of interest. Among them, OCN showed a very high expression in the P1 and P2, greater than the single-extract protocols that thus revealed a limitation in the collection of this protein.

The possibility to investigate, within these protocols, different precipitation and/or concentration methods and different buffers for resuspension, could overall ameliorate protein recovery. The TCA/sonication precipitation and the subsequent buffer changing with 7 M Urea provided the best protein recovery and staining in G extracts, while acetone precipitation and 7 M Urea resuspension was the greatest for the recovery and staining in E extracts, even if in the 1E2 and 1E3 extracts (P1) an insoluble white sediment was observed. This deposit that we supposed to be mineral residues, was not evident in the 1E1 extract (P1) obtained with TCA/sonication precipitation.

Also, in the TS (P8) and N (P6) extracts from single step-protocols a filamentous residue, consisting probably of an insoluble fraction of Type I Collagen [18], was observed. Overall, these deposits, which probably contain not solubilized proteins, could affect the proper estimation of protein content in the tested protocol.

Another issue that needs to be addressed in the search of an optimal protocol is the volume of extraction solution. For instance, in P3, the extract from 5 ml HCl was better in quantity and quality than that from 20 ml HCl. Similarly, even if the SDS extracts contained the same proteins, yield and expression were higher in the extract from a pellet that was demineralized by a smaller amount of HCl.

In some extracts (i.e. 2G2 from P2 and HCP from P7), we observed differences between a high total protein recovery, detected by Bradford and BCA assays, and a very low protein expression, observed by Western Blotting. This discrepancy may be attributable to the fact that in these extracts there were other proteins beside the ones we investigated. Indeed, the investigated proteins relative to osteoporosis are few considering the very high number of NCPs in bone ECM [34]. Otherwise, also the buffer used for extraction and/or for resuspension could cause this discordance. Indeed, solutions containing a high salt amount, as the HCP extract from P7, could be not fully suitable for the SDS-PAGE system in Western Blotting, thus making the protein detection difficult [43]. For this reason, P7 was not optimal for Western Blotting analysis, but its high protein recovery makes it a good protocol to analyse proteins by other assays such as HPLC [9]. On the other hand, the solutions containing SDS, like those used in P3, P5, P6 and P8, were compatible with SDS-PAGE system and showed a wide range of proteins detectable.

## 5. Conclusions

Collectively, we drew-up two single-extract protocols (P5 and P8) with optimal recovery and ideal protein content for the main proteins involved in osteoporosis and that can be used for a satisfactory analysis of ECM proteins in pathological bone samples. These protocols need, however, to be supported by the multi-extract protocols for a punctual

detection of proteins like OCN (e.g. P1 or P2). We also optimised the precipitation methods in the multi-extract protocols based on the different components of the starting solution employed. We observed that the proposed demineralization processes before the extraction could cause protein loss, thus hampering accurate protein detection.

This study provides useful protocols to investigate the protein content in bone ECM. It serves as a baseline for the definition of appropriate strategies in the study of bone proteins in medical research, to investigate their involvement in the onset and continuation of bone metabolic diseases, like osteoporosis. Furthermore, more information about the protein content of bone ECM could represent a starting point to design appropriate scaffolds. Indeed, the inclusion in biomaterials of one or more crucial proteins can be central to develop in vitro models for physiological or pathological bone conditions and/or for the bio-fabrication of customized 3D scaffolds capable to properly modulate the feedback loop in bone remodelling altered in osteoporosis.

Supplementary data to this article can be found online at <https://doi.org/10.1016/j.bone.2020.115363>.

### CRedit authorship contribution statement

**Caterina Licini:**Methodology, Formal analysis, Writing - original draft, Writing - review & editing.**Giorgia Montalbano:**Methodology, Formal analysis, Writing - review & editing.**Gabriela Ciapetti:**Writing - review & editing.**Giorgia Cerqueni:**Writing - review & editing.**Chiara Vitale-Brovarone:**Conceptualization, Writing - review & editing.**Monica Mattioli-Belmonte:**Conceptualization, Supervision, Writing - review & editing.

### Declaration of competing interest

None.

### Acknowledgments

The authors are grateful to Dr. Andreil Hossein for her English revision.

### Funding

This project has received funding from the European Research Council (ERC) under the European Union's Horizon 2020 research and innovation programme (grant agreement No 681798 - BOOST) ([www.ercprojectboost.eu](http://www.ercprojectboost.eu)) and by the Italian Ministry of Education, Universities and Research (MIUR), Progetto FARE Ricerca in Italia (GRACE). No benefits in any form have been or will be, received from a commercial party directly, or indirectly, related to the subject of this article.

### References

- [1] D. Sommerfeldt, C. Rubin, Biology of bone and how it orchestrates the form and function of the skeleton, *Eur. Spine J.* 10 (2001) S86–S95, <https://doi.org/10.1007/s005860100283>.
- [2] Y. Bala, D. Farlay, G. Boivin, Bone mineralization: from tissue to crystal in normal and pathological contexts, *Osteoporos. Int.* 24 (2013) 2153–2166, <https://doi.org/10.1007/s00198-012-2228-y.3>.
- [3] M.E. Fleet, The carbonate ion in hydroxyapatite: recent X-ray and infrared results, *Front. Biosci. (Elite Ed.)* 5 (2013) 643–652.
- [4] E. Solheim, Growth factors in bone, *Int. Orthop.* 22 (1998) 410–416, <https://doi.org/10.1007/s002640050290>.
- [5] R.V. Iozzo, L. Schaefer, Proteoglycan form and function: a comprehensive nomenclature of proteoglycans, *Matrix Biol.* 42 (2015) 11–55, <https://doi.org/10.1016/j.matbio.2015.02.003>.
- [6] J.P. Bilezikian, L.G. Raisz, G.A. Rodan, *Principles of Bone Biology*, Second edition, Academic Press, San Diego, California, USA, 2002.
- [7] P.A. Price, A.S. Otsuka, J.W. Poser, J. Kristaponis, N. Raman, Characterization of a  $\gamma$ -carboxyglutamic acid-containing protein from bone, *Proc. Natl. Acad. Sci. U. S. A.* 73 (1976) 1447–1451.
- [8] A.I. Alford, K.M. Kozloff, K.D. Hankenson, Extracellular matrix networks in bone remodeling, *Int. J. Biochem. Cell Biol.* 65 (2015) 20–31, <https://doi.org/10.1016/j.biocel.2015.05.008>.
- [9] T.P. Cleland, D. Vashishth, Bone protein extraction without demineralization utilizing principles from hydroxyapatite chromatography, *Anal. Biochem.* 472 (2015) 62–66, <https://doi.org/10.1016/j.ab.2014.12.006>.
- [10] J.D. Termine, A.B. Belcourt, K.M. Conn, H.K. Kleinman, Mineral and collagen-binding proteins of fetal calf bone, *J. Biol. Chem.* 256 (1981) 10403–10408.
- [11] Y. Kuboki, H. Takita, T. Komori, M. Mizuno, E. Furuuchi, K. Taniguchi, Separation of bone matrix proteins by calcium-induced precipitation, *Calcif. Tissue Int.* 44 (1989) 269–277, <https://doi.org/10.1007/BF02553761>.
- [12] T.K. Sampath, A.H. Reddi, Dissociative extraction and reconstitution of extracellular matrix components involved in local bone differentiation, *Proc. Natl. Acad. Sci. U. S. A.* 78 (1981) 7599–7603.
- [13] C. Wang, X. Wang, X. Xu, X. Yuan, W. Gou, A. Wang, Q. Guo, J. Peng, S. Lu, Bone microstructure and regional distribution of osteoblast and osteoclast activity in the osteonecrotic femoral head, *PLoS One* 9 (2014) e96361, <https://doi.org/10.1371/journal.pone.0096361>.
- [14] Q. Wei, L. Huang, X. Tan, Z. Chen, S. Chen, W. Deng, Serum osteopontin levels in relation to bone mineral density and bone turnover markers in postmenopausal women, *Scand. J. Clin. Lab. Invest.* 76 (2016) 33–39, <https://doi.org/10.3109/00365513.2015.1087045>.
- [15] T.H. Schmidt-Schultz, M. Schultz, Bone protects proteins over thousands of years: extraction, analysis, and interpretation of extracellular matrix proteins in archaeological skeletal remains, *Am. J. Phys. Anthropol.* 123 (2004) 30–39, <https://doi.org/10.1002/ajpa.10308>.
- [16] T.P. Cleland, K. Voegelé, M.H. Schweitzer, Empirical evaluation of bone extraction protocols, *PLoS One* 7 (2012) e31443, <https://doi.org/10.1371/journal.pone.0031443>.
- [17] E.R. Schroeter, C.J. DeHart, M.H. Schweitzer, P.M. Thomas, N.L. Kelleher, Bone protein “extractomics”: comparing the efficiency of bone protein extractions of Gallus gallus in tandem mass spectrometry, with an eye towards paleoproteomics, *PeerJ* 4 (2016), <https://doi.org/10.7717/peerj.2603>.
- [18] J.D. Termine, A.B. Belcourt, P.J. Christner, K.M. Conn, M.U. Nylen, Properties of dissociatively extracted fetal tooth matrix proteins, *J. Biol. Chem.* 255 (1980) 9760–9768.
- [19] L. Zhang, W.-H. Li, Mammalian housekeeping genes evolve more slowly than tissue-specific genes, *Mol. Biol. Evol.* 21 (2004) 236–239, <https://doi.org/10.1093/molbev/msh010>.
- [20] P.G. Robey, M.F. Young, L.W. Fisher, T.D. McClain, Thrombospondin is an osteoblast-derived component of mineralized extracellular matrix, *J. Cell Biol.* 108 (1989) 719–727, <https://doi.org/10.1083/jcb.108.2.719>.
- [21] M.T. Kaartinen, S. El-Maadawy, N.H. Räsänen, M.D. McKee, Tissue transglutaminase and its substrates in bone, *J. Bone Miner. Res.* 17 (2002) 2161–2173, <https://doi.org/10.1359/jbmr.2002.17.12.2161>.
- [22] M. Buckley, S. Whitcher Kansa, S. Howard, S. Campbell, J. Thomas-Oates, M. Collins, Distinguishing between archaeological sheep and goat bones using a single collagen peptide, *J. Archaeol. Sci.* 37 (2010) 13–20, <https://doi.org/10.1016/j.jas.2009.08.020>.
- [23] S.M. Lyon, A. Mayampurath, M.R. Rogers, D.J. Wolfgeher, S.M. Fisher, S.L. Volchenboum, T.-C. He, R.R. Reid, A method for whole protein isolation from human cranial bone, *Anal. Biochem.* 515 (2016) 33–39, <https://doi.org/10.1016/j.ab.2016.09.021>.
- [24] C. Licini, C. Vitale-Brovarone, M. Mattioli-Belmonte, Collagen and non-collagenous proteins molecular crosstalk in the pathophysiology of osteoporosis, *Cytokine Growth Factor Rev.* 49 (2019) 59–69, <https://doi.org/10.1016/j.cytogfr.2019.09.001>.
- [25] C.M. Sprecher, F. Schmidutz, T. Helfen, R.G. Richards, M. Blauth, S. Milz, Histomorphometric assessment of cancellous and cortical bone material distribution in the proximal humerus of normal and osteoporotic individuals: significantly reduced bone stock in the metaphyseal and subcapital regions of osteoporotic individuals, *Medicine (Baltimore)* 94 (2015) e2043, <https://doi.org/10.1097/MD.0000000000002043>.
- [26] R.I. Krohn, The colorimetric detection and quantitation of total protein, *Curr. Protoc. Cell Biol.* 52 (2011) A.3H.1–A.3H.28, <https://doi.org/10.1002/0471143030.cba03hs52>.
- [27] H.A. Goldberg, C. Domenicucci, G.A. Pringle, J. Sodek, Mineral-binding proteoglycans of fetal porcine calvarial bone, *J. Biol. Chem.* 263 (1988) 12092–12101.
- [28] O.E. Craig, M.J. Collins, The removal of protein from mineral surfaces: implications for residue analysis of archaeological materials, *J. Archaeol. Sci.* 29 (2002) 1077–1082, <https://doi.org/10.1006/jasc.2001.0757>.
- [29] S. Singh, D. Kumar, A.K. Lal, Serum osteocalcin as a diagnostic biomarker for primary osteoporosis in women, *J. Clin. Diagn. Res.* 9 (2015) RC04–RC07, <https://doi.org/10.7860/JCDR/2015/14857.6318>.
- [30] E. Fic, S. Kedracka-Krok, U. Jankowska, A. Pirog, M. Dziedzicka-Wasylewska, Comparison of protein precipitation methods for various rat brain structures prior to proteomic analysis, *Electrophoresis* 31 (2010) 3573–3579, <https://doi.org/10.1002/elps.201000197>.
- [31] D. Rajalingam, C. Loftis, J.J. Xu, T.K.S. Kumar, Trichloroacetic acid-induced protein precipitation involves the reversible association of a stable partially structured intermediate, *Protein Sci.* 18 (2009) 980–993, <https://doi.org/10.1002/pro.108>.
- [32] S.C. Taylor, A. Posch, The design of a quantitative western blot experiment, *Biomed. Res. Int.* 2014 (2014) 1–8, <https://doi.org/10.1155/2014/361590>.
- [33] K.A. Janes, An analysis of critical factors for quantitative immunoblotting, *Sci. Signal.* 8 (2015) rs2, <https://doi.org/10.1126/scisignal.2005966>.
- [34] R. Florencio-Silva, G.R. da S. Sasso, E. Sasso-Cerri, M.J. Simões, P.S. Cerri, Biology of bone tissue: structure, function, and factors that influence bone cells, *Biomed.*

- Res. Int. 2015 (2015), <https://doi.org/10.1155/2015/421746>.
- [35] G.E. Sroga, D. Vashishth, Effects of bone matrix proteins on fracture and fragility in osteoporosis, *Curr. Osteoporosis Rep* 10 (2012) 141–150, <https://doi.org/10.1007/s11914-012-0103-6>.
- [36] L. Litovchick, Staining the Blot for Total Protein With Ponceau S, *Cold Spring Harb Protoc* 3 (2020), <https://doi.org/10.1101/pdb.prot098459> pdb.prot098459.
- [37] A. Goldman, S. Harper, D.W. Speicher, Detection of proteins on blot membranes, *Curr. Protoc. Protein Sci.* 86 (2016) 10.8.1–10.8.11, <https://doi.org/10.1002/cpps.15>.
- [38] H.I. Roach, Why does bone matrix contain non-collagenous proteins? The possible roles of osteocalcin, osteonectin, osteopontin and bone sialoprotein in bone mineralisation and resorption, *Cell Biol. Int.* 18 (1994) 617–628, <https://doi.org/10.1006/cbir.1994.1088>.
- [39] J. Chen, M.D. McKee, A. Nanci, J. Sodek, Bone sialoprotein mRNA expression and ultrastructural localization in fetal porcine calvarial bone: comparisons with osteopontin, *Histochem. J.* 26 (1994) 67–78, <https://doi.org/10.1007/BF00209251>.
- [40] Y. Mochida, D. Parisuthiman, S. Pornprasertsuk-Damrongsri, P. Atsawasuwan, M. Sricholpech, A.L. Boskey, M. Yamauchi, Decorin modulates collagen matrix assembly and mineralization, *Matrix Biol.* 28 (2009) 44–52, <https://doi.org/10.1016/j.matbio.2008.11.003>.
- [41] L. Gao, Z. Wang, Z. Li, C. Zhang, D. Zhang, The characterization of acid and pepsin soluble collagen from ovine bones (Ujumuqin sheep), *J. Integr. Agric.* 17 (2018) 704–711, [https://doi.org/10.1016/S2095-3119\(17\)61751-9](https://doi.org/10.1016/S2095-3119(17)61751-9).
- [42] T.P. Cleland, Solid digestion of demineralized bone as a method to access potentially insoluble proteins and post-translational modifications, *J. Proteome Res.* 17 (2018) 536–542, <https://doi.org/10.1021/acs.jproteome.7b00670>.
- [43] Y.P. See, P.M. Olley, G. Jackowski, The effects of high salt concentrations in the samples on molecular weight determination in sodium dodecyl sulfate polyacrylamide gel electrophoresis, *Electrophoresis* 6 (1985) 382–387.