

Investigation on brittle fracture in rounded V-notched structures by Finite Fracture Mechanics

*Original*

Investigation on brittle fracture in rounded V-notched structures by Finite Fracture Mechanics / Sapora, ALBERTO GIUSEPPE; Cornetti, Pietro; Carpinteri, Alberto. - ELETTRONICO. - (2011), pp. 155-158. (Intervento presentato al convegno Mesomechanics 2011 tenutosi a Vicenza nel 6-8 luglio 2011).

*Availability:*

This version is available at: 11583/2499417 since: 2016-05-06T14:36:40Z

*Publisher:*

*Published*

DOI:

*Terms of use:*

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

*Publisher copyright*

(Article begins on next page)

## Investigation on brittle fracture in rounded V-notched structures by Finite Fracture Mechanics

Alberto Sapora<sup>a\*</sup>, Pietro Cornetti<sup>a</sup>, Alberto Carpinteri<sup>a</sup>

*Department of Structural Engineering and Geotechnics, Politecnico di Torino, Corso Duca degli Abruzzi 24, 10129 Torino, Italy*

---

### Abstract

In the present work, Finite Fracture Mechanics (FFM) is applied to investigate the brittle fracture behaviour of rounded V-notched structures subjected to mode I loading. According to the criterion, fracture does not propagate continuously, but by finite crack extensions, whose value is determined by the contemporaneous fulfilment of a stress requirement and an energy balance. Consequently, the crack advance becomes a structural parameter. By assuming the apparent generalized stress intensity factor as the governing failure parameter, as expected within brittle structural behaviour, the expression for the apparent generalized fracture toughness as a function of the material properties as well as of the notch opening angle and the notch radius is achieved. FFM predictions are compared with those provided by other theoretical approaches based on a critical distance and with experimental data available in the Literature, showing a good agreement.

*Keywords:* rounded V-notches; mode I; brittle fracture; Finite Fracture Mechanics.

---

### 1. Introduction

Different criteria based on a linear-elastic analysis combined with an internal length have been proposed to deal with fracture initiation of brittle notched structures subjected to mode I loading [1-8]. For U-notched samples it has been shown that failure load predictions related to different approaches are generally very close [9]. On the other hand, for what concerns V-notched specimens, the coupled FFM criterion generally provides the most accurate results [7-8]. FFM was introduced to remove some inconsistencies related to the criteria previously introduced [2-5], according to which either stress or energetic considerations result violated. In the present work, it is applied to estimate the failure loads of rounded V-notched structures (Fig.1), subjected to mode I loading [10]. The analysis involves the characterization of the stress field and the stress intensity factor (SIF) functions ahead of the notch tip, which leads to the solution of non-linear equations.

---

\* Corresponding author. Tel.: +39 011 0904911; fax:+39 011 0904899.

E-mail address: alberto.sapora@polito.it.

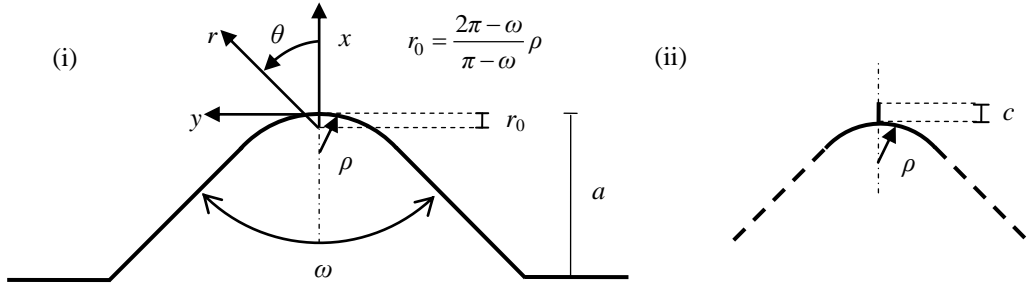


Fig. 1. (i) Rounded V-notch with Cartesian and polar coordinate systems. (ii) Crack of length  $c$  stemming from the notch tip.

## 2. Finite Fracture Mechanics

The FFM criterion [7-8] is based on the hypothesis of a finite crack advance  $\Delta$  and assumes a contemporaneous fulfilment of two conditions. The former requires that the average stress  $\sigma_y(x)$  upon the crack advance  $\Delta$  is higher than material tensile strength  $\sigma_u$

$$\int_0^{\Delta} \sigma_y(x) dx \geq \sigma_u \Delta. \quad (1)$$

The latter one ensures that the energy available for a crack increment  $\Delta$  is higher than the energy necessary to create the new fracture surface:

$$\int_0^{\Delta} K_I^2(c) dc \geq K_{Ic}^2 \Delta, \quad (2)$$

$K_I(c)$  and  $K_{Ic}$  being the SIFs related to a crack of length  $c$  stemming from the notch root and the fracture toughness, respectively. For positive geometries, in critical conditions, Eqs.(1-2) can be grouped into a system of two equations in two unknowns: the crack advancement and the failure load.

### 2.1. Stress field ahead of the notch tip

By assuming that the notch tip radius  $\rho$  is sufficiently small with respect to the notch depth  $a$  (Fig. 1), the stress field along the notch bisector could be expressed in polar coordinates as [11]:

$$\sigma_\theta(r, 0) = \frac{K_I^{V,\rho}}{(2\pi r)^{1-\lambda}} \left[ 1 + (r_0/r)^{\lambda-\mu} \eta_\theta(0) \right], \quad (3)$$

where  $K_I^{V,\rho}$  is the apparent generalized stress intensity factor. The distance between the notch tip and the origin of the polar coordinates system is denoted by  $r_0$ : it depends on the notch radius  $\rho$  and, as well as the eigenvalues  $\lambda$  and  $\mu$ , and the function  $\eta_\theta(0)$ , whose values are tabulated in [11], on the notch opening angle  $\omega$ .

## 2.2. Stress intensity factor function

In order to evaluate the SIF function  $K_I(c)$  related to a small crack of length  $c$  emanating from the notch root (Fig.1), we have performed some numerical simulations by means of FRANC2D<sup>®</sup> code [12] on notched structures under tension: different notch opening angles with different ratios  $c/\rho$  ranging from 0.01 to 10 have been taken into account, provided that  $a/\rho=b/a=20$ ,  $b$  being the overall geometric dimension. On the basis of the obtained results, we propose the following expression for the function  $K_I(c)$ :

$$K_I(c) = \alpha K_I^{V,\rho} \sqrt{c} \left[ \left( \frac{\alpha}{\beta} \right)^{\frac{1}{1-\lambda}} c + r_0 \right]^{\lambda-1}, \quad (4)$$

where  $\alpha=1.12\sqrt{\pi} (1+\eta_\theta(0)) (2\pi)^{\lambda-1}$  and  $\beta$  can be found tabulated in [8] (according to the present notation, it increases from unity, when  $\omega=0^\circ$ , up to  $1.12\sqrt{\pi}$ , when  $\omega=180^\circ$ ). For a very short crack ( $c/\rho \ll 1$ ), the notch-crack problem can be treated approximately as an edge crack subjected to the local peak stress: Eq.(4) provides consistently  $K_I(c)=1.12\sigma_{\max}\sqrt{\pi}c$  with  $\sigma_{\max}=\sigma_\theta(r_0, 0)$  (Eq.(3)). On the other hand, for a very long crack ( $c/\rho \gg 1$ ), the notch radius effect becomes negligible and Eq.(4) provides  $K_I(c)=\beta K_I^V c^{\lambda-0.5}$ , i.e. the SIF related to a crack stemming from a sharp V-notch. For intermediate values, Eq.(4) generally provides good results: the most significant deviations (below 10%) from the numerical predictions emerge for  $0.2 < c/\rho < 1$  and  $\omega \leq 90^\circ$ . Errors decrease as  $\omega$  increases.

In order to apply the FFM criterion, Eqs. (3) and (4) must be inserted into Eqs. (1) and (2), respectively (notice that  $x=r-r_0$ ). By supposing that failure takes place when the apparent generalized stress intensity factor reaches its critical conditions  $K_I^{V,\rho} = K_{Ic}^{V,\rho}$  (as expected within brittle structural behaviour) and integrating, some analytical passages lead to the following expression for the apparent generalized fracture toughness  $K_{Ic}^{V,\rho}$ :

$$K_{Ic}^{V,\rho} = \sigma_u r_0^{1-\lambda} \sigma(\bar{\Delta}_c), \quad \text{with} \quad r_0 = (K_{Ic} / \sigma_u)^2 g(\bar{\Delta}_c) / \sigma^2(\bar{\Delta}_c), \quad \text{and} \quad \bar{\Delta}_c = \Delta_c / r_0. \quad (5)$$

The two functions  $\sigma$  and  $g$  are expressed analytically by the following relationships:

$$\sigma(\bar{\Delta}_c) = (2\pi)^{1-\lambda} \bar{\Delta}_c \left\{ \left[ \left( \bar{\Delta}_c + 1 \right)^\lambda - 1 \right] / \lambda + \eta_\theta(0) \left[ \left( \bar{\Delta}_c + 1 \right)^\mu - 1 \right] / \mu \right\}^{-1},$$

$$g(\bar{\Delta}_c) = \frac{\bar{\Delta}_c}{\beta^2} \left\{ \left[ \left( \bar{\Delta}_c + \left( \frac{\beta}{\alpha} \right)^{\frac{1}{1-\lambda}} \right)^{2\lambda} - \left( \frac{\beta}{\alpha} \right)^{\frac{2\lambda}{1-\lambda}} \right] / 2\lambda - \left( \frac{\beta}{\alpha} \right)^{\frac{1}{1-\lambda}} \left[ \left( \bar{\Delta}_c + \left( \frac{\beta}{\alpha} \right)^{\frac{1}{1-\lambda}} \right)^{2\lambda-1} - \left( \frac{\beta}{\alpha} \right)^{\frac{2\lambda-1}{1-\lambda}} \right] / (2\lambda-1) \right\}^{-1}.$$

## 3. Experimental validation

The theoretical predictions from FFM (Eq.(5)) are compared with some experimental results available in the Literature [13-14] and with those provided by the simple point stress (PS) criterion [1]. Details of the sample geometry and the material properties (PMMA at  $-60^\circ$  [13] and Alumina-7%Zirconia [14]) can be found in the quoted references. As can be seen (Fig.2), FFM predictions better agree with experimental data, the maximum percentage error being nearly 10% for the last two data sets related to the  $150^\circ$ -notched PMMA samples. Indeed, in these cases, the notch radius is not so small with respect to the notch

depth ( $\rho/a \approx 0.17$ ): thus, the stress field according to Eq.(3) results a little overestimated. Summarizing, the good fitting found (Fig.2) confirms the validity of the present approach as well as that related to the expression proposed for function  $K_I(c)$  (Eq.(4)).

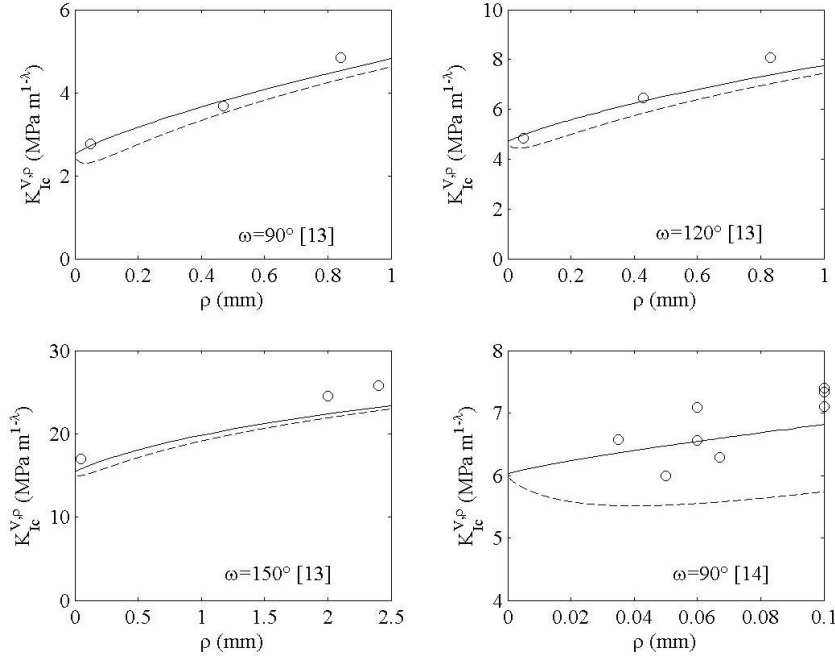


Fig. 2.  $K_{Ic}^{V,\rho}$  vs.  $\rho$ : experimental data (circle) and theoretical predictions according to the PS criterion (dashed line) and FFM.

## Acknowledgments

The financial support of the Italian Ministry of Education, University and Research (MIUR) to the Project “Advanced applications of Fracture Mechanics for the study of integrity and durability of materials and structures” within the “Programmi di ricerca scientifica di rilevante interesse nazionale (PRIN)” program for the year 2008 is gratefully acknowledged.

## References

- [1] Carpinteri A, Stress-singularity and generalized fracture toughness at the vertex of re-entrant corners, *Eng Fract Mech* 1987;**26**:143-55.
- [2] Taylor D, Predicting the fracture strength of ceramic materials using the theory of critical distances. *Eng Fract Mech* 2004;**71**:2407-16.
- [3] Seweryn A, Brittle fracture criterion for structures with sharp notches. *Eng Fract Mech* 1994;**47**:673-681.
- [4] Sih G, Macdonald B, Fracture mechanics applied to engineering problems-strain energy density fracture criterion. *Eng Fract Mech* 1974;**6**:361-386.
- [5] Lazzarin P, Zambardi R, A finite-volume-energy based approach to predict the static and fatigue behaviour of components with sharp V-shaped notches. *Int J Fract* 2001;**112**:275-298.
- [6] Leguillon D, Strength or toughness? A criterion for crack onset at a notch. *Eur J Mech A/Solids* 2002;**21**:61-72.
- [7] Carpinteri A, Cornetti P, Pugno N, Sapora A, Taylor D, A finite fracture mechanics approach to structures with sharp V-notches. *Eng Fract Mech* 2008;**75**:1736-52.
- [8] Carpinteri A, Cornetti P, Pugno N, Sapora A, On the most dangerous V-notch- *Int J Solid Struct* 2010;**47**:887-93.
- [9] Gomez FJ, Guinea GV, Elices M, Failure criteria for linear elastic materials with U-notches. *Int J Fract* 2006;**141**:99-113.
- [10] Ayatollahi MR, Torabi AR, Brittle fracture in rounded-tip V-shaped notches. *Materials and Design* 2010;**31**:60-67.
- [11] Filippi S, Lazzarin P, Tovo R, Developments of some explicit formulas useful to describe elastic stress fields ahead of notches in plates. *Int J Solid Struct* 2002;**39**:4543-65.

- [12] Ingraffea AR, Wawrzynek PA, User's guide for FRAN2D Version 3.1 1993 [www.cfg.cornell.edu](http://www.cfg.cornell.edu).
- [13] Gomez FJ, Elices M, A fracture criterion for blunted V-notched samples. *Int J Fract* 2004;**127**:239-64.
- [14] Yoshibah Z, Bubissa A, Gilad I, Fracture criteria for brittle elastic materials. *Int J Fract* 2004;**125**:307-33.