

Characterization of the recovery of mechanical properties of ion-implanted diamond after thermal annealing

*Original*

Characterization of the recovery of mechanical properties of ion-implanted diamond after thermal annealing / Mohr, M.; Picollo, F.; Battiato, A.; Bernardi, E.; Forneris, J.; Tengattini, A.; Enrico, E.; Boarino, L.; Bosia, F.; Fecht, H. -J.; Olivero, P.. - In: DIAMOND AND RELATED MATERIALS. - ISSN 0925-9635. - 63:(2016), pp. 75-79.  
[10.1016/j.diamond.2015.11.008]

*Availability:*

This version is available at: 11583/2774893 since: 2019-12-19T22:20:17Z

*Publisher:*

Elsevier Ltd

*Published*

DOI:10.1016/j.diamond.2015.11.008

*Terms of use:*

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

*Publisher copyright*

Elsevier postprint/Author's Accepted Manuscript

© 2016. This manuscript version is made available under the CC-BY-NC-ND 4.0 license  
<http://creativecommons.org/licenses/by-nc-nd/4.0/>. The final authenticated version is available online at:  
<http://dx.doi.org/10.1016/j.diamond.2015.11.008>

(Article begins on next page)

# AFM characterization of free-standing diamond microcantilevers for the investigation of the damage-induced variation of Young's modulus

M. Mohr<sup>1</sup>, F. Picollo<sup>2,3,4</sup>, A. Battiato<sup>3,2,4</sup>, E. Bernardi<sup>3,2,4</sup>, J. Forneris<sup>3,2,4</sup>, A. Tengattini<sup>3,2,4</sup>,  
E. Enrico<sup>6</sup>, L. Boarino<sup>6</sup>, F. Bosia<sup>3,2,4</sup>, H.-J. Fecht<sup>1</sup>, P. Olivero<sup>3,2,4\*</sup>

<sup>1</sup>*Institute of Micro and Nanomaterials, Ulm University, Ulm, Germany.*

<sup>2</sup>*Istituto Nazionale di Fisica Nucleare (INFN), Section of Torino, Italy.*

<sup>3</sup>*Physics Department and “Nanostructured Interfaces and Surfaces” Inter-departmental Centre - University of Torino, Torino, Italy.*

<sup>4</sup>*Consorzio Nazionale Inter-universitario per le Scienze Fisiche della Materia (CNISM), Section of Torino, Italy.*

<sup>5</sup>*Istituto Nazionale di Fisica Nucleare (INFN), Legnaro National Laboratories, Padova, Italy.*

<sup>6</sup>*Nanofacility Piemonte, Istituto Nazionale di Ricerca Metrologica (INRiM), Torino, Italy.*

\* corresponding author: [paolo.olivero@unito.it](mailto:paolo.olivero@unito.it)

**Keywords:** diamond, ion-induced damage, ion beam lithography, mechanical properties, atomic force microscopy

## Abstract

Due to their outstanding mechanical properties, diamond and diamond-like materials find significant technological applications ranging from well-established industrial fields (cutting tools, coatings, etc.) to more advanced mechanical devices as micro- and nano-electromechanical systems. The use of energetic ions is a powerful and versatile tool to fabricate three-dimensional micro-mechanical structures. In this context, it is of paramount importance to have an accurate knowledge of the effects of ion-induced structural damage on the mechanical properties of this

material, firstly to predict potential undesired side-effects of the ion implantation process, and possibly to tailor the desired mechanical properties of the fabricated devices. We present an Atomic Force Microscopy (AFM) characterization of free-standing cantilevers in single-crystal diamond obtained by a FIB-assisted lift-off technique, which allows a determination of the Young's modulus of the diamond crystal after the MeV ion irradiation process concurrent to the fabrication of the microstructures. The AFM measurements were performed with the beam-bending technique, showing that the thermal annealing process adopted during the microfabrication process allows for an effective recovery of the mechanical properties of the pristine crystal.

## 1. Introduction

MeV ion implantation has been widely exploited in recent years for the micro-fabrication of single-crystal diamond, through the implementation of the so-called "lift-off technique" [1-4]. This technique can be effectively adopted to fabricate micro-mechanical structures in single-crystal diamond, with applications ranging from high-frequency MEMS devices [5-11] to opto-mechanical resonators [12], thus taking advantage of the extreme mechanical properties of diamond [13]. Recently, the latter topic attracted significant interest due to the outstanding properties of nitrogen-vacancy centers in diamond [14], whose spin-dependent optical transition can effectively couple with local mechanical stresses [15-17]. To this end, various different techniques have been employed to fabricate opto-mechanical resonators in diamond [18-21].

In the case of the lift-off technique, the fabrication process is based on the local conversion of diamond to a sacrificial graphitic layer through MeV-ion-induced damage [4]. The fabrication technique is very versatile, because the local induced damage density can be controlled by varying implantation parameters (namely, ion energy, species and fluence). Nonetheless, a residual damage density (and related mechanical stress) is induced in the non-sacrificial regions as a side-effect of the fabrication technique [22]. Similarly, also with other fabrication techniques [18-21], a residual

damage can be induced in the fabricated opto-mechanical microstructures, particularly if ion implantation is adopted to induce the formation of nitrogen-vacancy centers [23]. For these reasons, it is necessary to accurately estimate deformation and stress levels to reliably design and fabricate MEMS structures. Moreover, the variation of elastic properties of damaged diamond as a function of induced damage density and post-processing (annealing) parameters remains to be clarified. In particular the Young's modulus of ion-implanted diamond can potentially vary between that of pristine diamond ( $>1$  TPa, in the presence of no damage) to that of amorphous carbon ( $\sim 10$  GPa, for full amorphization), i.e. over two orders of magnitude. Clearly, this large variation in elastic properties is likely to strongly affect modelling results in the fabrication of mechanical and opto-mechanical resonators. Attempts have been made to experimentally derive the variation of elastic properties of diamond as a function of induced damage, but only indirect estimations with limited accuracy have been obtained [24]. This lack of experimental data is partly due to its high Young's modulus, which makes it difficult to perform indentation experiments. Here, we perform a study of the elastic properties of ion-implanted diamond by means of Atomic Force Microscope (AFM) measurements on free-standing cantilever structures microfabricated in single-crystal diamond with FIB-assisted lift-off technique [3, 4].

## 2. Micro-fabrication

An artificial diamond sample grown by High Pressure High Temperature (HPHT) by ElementSix (UK) was employed in this work. The sample is  $2.6 \times 2.6 \times 0.5$  mm<sup>3</sup> in size and is classified as type Ib, on the basis of a nominal concentration of substitutional nitrogen  $\sim 500$  ppm. The sample is cut along the [100] crystal direction and is optically polished on one of the two opposite large faces. The sample was implanted at room temperature across one of the polished surfaces with 800 keV He<sup>+</sup> ions at the AN2000 accelerator of the INFN National Laboratories of Legnaro with a focused ion beam, in order to deliver a fluence of  $1 \times 10^{17}$  cm<sup>-2</sup>. The microbeam spot was  $\sim 10$   $\mu$ m in

diameter, and was raster-scanned to implant a rectangular area of  $\sim 500 \times 200 \mu\text{m}^2$ . The high density of damage induced by ion implantation promotes the conversion of the diamond lattice into an amorphous phase within a layer which is located at  $\sim 1.4 \mu\text{m}$  below the sample surface, as shown in Fig. 1.


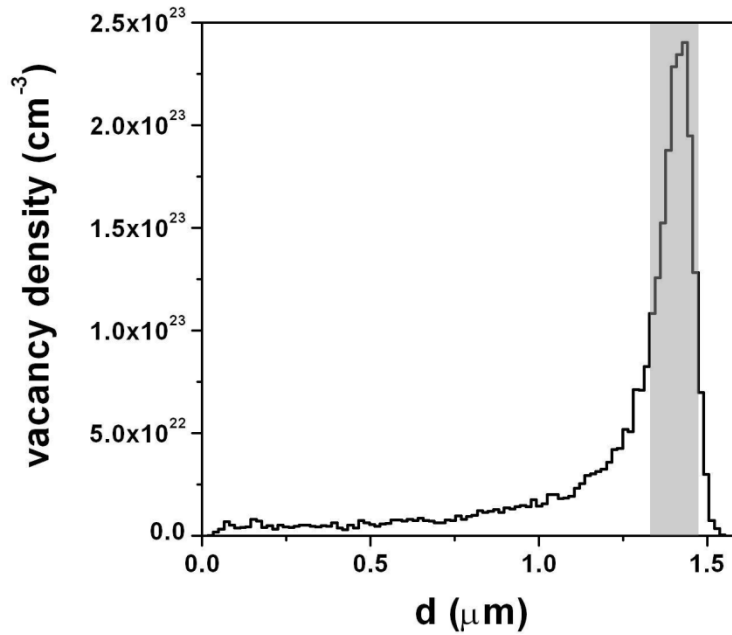


Fig. 1: depth profile of the vacancy density induced by 800 keV  $\text{He}^+$  ion implantation at fluence  $1 \times 10^{17} \text{ cm}^{-2}$ , as evaluated with SRIM2013.00 Monte Carlo code [25] and assuming a linear dependence of the induced vacancy density from the implantation fluence [26].

The sample was then annealed in high vacuum ( $\sim 10^{-6}$  mbar) at 1000 °C for 1 h, to convert the highly-damaged regions located at the ion end of range to a graphitic phase while removing the structural sub-threshold damage introduced in the layer overlying the damaged region. Following the fabrication scheme described in [1], FIB milling with 30 keV  $\text{Ga}^+$  ions was subsequently performed on the implanted area, to expose the sub-superficial graphitic layer to the subsequent etching step, while defining the geometries of three different cantilever structures characterized by different widths (see Fig. 2). A thin Au film was deposited on the sample surface to avoid charge effects during FIB micro-machining. The sample was then exposed to contact-less electrochemical

93 etching [27]: the sample was immersed for several hours in de-ionized water with the region of  
94 interest comprised between two close (i.e. few millimeters) Pt electrodes kept at a DC voltage  
95 difference of  $\sim 100$  V. The process resulted in the selective removal of the sacrificial graphitic layer  
96 and in the creation of free-standing cantilever structures with a lateral geometry defined by the  
97 previous FIB micromachining, i.e. a length of  $117\text{ }\mu\text{m}$  for cantilevers #1 and #2 and of  $111\text{ }\mu\text{m}$  for  
98 cantilever #3. The widths of cantilevers #1, #2 and #3 were respectively  $13\text{ }\mu\text{m}$ ,  $9\text{ }\mu\text{m}$  and  $22\text{ }\mu\text{m}$ .  
99 The thickness of all cantilevers corresponded to the penetration depth of the employed  $800\text{ keV}$   
100 ions, i.e.  $1.3\text{ }\mu\text{m}$ . As shown in Fig. 2, all cantilevers are slightly bent by the inner stresses caused by  
101 residual damage induced during the fabrication process within the “cap layer” comprised between  
102 the sub-superficial graphitic layer and the sample surface.

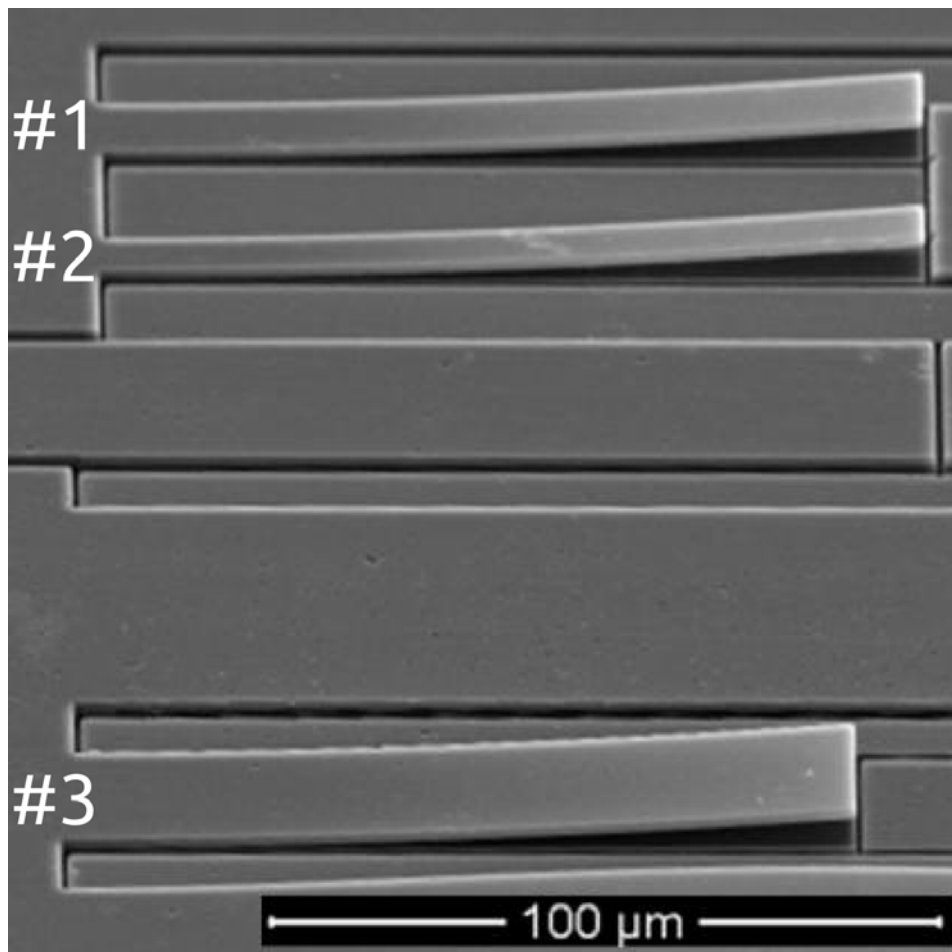

103  
104 *Fig. 2: SEM micrograph of the three free-standing cantilever structures fabricated in single-crystal*  
105 *diamond by means of the FIB-assisted lift-off technique.*

### 3. AFM Characterisation

In order to determine the Young's modulus of the diamond, a beam-bending method was employed [28-30]. The method consists in loading the microstructures using an AFM cantilever. As shown in Fig. 3, the deflection  $d$  of the probing AFM cantilever for the displacement  $z$  of the piezomotor is measured by means of a laser diode and a position-sensitive photodiode (Veeco Dimension 3100).

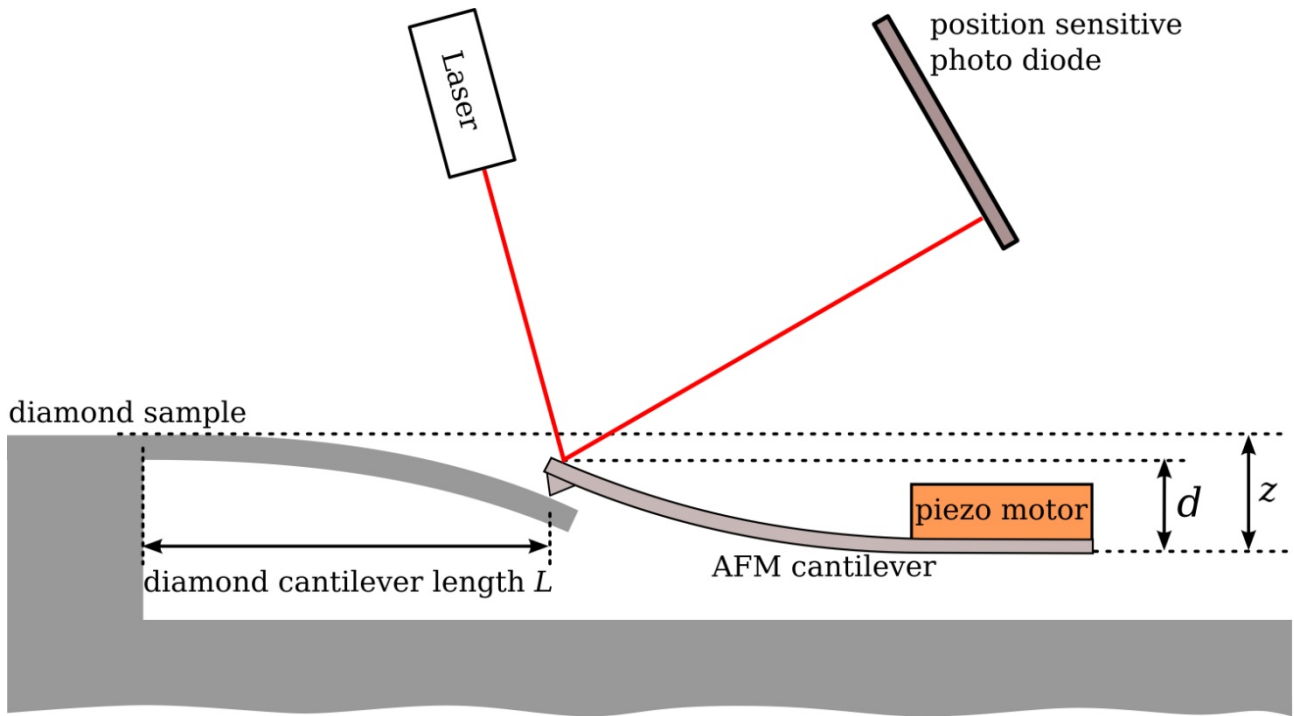


Fig. 3: Schematic representation (not to scale) of the beam-bending technique employed to measure the Young's modulus of the microfabricated diamond cantilevers. An AFM cantilever loads the diamond microstructure at a length  $L$ , while the displacement  $d$  of the AFM cantilever is measured as a function of the piezomotor displacement  $z$ .

The effective stiffness  $k_{eff}$  of the system based on the coupling of the two cantilever structures is measured by recording approach curves. The effective stiffness  $k_{eq}$  is equal to:

$$k_{eff} = \frac{1}{\frac{1}{k_{AFM}} + \frac{1}{k_{diam}}} \quad (1)$$

where  $k_{AFM}$  and  $k_{diam}$  are respectively the stiffness values of the probing AFM cantilever and of the diamond cantilever under test. The  $d/z$  value is equal to [28]:

$$\frac{d}{z} = \frac{k_{eff}}{k_{AFM}} \quad (2)$$

Thus, the stiffness of the beam under test can be determined, if the stiffness of the AFM cantilever is known. The adopted AFM cantilever is a single-crystalline silicon cantilever (NCLR, Nanoworld). Its geometry is precisely determined by means of SEM microscopy and its stiffness was evaluated as  $k_{AFM} = (57.0 \pm 1.2) \text{ N m}^{-1}$ .

The three diamond cantilevers mentioned above were investigated, and for each of them the stiffness values were measured in correspondence of several (i.e. >5) different positions along the cantilever axis. The stiffness of the diamond cantilever is determined by the following formula:

$$k_{diam} = \frac{3 \cdot E \cdot I}{(1 - \nu^2) \cdot L^3} \quad (3)$$

where  $E$  is its Young's modulus,  $I$  is its areal moment of inertia,  $\nu$  is its Poisson's ratio, and  $L$  is its length, i.e. the distance from the clamping point where the load is applied [31]. Due to a possible systematic error in the determination of the cantilever length and the finite stiffness of the cantilever fixture, we used the following correction to fit the  $k_{diam}$  vs  $L$  trend [32, 33]:

$$k_{diam} = \frac{3 \cdot E \cdot I}{(1 - \nu^2) \cdot (L + L_0)^3} \quad (4)$$

The Poisson's ratio was estimated with the value corresponding to pristine undamaged diamond, i.e. 0.105 [34], considering bending along the (100) direction, consistently with the well-defined orientation of the structure with respect to the crystal orientation. The geometry of the diamond



beams was measured by means of SEM microscopy and the moment of inertia  $I$  for each cantilever was calculated by taking into consideration their slightly trapezoidal beam cross-section (see Fig. 4), as follows [35]:

$$I = \frac{h^3}{36} \cdot \frac{(b_1^2 + 4 \cdot b_1 \cdot b_2 + b_2^2)}{(b_1 + b_2)} \quad (5)$$

where  $h$  is the thickness of the cantilever and  $b_1$  and  $b_2$  are the two widths of the trapezoidal cross section (see Fig. 4). The Young's modulus  $E$  of the diamond cantilever is then calculated using by fitting the  $k_{diam}$  vs  $L$  trend with Eq. (4), in which the moment of inertia  $I$  is estimated as reported in Eq. (5).

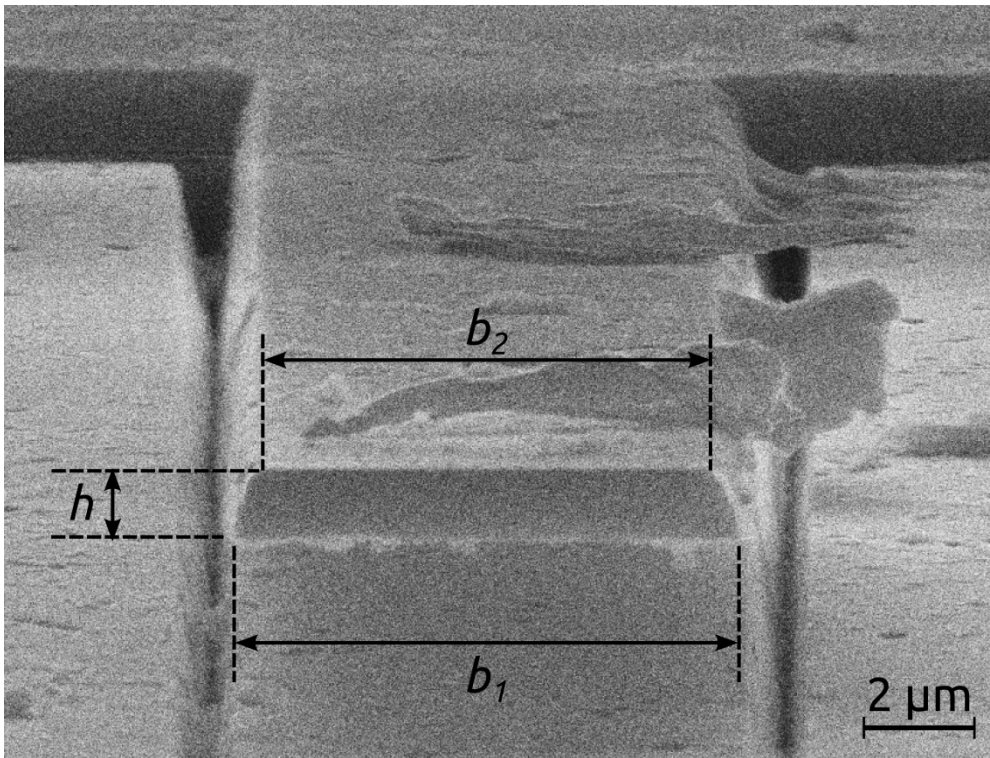


Fig. 4: SEM micrograph of the trapezoidal cross-section of cantilever #2.  $h$  is the thickness of the cantilever, while  $b_1$  and  $b_2$  are respectively the lower and upper widths of the cross section.

Representative results of the  $k_{diam}$  vs  $L$  measurements relative to cantilever #3 are reported in Fig. 5a, together with the fitted curve (see using Eq. (4)). The fit of the experimental data is very

satisfactory, yielding a Young's modulus value of  $E = (9.6 \pm 1.1) \times 10^2$  GPa. The Young's moduli for the three cantilevers are reported in Fig. 5b, together with their weighted average value and its relevant uncertainty, as well as with a comparison with the reference value of pristine single-crystal diamond. In the case of cantilever #1, the discrepancy between the measured Young's modulus and the reference value is statistically significant, and the calculated stiffness value is exceedingly high. This can be tentatively attributed to a non-ideal detachment of the beam from the substrate during the etching fabrication process, which potentially increases the stiffness of the structure and yields incorrect values when using the above formulas. Nevertheless, the weighted average of the three Young's modulus values yields an estimation of  $E = (1.11 \pm 0.08)$  TPa, which is statistically compatible with the reference value in literature for single-crystal diamond, i.e. 1.05 TPa [36]. This compatibility is remarkable, particularly if it is considered that we assumed a value of the Poisson's ratio corresponding to the pristine diamond, thus introducing a potential systematic error. Since single-crystal diamond is mechanically anisotropic [34], with the Young's modulus in the (100) direction can be calculated as follows:

$$E_{(100)} = \frac{1}{S_{11}} \quad (6)$$

where  $S_{11}$  is the 11 component of elastic coefficient tensor  $S_{ij}$  according to the standard notation. Thus, the Poisson's ratio describing the contraction in the (001) direction due to tension in the (100) direction can be calculated as follows:

$$\nu_{(100)} = -S_{12} \cdot E_{100} \quad (7)$$

From the values of the  $S_{ij}$  elastic coefficients reported in [37], we obtain  $E_{(100)} = 1.05$  TPa and  $\nu_{(100)} = 0.11$ . Again, these values are close to the literature values for single-crystal diamond [36].

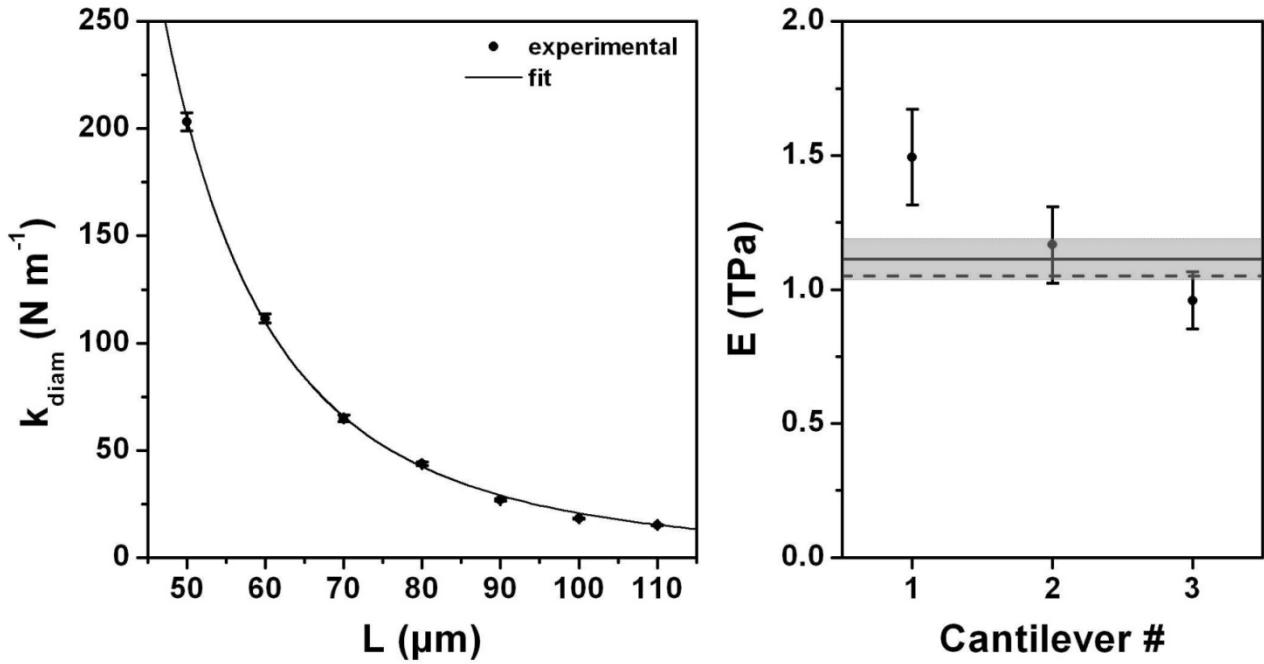


Fig. 5: a) experimental values (dots) of the stiffness of cantilever #3 at different beam lengths together with the relevant fitting curve (line). b) Young's moduli for the three cantilevers estimated from the fit of the experimental data (dots), together with the weighted average value (solid line) and the relevant uncertainty (grey box); the Young's modulus value for pristine single-crystal diamond taken from literature [36] is reported for comparison (dashed line).

#### 4. Conclusions

We demonstrated the feasibility and reliability of an AFM-based beam-bending technique to determine the mechanical properties single-crystal diamond cantilevers, and investigated the effects of MeV ion implantation and subsequent high-temperature annealing on these mechanical properties. The obtained results provide direct evidence that both the Young's modulus and Poisson's ratio values of diamond after sub-graphitization-threshold irradiation and high-temperature annealing are fully recovered to their pristine values. These results provide useful information for the reliable design of (opto-) mechanical resonators in single-crystal diamond. We envisage to repeat these measurements on micro-structures subjected to controlled ion irradiation,

with the purpose of directly investigating the effect of ion-induced damage on their mechanical properties, thus allowing the fine-tuning of their resonance frequencies.

## **Acknowledgements**

This work was supported by the following projects: “DiNaMo” (young researcher grant, project n° 157660) by INFN; FIRB “Futuro in Ricerca 2010” (CUP code: D11J11000450001) funded by MIUR and “A.Di.N-Tech.” (CUP code: D15E13000130003) funded by the University of Torino and “Compagnia di San Paolo”. The MeV ion beam lithography activity was performed within the “Dia.Fab.” experiment of the INFN Legnaro National Laboratories. The FIB lithography was performed at the “NanoFacility Piemonte” laboratory, which is supported by the “Compagnia di San Paolo” Foundation.

**References**

- [1] N.R. Parikh, J.D. Hunn, E. McGucken, M.L. Swanson, C.W. White, R.A. Rudder, D.P. Malta, J.B. Posthill, R.J. Markunas, Single-crystal diamond plate liftoff achieved by ion implantation and subsequent annealing. *Applied Physics Letters*, 61 (1992) 3124-3126.
- [2] J.D. Hunn, S.P. Withrow, C.W. White, R.E. Clausing, L. Heatherly, C.P. Christensen, Fabrication of single-crystal diamond microcomponents. *Applied Physics Letters*, 65 (1994) 3072-3074.
- [3] P. Olivero, S. Rubanov, P. Reichart, B.C. Gibson, S.T. Huntington, J. Rabeau, A.D. Greentree, J. Salzman, D. Moore, D.N. Jamieson, S. Prawer, Ion-beam-assisted lift-off technique for three-dimensional micromachining of freestanding single-crystal diamond. *Advanced Materials*, 17 (2005) 2427-+.
- [4] B.A. Fairchild, P. Olivero, S. Rubanov, A.D. Greentree, F. Waldermann, R.A. Taylor, I. Walmsley, J.M. Smith, S. Huntington, B.C. Gibson, D.N. Jamieson, S. Prawer, Fabrication of Ultrathin Single-Crystal Diamond Membranes. *Advanced Materials*, 20 (2008) 4793-4798.
- [5] C.F. Wang, E.L. Hu, J. Yang, J.E. Butler, Fabrication of suspended single crystal diamond devices by electrochemical etch. *Journal of Vacuum Science & Technology B*, 25 (2007) 730-733.
- [6] M. Liao, S. Hishita, E. Watanabe, S. Koizumi, Y. Koide, Suspended Single-Crystal Diamond Nanowires for High-Performance Nanoelectromechanical Switches. *Advanced Materials*, 22 (2010) 5393-5397.
- [7] M. Liao, C. Li, S. Hishita, Y. Koide, Batch production of single-crystal diamond bridges and cantilevers for microelectromechanical systems. *J Micromech Microeng*, 20 (2010) 085002.
- [8] M.K. Zalalutdinov, M.P. Ray, D.M. Photiadis, J.T. Robinson, J.W. Baldwin, J.E. Butler, T.I. Feygelson, B.B. Pate, B.H. Houston, Ultrathin Single Crystal Diamond Nanomechanical Dome Resonators. *Nano Letters*, 11 (2011) 4304-4308.

- 241 [9] M.P. Ray, T.I. Feygelson, J.E. Butler, J.W. Baldwin, B.H. Houston, B.B. Pate, M.K.  
242 Zalalutdinov, Dissipation in single crystal diamond micromechanical annular plate resonators. *Diam*  
243 *Relat Mater*, 20 (2011) 1204-1207.
- 244 [10] M. Liao, Z. Rong, S. Hishita, M. Imura, S. Koizumi, Y. Koide, Nanoelectromechanical switch  
245 fabricated from single crystal diamond: Experiments and modeling. *Diam Relat Mater*, 24 (2012)  
246 69-73.
- 247 [11] M. Liao, M. Toda, L. Sang, S. Hishita, S. Tanaka, Y. Koide, Energy dissipation in micron- and  
248 submicron-thick single crystal diamond mechanical resonators. *Applied Physics Letters*, 105 (2014)  
249 251904.
- 250 [12] J.C. Lee, D.O. Bracher, S. Cui, K. Ohno, C.A. McLellan, X. Zhang, P. Andrich, B. Alemán,  
251 K.J. Russell, A.P. Magyar, I. Aharonovich, A. Bleszynski Jayich, D. Awschalom, E.L. Hu,  
252 Deterministic coupling of delta-doped nitrogen vacancy centers to a nanobeam photonic crystal  
253 cavity. *Applied Physics Letters*, 105 (2014) 261101.
- 254 [13] H.-J. Fecht, K. Brühne, P. Gluche, "Carbon-based Nanomaterials and Hybrids-Synthesis,  
255 Properties and Commercial Applications", Pan Stanford Publishing, Singapore (2014)
- 256 [14] V. Acosta, P. Hemmer, Nitrogen-vacancy centers: Physics and applications. *MRS Bulletin*, 38  
257 (2013) 127-130.
- 258 [15] P. Olivero, F. Bosia, B.A. Fairchild, B.C. Gibson, A.D. Greentree, P. Spizzirri, S. Praver,  
259 Splitting of photoluminescent emission from nitrogen-vacancy centers in diamond induced by ion-  
260 damage-induced stress. *New Journal of Physics*, 15 (2013).
- 261 [16] L.J. Rogers, S. Armstrong, M.J. Sellars, N.B. Manson, Infrared emission of the NV centre in  
262 diamond: Zeeman and uniaxial stress studies. *New Journal of Physics*, 10 (2008) 103024.
- 263 [17] M.W. Doherty, V.V. Struzhkin, D.A. Simpson, L.P. McGuinness, Y. Meng, A. Stacey, T.J.  
264 Karle, R.J. Hemley, N.B. Manson, L.C.L. Hollenberg, S. Praver, Electronic Properties and  
265 Metrology Applications of the Diamond NV<sup>-</sup> Center under Pressure. *Physical Review Letters*, 112  
266 (2014) 047601.

- 267 [18] E.R. MacQuarrie, T.A. Gosavi, N.R. Jungwirth, S.A. Bhawe, G.D. Fuchs, Mechanical Spin  
268 Control of Nitrogen-Vacancy Centers in Diamond. *Phys Rev Lett*, 111 (2013) 227602.
- 269 [19] P. Ovartchaiyapong, K.W. Lee, B.A. Myers, A.C.B. Jayich, Dynamic strain-mediated coupling  
270 of a single diamond spin to a mechanical resonator. *Nature Communications*, 5 (2014) 5429.
- 271 [20] J. Teissier, A. Barfuss, P. Appel, E. Neu, P. Maletinsky, Strain Coupling of a Nitrogen-  
272 Vacancy Center Spin to a Diamond Mechanical Oscillator. *Physical Review Letters*, 113 (2014)  
273 020503.
- 274 [21] E.R. MacQuarrie, T.A. Gosavi, A.M. Moehle, N.R. Jungwirth, S.A. Bhawe, G.D. Fuchs,  
275 Coherent control of a nitrogen-vacancy center spin ensemble with a diamond mechanical resonator.  
276 *Optica*, 2 (2015) 233-238.
- 277 [22] P. Olivero, S. Rubanov, P. Reichart, B.C. Gibson, S.T. Huntington, J.R. Rabeau, A.D.  
278 Greentree, J. Salzman, D. Moore, D.N. Jamieson, S. Praver, Characterization of three-dimensional  
279 microstructures in single-crystal diamond. *Diam Relat Mater*, 15 (2006) 1614-1621.
- 280 [23] S. Pezzagna, D. Rogalla, D. Wildanger, J. Meijer, A. Zaitsev, Creation and nature of optical  
281 centres in diamond for single-photon emission—overview and critical remarks. *New Journal of*  
282 *Physics*, 13 (2011) 035024.
- 283 [24] R.A. Khmel'nitsky, V.A. Dravin, A.A. Tal, E.V. Zavedeev, A.A. Khomich, A.V. Khomich,  
284 A.A. Alekseev, S.A. Terentiev, Damage accumulation in diamond during ion implantation. *J Mater*  
285 *Res*, 30 (2015) 1583-1592.
- 286 [25] J.F. Ziegler, M.D. Ziegler, J.P. Biersack, SRIM – The stopping and range of ions in matter  
287 (2010). *Nuclear Instruments and Methods in Physics Research Section B: Beam Interactions with*  
288 *Materials and Atoms*, 268 (2010) 1818-1823.
- 289 [26] F. Bosia, S. Calusi, L. Giuntini, S. Lagomarsino, A. Lo Giudice, M. Massi, P. Olivero, F.  
290 Picollo, S. Sciortino, A. Sordini, M. Vannoni, E. Vittone, Finite element analysis of ion-implanted  
291 diamond surface swelling. *Nuclear Instruments & Methods in Physics Research Section B-Beam*  
292 *Interactions with Materials and Atoms*, 268 (2010) 2991-2995.

- 293 [27] M. Marchywka, P.E. Pehrsson, S.C. Binari, D. Moses, Electrochemical Patterning of  
294 Amorphous Carbon on Diamond. Journal of The Electrochemical Society, 140 (1993) L19-L22.
- 295 [28] C. Serre, P. Gorostiza, A. Perez-Rodriguez, F. Sanz, J.R. Morante, Measurement of  
296 micromechanical properties of polysilicon microstructures with an atomic force microscope. Sensor  
297 Actuat a-Phys, 67 (1998) 215-219.
- 298 [29] C. Serre, A. Perez-Rodriguez, J.R. Morante, P. Gorostiza, J. Esteve, Determination of  
299 micromechanical properties of thin films by beam bending measurements with an atomic force  
300 microscope. Sensor Actuat a-Phys, 74 (1999) 134-138.
- 301 [30] E. Sillero, O.A. Williams, V. Lebedev, V. Cimalla, C.C. Rohlig, C.E. Nebel, F. Calle, Static  
302 and dynamic determination of the mechanical properties of nanocrystalline diamond  
303 micromachined structures. J Micromech Microeng, 19 (2009).
- 304 [31] L.D. Landau, E.M. Lifshits, Theory of elasticity, 2d English ed., Pergamon Press, Oxford, New  
305 York,, 1970.
- 306 [32] S.P. Baker, W.D. Nix, Mechanical-Properties of Compositionally Modulated Au-Ni Thin-  
307 Films - Nanoindentation and Microcantilever Deflection Experiments. J Mater Res, 9 (1994) 3131-  
308 3145.
- 309 [33] T.Y. Zhang, M.H. Zhao, C.F. Qian, Effect of substrate deformation on the microcantilever  
310 beam-bending test. J Mater Res, 15 (2000) 1868-1871.
- 311 [34] C.A. Klein, G.F. Cardinale, Young's modulus and Poisson's ratio of CVD diamond. Diam  
312 Relat Mater, 2 (1993) 918-923.
- 313 [35] J.M. Gere, S. Timoshenko, Mechanics of materials, 4th ed., PWS Pub Co., Boston, 1997.
- 314 [36] C.A. Klein, G.F. Cardinale, Young Modulus and Poisson Ratio of Cvd Diamond. P Soc Photo-  
315 Opt Ins, 1759 (1992) 178-192.
- 316 [37] R. Vogelgesang, A.K. Ramdas, S. Rodriguez, M. Grimsditch, T.R. Anthony, Brillouin and  
317 Raman scattering in natural and isotopically controlled diamond. Phys Rev B, 54 (1996) 3989-  
318 3999.



