

Integrated and comparative Structural-LCA analysis of unbound and cement-stabilized construction and demolition waste aggregate for subbase road pavement layers formation

Original

Integrated and comparative Structural-LCA analysis of unbound and cement-stabilized construction and demolition waste aggregate for subbase road pavement layers formation / Tefa, L.; Bianco, I.; Blengini, G. A.; Bassani, M.. - In: JOURNAL OF CLEANER PRODUCTION. - ISSN 0959-6526. - STAMPA. - 352:(2022), p. 131599. [10.1016/j.jclepro.2022.131599]

Availability:

This version is available at: 11583/2960692 since: 2023-05-04T08:38:03Z

Publisher:

Elsevier

Published

DOI:10.1016/j.jclepro.2022.131599

Terms of use:

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

Publisher copyright

Elsevier postprint/Author's Accepted Manuscript

© 2022. This manuscript version is made available under the CC-BY-NC-ND 4.0 license
<http://creativecommons.org/licenses/by-nc-nd/4.0/>. The final authenticated version is available online at:
<http://dx.doi.org/10.1016/j.jclepro.2022.131599>

(Article begins on next page)

Integrated and Comparative Structural-LCA Analysis of Unbound and Cement-Stabilized Construction and Demolition Waste Aggregate for Subbase Road Pavement Layers Formation

Tefa*, L., Bianco, I., Blengini, G.A., and M. Bassani

Department of Environment, Land and Infrastructure Engineering, Politecnico di Torino, Torino, Italy

Luca Tefa: luca.tefa@polito.it

Isabella Bianco: isabella.bianco@polito.it

Gian Andrea Blengini: giovanni.blengini@polito.it

Marco Bassani: marco.bassani@polito.it

* corresponding author

ABSTRACT

A more extensive use of recycled aggregate in road construction is key to meeting the ambitious targets of the EU circular economy action plan. However, scepticism among designers, contractors and road agencies remains a bottleneck. This integrated structural-environmental study demonstrates the advantages of using recycled construction and demolition waste aggregate (CDW-RA) in substitution of primary natural aggregate (NA) for the formation of subbase layers in both flexible and semi-rigid road pavements. The structural responses of different pavements with a 0.30 m subbase layer made up of four materials, i.e., two unbound and two cement-stabilized obtained including NA and CDW-RA, were compared. The environmental-related impacts were also assessed by means of a life cycle assessment (LCA).

Laboratory tests and structural design led to pavement structures with the same thickness for the upper hot-mix asphalt layers, i.e., 0.26 and 0.28 m for the two unbound and the two cement-stabilized subbase materials respectively. The pavement with unbound CDW-RA subbase showed the best LCA outcomes because of the more favourable environmental performance of CDW-RA compared to NA. Although the stabilization of NA and CDW-RA reduces the thickness of the top hot-mix asphalt layers by 0.02 m, the environmental benefits are outweighed by the impact associated with the usage of cement. This study encourages the use of CDW-RA in road subbase layers with similar characteristics to those investigated here. The LCA results also support the use of alternative and more environmentally friendly binders that can enhance the environmental sustainability of stabilized materials in road construction.

36 **KEYWORDS:** Construction and demolition waste, pavement structural design, life cycle
37 assessment, road subbase construction, recycled aggregates

38
39 **HIGHLIGHTS**

- 40 • An integrated and comparative structural-LCA analysis of flexible and semi-rigid road pavements
- 41 • Construction and demolition waste aggregate (CDW-RA) in lieu of natural aggregate (NA) for
42 subbase layer formation
- 43 • Unbound CDW-RA shows the most favourable LCA outcomes for the same pavement service life
- 44 • The thickness reduction in cement-stabilized materials offset by the negative environmental
45 impact of the use of cement
- 46 • Subbase with CDW-RA used in substitution of NA results in a reduction of 9% in pavement costs

47
48 **Submitted to *Journal of Cleaner Production* (Elsevier)**

49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

49 **1. INTRODUCTION**

50 The use of recycled aggregate is strategic for the sustainability of the construction sector and the
51 preservation of natural resources (Peng et al., 1997; Ghisellini et al., 2018). The recycling of
52 construction and demolition waste (CDW) is among the priorities of the European Circular Economy
53 Action Plan (European Commission, 2020). At present, the production of secondary aggregate from
54 CDW is increasing and, together with primary aggregates from quarrying activities, it is able to meet
55 the needs of the construction industry. In 2018, around 80% of the 850 million tons of CDW
56 generated in EU-28 was sent for recovery and recycling (Villoria Sáez and Osmani, 2019), while
57 2.45 billion tons of primary aggregates coming from quarries and gravel pits were produced
58 (European Aggregates Association, 2020).

59 CDW contains solid particles of concrete, asphalt, ceramics, and soils, all of which can be reused
60 as road construction materials. CDW is transformed into recycled aggregate (RA) through cleaning,
61 crushing and sieving operations (Kourmpanis et al., 2008; Marzouk and Azab, 2014; Zhao et al.,
62 2010). Due to the large volume involved, the greatest amount of CDW-RA is currently employed as
63 a filling material in earthworks (Arulrajah et al., 2013; Cardoso et al., 2016), and occasionally in
64 unbound and stabilized layers of road pavements (Ossa et al., 2016; Tefa et al., 2021). In these
65 applications, CDW-RA performs satisfactorily (Bassani and Tefa, 2018; Bennert et al., 2000; Leite
66 et al., 2011; Tavira et al., 2018) and is also appreciated because it is cheaper than natural aggregates
67 (Zhao et al., 2021).

68 Despite this evidence, there is significant scepticism among engineers and contractors regarding
69 the use of CDW-RA due to the low quality of some recycled products and the conservative approach
70 among users (Silva et al., 2019). Furthermore, several contractual clauses still require the exclusive
71 use of materials of natural origin, hence ruling out the use of CDW-RA (Park and Tucker, 2017;
72 Huang et al., 2018). In the current scenario, the economic benefits of a widespread use of CDW-RA
73 in roadworks must be established beyond doubt, while also considering the significant
74 environmental, sustainability-related issues.

75
76 **1.1 Problem statement**

77 Flexible and semi-rigid road pavements are layered systems. Hot mix asphalt (HMA) top layers
78 require high quality aggregates but limited quantities of recycled materials. Conversely, the subbase
79 and the subgrade can be made up with a predominant amount of RA as they are subjected to lower
80 stress levels from vehicular traffic (Behiry, 2013). The mechanical properties of the subbase affect
81 the structural response of the upper HMA layers in terms of design life and thickness (Christopher
82 et al., 2006). Thicker HMA layers are necessary to compensate for a weaker subbase layer.
83 Therefore, the environmental balance of the entire pavement structure may be compromised if the
84 subbase contains low-quality RA.

85 A number of Life Cycle Assessment (LCA) studies have demonstrated the environmental
86 benefits of converting CDW into RA rather than resorting to the use of primary aggregates (Di Maria
87 et al., 2018; Knoeri et al., 2013; Marzouk and Azab, 2014; Jain et al., 2020; Simion et al., 2013). For
88 instance, Ghanbari et al. (2018) compared the energy consumption and the level of CO₂ emissions
89 for natural aggregate (NA) and RA production, concluding that CDW-RA is the best solution with 60
90 and 72% of energy saving and CO₂ emissions respectively. Other studies have demonstrated the
91 environmental benefits of CDW recycling with respect to NA quarrying (Blengini and Garbarino,
92 2010; Blengini et al., 2012; Faleschini et al., 2016; Borghi et al., 2018). However, in these studies
93 the LCA was limited to the production stage boundaries, i.e., the cradle-to-gate approach, without
94 exploring the implications of using RA instead of NA in the construction and in the service life of a
95 road pavement.

1.2 Study objective

96
97 This study integrates structural and LCA analyses so as to compare the environmental impacts of
98 the use of NA and CDW-RA in the subbase layer of flexible and semi-rigid road pavements.
99 Therefore, unbound granular materials (NA and CDW-RA), and cement-stabilized mixtures with both
100 NA and CDW-RA were included in the comparative analysis. This study extends the “cradle-to-gate”
101 approach, which typically characterizes LCA studies, to the specific application in which this
102 secondary resource is employed. To meet this objective, the structural response of the entire
103 pavement was assessed to determine the thickness of the upper HMA layers when different
104 materials were employed for the subbase layer.

105
106 This integrated structural-LCA approach was supported by a laboratory investigation aimed
107 at including the mechanical properties of the four subbase materials (i.e., unbound NA,
108 cement-stabilized NA, unbound CDW-RA, and cement-stabilized CDW-RA) in the analysis. Four
109 different pavement structures were considered while assuming the thickness of the HMA top layers
110 to be dependent on the stiffness of the four subbase materials. Thus, the same subbase layer
111 thickness and loading conditions were assumed for a standard 20-year service life. The LCA was
112 set up by considering a functional unit of 1 m² of pavement including HMA layers, the subbase, and
113 the subgrade.

114
115 Six different LCA scenarios were modelled and compared: two scenarios with unbound NA
116 and CDW-RA, and four others with cement-stabilized materials with the two aggregate types (NA
117 and CDW-RA) both of which were produced either in-plant or on-site before being laid on-site. The
118 LCA included all the relevant operations required to build the road pavement: (i) the production and
119 transport of raw and composite materials, (ii) the mixing in-plant or at the construction site of
120 cement-stabilized materials, (iii) the construction of pavement layers with laying and compaction
121 operations. Maintenance cycles and end-of-life scenarios were not included.

122 **2. METHODS**

123 **2.1 Structural design and analysis**

124 Table 1 lists the assumptions for (i) the structural behaviour of materials, (ii) the layer characteristics,
125 and (iii) the pavement composition. The stress-strain response of each pavement structure was
126 evaluated using KENPAVE pavement analysis software from Huang (2003). Three reference
127 seasonal periods (Winter, Summer, and Spring/Autumn) were considered to account for the thermo-
128 dependant behaviour of HMA layers. For each of these periods, the average temperature inside the
129 pavement was estimated from the mean air temperature in the Turin area (North-West of Italy)
130 according to the Witczak model (Witczak, 1972).

131 The HMA was considered a linear elastic isotropic material with a constant Poisson ratio of 0.35.
132 The elastic modulus (E_{HMA}) was assumed equal to the norm of the complex modulus ($|E^*_{HMA}|$) and
133 predicted according to the Hirsh model (Christensen Jr et al., 2003), which considers the shear
134 complex modulus of the bitumen (G^*) and the volumetric properties of the mixture (Table 2). G^* at
135 the specific temperature (depending on the seasonal period) and frequency (10 Hz) was retrieved
136 from the master curve and the corresponding model parameters of a 50/70 pen grade virgin bitumen
137 provided by Mazzoni et al. (2018). Base, binder, and wearing HMA layers were considered by
138 bonding them together with a tack coat of bitumen emulsion, thus a full adhesion was assumed in
139 the structural model. Similarly, the interface between the HMA base layer and stabilized subbase
140 was deemed to be fully bonded in the analysis due to the presence of a prime coat.

141 Each subbase material was modelled as non-linear elastic isotropic. Unbound and cement-
142 stabilized granular materials exhibit a stiffness that depends on the stress state (Lekarp et al., 2000).
143 As a result, in the structural analysis the 0.30 m subbase layer was split into six 0.05 m sublayers,
144 and the resilient modulus of each sublayer was iteratively calculated (Huang, 2003). The resilient
145 response of the subbase layer was determined according to the k - θ model (Hicks and Monismith,
146 1971) using the regression coefficients k_1 and k_2 , garnered from the laboratory tests performed on
147 subbase materials (see Section 3). A Poisson ratio of 0.40 and 0.25 was assumed for unbound and
148 cement-stabilized materials respectively. Details about the stress-strain response of the four
149 investigated subbase materials listed in Table 1 are in Section 3. Finally, the subgrade was modelled
150 as a semi-infinite elastic isotropic layer with a constant modulus of 50 MPa and a Poisson ratio of
151 0.45.

152 The pavement structure was designed to support $3 \cdot 10^6$ load applications of 80-kN equivalent
153 single axle load (Huang, 2003), which can be regarded as a medium loading condition for a two-lane
154 rural highway in Italy. The number of allowable load repetitions was estimated with the Asphalt
155 Institute criteria for (i) fatigue cracking due to repeated horizontal tensile strain at the bottom of the
156 HMA layers, and (ii) permanent deformation failure due to excessive repeated compressive vertical
157 strain at the top of the subgrade (Asphalt Institute, 1982). The Miner's law was used for the

158 cumulative damage computation for failures caused by fatigue and permanent deformations in the
 159 HMA layers and on top of the subgrade layer respectively (Huang, 2003).

160
 161

Table 1 – Hypotheses for the structural analysis of pavements

Layer	Thickness	Materials	Structural behaviour
HMA layers	variable	HMA	elastic, isotropic
Subbase	0.30 m	U-NA, U-CDW-RA, CS-NA, CS-CDW-RA	non-linear elastic, isotropic
Subgrade	semi-infinite	Soil	elastic, isotropic

9 Notes: HMA = hot mix asphalt, U-NA = unbound natural aggregates, U-CDW-RA = unbound construction and
 10 demolition waste recycled aggregate, CS-NA = cement-stabilized natural aggregate, CS-CDW-RA = cement stabilized
 11 construction and demolition waste recycled

162
 163

Table 2 – Assumptions on volumetric properties of HMA layers

Layer	Volume in the asphalt mixture (%)		
	Bitumen	Aggregate	Void content
Base	10.5	83.4	6.1
Binder	11.7	83.0	5.3
Wearing	12.9	82.7	4.1

164

165

2.2 Life Cycle Assessment

166

167

168

169

170

171

172

173

174

175

176

177

178

179

180

181

182

183

184

185

186

187

188

189

190

191

192

193

194

195

196

197

198

199

200

201

202

203

204

The LCA was developed according to (i) ISO 14040 (International Organization for Standardization, 2006a), (ii) ISO 14044 (International Organization for Standardization, 2006b), and (iii) International Reference Life Cycle Data System (ILCD) Handbook (European Commission - Joint Research Centre - Institute for Environment and Sustainability, 2010). The life cycle impact assessment (LCIA) was evaluated as per the ILCD Midpoint+ (version 1.0.9) and the Cumulative Energy Demand (CED) methods, as recommended by the European Commission, with attention paid to the indicators of (i) acidification, (ii) climate change, (iii) photochemical ozone formation, (iv) total human toxicity, (v) total consumption of non-renewable resources, and (vi) total consumption of renewable resources. The choice was based on the relevance of these impact categories to the construction sector and/or on the higher level of readiness of the calculation method (European Commission - Joint Research Centre - Institute for Environment and Sustainability, 2012). The analysis was supported by openLCA 1.10.3 software and Ecoinvent 3.1 database.

205

206

207

208

209

210

211

212

213

214

215

216

217

218

219

220

221

222

223

224

225

226

2.3 Functional unit and scenarios

Fig. 1 shows the functional unit of 1 m² of pavement structure considered in the LCA. The pavement section includes the HMA layers divided between the surface layer (wearing and binder course), and the road base; the subbase layer is made up of unbound or cement-stabilized NA and CDW-RA and is laid over the subgrade.

Starting from the four pavement structures deriving from a combination of four different subbase materials (U-NA, U-CDW-RA, CS-NA, CS-CDW-RA), a total of six LCA scenarios were analysed by considering two common construction techniques for cement-stabilized subbase materials: (i) in-plant mixing with subsequent transport of the cement-stabilized material to the construction site, and (ii) on-site mixing and laying by means of a soil stabilizer machine.

189 The following codes were adopted to univocally identify the six structural and LCA scenarios: (i)
 190 **U-NA**, unbound NA; (ii) **CS-NA-p**, cement-stabilized NA mixed in-plant; (iii) **CS-NA-s**,
 191 cement-stabilized NA mixed on the construction site; (iv) **U-CDW-RA**, unbound CDW-RA; (v) **CS-**
 192 **CDW-RA-p**, cement-stabilized CDW-RA mixed in-plant; and (vi) **CS-CDW-RA-s**, cement-stabilized
 193 CDW-RA mixed on the construction site.

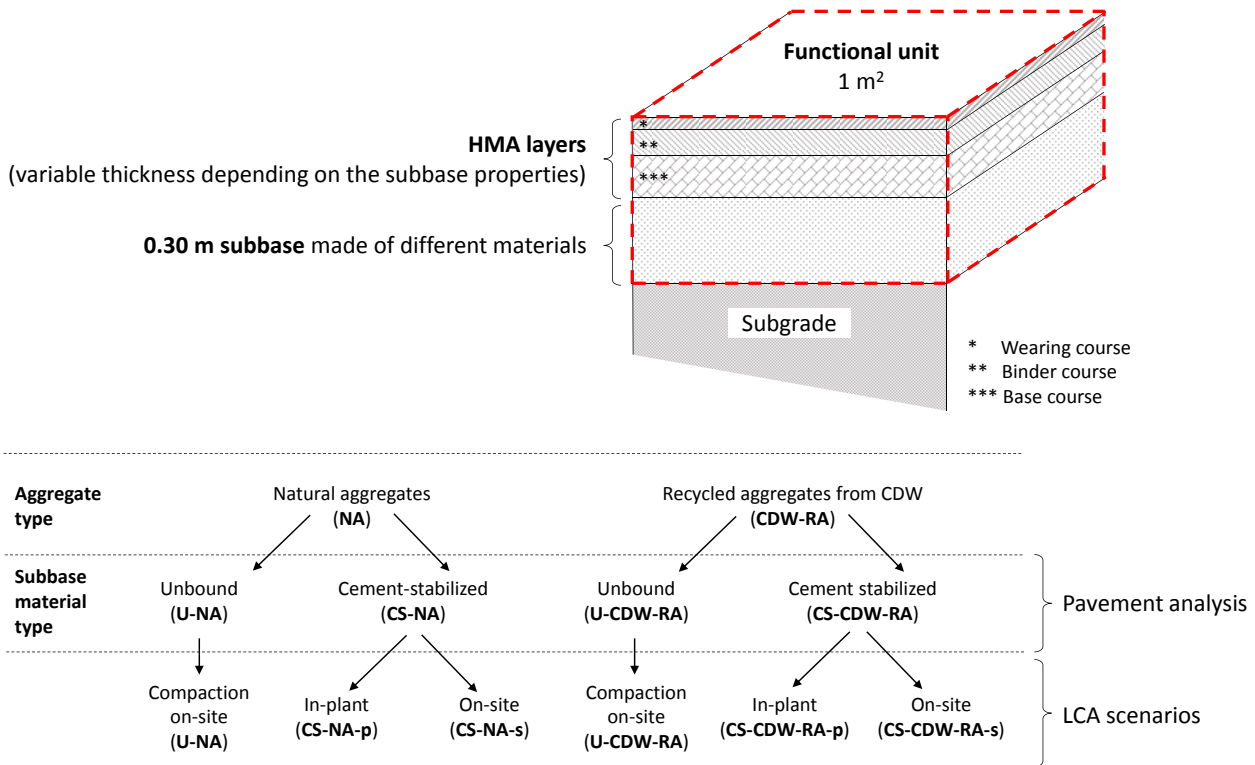


Fig. 1 – Section of the four functional units considered in the structural and LCA analyses of the six scenarios

2.4 System boundaries

The system boundaries included all relevant activities required for the six LCA scenarios, consistent with the adopted functional unit and considering the three sub-systems shown in Fig. 2. First, the production of primary (NA, cement, bitumen) or recycled (CDW-RA) materials was considered. Exploitation of non-renewable primary resources, quarrying operations with resource consumption, land use, emission levels, and the re-cultivation of the depleted quarry were included in the LCA model for the NA production (Blengini and Garbarino, 2010). In the case of CDW-RA, (i) the transport of waste from the construction/demolition site to the stationary recycling plant, (ii) treatment operations, and (iii) the avoidance of landfill operations for CDW were considered (Blengini and Garbarino, 2010). Moreover, a system expansion was introduced to consider the reduction in the production of primary steel due to the recovery of steel scraps in CDW (Borghi et al., 2018).

Primary/recycled materials were combined to evaluate the environmental impacts of the production of composite materials, i.e., cement-stabilized granular materials (CS-NA, CS-CDW-RA) and HMA, considering the levels of energy consumption for handling and mixing.

The construction of road pavement entailed: (i) transport, laying, humidification, and compaction of granular materials for the subbase formation, and (ii) paving and compaction for the HMA layer formation. Operations like cleaning, grubbing, and levelling of natural soil on which the embankment is built were not included in the system boundaries because they are identical in each scenario. Similarly, the preparation and the construction operations of the subgrade were not modelled in the LCA. Finally, maintenance and renovation phases were also excluded from the system boundaries.

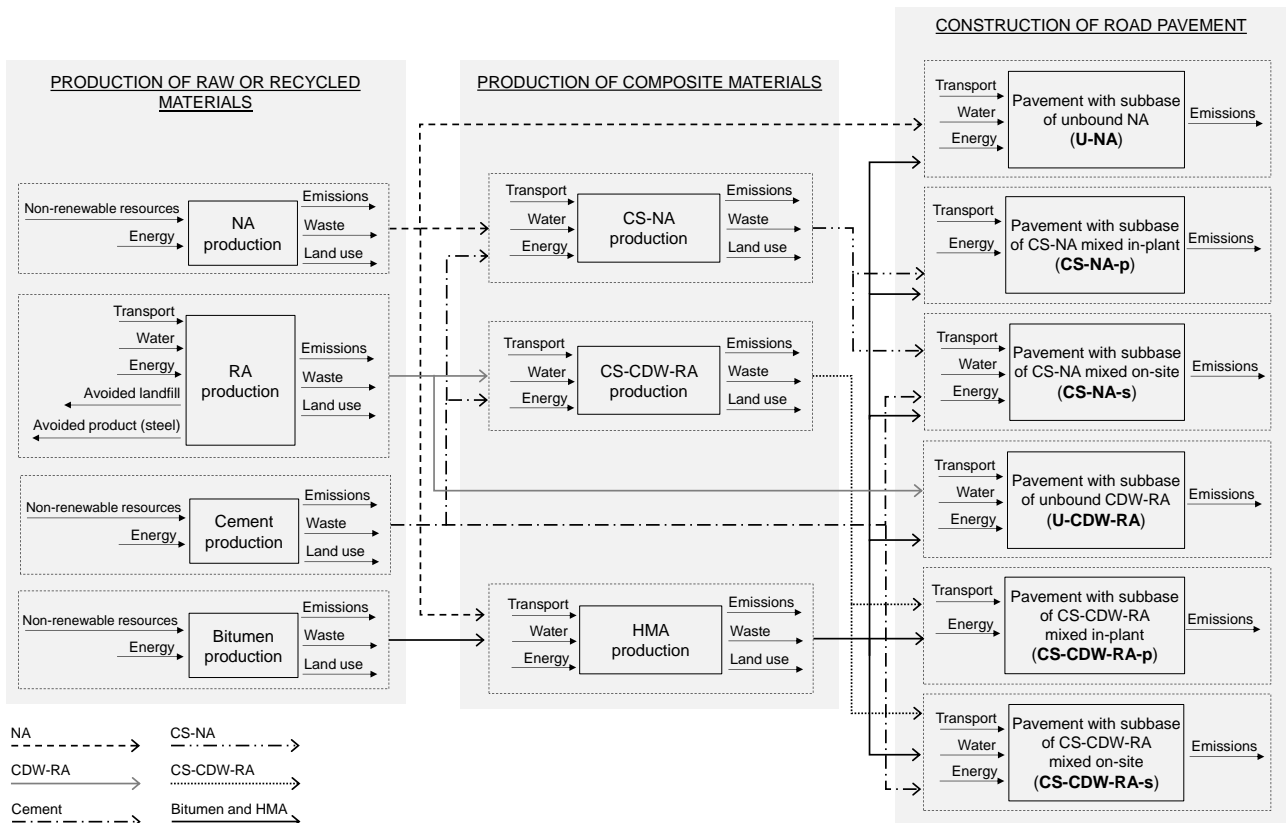


Fig. 2 – Schematic representation of system boundaries in the investigated LCA scenarios

3. LABORATORY TESTING OF THE STRUCTURAL PROPERTIES OF SUBBASE MATERIALS

A dedicated laboratory investigation aimed at characterizing the four unbound and stabilized materials was conducted. This stage was preparatory to obtaining the mechanical parameters of the subbase materials to be used as input data in the structural analysis.

Table 3 lists the mix-design proportions and the main properties of unbound (U-NA, U-CDW-RA) and cement-stabilized (CS-NA, CS-CDW-RA) subbase materials. To avoid any secondary effects on influencing factors, all materials had the same grading distribution in accordance with the Italian technical specifications (Ministero delle Infrastrutture e dei Trasporti, 2001). A Proctor study conforming to EN 13286-2 (European Committee for Standardization, 2010) was performed to estimate the optimum moisture content (w_{opt}). The two cement-stabilized materials included 3% in mass of a limestone Portland CEM-II/B-LL cement conforming to the EN 197-1 (European Committee for Standardization, 2011).

235

Table 3 – Composition and properties of granular materials employed in the construction of the subbase layer

Material	W _{opt} ⁽¹⁾ (%)	Stabilizer	%s ⁽²⁾	Curing (days)	Compacted dry density (kg/m ³)	k-θ model parameters and fitting evaluation			
						k ₁	k ₂	R ²	Se/Sy ⁽⁴⁾
U-NA	6.5	-	-	-	2168	698	0.69	0.99	0.094
CS-NA	6.5	CEM-II/B-LL ⁽³⁾	3.0	7	2172	3127	0.59	0.96	0.211
U-CDW-RA	8.5	-	-	-	1943	801	0.75	0.97	0.177
CS-CDW-RA	8.5	CEM-II/B-LL ⁽³⁾	3.0	7	2069	2771	0.60	0.90	0.322

Notes: ⁽¹⁾ optimal water content as mass percentage with respect to dry aggregates; ⁽²⁾ stabilizer content as mass percentage with respect to dry aggregates; ⁽³⁾ cement type II/B-LL according to EN 197 (European Committee for Standardization, 2011); ⁽⁴⁾ Se/Sy is the ratio between the standard error of estimate (Se) and the standard deviation (Sy) and expresses the goodness-of-fit as “excellent” for Se/Sy ≤ 0.35, “good” for 0.36 ≤ Se/Sy ≤ 0.55, “fair” for 0.56 ≤ Se/Sy ≤ 0.75, and “poor” for 0.76 ≤ Se/Sy ≤ 0.90 (Pellinen and Witczak, 2002).

Cylindrical specimens of 100 mm in diameter and 200 mm in height were compacted into four layers at the gyratory shear compactor (vertical pressure of 600 kPa, 100 gyrations for each of the four layers) and subjected to the repeated load triaxial tests for the resilient modulus (RM) measurement according to the AASHTO T-307 (American Association of State and Highway Transportation Officials, 2013). U-NA and U-CDW-RA specimens were tested immediately after compaction, while CS-NA and CS-CDW-RA specimens underwent mechanical tests after 7 days of curing at 90% of RH and at room temperature. All mixtures were replicated in three samples. Fig. 3 shows the average resilient modulus of the four subbase materials as a function of the first stress invariant (θ). RM test results were fitted according to the k-θ model (Hicks and Monismith, 1971) of eq. 1 for the estimation of regression coefficients k₁ and k₂ reported in Table 3.

$$RM = k_1 \cdot p_a \cdot \left(\frac{\theta}{p_a}\right)^{k_2} \quad (1)$$

(p_a is the reference atmospheric pressure).

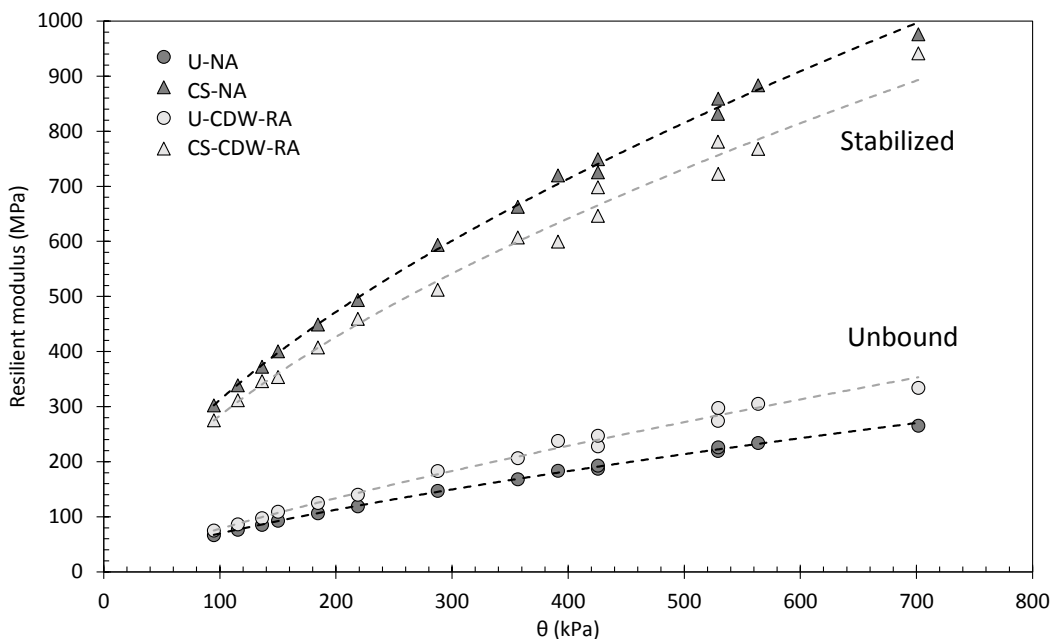


Fig. 3 – Resilient modulus as a function of θ for (a) NA and (b) CDW-RA in both unbound and cement-stabilized conditions

253 **4. LIFE CYCLE INVENTORY**

254 Life Cycle Inventory (LCI) data were collected from available literature specific to the Italian context.
 255 Interviews together with an analysis of energy consumption values were carried out to determine the
 256 LCI of the mixing plant to produce the cement-stabilized granular materials. The LCI data for the
 257 production of NA and CDW-RA were obtained from Blengini and Garbarino (2010). Eurobitume
 258 datasets of 2012 and 2020 (Eurobitume, 2012; Eurobitume, 2020) were used to model the production
 259 of bitumen emulsion and bitumen respectively. The LCA model of the pavement construction stage
 260 included the hourly production rates for roadwork machines and their respective fuel consumption
 261 rates (Celauro et al., 2017).

262 All materials were scheduled to be moved by road freight convoys from production facilities to
 263 mixing stations and/or the construction site. The travelled distances (Table 4) were selected based
 264 on the location of the aggregate quarrying/recycling plants and the binder (bitumen, bitumen
 265 emulsion, and cement) production plants in the North-West of Italy (Blengini and Garbarino, 2010).

267 **Table 4 – Assumptions on transport distances and truck type**

Material	Route	Truck	Travelled distance
CDW (waste)	Demolition site → CDW recycling plant	3.5-7.5 t (25% of mass) 7.5-16 t (25% of mass) 16-32 t (25% of mass) >32 t (25% of mass)	20 km
	Demolition site → Landfill	3.5-7.5 t (25% of mass) 7.5-16 t (25% of mass) 16-32 t (25% of mass) >32 t (25% of mass)	25 km
CDW steel scrap	CDW recycling plant → Steel production plant	>32 t	100 km
Cement	Production factory → Mixing plant for stabilized aggregates	16-32 t	50 km
	Production factory → Construction site	16-32 t	50 km
Bitumen	Production factory → Mixing plant for bituminous mixtures	16-32 t (50% of mass) >32 t (50% of mass)	100 km
U-NA	Quarrying plant → Mixing plant for bituminous mixtures	>32 t	30 km
	Quarrying plant → Construction site	>32 t	20 km
U-CDW-RA	Recycling plant → Construction site	>32 t	20 km
Water	Collecting plant → Construction site	16-32 t	10 km
CS-NA	Quarrying plant → Mixing plant	-	0 km ⁽¹⁾
	Mixing plant → Construction site	>32 t	20 km
CS-CDW-RA	Recycling plant → Mixing plant	-	0 km ⁽¹⁾
	Mixing plant → Construction site	>32 t	20 km
Bitumen emulsion	Production factory → Construction site	7.5-16 t	120 km
HMA	Mixing plant → Construction site	>32 t	25 km

268 Note: ⁽¹⁾ mixing plants were considered to be located inside the quarrying site (for NA) or the recycling station (for
 269 CDW-RA) thus no transportation of NA or CDW-RA was accounted for in the LCA of production of in-plant cement-
 270 stabilized materials.

271 **4.1 Production of raw materials**

272 **4.1.1 NA**

273 The LCA model of NA quarrying was based on data reported by Blengini and Garbarino (2010), and
 274 was in reference to the Piedmont region. A quantity of 0.12 kg of gasoline, 3.0 kWh of electricity, and
 275 0.06 kg of heavy fuel oil were the energy resources used to produce 1 ton of NA. The consumption

274 of 1.39 m³ of water, 0.044 kg of steel, 0.007 kg of rubber, and 0.002 kg of lubricating oil was included
275 in the model as well. According to Blengini and Garbarino (2010), inventory data for the quarrying of
276 NA also took into account factors relating to the quarrying plant construction and the recultivation of
277 the site.

278

279 4.1.2 CDW-RA

280 The CDW recycling process in stationary plants includes the transportation of waste from
281 demolition/construction sites to the plant, and the operations to produce recycled aggregates
282 (Blengini and Garbarino, 2010). The latter stage involves (i) cleaning operations of light materials
283 (i.e., plastic, wood, and paper) and separation of steel residues, (ii) crushing and (iii) sieving (Coelho
284 and Brito, 2013; Kourmpanis et al., 2008; Borghi et al., 2018).

285 The average distance from the demolition/construction site to the recycling plant was set equal
286 to 20 km according to De Melo et al. (2011) and Rodríguez et al. (2015). A data inventory for the
287 production of 1 ton of CDW-RA was taken from Blengini and Garbarino (2010), which assumed a
288 consumption of 3.6 kWh of electricity, 0.56 kg of gasoline, 0.007 m³ of water, 0.043 kg of steel,
289 0.019 kg of rubber, and 0.001 kg of lubricating oil. The LCI for RA production included flows and
290 processes due to the installation of the stationary recycling plant. For the purposes of the analyses,
291 an area of land extending to 25,000 m² was deemed to be occupied and transformed in use for 50
292 years and an annual production of 250,000 tons was considered for the recycling plant.

293 When CDW is recycled into RA, it is not disposed of into a landfill site, thus the avoidance of
294 CDW landfill was included in the LCA according to Blengini and Garbarino (2010). Meanwhile, the
295 reduction in the level of steel production needed due to the recovery of 0.13% in mass (Borghi et al.,
296 2018) of steel scraps contained in CDW-RA was also introduced into the LCA analysis.

297

298 4.1.3 Binders

299 The cement production was modelled using the Ecoinvent 3.1 database (Wernet et al., 2016), while
300 the Eurobitume LCI was adopted for modelling the impacts due to the production of the bitumen
301 (Eurobitume, 2020) and the bitumen emulsion (Eurobitume, 2012).

302

303 4.2 Production of composite materials

304 4.2.1 Cement-stabilized NA and RA (in-plant)

305 Data for the in-plant production of cement-stabilized material were gathered from different sources.
306 Average electricity consumption values for the mixing plant were calculated from technical
307 datasheets available in the Italian market. The consumption of lubricating oil and steel and energy
308 required for mixing aggregates and cement in a stationary plant were derived from Gschösser et al.
309 (2012) and adjusted for the investigated materials (Table 5).

310

311

312

313

314

315

316

312
1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

Table 5 – Energy and material resources required for producing 1 ton of cement-stabilized material

		CS-NA	CS-CDW-RA
Electricity	(kW)	0.41	0.46
Gasoline (1)	(MJ)	13.8	15.2
Lubricating oil	(kg)	0.007	0.008
Steel	(kg)	0.014	0.015
Mixing plant	(item)	$2.77 \cdot 10^{-7}$	$3.07 \cdot 10^{-7}$
NA	(kg)	1505	-
CDW-RA	(kg)	-	1337
Cement	(kg)	45	40
Water	(m ³)	0.10	0.11

Note: (1) Gasoline burned in wheel loader.

The mixing plants were considered to be located inside the quarrying site for NA, and at the recycling station for CDW-RA, thus no occupation and transformation in land use was included in the inventory analysis of the infrastructure. The production of cement-stabilized materials also included the consumption of NA or CDW-RA, water, and cement. No transportation of aggregates was added, while the transport distance of cement from the production factory was set equal to 50 km (Table 4).

4.2.2 Hot mix asphalt (HMA)

A data inventory for the production of 1 ton of HMA was derived from Gschösser et al. (2012) and included 11.1 MJ of gasoline burned by wheel loaders, 8.6 kWh of medium voltage electricity, 175.8 MJ of heat produced by natural gas and light fuel oil, 0.003 kg of lubricating oil and 0.009 m³ of water. The impact due to the construction of a HMA plant was included in the inventory and quantified as $2.51 \cdot 10^{-7}$. The production of HMA also requires NA (Section 4.1.1) and bitumen in different proportions depending on the bitumen-bounded layer, i.e., the base, binder, and wearing courses.

4.3 LCA modelling of the six scenarios for road construction

The LCA model for the six scenarios relating to the functional unit included some common activities. Primary/recycled materials and composite mixtures were to be transported from the plant to the construction site in dump trucks for the distances reported in Table 4. The construction of HMA layers was modelled according to the LCI of values for the productivity and fuel consumption of equipment documented in Celauro et al. (2017). The impact of (i) the dump trucks for the transportation of HMA mixtures, (ii) the road pavers for laying the material, and (iii) the tandem vibratory rollers for compaction were accounted for in the LCA inventory of HMA layer formation. Each HMA layer (road base, binder and wearing courses) was modelled so as to include the impacts and the consumption rates of bituminous emulsion used to form tack and prime coats. The thickness of the HMA layers varied depending on the scenario, thus different quantities of HMA were included in the input data.

The subbase construction was split into two sublayers of 0.15 m height each. Fig. 4 illustrates all the activities and equipment considered in the LCA model for the subbase formation. The layers made from unbound granular materials (U-NA, U-CDW-RA) were laid, levelled, water corrected, and

344 compacted. Cement-stabilized materials produced in plant (CS-NA-p, CS-CDW-RA-p) were
 345 considered simply laid and compacted on-site. For CS-NA-s and CS-CDW-RA-s scenarios (on-site
 346 mixing), (i) laying, (ii) spreading of cement, (iii) moistening and mixing through soil stabilizer
 347 machines (e.g., Pulvimixer), and (iv) compaction operations were all taken into account.

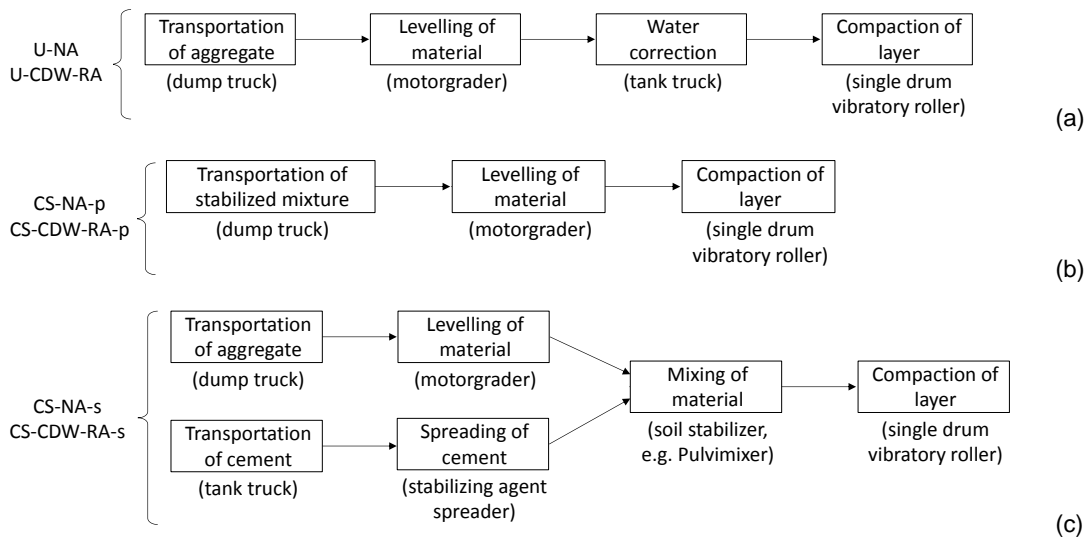


Fig. 4 – Operations included in the LCA model for the construction of subbase layer depending on the scenario: (a) U-NA, U-CDW-RA, (b) CS-NA-p, CS-CDW-RA-p, and (c) CS-NA-s, CS-CDW-RA-s

5. RESULTS AND DISCUSSION

5.1 Pavement structural analysis

Table 6 shows the results of the structural design of the road pavements for the four materials included in the subbase layer. Pavement structures with unbound materials (U-NA and U-CDW-RA scenarios) required a HMA layer to have a thickness of 0.28 m (0.16 m of base, 0.08 m of binder, and 0.04 m of wearing course) independently of the aggregate used (NA or CDW-RA).

The stabilization of both NA and CDW-RA with 3% (in mass) of cement entails an improvement in their stress-strain properties with respect to the unbound materials (Table 3 and Fig. 3). The structural analysis revealed that a stiffer subbase was able to reduce the horizontal tensile strain at the bottom of the HMA base layer (423.6 and 371.5 $\mu\text{m}/\text{m}$ for the U-NA and CS-NA; 422.1 and 378.6 $\mu\text{m}/\text{m}$ for the U-CDW-RA and CS-CDW-RA respectively). The vertical strain at the top of the subgrade remains almost constant regardless of the subbase material treatment (117.6 and 123.3 $\mu\text{m}/\text{m}$ for the U-NA and CS-NA; 118.1 and 124.1 $\mu\text{m}/\text{m}$ for the U-CDW-RA and CS-CDW-RA respectively). Therefore, a stiffer subbase made up of stabilized aggregates ensures a longer pavement service life than a subbase made of unbound aggregates. According to the assumption made in this study (i.e., HMA layer thickness adjusted to achieve a 20-year service life under design traffic), a reduction of 0.02 m in the upper HMA layer thickness for cement-stabilized subbases was assumed (Section 2.1). Table 6 shows the thickness (input for the structural analysis) and the critical strains resulting from the six scenarios.

Therefore, the total thickness of the HMA layer (i.e., 0.14, 0.08, and 0.04 m of base, binder, and wearing course respectively) of pavements with cement-stabilized subbase was set equal to 0.26 m independently of the origin of the aggregate (CS-NA or CS-CDW-RA). The structural analysis indicates that the use of CDW-RA in place of NA does not require thicker HMA layers due to the similar mechanical properties shown by NA and CDW-RA in both their non-stabilized and stabilized forms, as evidenced in Fig. 3.

Table 6 also summarizes the total cost (per m²) for each scenario, derived from the unit cost of construction of each road layer as per the Regional Unit Cost list of the Piedmont Region, Italy (Regione Piemonte, 2021). The pavement structure with U-CDW-RA subbase has the lowest total construction costs (47.30 €/m²) due to the significantly lower unit cost of recycled aggregates with respect to NA. Comparing U-NA and U-CDW-RA pavement solutions, the latter results in a cost saving of 9.5%. Despite the stabilization with cement of both types of aggregates leading to a thinner HMA base, the high construction unit costs of cement-stabilized subbase increase the total costs of CS-NA and CS-CDW-RA scenarios by 4.6 and 5.1% in comparison to pavements with unbound subbase layers (U-NA and U-CDW-RA).

Table 6 – Thickness, structural response, and total costs (m²) of pavement layers for the six LCA scenarios.

LCA scenarios	U-NA	U-CDW-RA	CS-NA-p CS-NA-s	CS-CDW-RA-p CS-CDW-RA-s
Thickness (m)				
Subbase	0.30	0.30	0.30	0.30
HMA base	0.16	0.16	0.14	0.14
HMA binder	0.08	0.08	0.08	0.08
HMA wearing	0.04	0.04	0.04	0.04
Structural response in strain for 20-year design life (µm/m)				
Horizontal strain at the bottom of HMA base	423.6	422.1	416.9	425.6
Vertical strain on top of the subgrade layer	117.6	118.1	137.8	138.8
Unit costs (€/m³) (*)				
Subbase	28.88	12.16	46.85	30.13
HMA base			144.02	
HMA binder			162.76	
HMA wearing			189.62	
Total costs (€/m²)	52.31	47.30	54.83	49.81

Notes: HMA = hot mix asphalt, (*) = Unit Costs list (Regione Piemonte, 2021).

5.2 LCIA of subbase materials production

Fig. 5 compares the main impacts arising from the production of 1 ton of different subbase materials albeit it only includes the LCA results to produce unbound (NA and CDW-RA) and cement-stabilized NA and CDW-RA materials mixed in-plant.

The LCA outcomes indicate that the production of CDW-RA has a lower environmental impact and resource consumption than the production of NA. All ILCD and CED indicators show negative values for the CDW-RA production, thus confirming the environmental benefits of this waste treatment. For instance, the acidification indicator (Fig. 5-a), which is mainly caused by air emissions of NH₃, NO₂, and SO_x (Joint Research Centre and Institute for Environment and Sustainability,

398 2012), is equal to 0.019 Mole H⁺ eq./ton for NA, while it results negative and equal
399 to -0.036 Mole H⁺ eq./ton in the case of CDW-RA. Analogously, when considering the consumption
400 of non-renewable resources (Fig. 5-e), its value is equal to 44.3 and -119.6 MJ/t for NA and CDW-RA
401 production respectively. The negative impact values for CDW-RA production are mainly ascribable
402 to the environmental benefits stemming from the avoided CDW landfill (Blengini and Garbarino,
403 2010). This aspect can be appreciated in the climate change contribution analysis of Fig. 6-b, which
404 expresses the percentage contributions of each factor to the overall climate change impact arising
405 from the production of 1 ton of CDW-RA. The avoidance of CDW landfilling accounts for an
406 environmental credit (i.e., a negative impact) of 229.4% when determining the impact of total climate
407 change, thus compensating for the impacts (positive) of the operations conducted to convert the
408 waste into a resource. In line with previous LCA studies on the management of CDW (Bovea and
409 Powell, 2016; Chowdhury et al., 2010; Hossain et al., 2016), the transport of waste from the
410 generation site to the recycling plant represents the greatest contribution (almost 79%) to the climate
411 change impact figure. A significant contribution to the same indicator is also caused by the
412 consumption of electricity and fossil fuels during the recycling operations. The beneficial impact due
413 to the recovery of steel is limited because of the small percentage of steel scraps in CDW set equal
414 to 0.13%.

415 As far as NA is concerned (Fig. 6-a), around two thirds of the climate change value
416 (2.93 kg CO₂ eq./ton) due to its production is caused by the electricity consumption needed to quarry
417 and treat the raw material.

418 The LCA results in Fig. 5 indicate that the addition of small quantities of cement to both NA and
419 CDW-RA significantly increases the impacts. The acidification indicator increases around 3.5 and 2
420 times when passing from NA and CDW-RA to CS-NA and CS-CDW-RA respectively. When cement
421 is added to stabilize the granular material, there is a marked increment in the climate change results,
422 as well as the consumption of non-renewable (Fig. 5-e) and renewable (Fig. 5-f) resources. When
423 considering the production of CS-CDW-RA, the addition of cement nullifies the environmental credits
424 gained from CDW-RA production. Fig. 7 shows that the presence of cement in stabilized materials
425 makes the greatest contribution to climate change (around 85.8% and 117.0% for CS-NA and CS-
426 CDW-RA respectively), while the impact figures due to the aggregate production and mixing
427 operations become relatively negligible.

428 Despite the use of limestone Portland cement significantly increasing all environmental
429 indicators, the production of CS-CDW-RA has a lower environmental impact and resource
430 consumption than the more common and traditional CS-NA because of the environmental credits
431 associated with CDW-RA production. From an LCA point of view, the outcomes of this level of
432 investigation strengthen the case for the use of CDW-RA in substitution of NA to produce cement-
433 stabilized material to be employed in the subbase layers of road pavements.



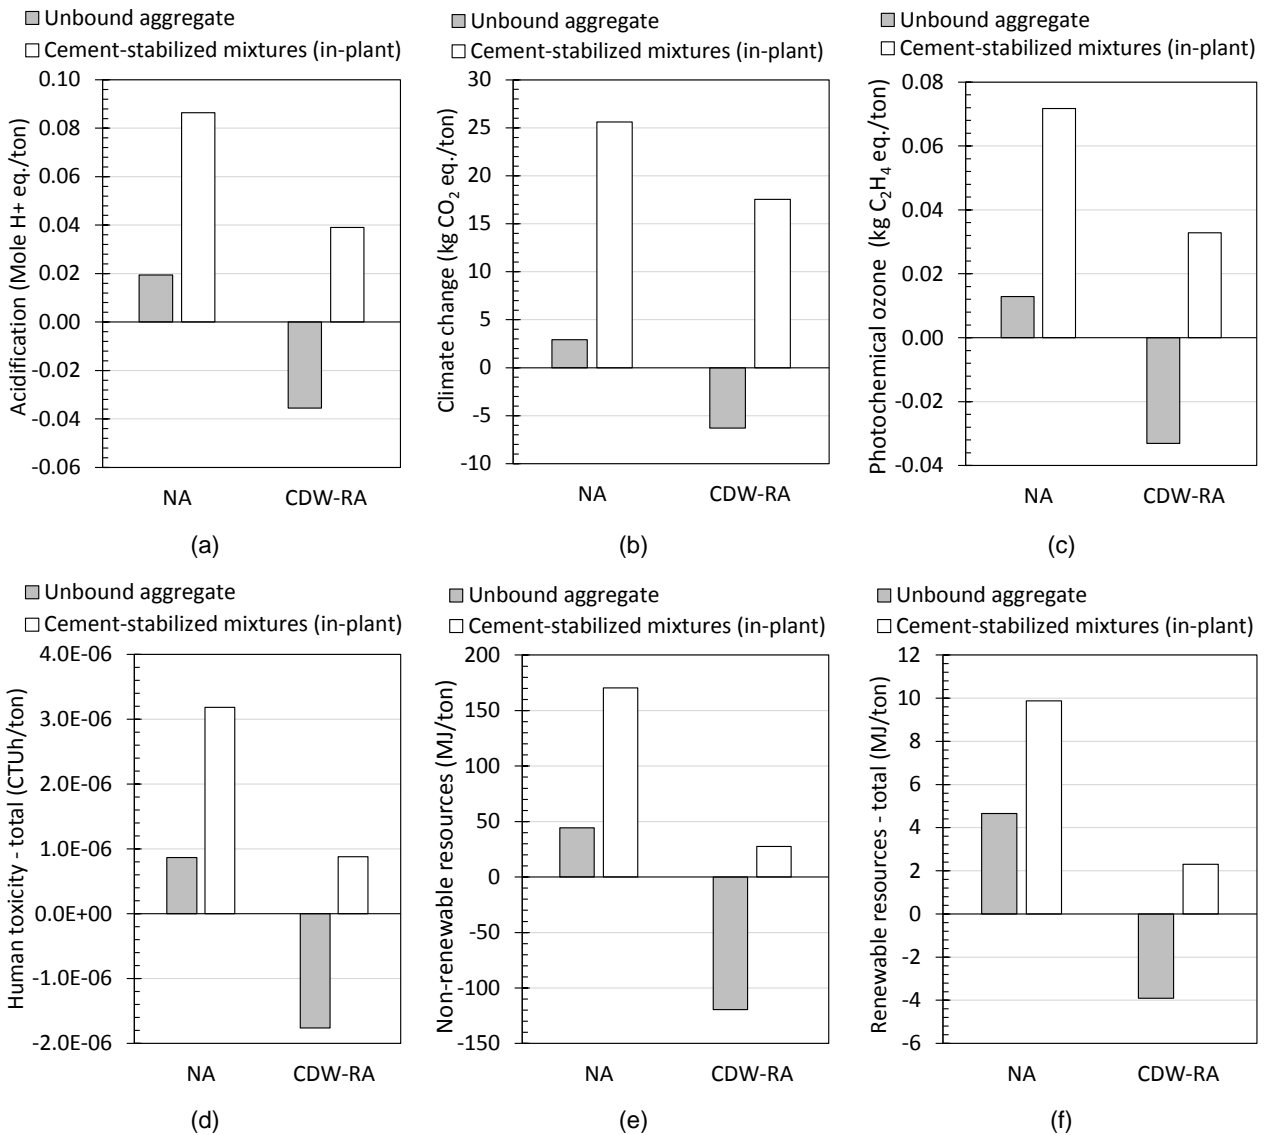


Fig. 5 – Impacts associated with the production of 1 ton of NA (unbound and cement-stabilized) and CDW-RA (unbound and cement-stabilized), for subbase layer formation: (a) acidification, (b) climate change, (c) photochemical ozone formation, (d) total human toxicity, (e) total consumption of non-renewable resources, (f) total consumption of renewable resources

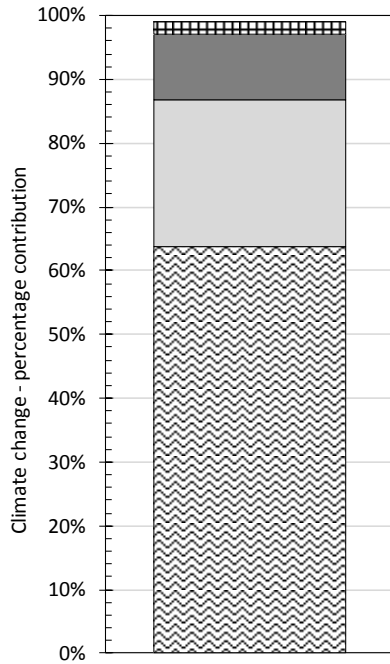

	Impact amount (kg CO ₂ eq.)	% value ⁽²⁾
Electricity	1.87	63.7%
Diesel and oil	0.68	23.2%
Infrastructure	0.30	10.1%
Steel	0.06	2.2%
Others ⁽¹⁾	0.02	0.8%
Total	2.93	100.0%


(a)

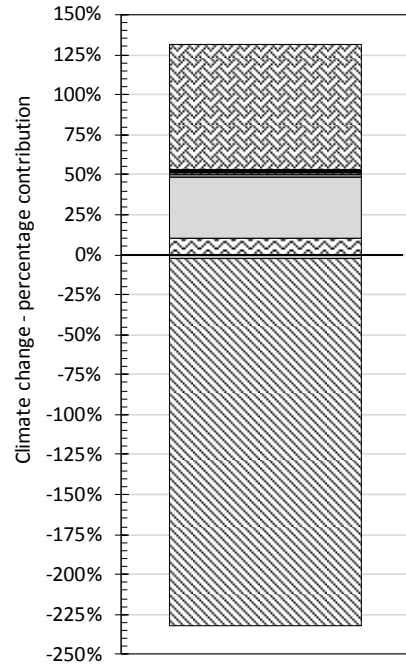

	Impact amount (kg CO ₂ eq.)	% value ⁽²⁾
Electricity	0.62	9.9%
Diesel and oil	2.42	38.3%
Infrastructure	0.14	2.2%
Steel	0.09	1.4%
Transport	4.98	78.9%
Rubber	0.08	1.2%
Steel recovery	-0.16	-2.5%
Landfill avoidance	-14.46	-229.4%
Others ⁽¹⁾	0.00	0.0%
Total	-6.31	-100.0%


(b)

Fig. 6 – Impact amounts and percentage contributions to climate change impact associated with the production of 1 ton of (a) U-NA and (b) U-CDW-RA. Notes: ⁽¹⁾ “Others” include all factors with a percentage contribution lower than 1.0%. ⁽²⁾ The “%value” is the ratio between the impact amount and the total. In the case of negative total impact (U-CDW-RA), the sum of %value is -100%. For instance, considering that the impact of electricity on the production of 1 ton of U-NA is +1.87 kg CO₂ eq., its percentage contribution (% value) to the total climate change of +2.93 kg CO₂ eq. is 63.7% [= 100 · 1.87 / |2.93|]. In the case of production of 1 ton of U-CDW-RA, the electricity consumption generates +0.62 kg CO₂ eq., which is 9.9% [= 100 · 0.62 / |-6.31|] of the total (-6.31 kg CO₂ eq.) impact. The negative total impact of U-CDW-RA is due to the steel recovery and landfilling avoidance. The latter two factors permit the saving of 0.16 and 14.46 kg CO₂ eq. respectively, thus contributing as negative percentages to the total impact: steel recovery: -2.5% [= 100 · (-0.16) / |-6.31|], landfill avoidance -229.4% [= 100 · (-14.46) / |-6.31|].

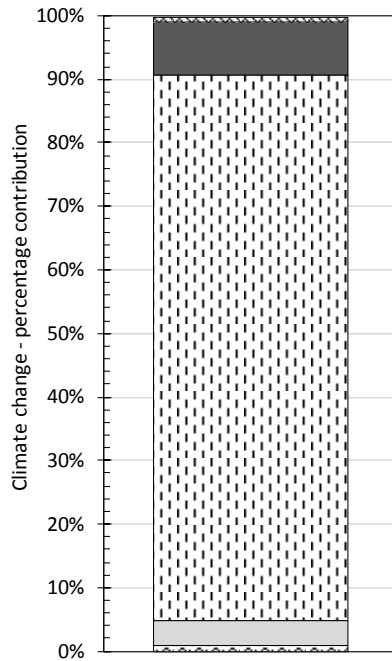

	Impact amount (kg CO ₂ eq.)	% value ⁽²⁾
Electricity	0.23	0.8%
Diesel and oil	1.17	4.0%
Transport	0.23	0.8%
NA	2.42	8.3%
Cement	24.90	85.8%
Others ⁽¹⁾	0.09	0.3%
Total	29.03	100.0%

(a)

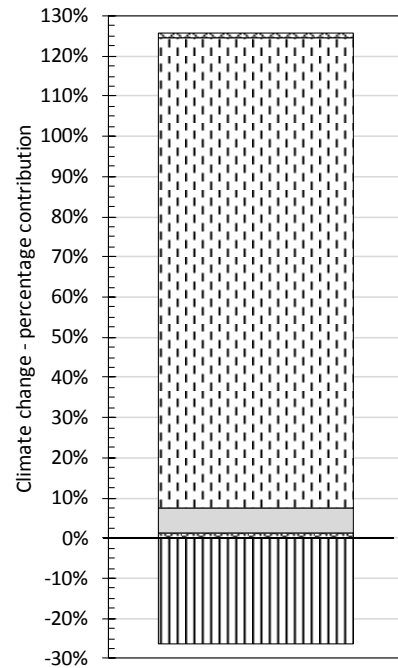

	Impact amount (kg CO ₂ eq.)	% value ⁽²⁾
Electricity	0.25	1.2%
Diesel and oil	1.27	6.2%
Transport	0.29	1.4%
CDW-RA	-5.45	-26.3%
Cement	24.22	117.0%
Others ⁽¹⁾	0.11	0.5%
Total	20.70	100.0%

(b)

Fig. 7 – Contributions to climate change impact associated with the production of 1 ton of (a) CS-NA and (b) CS-CDW-RA (in-plant). Notes: ⁽¹⁾ “Others” include all factors with a percentage contribution lower than 1.0%. ⁽²⁾ The “%value” is the ratio between the impact amount and the total.


5.3 LCIA for the road pavement construction

5.3.1 Road pavements with unbound subbase layers

Fig. 8 shows the LCIA results for the subbase layer containing U-NA and U-CDW-RA. For each impact category, the results are expressed as a percentage of the maximum value obtained in that category.

The indicators are always lower in the case of pavement structures with CDW-RA than they are with NA. The U-CDW-RA-C scenario leads to an average reduction of 20-25% in almost all indicators (acidification, climate change, freshwater ecotoxicity, freshwater eutrophication, total human toxicity, ionizing radiation, marine eutrophication, ozone depletion, particulate matter, photochemical ozone formation, mineral resources depletion, terrestrial eutrophication, and total renewable resources). Both the U-NA and U-CDW-RA pavement structures have the same thickness, thus the environmental advantages deriving from the production of CDW-RA (discussed in Section 5.2) are entirely reflected in the construction of the pavement. The two scenarios show large differences in terms of land use: while the production of NA radically transforms the territory due to quarrying

471 operations, the recycling of CDW and the storage of CDW-RA takes place in localized areas and
 472 large spaces of land are saved from being designated landfill sites for waste disposal.

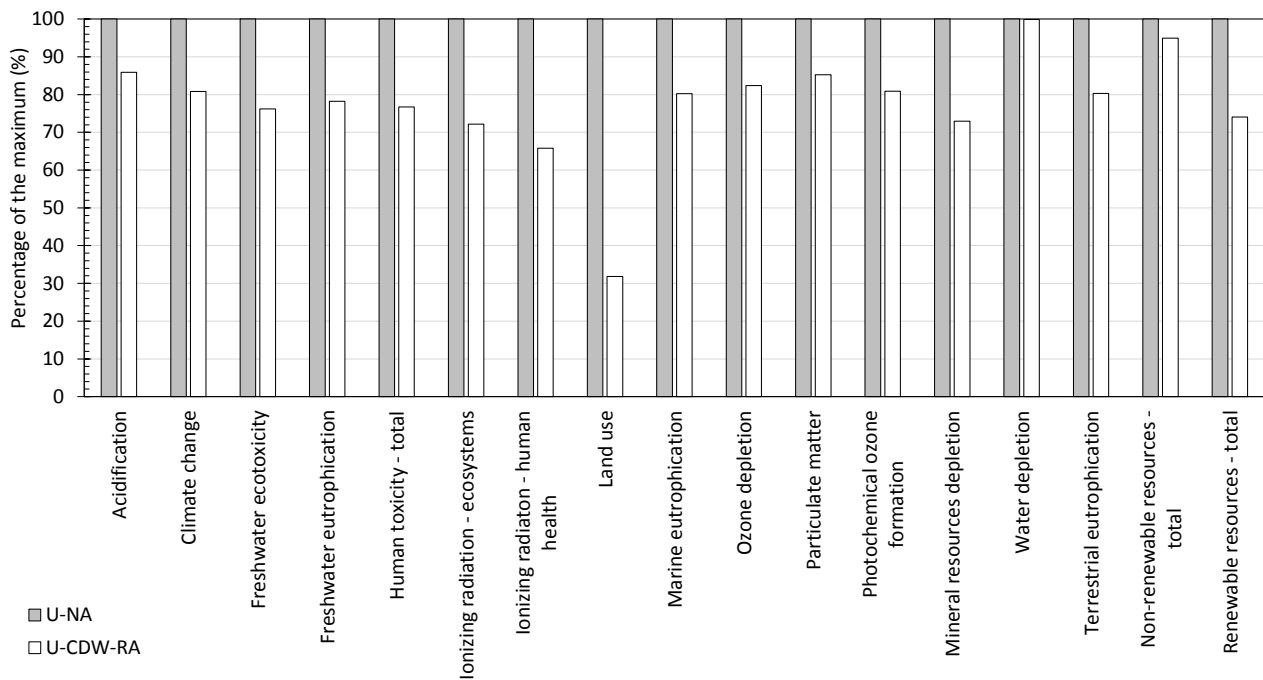


474 **Fig. 8 – Comparative ILCD 2011 (midpoint) and CED results for the construction of 1 m² of road pavement with**
 475 **subbase layer containing U-NA or U-CDW-RA.**

478 5.3.2 Road pavements with cement-stabilized subbase layers

479 Fig. 9 illustrates the LCA impacts depending on (i) the cement-stabilized materials employed in the
 480 subbase layer and (ii) the different construction techniques (in-plant production or on-site mixing).
 481 Once again, the results are shown as a percentage of the maximum value obtained in each impact
 482 category. The pavement structure with CS-NA in the subbase layer shows greater impacts than the
 483 one made from CS-CDW-RA. Both scenarios have HMA layers of equal thickness (see Section 5.1),
 484 therefore the environmental advantages of the CS-CDW-RA scenario derive entirely from the use of
 485 CDW-RA in lieu of NA. In line with pavement solutions with unbound subbases (U-NA and
 486 U-CDW-RA), the use of CDW-RA in cement-stabilized layers leads to an average reduction of 20-
 487 25% in all ILCD and CED impact indicators with respect to the CS-NA-p and CS-NA-s scenarios.

488 The stabilization technique (in-plant or on-site) has a marginal influence on the environmental
 489 impact calculation. When the material is mixed in a plant, the impact is slightly higher than when it is
 490 prepared on-site. The difference is attributable to the higher energy consumption (electricity and
 491 gasoline) of mixing plants. These LCA outcomes are valid under the hypothesis that cement-
 492 stabilized materials produced directly on-site have the same properties as those mixed in-plant.
 493 However, it is worth mentioning that a better control of mix proportion is usually obtained in-plant,
 494 where aggregates, stabilizing agent, and water are precisely dosed. The stabilization of materials

495 on-site by means of soil stabilizers is less precise and characterized by less accurate dosage of
 496 constituent materials.

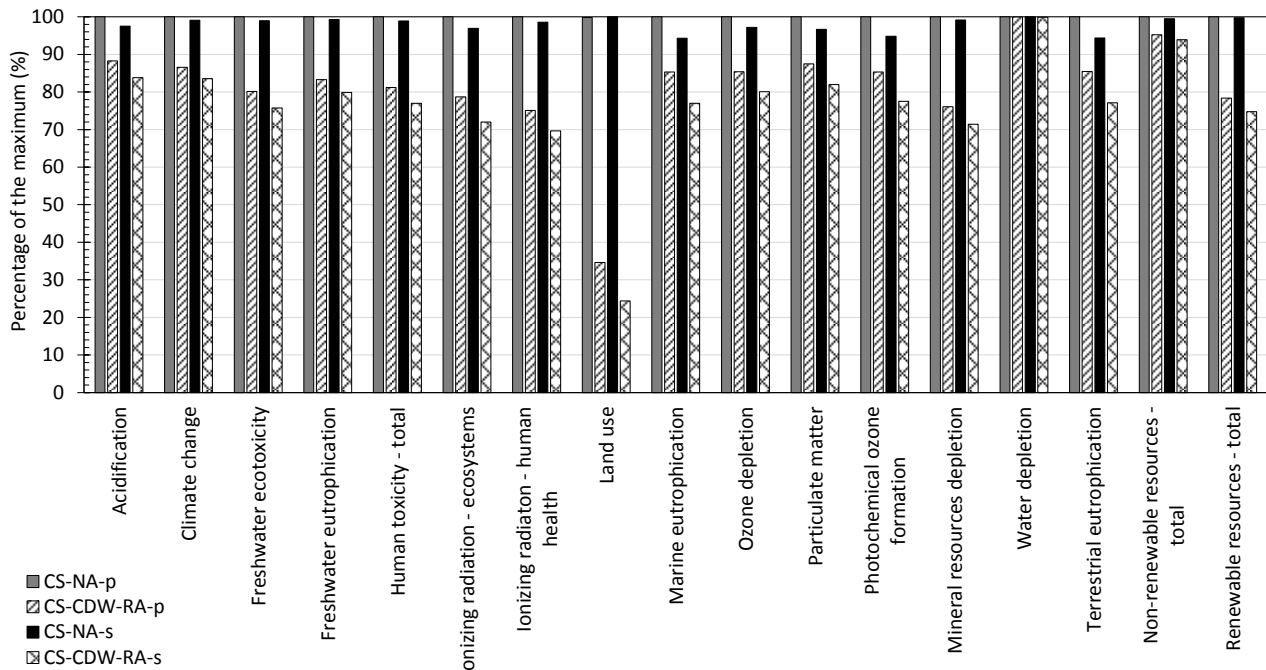

498 **Fig. 9 – Comparative ILCD 2011 (midpoint) and CED results for the construction of 1 m² of road pavement**
 499 **according to the different scenarios for cement-stabilized subbase materials.**

502 5.3.3 Comparison between scenarios

503 Fig. 10 shows the best scenario of the six considered. Apart from the consumption of non-renewable
 504 resources impact category (Fig. 10-e), the impacts of pavements including cement-stabilized
 505 subbase layers are greater than those containing unbound aggregates.

506 The CS-NA-p and CS-NA-s scenarios have a greater influence on the values of the impact
 507 indicators. In these cases, the benefits deriving from the reduction of 0.02 m in the HMA road base
 508 layer with respect to the U-NA scenario do not offset the negative environmental impacts deriving
 509 from the use of cement. The same consideration holds when CS-CDW-RA-p and CS-CDW-RA-s
 510 scenarios are compared to the U-CDW-RA one. The benefits of a 0.02-m thinner HMA base layer
 511 do not compensate for the impact of cementitious products in the subbase layer. Conversely, despite
 512 U-CDW-RA implying a thicker HMA base layer, this scenario is the least impactful among those
 513 analysed here due to the significant advantages deriving from the production of CDW-RA without
 514 the use of cement.

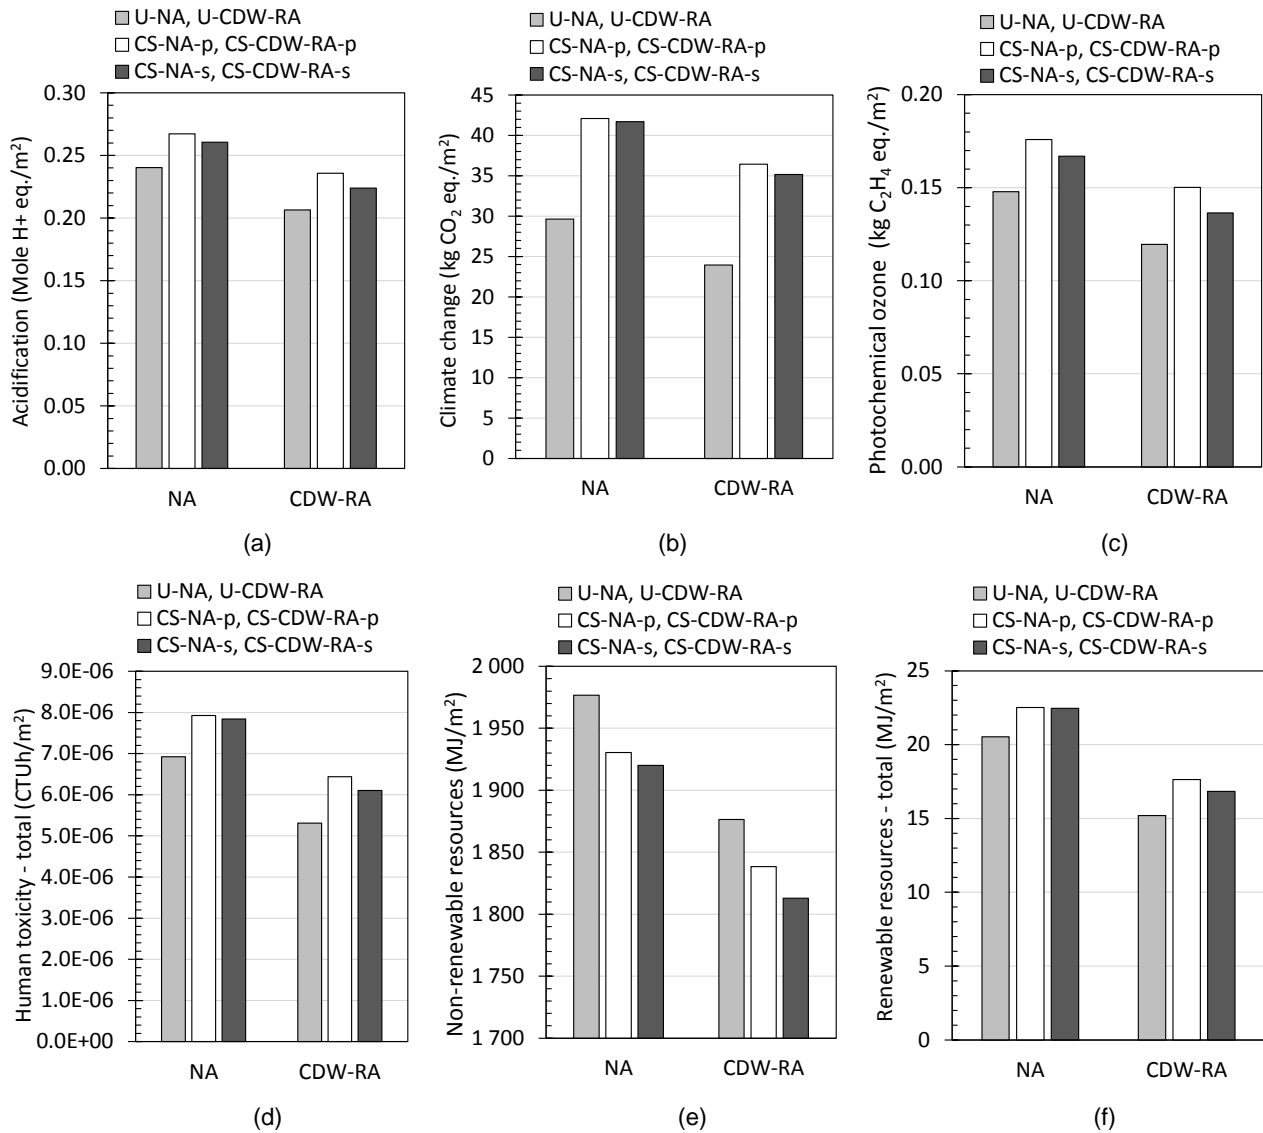


Fig. 10 – Impacts associated with the construction of 1 m² of pavement with unbound and CS materials in the subbase (U-NA, U-CDW-RA, CS-NA and CS-CDW-RA) and different construction techniques (mixing in-plant or on-site for cement-stabilized mixtures): (a) acidification, (b) climate change, (c) photochemical ozone formation, (d) total human toxicity, (e) total consumption of non-renewable resources, (f) total consumption of renewable resources.

A comparison between the CS-CDW-RA-p and CS-CDW-RA-s scenarios and that of the U-NA-C is of interest. Acidification (Fig. 10-a), photochemical ozone formation (Fig. 10-c), total human toxicity (Fig. 10-d), and renewable resource consumption (Fig. 10-f) indicators suggest that road pavements with cement-stabilized CDW-RA subbase layers have a more favourable LCA than the reference U-NA scenario. These outcomes reveal that, for some impact indicators, the use of CS-CDW-RA in place of simply compacted NA leads to some environmental benefits due to the small but significant decrease in the thickness of the HMA road base. These advantages would be even more relevant if more sustainable stabilizing agents could guarantee a similar or even better structural behaviour. Alternative stabilizers to limestone Portland cement (e.g., more sustainable blended cements, supplementary cementitious products, alkali-activated binders, etc.) could improve the LCA results associated with the climate change indicator. In fact, the high environmental impact of the cement

535 industry (Worrell et al., 2001; Schneider et al., 2011) results in significant increases in the emissions
536 of equivalent CO₂ in scenarios with cement-stabilized subbases (Fig. 10-b). Fig. 11 emphasizes the
537 contribution of each pavement layer to the climate change indicator. For U-NA and U-CDW-RA
538 scenarios, the subbase layer accounts for around 10% of the climate change for the total pavement
539 construction. For the sake of clarity, the contribution analysis of the U-CDW-RA scenario breaks
540 through the value of 100% to compensate for the negative contribution of the subbase layer. As
541 previously mentioned, the construction of the U-RA-CDW subbase garners environmental credits in
542 terms of LCA thanks to its avoidance of CDW recycling. Despite the addition of very small quantities
543 of cement, when the subbase layer is built with cement-stabilized NA (CS-NA-S-p and CS-NA-S-s
544 scenarios) its contribution to climate change increases to 40% of the entire pavement construction.
545 In the case of cement-stabilized RA, the contribution is lower (around 30%) since the 10%
546 contribution from the avoided impact of CDW-RA production is included in the LCA balance as a
547 credit.

548 The contribution analysis in Fig. 12 explains the results of Fig. 10-e related to the consumption
549 of non-renewable resources. The high values relating to the construction of HMA layers are
550 ascribable to the higher levels of energy consumed in the production processes of bitumen and HMA
551 (Androjić and Alduk, 2016). According to this impact indicator, the subbase layer has a marginal
552 contribution, from -2.7 to 6.7%, to the functional unit, while the major contribution, always greater
553 than 93%, is due to the HMA layers formation. For this reason, 0.02 m more of HMA in the U-NA
554 and U-CDW-RA scenarios leads to 2.4% and 2.1% of non-renewable resource consumption in
555 comparison with CS-NA-p and CS-CDW-RA-p scenarios respectively. Vice versa, scenarios with
556 thinner HMA layers (i.e., those with a cement-stabilized subbase layer), consume fewer
557 non-renewable resources, notwithstanding the use of cement.

558
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
61
62
63
64
65

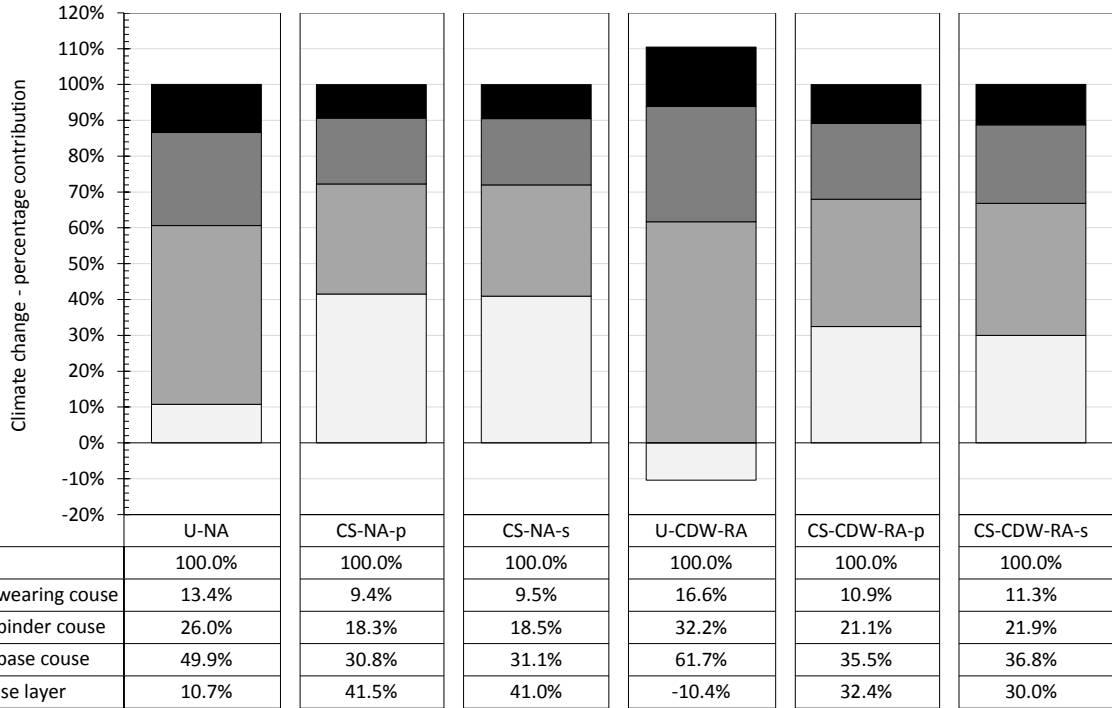


Fig. 11 – Contributions to climate change impact associated with the construction of 1 m² of road pavement according to different scenarios

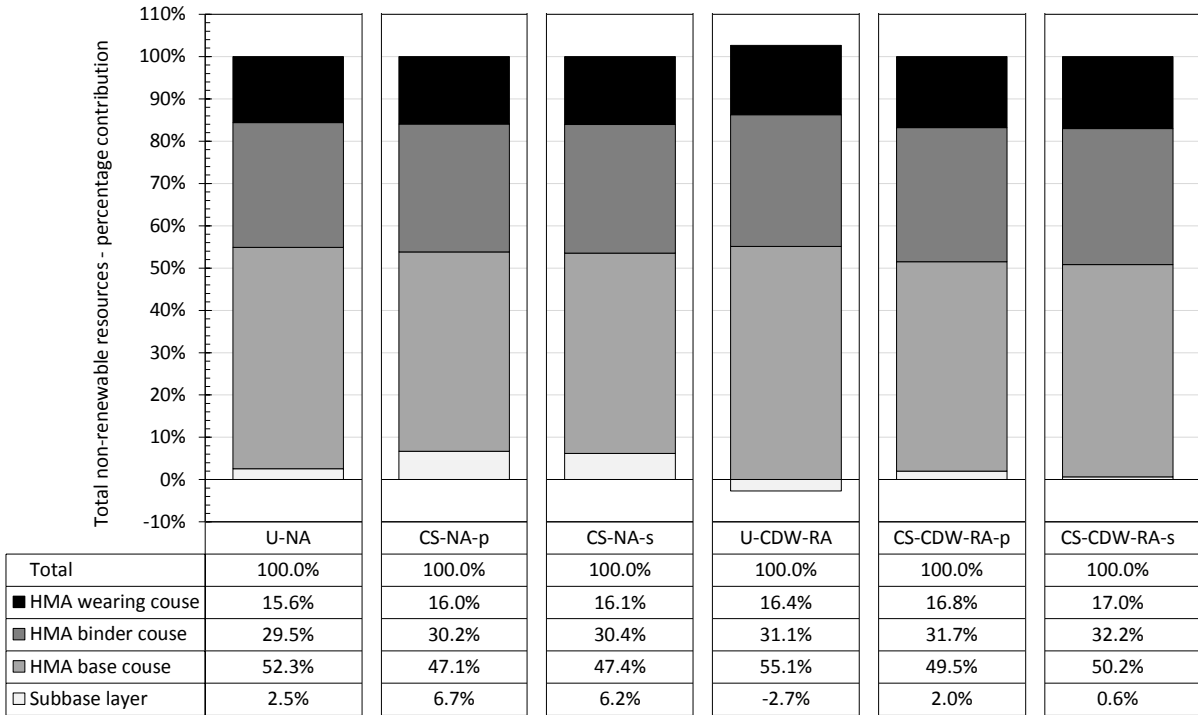


Fig. 12 – Contributions to consumption of non-renewable resources associated with the construction of 1 m² pavement according to different scenarios

570 **6. CONCLUSION**

571 **6.1 Key findings**

572 This integrated structural-LCA study was aimed at evaluating and comparing six different scenarios
573 depending on (i) the unbound and cement-stabilized material included in the subbase and (ii) the
574 construction technique adopted. The key findings of the structural analysis are as follows:

- 575 • the same total HMA layer thickness (equal to 0.28 m) can be adopted by using 0.30 m of NA or
576 CDW-RA in the subbase due to the comparable mechanical properties of the two alternative
577 aggregates;
- 578 • similar conclusions are drawn when pavement structures with cement-stabilized NA and
579 CDW-RA are compared to each other; therefore, primary and secondary aggregates of similar
580 performance lead to comparable structural performance levels in a road pavement system;
- 581 • the addition of 3% of limestone Portland cement (CEM-II/B-LL) as a stabilizer to both granular
582 materials reduces the thickness of bound HMA layers by 0.02 m.

583
584 The key findings of the LCA as they relate to the construction of the road pavement are as
585 follows:

- 586 • the ILCD and CED impact indicators are all lower for the production of CDW-RA than they are
587 for the production of NA from quarrying activities, mainly because of the environmental credits
588 awarded for the avoidance of CDW landfilling;
- 589 • transport accounts for 79% of the climate change indicator for CDW-RA, so it is fundamental to
590 limit the distance between the waste generation site and the recycling plant so as to preserve
591 the environmental credit gained from its recycling;
- 592 • when considering the construction of the entire pavement, the environmental benefits of the
593 CDW-RA production are preserved; the U-CDW-RA scenario exhibits climate change and
594 renewable resources indicators which are 16% and 35% lower respectively than those for the
595 U-NA one;
- 596 • the environmental impact and resource consumption due to the in-plant production of
597 cement-stabilized granular material is attributable to the use of cement, the production of which
598 is highly energy intensive;
- 599 • despite pavements with both cement-stabilized NA and CDW-RA subbases requiring 0.02 m
600 less HMA in the road base layer, the environmental benefits of using lower quantities of HMA
601 are lost due to the impact of cement;
- 602 • the on-site mixing of stabilized subbase materials provides some environmental benefit mainly
603 due to energy savings in comparison to the in-plant mixing; considering the climate change
604 factor, CS-NA-s and CS-CDW-RA-s had 1.0 and 3.6% lower values in comparison with CS-NA-p
605 and CS-CDW-RA-p respectively; and 0.5 and 1.4% lower total non-renewable consumption

- 606 indicator values respectively for scenarios with NA and CDW-RA stabilized on-site with respect
607 to those from the in-plant mixing;
- 608 • CS-CDW-RA-p and CS-CDW-RA-s scenarios revealed advantages with respect to the U-NA
609 one for the majority of ILCD and CED impact indicators; however, to register positive results in
610 terms of climate change, alternatives to CEM-II/B-LL must be considered;
 - 611 • according to the ILCD impact category, the U-CDW-RA scenario is the most favourable because
612 of the lowest impacts; the use of CDW-RA in lieu of NA and the avoidance of cementitious
613 products counterbalance the necessity of a thicker HMA base layer;
 - 614 • in contrast, since CDW-RA requires a thicker road base made with HMA, there is a greater
615 consumption of non-renewable resources (according to the CED method); therefore, for this
616 impact indicator both CS-CDW-RA-p and CS-CDW-RA-s scenarios are the most favourable.

617
618

6.2 Implications

619 In light of the results of this integrated and comparative structural-LCA analysis, the use of CDW-RA
620 as an alternative to NA is more favourable in terms of environmental impact. This study supports the
621 design decisions of engineers who tend to opt for the use of CDW-RA for road pavements. Moreover,
622 the use of CDW-RA is also encouraged because of its lower costs. In both cases of unbound and
623 cement-stabilized subbases, more than 9% of total costs can be saved by using CDW-RA in
624 substitution of NA.

625 The impact of HMA layers is significant in terms of overall costs and energy consumption
626 values, thus the use of recycled materials (i.e., reclaimed asphalt) and more sustainable production
627 cycles (i.e., warm mixtures) should be advocated for with this category of material too. This study
628 evidences the predominant environmental impact of cement in cement-stabilized materials (more
629 than 85% of climate change). This outcome encourages new research to develop alternative binders
630 to cement in order to reduce the environmental impacts of cement-stabilized road subbase layers.

631
632

6.3 Limitation and future needs

633 Both structural design and LCA modelling were based on several hypotheses and estimates that are
634 valid for the Piedmont area (North-West of Italy) and should be reconsidered for different locations.
635 Fluctuations in the availability of both natural and recycled materials may change the conclusions in
636 terms of costs and environmental impacts. Furthermore, differences in the configuration and location
637 of quarries in the territory may result in disparate transportation distances and, therefore, different
638 costs and impacts. Similarly, different configurations of the recycling plants (i.e., mobile, semi-mobile,
639 fixed), type of incoming waste, distribution of recycling stations throughout the territory all influence
640 the LCA outcomes. Availability and fuel costs are also linked to the specific geographical area, as
641 well as the production process for electricity (i.e., from renewable or non-renewable resources). All

642
643
644
645
646
647
648
649
650
651
652
653
654
655

642 these factors combine to influence the costs of management, transport, and construction operations
643 and have an impact on the environment.

644 Since this LCA study specifically aimed at evaluating the construction stage of road pavements
645 with the same service life, maintenance and end-of-life scenarios were not included in the analysis.
646 It should be noted that more accurate assumptions on the effects of material properties and
647 construction processes deserve specific investigations. In terms of the structural design of road
648 pavements, this study considered the specific environmental and traffic conditions for a medium-
649 trafficked two-lane rural highway in Italy. The extension to different traffic conditions (i.e., more and
650 less trafficked roads) will evaluate the advantages of employing recycled materials as well as
651 stabilized products in subbase pavement layers.

652 On a final note, further research is necessary to evaluate the use of more sustainable
653 stabilizers than cement because of its significant impact on ILCD and CED indicators in this
654 investigation.

655

656 **ACKNOWLEDGEMENTS**

657 The research was funded with the European Regional Development Fund by the Regione Piemonte
658 (P.O.R. FESR 2014-2020, Asse I, Azione I.1b.1.2, PRISM-E) in the frame of INTREC (INnovative
659 Technologies for RECYcled aggregates from construction and demolition waste in road
660 constructions) project. The cooperation with CAVIT S.p.A. in this project is greatly acknowledged.

661

662 **REFERENCES**

- 663 American Association of State and Highway Transportation Officials, 2013. Standard method of test
664 for determining the resilient modulus of soils and aggregate materials, AASHTO T 307-99.
- 665 Androjić, I., Alduk, Z.D., 2016. Analysis of energy consumption in the production of hot mix asphalt
666 (batch mix plant). *Can. J. Civ. Eng.* 43, 1044–1051. <https://doi.org/10.1139/cjce-2016-0277>
- 667 Arulrajah, A., Piratheepan, J., Disfani, M.M., Bo, M.W., 2013. Geotechnical and Geoenvironmental
668 Properties of Recycled Construction and Demolition Materials in Pavement Subbase
669 Applications. *Journal of Materials in Civil Engineering* 25, 1077–1088.
670 [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0000652](https://doi.org/10.1061/(ASCE)MT.1943-5533.0000652)
- 671 Asphalt Institute, 1982. Research and Development of the Asphalt Institute's Thickness Design
672 Manual (MS-1), 9th edition (Research Report No. 82-2). Asphalt Institute, Lexington, KY,
673 United States.
- 674 Bassani, M., Tefa, L., 2018. Compaction and freeze-thaw degradation assessment of recycled
675 aggregates from unseparated construction and demolition waste. *Construction and Building*
676 *Materials* 160, 180–195. <https://doi.org/10.1016/j.conbuildmat.2017.11.052>
- 677 Behiry, A.E.A.E.-M., 2013. Utilization of cement treated recycled concrete aggregates as base or
678 subbase layer in Egypt. *Ain Shams Engineering Journal* 4, 661–673.
679 <https://doi.org/10.1016/j.asej.2013.02.005>
- 680 Bennert, T., Papp Jr, W., Maher, A., Gucunski, N., 2000. Utilization of construction and demolition
681 debris under traffic-type loading in base and subbase applications. *Transportation research*
682 *record: journal of the transportation research board* 33–39.
- 683 Blengini, G.A., Garbarino, E., 2010. Resources and waste management in Turin (Italy): the role of
684 recycled aggregates in the sustainable supply mix. *Journal of Cleaner Production* 18, 1021–
685 1030. <https://doi.org/10.1016/j.jclepro.2010.01.027>

61
62
63
64
65

- 686 Blengini, G.A., Garbarino, E., Šolar, S., Shields, D.J., Hámor, T., Vinai, R., Agioutantis, Z., 2012. Life
687 Cycle Assessment guidelines for the sustainable production and recycling of aggregates: the
688 Sustainable Aggregates Resource Management project (SARMa). *Journal of Cleaner
689 Production* 27, 177–181. <https://doi.org/10.1016/j.jclepro.2012.01.020>
- 690 Borghi, G., Pantini, S., Rigamonti, L., 2018. Life cycle assessment of non-hazardous Construction
691 and Demolition Waste (CDW) management in Lombardy Region (Italy). *Journal of Cleaner
692 Production* 184, 815–825. <https://doi.org/10.1016/j.jclepro.2018.02.287>
- 693 Bovea, M.D., Powell, J.C., 2016. Developments in life cycle assessment applied to evaluate the
694 environmental performance of construction and demolition wastes. *Waste Management* 50,
695 151–172. <https://doi.org/10.1016/j.wasman.2016.01.036>
- 696 Cardoso, R., Silva, R.V., Brito, J. de, Dhir, R., 2016. Use of recycled aggregates from construction
697 and demolition waste in geotechnical applications: A literature review. *Waste Management*
698 49, 131–145. <https://doi.org/10.1016/j.wasman.2015.12.021>
- 699 Celauro, C., Corriere, F., Guerrieri, M., Lo Casto, B., Rizzo, A., 2017. Environmental analysis of
700 different construction techniques and maintenance activities for a typical local road. *Journal
701 of Cleaner Production* 142, 3482–3489. <https://doi.org/10.1016/j.jclepro.2016.10.119>
- 702 Chowdhury, R., Apul, D., Fry, T., 2010. A life cycle based environmental impacts assessment of
703 construction materials used in road construction. *Resources, Conservation and Recycling*
704 54, 250–255. <https://doi.org/10.1016/j.resconrec.2009.08.007>
- 705 Christensen Jr, D.W., Pellinen, T., Bonaquist, R.F., 2003. Hirsch model for estimating the modulus
706 of asphalt concrete, in: *Journal of the Association of Asphalt Paving Technologists*.
707 Presented at the Asphalt Paving Technology 2003 Association of Asphalt Paving
708 Technologists (AAPT).
- 709 Christopher, B.R., Schwartz, C.W., Boudreaux, R., Ryan R. Berg & Associates, Inc., 2006.
710 *Geotechnical Aspects of Pavements (Final Report No. FHWA-NHI-05-037)*. Federal Highway
711 Administration, Woodbury, MN, US.
- 712 Coelho, A., Brito, J. de, 2013. Environmental analysis of a construction and demolition waste
713 recycling plant in Portugal – Part I: Energy consumption and CO2 emissions. *Waste
714 Management* 33, 1258–1267. <https://doi.org/10.1016/j.wasman.2013.01.025>
- 715 De Melo, A.B., Gonçalves, A.F., Martins, I.M., 2011. Construction and demolition waste generation
716 and management in Lisbon (Portugal). *Resources, Conservation and Recycling* 55, 1252–
717 1264. <https://doi.org/10.1016/j.resconrec.2011.06.010>
- 718 Di Maria, A., Eyckmans, J., Van Acker, K., 2018. Downcycling versus recycling of construction and
719 demolition waste: Combining LCA and LCC to support sustainable policy making. *Waste
720 Management* 75, 3–21. <https://doi.org/10.1016/j.wasman.2018.01.028>
- 721 Eurobitume, 2020. *The Eurobitume Life-Cycle Inventory for Bitumen. Version 3.1*. European Bitumen
722 Association, Brussels, Belgium.
- 723 Eurobitume, 2012. *Life-Cycle Inventory: Bitumen. 2nd Edition*. European Bitumen Association,
724 Brussels, Belgium.
- 725 European Aggregates Association, 2020. *A sustainable industry for a sustainable Europe. Annual
726 review 2019-2020 (Annual report)*. Brussels, Belgium.
- 727 European Commission, 2020. *Communication from the Commission to the European Parliament,
728 the Council, the European Economic and Social Committee and the Committee of the
729 Regions. A new Circular Economy Action Plan for a Cleaner and more Competitive Europe,*
730 COM/2020/98.
- 731 European Commission - Joint Research Centre - Institute for Environment and Sustainability, 2012.
732 *Characterisation factors of the ILCD - Recommended Life Cycle Impact Assessment
733 methods - Database and supporting information (No. EUR 25167)*. Publications Office of the
734 European Union, Luxembourg.
- 735 European Commission - Joint Research Centre - Institute for Environment and Sustainability, 2010.
736 *International Reference Life Cycle Data System (ILCD) Handbook - General guide for Life
737 Cycle Assessment - Provisions and Action Steps (No. EUR 24378 EN)*. Publications Office
738 of the European Union, Luxembourg.
- 739 European Committee for Standardization, 2011. *Cement - Part 1: Composition, specifications and
740 conformity criteria for common cements, EN 197-1:2011*.

61
62
63
64
65

- 741 European Committee for Standardization, 2010. Unbound and hydraulically bound mixtures - Part 2:
742 Test methods for laboratory reference density and water content - Proctor compaction, EN
743 13286-2:2010.
- 744 Faleschini, F., Zanini, M.A., Pellegrino, C., Pasinato, S., 2016. Sustainable management and supply
745 of natural and recycled aggregates in a medium-size integrated plant. *Waste Management*
746 49, 146–155. <https://doi.org/10.1016/j.wasman.2016.01.013>
- 747 Ghanbari, M., Abbasi, A.M., Ravanshadnia, M., 2018. Production of natural and recycled
748 aggregates: the environmental impacts of energy consumption and CO2 emissions. *J Mater*
749 *Cycles Waste Manag* 20, 810–822. <https://doi.org/10.1007/s10163-017-0640-2>
- 750 Ghisellini, P., Ripa, M., Ulgiati, S., 2018. Exploring environmental and economic costs and benefits
751 of a circular economy approach to the construction and demolition sector. A literature review.
752 *Journal of Cleaner Production* 178, 618–643. <https://doi.org/10.1016/j.jclepro.2017.11.207>
- 753 Gschösser, F., Wallbaum, H., Boesch, M.E., 2012. Life-cycle assessment of the production of Swiss
754 road materials. *Journal of Materials in Civil Engineering* 24, 168–176.
755 [https://doi.org/10.1061/\(ASCE\)MT.1943-5533.0000375](https://doi.org/10.1061/(ASCE)MT.1943-5533.0000375)
- 756 Hicks, R.G., Monismith, C.L., 1971. Factors influencing the resilient response of granular materials.
757 *Highway Research Record* 15–31.
- 758 Hossain, Md.U., Poon, C.S., Lo, I.M.C., Cheng, J.C.P., 2016. Comparative environmental evaluation
759 of aggregate production from recycled waste materials and virgin sources by LCA.
760 *Resources, Conservation and Recycling* 109, 67–77.
761 <https://doi.org/10.1016/j.resconrec.2016.02.009>
- 762 Huang, B., Wang, X., Kua, H., Geng, Y., Bleischwitz, R., Ren, J., 2018. Construction and demolition
763 waste management in China through the 3R principle. *Resources, Conservation and*
764 *Recycling* 129, 36–44. <https://doi.org/10.1016/j.resconrec.2017.09.029>
- 765 Huang, Y.H., 2003. *Pavement Analysis and Design*, 2nd Edition. ed. Pearson, Upper Saddle River,
766 NJ.
- 767 International Organization for Standardization, 2006a. Environmental management - Life cycle
768 assessment - Principles and framework, ISO 14040:2006.
- 769 International Organization for Standardization, 2006b. Environmental management - Life cycle
770 assessment - Requirements and guidelines, ISO 14044:2006.
- 771 Jain, S., Singhal, S., Pandey, S., 2020. Environmental life cycle assessment of construction and
772 demolition waste recycling: A case of urban India. *Resources, Conservation and Recycling*
773 155, 104642. <https://doi.org/10.1016/j.resconrec.2019.104642>
- 774 Joint Research Centre, Institute for Environment and Sustainability, 2012. Characterisation factors
775 of the ILCD Recommended Life Cycle Impact Assessment methods (Database and
776 Supporting Information No. EUR 25167 EN). European Commission, Luxembourg.
- 777 Knoeri, C., Sanyé-Mengual, E., Althaus, H.-J., 2013. Comparative LCA of recycled and conventional
778 concrete for structural applications. *The International Journal of Life Cycle Assessment* 18,
779 909–918. <https://doi.org/10.1007/s11367-012-0544-2>
- 780 Kourmpanis, B., Papadopoulos, A., Moustakas, K., Stylianou, M., Haralambous, K.J., Loizidou, M.,
781 2008. Preliminary study for the management of construction and demolition waste. *Waste*
782 *Management & Research* 26, 267–275. <https://doi.org/10.1177/0734242X07083344>
- 783 Leite, F. da C., Motta, R. dos S., Vasconcelos, K.L., Bernucci, L., 2011. Laboratory evaluation of
784 recycled construction and demolition waste for pavements. *Construction and Building*
785 *Materials* 25, 2972–2979. <https://doi.org/10.1016/j.conbuildmat.2010.11.105>
- 786 Lekarp, F., Isacsson, U., Dawson, A., 2000. State of the Art. I: Resilient Response of Unbound
787 Aggregates. *Journal of Transportation Engineering* 126, 66–75.
788 [https://doi.org/10.1061/\(ASCE\)0733-947X\(2000\)126:1\(66\)](https://doi.org/10.1061/(ASCE)0733-947X(2000)126:1(66))
- 789 Marzouk, M., Azab, S., 2014. Environmental and economic impact assessment of construction and
790 demolition waste disposal using system dynamics. *Resources, Conservation and Recycling*
791 82, 41–49. <https://doi.org/10.1016/j.resconrec.2013.10.015>
- 792 Mazzoni, G., Bocci, E., Canestrari, F., 2018. Influence of rejuvenators on bitumen ageing in hot
793 recycled asphalt mixtures. *Journal of Traffic and Transportation Engineering (English Edition)*
794 5, 157–168. <https://doi.org/10.1016/j.jtte.2018.01.001>
- 795 Ministero delle Infrastrutture e dei Trasporti, 2001. Studio a carattere pre-normativo delle norme
796 tecniche di tipo prestazionale per capitolati speciali d'appalto.

- 797 Ossa, A., García, J.L., Botero, E., 2016. Use of recycled construction and demolition waste (CDW)
798 aggregates: A sustainable alternative for the pavement construction industry. *Journal of*
799 *Cleaner Production* 135, 379–386. <https://doi.org/10.1016/j.jclepro.2016.06.088>
- 800 Park, J., Tucker, R., 2017. Overcoming barriers to the reuse of construction waste material in
801 Australia: a review of the literature. *International Journal of Construction Management* 17,
802 228–237. <https://doi.org/10.1080/15623599.2016.1192248>
- 803 Pellinen, T., Witczak, M., 2002. Use of stiffness of hot-mix asphalt as a simple performance test.
804 *Transportation Research Record: Journal of the Transportation Research Board* 80–90.
- 805 Peng, C.-L., Scorpio, D.E., Kibert, C.J., 1997. Strategies for successful construction and demolition
806 waste recycling operations. *Construction Management and Economics* 15, 49–58.
807 <https://doi.org/10.1080/014461997373105>
- 808 Regione Piemonte, 2021. *Prezzario Regione Piemonte 2021 - Allegato B - Elenco Prezzi Unitari*
809 [WWW Document]. URL [http://www.sistemapiemonte.it/cms/privati/territorio/servizi/929-](http://www.sistemapiemonte.it/cms/privati/territorio/servizi/929-consultazione-prezzario-regionale-opere-pubbliche/3596-prezzario-2021)
810 [consultazione-prezzario-regionale-opere-pubbliche/3596-prezzario-2021](http://www.sistemapiemonte.it/cms/privati/territorio/servizi/929-consultazione-prezzario-regionale-opere-pubbliche/3596-prezzario-2021) (accessed 9.1.21).
- 811 Rodríguez, G., Medina, C., Alegre, F.J., Asensio, E., Sánchez de Rojas, M.I., 2015. Assessment of
812 Construction and Demolition Waste plant management in Spain: in pursuit of sustainability
813 and eco-efficiency. *Journal of Cleaner Production* 90, 16–24.
814 <https://doi.org/10.1016/j.jclepro.2014.11.067>
- 815 Schneider, M., Romer, M., Tschudin, M., Bolio, H., 2011. Sustainable cement production—present
816 and future. *Cement and Concrete Research, Special Issue: 13th International Congress on*
817 *the Chemistry of Cement* 41, 642–650. <https://doi.org/10.1016/j.cemconres.2011.03.019>
- 818 Silva, R.V., de Brito, J., Dhir, R.K., 2019. Use of recycled aggregates arising from construction and
819 demolition waste in new construction applications. *Journal of Cleaner Production* 236,
820 117629. <https://doi.org/10.1016/j.jclepro.2019.117629>
- 821 Simion, I.M., Fortuna, M.E., Bonoli, A., Gavrilesco, M., 2013. Comparing environmental impacts of
822 natural inert and recycled construction and demolition waste processing using LCA. *Journal*
823 *of Environmental Engineering and Landscape Management* 21, 273–287.
824 <https://doi.org/10.3846/16486897.2013.852558>
- 825 Tavira, J., Jiménez, J.R., Ayuso, J., Sierra, M.J., Ledesma, E.F., 2018. Functional and structural
826 parameters of a paved road section constructed with mixed recycled aggregates from non-
827 selected construction and demolition waste with excavation soil. *Construction and Building*
828 *Materials* 164, 57–69. <https://doi.org/10.1016/j.conbuildmat.2017.12.195>
- 829 Tefa, L., Bassani, M., Coppola, B., Palmero, P., 2021. Strength development and environmental
830 assessment of alkali-activated construction and demolition waste fines as stabilizer for
831 recycled road materials. *Construction and Building Materials* 289, 123017.
832 <https://doi.org/10.1016/j.conbuildmat.2021.123017>
- 833 Villoria Sáez, P., Osmani, M., 2019. A diagnosis of construction and demolition waste generation
834 and recovery practice in the European Union. *Journal of Cleaner Production* 241, 118400.
835 <https://doi.org/10.1016/j.jclepro.2019.118400>
- 836 Wernet, G., Bauer, C., Steubing, B., Reinhard, J., Moreno-Ruiz, E., Weidema, B., 2016. The
837 ecoinvent database version 3 (part I): overview and methodology. *Int J Life Cycle Assess* 21,
838 1218–1230. <https://doi.org/10.1007/s11367-016-1087-8>
- 839 Witczak, M.W., 1972. Design of full-depth asphalt airfield pavements, in: *Third International*
840 *Conference on the Structural Design of Asphalt Pavements* Sept. 11-15, 1972. Presented at
841 the Third International Conference on the Structural Design of Asphalt Pavements, London,
842 UK, pp. 550–567.
- 843 Worrell, E., Price, L., Martin, N., Hendriks, C., Meida, L.O., 2001. Carbon dioxide emissions from the
844 global cement industry. *Annual review of energy and the environment* 26, 303–329.
- 845 Zhao, W., Leefink, R.B., Rotter, V.S., 2010. Evaluation of the economic feasibility for the recycling
846 of construction and demolition waste in China—The case of Chongqing. *Resources,*
847 *Conservation and Recycling* 54, 377–389. <https://doi.org/10.1016/j.resconrec.2009.09.003>
- 848 Zhao, Y., Goulias, D., Tefa, L., Bassani, M., 2021. Life Cycle Economic and Environmental Impacts
849 of CDW Recycled Aggregates in Roadway Construction and Rehabilitation. *Sustainability* 13,
850 8611. <https://doi.org/10.3390/su13158611>

61
62
63
64
65