

Lipopeptides from *Bacillus subtilis* AC7 inhibit adhesion and biofilm formation of *Candida albicans* on silicone

Original

Lipopeptides from *Bacillus subtilis* AC7 inhibit adhesion and biofilm formation of *Candida albicans* on silicone / Ceresa, Chiara; Rinaldi, Maurizio; Chiono, Valeria; Carmagnola, Irene; Allegrone, Gianna; Fracchia, Letizia. - In: ANTONIE VAN LEEUWENHOEK. - ISSN 0003-6072. - 109:(2016), pp. 1375-1388. [10.1007/s10482-016-0736-z]

Availability:

This version is available at: 11583/2649103 since: 2016-11-25T13:14:15Z

Publisher:

Springer Netherlands

Published

DOI:10.1007/s10482-016-0736-z

Terms of use:

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

Publisher copyright

Springer postprint/Author's Accepted Manuscript

This version of the article has been accepted for publication, after peer review (when applicable) and is subject to Springer Nature's AM terms of use, but is not the Version of Record and does not reflect post-acceptance improvements, or any corrections. The Version of Record is available online at: <http://dx.doi.org/10.1007/s10482-016-0736-z>

(Article begins on next page)

Dear Author,

Here are the proofs of your article.

- You can submit your corrections **online**, via **e-mail** or by **fax**.
- For **online** submission please insert your corrections in the online correction form. Always indicate the line number to which the correction refers.
- You can also insert your corrections in the proof PDF and **email** the annotated PDF.
- For fax submission, please ensure that your corrections are clearly legible. Use a fine black pen and write the correction in the margin, not too close to the edge of the page.
- Remember to note the **journal title**, **article number**, and **your name** when sending your response via e-mail or fax.
- **Check** the metadata sheet to make sure that the header information, especially author names and the corresponding affiliations are correctly shown.
- **Check** the questions that may have arisen during copy editing and insert your answers/ corrections.
- **Check** that the text is complete and that all figures, tables and their legends are included. Also check the accuracy of special characters, equations, and electronic supplementary material if applicable. If necessary refer to the *Edited manuscript*.
- The publication of inaccurate data such as dosages and units can have serious consequences. Please take particular care that all such details are correct.
- Please **do not** make changes that involve only matters of style. We have generally introduced forms that follow the journal's style. Substantial changes in content, e.g., new results, corrected values, title and authorship are not allowed without the approval of the responsible editor. In such a case, please contact the Editorial Office and return his/her consent together with the proof.
- If we do not receive your corrections **within 48 hours**, we will send you a reminder.
- Your article will be published **Online First** approximately one week after receipt of your corrected proofs. This is the **official first publication** citable with the DOI. **Further changes are, therefore, not possible.**
- The **printed version** will follow in a forthcoming issue.

Please note

After online publication, subscribers (personal/institutional) to this journal will have access to the complete article via the DOI using the URL: [http://dx.doi.org/\[DOI\]](http://dx.doi.org/[DOI]).

If you would like to know when your article has been published online, take advantage of our free alert service. For registration and further information go to: <http://www.link.springer.com>.

Due to the electronic nature of the procedure, the manuscript and the original figures will only be returned to you on special request. When you return your corrections, please inform us if you would like to have these documents returned.

Metadata of the article that will be visualized in OnlineFirst

Please note: Images will appear in color online but will be printed in black and white.

ArticleTitle Lipopeptides from *Bacillus subtilis* AC7 inhibit adhesion and biofilm formation of *Candida albicans* on silicone

Article Sub-Title

Article CopyRight Springer International Publishing Switzerland
(This will be the copyright line in the final PDF)

Journal Name Antonie van Leeuwenhoek

Corresponding Author

Family Name	Fracchia
Particle	
Given Name	Letizia
Suffix	
Division	Department of Pharmaceutical Sciences
Organization	Università del Piemonte Orientale "A. Avogadro"
Address	Largo Donegani 2, 28100, Novara, Italy
Email	letizia.fracchia@uniupo.it
ORCID	http://orcid.org/0000-0003-3505-1919

Author

Family Name	Ceresa
Particle	
Given Name	Chiara
Suffix	
Division	Department of Pharmaceutical Sciences
Organization	Università del Piemonte Orientale "A. Avogadro"
Address	Largo Donegani 2, 28100, Novara, Italy
Email	
ORCID	

Author

Family Name	Rinaldi
Particle	
Given Name	Maurizio
Suffix	
Division	Department of Pharmaceutical Sciences
Organization	Università del Piemonte Orientale "A. Avogadro"
Address	Largo Donegani 2, 28100, Novara, Italy
Email	
ORCID	

Author

Family Name	Chiono
Particle	
Given Name	Valeria
Suffix	
Division	Department of Mechanical and Aerospace Engineering
Organization	Politecnico di Torino

Address Corso Duca degli Abruzzi 24, 10129, Turin, Italy
Email
ORCID

Author Family Name **Carmagnola**
Particle
Given Name **Irene**
Suffix
Division Department of Mechanical and Aerospace Engineering
Organization Politecnico di Torino
Address Corso Duca degli Abruzzi 24, 10129, Turin, Italy
Email
ORCID

Author Family Name **Allegrone**
Particle
Given Name **Gianna**
Suffix
Division Department of Pharmaceutical Sciences
Organization Università del Piemonte Orientale "A. Avogadro"
Address Largo Donegani 2, 28100, Novara, Italy
Email
ORCID

Schedule Received 27 April 2016
Revised
Accepted 12 July 2016

Abstract *Candida albicans* is the major fungus that colonises medical implants, causing device-associated infections with high mortality. Antagonistic bacterial products with interesting biological properties, such as biosurfactants, have recently been considered for biofilm prevention. This study investigated the activity of lipopeptide biosurfactant produced by *Bacillus subtilis* AC7 (AC7 BS) against adhesion and biofilm formation of *C. albicans* on medical-grade silicone elastomeric disks (SEDs). Chemical analysis, stability, surface activities of AC7 BS crude extract and physicochemical characterisation of the coated silicone disk surfaces were also carried out. AC7 BS showed a good reduction of water surface tension, low critical micelle concentration, good emulsification activity, thermal resistance and pH stability. Co-incubation with 2 mg ml⁻¹ AC7 BS significantly reduced adhesion and biofilm formation of three *C. albicans* strains on SEDs in a range of 67–69 % and of 56–57 %, respectively. On pre-coated SEDs, fungal adhesion and biofilm formation were reduced by 57–62 % and 46–47 %, respectively. Additionally, AC7 BS did not inhibit viability of *C. albicans* strains in both planktonic and sessile form. Chemical analysis of the crude extract revealed the presence of two families of lipopeptides, principally surfactin and a lower percentage of fengycin. The evaluation of surface wettability indicated that AC7 BS coating of SEDs surface was successful although uneven. AC7 BS significantly prohibits the initial deposition of *C. albicans* and slows biofilm growth, suggesting a potential role of biosurfactant coatings for preventing fungal infection associated with silicone medical devices.

Keywords (separated by '-') Anti-adhesion - Biofilm - Medical device - Lipopeptide biosurfactant - Coating - *Candida albicans*

Footnote Information

2 **Lipopeptides from *Bacillus subtilis* AC7 inhibit adhesion**
3 **and biofilm formation of *Candida albicans* on silicone**

4 Chiara Ceresa · Maurizio Rinaldi · Valeria Chiono · Irene Carmagnola ·
5 Gianna Allegrone · Letizia Fracchia 

6 Received: 27 April 2016 / Accepted: 12 July 2016
7 © Springer International Publishing Switzerland 2016

8 **Abstract** *Candida albicans* is the major fungus that
9 colonises medical implants, causing device-associated
10 infections with high mortality. Antagonistic bacterial
11 products with interesting biological properties, such as
12 biosurfactants, have recently been considered for
13 biofilm prevention. This study investigated the activity
14 of lipopeptide biosurfactant produced by *Bacillus*
15 *subtilis* AC7 (AC7 BS) against adhesion and biofilm
16 formation of *C. albicans* on medical-grade silicone
17 elastomeric disks (SEDs). Chemical analysis, stabil-
18 ity, surface activities of AC7 BS crude extract and
19 physicochemical characterisation of the coated sili-
20 cone disk surfaces were also carried out. AC7 BS
21 showed a good reduction of water surface tension, low
22 critical micelle concentration, good emulsification
23 activity, thermal resistance and pH stability. Co-
24 incubation with 2 mg ml⁻¹ AC7 BS significantly
25 reduced adhesion and biofilm formation of three *C.*
26 *albicans* strains on SEDs in a range of 67–69 % and of
27 56–57 %, respectively. On pre-coated SEDs, fungal
28 adhesion and biofilm formation were reduced by

57–62 % and 46–47 %, respectively. Additionally, 29
AC7 BS did not inhibit viability of *C. albicans* strains 30
in both planktonic and sessile form. Chemical analysis 31
of the crude extract revealed the presence of two 32
families of lipopeptides, principally surfactin and a 33
lower percentage of fengycin. The evaluation of 34
surface wettability indicated that AC7 BS coating of 35
SEDs surface was successful although uneven. AC7 36
BS significantly prohibits the initial deposition of *C.* 37
albicans and slows biofilm growth, suggesting a 38
potential role of biosurfactant coatings for preventing 39
fungal infection associated with silicone medical 40
devices. 41

Keywords Anti-adhesion · Biofilm · Medical 42
device · Lipopeptide biosurfactant · Coating · *Candida* 43
albicans 44

Introduction 45

In recent years, a significant increase in the incidence 46
of human fungal infections has been observed. *Can-* 47
dida species are the major problem, especially in 48
immunocompromised patients (Espinel-Ingroff et al. 49
2009; van De Veerdonk et al. 2010; Ruhnke et al. 50
2011), representing the fourth most common cause of 51
nosocomial bloodstream infections (Wisplinghoff 52
et al. 2004). Invasive candidiasis presents a high 53

A1 C. Ceresa · M. Rinaldi · G. Allegrone · L. Fracchia (✉)
A2 Department of Pharmaceutical Sciences, Università del
A3 Piemonte Orientale “A. Avogadro”, Largo Donegani 2,
A4 28100 Novara, Italy
A5 e-mail: letizia.fracchia@uniupo.it

A6 V. Chiono · I. Carmagnola
A7 Department of Mechanical and Aerospace Engineering,
A8 Politecnico di Torino, Corso Duca degli Abruzzi 24,
A9 10129 Turin, Italy

54 global mortality rate, ranging from 36 to 63 % in
 55 different patient groups (Guery et al. 2009; van De
 56 Veerdonk et al. 2010) and represents a significant
 57 problem in terms of patient management and health-
 58 care costs in the public health system (Kullberg et al.
 59 2011).

60 Among the *Candida* species isolated from humans,
 61 *Candida albicans* is frequently associated with the
 62 formation of biofilms on a wide variety of medical
 63 devices (Crump and Collignon 2000; Goldberg et al.
 64 2000; Karchmer 2000; Maki and Tambyah 2001). *C.*
 65 *albicans* biofilms consist of structured surface-associ-
 66 ated cell communities embedded in an extracellular
 67 matrix that have distinct phenotypes compared to their
 68 planktonic cell counterparts (Fanning and Mitchell
 69 2012). The presence of the biofilm plays a key role on
 70 *C. albicans* pathogenesis, by protecting the microor-
 71 ganism from host defences and reducing significantly
 72 its susceptibility to antifungal agents (Hawser and
 73 Douglas 1994; Lazzell et al. 2009). Furthermore, the
 74 tenacity with which *C. albicans* infects indwelling
 75 medical devices necessitates, in almost all the cases,
 76 their removal (Kojic and Darouiche 2004).

77 For these reasons, the development of new tech-
 78 nologies to counteract *C. albicans* biofilm growth
 79 represents a major challenge in clinical practice and
 80 preventive medicine. Among microbial metabolites,
 81 biosurfactants have gained importance thanks to their
 82 interesting biological properties, such as the ability to
 83 disrupt membranes and to affect the adhesion proper-
 84 ties of cells/microorganisms (Cameotra and Makkar
 85 2004; Singh and Cameotra 2004; Seydlová and
 86 Svobodová 2008; Rodrigues and Teixeira 2010).
 87 Biosurfactants are amphiphathic compounds with both
 88 hydrophilic and hydrophobic moieties that exhibit
 89 surface activities at interfaces (Banat et al. 2010).
 90 Adsorption of biosurfactants to a substratum surface
 91 modifies its hydrophobicity, interfering with microbial
 92 adhesion and desorption processes (Rodrigues et al.
 93 2006a; Biniarz et al. 2015). Pre-coating catheters and
 94 other medical implantable materials with biosurfac-
 95 tants could represent a preventive strategy to inhibit
 96 pathogenic biofilm growth, thus reducing the use of
 97 pharmaceuticals and antibiotics (Rodrigues et al.
 98 2006b; Singh et al. 2007; Falagas and Makris 2009).

99 In this study, the ability of the lipopeptide biosur-
 100 factant AC7 produced by *Bacillus subtilis* (AC7 BS) to
 101 inhibit adhesion and biofilm formation of three *C.*
 102 *albicans* strains was evaluated by co-incubation and

pre-coating on silicone elastomer at physiological 103
 conditions. Lipopeptides activity was determined by 104
 means of the crystal violet staining and the viable cell 105
 counting methods. Moreover, AC7 BS was chemically 106
 characterised and its stability and surface activities 107
 measured. Surface physicochemical characterisations 108
 of the AC7 BS coated silicone were also carried out. 109

Materials and methods 110

Microorganisms and culture conditions 111

The endophytic biosurfactant-producing strain AC7 112
 was isolated from the inside of stems of *Robinia* 113
pseudoacacia and was genotypically identified by 114
 complete 16S rDNA sequence analysis (DSMZ Iden- 115
 tification Service, Braunschweig, Germany) as *B.* 116
subtilis. For biofilm assays, the strain *C. albicans* 117
 IHEM 2894 was purchased from The Belgian Co- 118
 ordinated Collections of Microorganisms (BCCM). *C.* 119
albicans 40 (DSM 29204) and 42 (DSM 29205) are 120
 two wild strains (courtesy of Hospital “Maggiore della 121
 Carità”, Novara, Italy), clinically isolated from central 122
 venous catheter and urinary catheter, respectively, and 123
 deposited by the Authors in the DSMZ collection. 124
 Strain *B. subtilis* AC7 was stored at -80°C in Luria- 125
 Bertani (LB) broth (Sigma-Aldrich) supplemented 126
 with 25 % glycerol and grown on LB agar plates for 127
 24 h at 28°C . *C. albicans* strains were stored at 128
 -80°C in Sabouraud dextrose broth (Sigma-Aldrich) 129
 supplemented with 25 % glycerol and grown for 24 h 130
 at 37°C on Sabouraud Dextrose Agar (SDA) plates. 131

Critical micelle concentration, emulsification 132
 index and stability study of AC7 BS 133

AC7 BS crude extract was obtained according to the 134
 method described by Rivardo et al. (2009). Surface 135
 tension of 0.5, 1.0 and 2.0 mg ml⁻¹ AC7 BS solutions 136
 in alkaline distilled water was measured by using a 137
 ring tensiometer (KSV Sigma 703D). Results for 138
 surface tension measurements were expressed as 139
 mN m⁻¹ and compared with alkaline distilled water. 140
 Critical micelle concentration (CMC) was determined 141
 on serially diluted biosurfactant solutions in alkaline 142
 distilled water (from 0.01 to 0.5 mg ml⁻¹). Surface 143
 tension of each dilution was determined in triplicate. 144
 The CMC was assessed from the intercept of two 145

Author Proof

146	straight lines extrapolated from the concentration-	100 µl of sterile PBS were used. <i>C. albicans</i> suspen-	191
147	dependent and concentration-independent sections of	sions at a concentration ranging from 1 to 5 × 10 ⁵	192
148	a curve plotted between biosurfactant concentration	colony-forming units (CFU) ml ⁻¹ were prepared in	193
149	and surface tension values.	sterile double-strength Roswell Park Memorial Insti-	194
150	The heat/cold stability of 0.5, 1.0 and 2.0 mg ml ⁻¹	tute (RPMI) 1640 medium (Sigma-Aldrich) buffered	195
151	AC7 BS solutions was evaluated by measuring the	with 3-(<i>N</i> -morpholino)propanesulfonic acid buffer	196
152	emulsification index at 24 h E ₂₄ (%) (Franzetti et al.	(MOPS) (Sigma-Aldrich) and supplemented with D-	197
153	2012) and surface tension after treatment at 100 °C for	glucose (2 % final concentration), pH 7.0. Subse-	198
154	1 h, at 121 °C for 15 min and at -80 °C for 24 h. To	quently, 100 µl of the <i>Candida</i> suspensions were	199
155	study pH stability, the pH of the AC7 BS solutions	added to each well, to obtain final concentrations of	200
156	(0.5, 1.0, 2.0 mg ml ⁻¹) was adjusted to different pH	AC7 BS ranging from 0.03 to 3 mg ml ⁻¹ , and to the	201
157	values (3–11) with 1 M NaOH or 1 M HCl. After-	control wells. Blank wells were prepared by mixing	202
158	wards, the surface tension and the E ₂₄ were measured.	100 µl double-strength RPMI with 100 µl of the	203
159	Assays were carried out in triplicate.	biosurfactant solutions (from 0.06 to 6 mg ml ⁻¹) or	204
160	Chemical characterisation of AC7 BS	PBS. The plate was incubated at 37 °C for 24 h in	205
161	The chemical characterisation of the crude extract was	static conditions. Finally, OD ₄₅₀ was measured for	206
162	performed according to the method described by Pecci	each well using a Ultramark Microplate Imaging	207
163	et al. (2010), with and slight modifications. An aliquot	System (Bio-Rad). The data were normalised with	208
164	of the biosurfactant extract was dissolved in methanol/	respect to the value of the corresponding blank wells.	209
165	acetonitrile (50/50 v/v) to obtain a 1000 µg ml ⁻¹	Assays were carried out in triplicate.	210
166	stock solution. Freshly prepared working solutions	Medical-grade silicone elastomeric disks	211
167	were made by diluting the stock solution with	preparation	212
168	methanol/water (50/50 v/v) to 10 µg ml ⁻¹ solutions	Medical-grade silicone elastomeric disks (SEDs)	213
169	Mass spectrometry analyses were done on a LCQ	(TECNOEXTR Srl, Italy) used in the study were	214
170	DECA XP Plus (Thermo Finnigan, San Jose, CA,	15 mm in diameter and 1.5 mm in thickness for	215
171	USA) IonTrap mass instrument equipped with an ESI	experiments in 12-well tissue culture plates, and	216
172	source. Samples (10 µg/ml solutions) were injected	10 mm in diameter and 1.5 mm in thickness for	217
173	with a syringe at 5 µl min ⁻¹ flow rate. Source voltage	experiments in 24-well tissue culture plates. Cleaning	218
174	and capillary voltage were at 4.80 kV and 23 V in	and sterilisation of SEDs was carried out according to	219
175	positive mode. The capillary temperature was main-	the method described by Busscher et al. (1997).	220
176	tained at 350 °C and nitrogen was used as nebulising	Briefly, disks were immersed in 200 ml of distilled	221
177	gas at 30 arbitrary units. Data were acquired in	water supplemented with 1.4 % (v/v) of RBS TM 50	222
178	positive MS total ion scan mode (mass scan range <i>m/z</i>	solution (Sigma-Aldrich), sonicated for 5 min at	223
179	100–2000) and MS/MS product ion scan mode with	60 kHz using Elma S30H (Elmasonic, VWR Interna-	224
180	normalised collision energy (nce %) optimised for	tional) and rinsed in 1 l of MilliQ water twice. Then,	225
181	each precursor ion selected: <i>m/z</i> 1030, 38 %; 1044 and	disks were submerged in 20 ml of methanol (99 %)	226
182	1058, 39 %; 1478 and 1506, 35 %.	(Sigma-Aldrich), rinsed twice and autoclaved for	227
183	Antifungal susceptibility testing against	15 min at 121 °C.	228
184	<i>Candida albicans</i> planktonic cells	Antifungal susceptibility of <i>Candida albicans</i>	229
185	AC7 BS antifungal activity towards planktonic cells of	biofilms	230
186	<i>C. albicans</i> strains was assessed according to	<i>Candida albicans</i> cells were cultivated for 24 h at	231
187	EUCAST guidelines (Rodriguez-Tudela et al. 2008).	37 °C on SDA plates. Cells were then suspended in	232
188	Briefly, 100 µl of AC7 BS solutions (from 0.06 to	Phosphate Buffered Saline (PBS) solution with 10 %	233
189	6 mg ml ⁻¹) were added in a 96-well microtiter plate	Fetal Bovine Serum (FBS) and standardised to	234
190	(Bioster). In control wells (no biosurfactant added),	1 × 10 ⁷ CFU ml ⁻¹ . One milliliter of this fungal	235

suspension was used to submerge silicone disks previously inserted in a 24-well plate (Greiner bio-one). After incubation in static conditions at 37 °C for 1.5 h (adhesion phase), disks were transferred into a new 24-well plate and submerged in 1 ml of Yeast Nitrogen Base with 50 mmol l⁻¹ Dextrose (YNBD) medium with 10 % of FBS and incubated at 37 °C for 24 h at 90 rpm (biofilm growth phase). Mature biofilms were then treated with different concentrations of AC7 BS in YNBD + 10 % FBS (ranging from 0.06 to 3 mg ml⁻¹) and incubated for an additional 24 h at 37 °C in static conditions. As controls, mature biofilms were submerged in 1 ml YNBD + 10 % FBS. The antifungal activity of AC7 BS was evaluated by the {2,3-bis (2-methoxy-4-nitro-5-sulfophenyl)-5-[(phenylamino) carbonyl]-2H-tetrazolium hydroxide} (XTT) (Sigma-Aldrich) colorimetric assay. Disks were transferred into new plates and submerged in 1 ml of PBS containing 12.5 µl of XTT solution (1 mg ml⁻¹) and 1 µl of 1 mmol l⁻¹ menadione solution (Sigma-Aldrich). Blank disks (disks without biofilm), submerged in the XTT/menadione mixture were also prepared. Plates were covered with an aluminum foil and incubated at 37 °C for 5 h at 90 rpm. Finally, 150 µl were collected from each well and transferred to a 96-well plate for OD₄₉₀ measurement using an Ultramark microplate imaging system (Bio-Rad Laboratories Srl, Segrate MI, Italy). The data were normalised with respect to the value of blanks (background). All assays were carried out in triplicate.

267 Anti-adhesion and anti-biofilm assays against
268 *C. albicans* strains

269 *Co-incubation assays*

270 Five hundred microliters of *C. albicans* suspensions
271 (2 × 10⁷ CFU ml⁻¹) in PBS + 20 % FBS, were
272 added to each well of a 24-well plates (Greiner bio-
273 one) containing a silicone disk together with either
274 500 µl of 2 × AC7 BS solutions (1, 2, 4 and
275 6 mg ml⁻¹) (test groups) or PBS (control group).
276 After 1.5 h of incubation (*C. albicans* adhesion
277 phase), the disks were transferred into a new plate
278 and placed in either 1 ml of YNBD + 10 % FBS with
279 0 mg ml⁻¹ (control group) or 0.5, 1, 2, 3 mg ml⁻¹
280 AC7 BS (test groups) and incubated for 24 h at 37 °C

at 90 rpm. The reduction of adherent cells and biofilm
biomass was evaluated after 1.5 and 24 h by crystal
violet (CV) staining. The supernatants were discarded
and the disks were washed three times with PBS for
removal of non-adherent cells. Afterwards, disks were
dried at 37 °C for 2 h and submerged into 1 ml of a
0.2 % CV solution for 10 min. The CV solution was
removed by washing with distilled water and the disks
air-dried. Finally, bound CV was released by adding
2 ml of 33 % acetic acid (Sigma-Aldrich) and OD₅₇₀
was measured using a Ultramark microplate imaging
system (Bio-Rad Laboratories Srl, Segrate MI, Italy).
Assays were carried out in triplicate and the experi-
ments were repeated two times.

Pre-coating assays

SEDs were dipped in 2 ml of AC7 BS solution at
concentrations ranging from 0.5 to 3 mg ml⁻¹ (test
groups) or in PBS only (control group) and incubated
at 37 °C for 24 h at 140 rpm. Disks were then placed
in 12-well plates containing two milliliters of *C.*
albicans suspensions, standardised to 1 × 10⁷
CFU ml⁻¹. After 1.5 h of incubation (adhesion
phase), the disks were transferred into 2 ml
YNBD + 10 % FBS and incubated at 37 °C with
gentle shaking for 24 h. The reduction of adherent
cells and biofilm biomass were evaluated after 1.5 and
24 h with CV staining method as indicated previously.

Furthermore, the anti-adhesion and anti-biofilm
activity of silicone disks pre-coated with AC7 BS at a
concentration of 2 mg ml⁻¹ was evaluated by means
of the viable-cell counting method. Silicone disks and
C. albicans suspensions were prepared as described
previously. After 1.5 h and 24 h of incubation, the
supernatants were discarded and the disks were
washed three times with PBS to remove non-adherent
cells. Then, the disks were inserted into 50 ml tubes
containing 10 ml PBS and subjected to four cycles of
sonication (30 s) and stirring (30 s) for cells detach-
ment. The disrupted biofilm cells were serially diluted
in PBS and 1 ml of each dilution was incorporated into
melted SDA using the pour-plate method.

Agar plates were incubated at 37 °C for 24 h and
colonies were then enumerated. Assays were carried
out in triplicate and experiments were repeated two
times. Results were expressed as mean log₁₀ CFU/
disk ± standard deviations.

327 Surface physicochemical characterisation

328 For the physicochemical characterisation, a set of six
 329 AC7 BS pre-coated and six control (PBS treated)
 330 SEDs was prepared as described previously. In order
 331 to simulate a pre-coating assay, three of the AC7 BS
 332 pre-coated and three of the control SEDs were
 333 subjected to the same procedures as described in the
 334 previous section (up to the three washing steps with
 335 PBS after 1.5 h of incubation) with the only difference
 336 that sterile YNBD + 10 % FBS was added to the
 337 disks instead of the *C. albicans* suspensions.

338 The wettability of SEDs was evaluated by water
 339 contact angle measurements using a CAM 200 KSV
 340 Instrument (Biolin Scientific), equipped with Tetha
 341 software. Static water contact angle was measured
 342 using the sessile drop I Milli-Q water drops) at room
 343 temperature. The static contact angle method was
 344 calculated as the average value from five
 345 measurements.

346 The surface chemical properties of SEDs were
 347 analysed by infrared spectroscopy in an IR Perkin-
 348 Elmer Frontier spectrophotometer equipped with an
 349 attenuated total reflectance (ATR-FTIR) device using
 350 a Germanium crystal. Spectra were recorded with a
 351 resolution of 4 cm⁻¹ and averaged over 36 scans.

352 Statistical analysis of data

353 Statistical analysis and graphs were elaborated by
 354 means of the statistical program R, 3.1.2 (R Develop-
 355 ment Core Team, <http://www.R-project.org>). Two-
 356 way ANOVA was used to compare optical densities of
 357 planktonic cells and pre-formed biofilm at different
 358 AC7 BS concentrations for the three *C. albicans*
 359 strains. Tukey's Honest Significant Difference (HSD)
 360 method was used as ANOVA post hoc test. The Welch
 361 Two Sample *t* test was performed to investigate the
 362 effect of AC7 BS on the three *Candida* stains adhesion
 363 and biofilm formation in pre-coating assays, carried
 364 out by means of the viable cell counting method.
 365 Results were considered to be statistically significant
 366 when *P* < 0.05. To estimate log₁₀ CFU/disk from
 367 colony counts, the R package dupiR was used (Co-
 368 moglio et al. 2013). This package allows estimation,
 369 from a set of counts, the population size and its
 370 uncertainty using a Bayesian approach under minimal
 371 information on the distributions; this is particularly
 372 helpful in situations where one faces with low counts.

Results

Critical micellar concentration and stability study
 of AC7 BS

Critical micellar concentration (CMC) was evaluated
 for the AC7 BS crude extract. An AC7 BS solution at a
 concentration of 0.5 mg ml⁻¹ reduced the surface
 tension of alkaline distilled water from 72.4 to 31.4
 mN m⁻¹ (Fig. 1). Serial dilutions of this solution
 showed a gradual increase of surface tension up to
 38.2 mN m⁻¹ at the concentration of 62.5 µg ml⁻¹.
 Then, surface tension rapidly increased to
 54.9 mN m⁻¹ at the concentration of 7.8 µg ml⁻¹.
 The CMC value for AC7 BS was 31.9 µg ml⁻¹.

Studies on the pH stability of AC7 BS, carried out at
 0.5, 1.0 and 2.0 mg ml⁻¹, demonstrated that it was
 stable over a wide pH range (Table 1). At pH ranging
 from 6 to 11, the surface tension was preserved
 without large deviations at all of the three concentra-
 tions tested. In particular, the highest surface activity
 of AC7 BS solutions at 0.5, 1.0 and 2.0 mg ml⁻¹ was
 found at pH 6.0 with values of 28.45, 28.53 and
 29.26 mN m⁻¹, respectively. At pH 11.0 the values
 were 30.76, 30.91 and 30.92 mN m⁻¹. At pH ≤ 5, the
 surface tension of the three AC7BS solutions
 increased and reached, at pH 3, values of 49.01,
 40.64 and 37.20 mN m⁻¹. The mean emulsification
 index at 24 h (E₂₄) of AC7 BS solutions was not
 altered at pH from 7 to 11 (about 60 % at all three
 concentrations tested), but it was absent when the pH

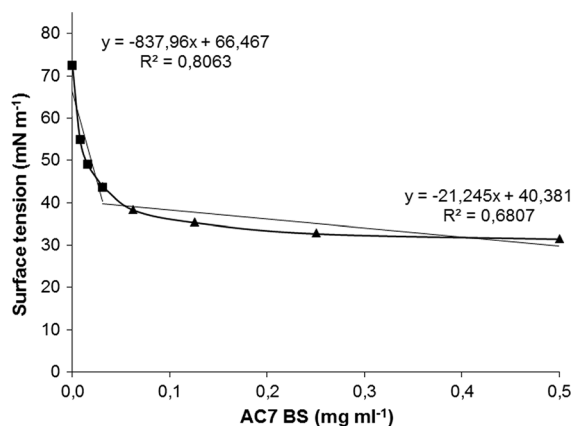


Fig. 1 A plot of surface tension as a function of concentration of AC7 BS after purification. Standard deviation was ranging between ±0.3 mN m⁻¹

Author Proof

Table 1 Surface tension and emulsification index at 24 h (E_{24}) of AC7 BS solutions as a function of pH

pH	0.5 mg ml ⁻¹			1 mg ml ⁻¹			2 mg ml ⁻¹		
	Surface tension (mN m ⁻¹)		E_{24h} (%)	Surface tension (mN m ⁻¹)		E_{24h} (%)	Surface tension (mN m ⁻¹)		E_{24h} (%)
	Mean	SD ^a		Mean	SD		Mean	SD	
3.0	49.01	0.35	0	40.64	0.17	0	37.20	0.13	0
4.0	49.40	0.29	0	36.54	0.25	0	35.42	0.08	0
5.0	37.53	0.39	0	31.32	0.17	0	30.74	0.28	0
6.0	28.45	0.10	0	28.53	0.36	0	29.26	0.43	0
7.0	30.50	0.17	60.5	30.49	0.22	60	30.36	0.17	60
8.0	30.95	0.18	60.5	30.45	0.17	60	30.64	0.06	60
9.0	30.96	0.14	60.5	30.47	0.30	60	30.84	0.44	60
10.0	31.13	0.22	60.5	30.82	0.27	60	30.62	0.31	60
11.0	30.76	0.32	60.5	30.91	0.30	60	30.92	0.14	60

Surface tension of alkaline distilled water was 72.4 mN m⁻¹

^a SD standard deviation

402 was reduced. At pH 7 (the condition used in the anti-
403 adhesion and anti-biofilm assays reported here), AC7
404 BS solutions showed an E_{24} of about 60 % and a mean
405 surface tension value of 30.45 mN m⁻¹.

406 The studies on the effect of heat/cold treatment on
407 AC7 BS solutions at 0.5, 1.0 and 2.0 mg ml⁻¹
408 demonstrated no evident changes in surface tension
409 and E_{24} . In particular, the treatment at 100 °C for 1 h,
410 at 121 °C for 15 min and at -80 °C for 24 h did not
411 alter the ability of AC7 BS solutions to decrease water
412 surface tension and its emulsification property; more-
413 over, the emulsions remained indefinitely stable.

414 Chemical characterisation of AC7 BS

415 The positive ESI-MS analysis of the crude extract
416 showed the presence of homologues of two lipopep-
417 tide families, surfactin and fengycin, respectively
418 (Fig. 2). The surfactin family member was composed
419 mainly of C13, C14 and C15 surfactin homologues,
420 whose structures were confirmed by the product ion
421 spectra of the sodiated molecules $[M + Na]^+$ at m/z
422 1030, 1044 and 1058. The fengycin family member
423 was composed of two main fengycin isoforms corre-
424 sponding to C17 fengycin A and C17 fengycin B,
425 whose structures were confirmed by the product ion
426 spectra of the protonated molecules $[M + H]^+$ at m/z
427 1478 and 1506, respectively. The relative amount of
428 the two families in the crude extract was about 98 %
429 surfactin and 2 % fengycin.

Antifungal susceptibility testing against *Candida* 430
albicans planktonic cells and biofilms 431

432 AC7 BS susceptibility testing was carried out on *C.* 432
albicans strains 40, 42 and IHEM 2894 planktonic 433
cells and pre-formed biofilms by means of EUCAST 434
and XTT methods, respectively. Optical densities at 435
450 nm and at 490 nm versus the biosurfactant 436
concentration are shown in Fig. 3. Two-way ANOVA 437
analysis indicated that both OD₄₅₀ and OD₄₉₀ were not 438
significantly associated with biosurfactant concentra- 439
tions, showing that no antifungal activity against 440
planktonic cells or biofilms was detected for any of the 441
strains. For biofilm formation, OD₄₉₀ was significantly 442
different among the three strains ($P = 0.006371$). 443
Tukey's HSD post hoc test showed that OD₄₉₀ was 444
significantly higher for *C. albicans* IHEM 2894 445
suggesting that this strain is a stronger biofilm 446
producer. 447

Anti-adhesion and anti-biofilm activity of AC7 BS 448
against *Candida albicans* strains 449

450 The anti-adhesion and anti-biofilm activity of AC7 BS 450
concentrations ranging from 0.5 to 3 mg ml⁻¹ in co- 451
incubation and in pre-coating conditions were evalu- 452
ated by the CV method, which stains total biofilm 453
biomass (cells and extracellular matrix). Figure 4 454
shows how uncoated and AC7 BS coated SEDs 455
appeared after treatment with CV. On uncoated SEDs, 456

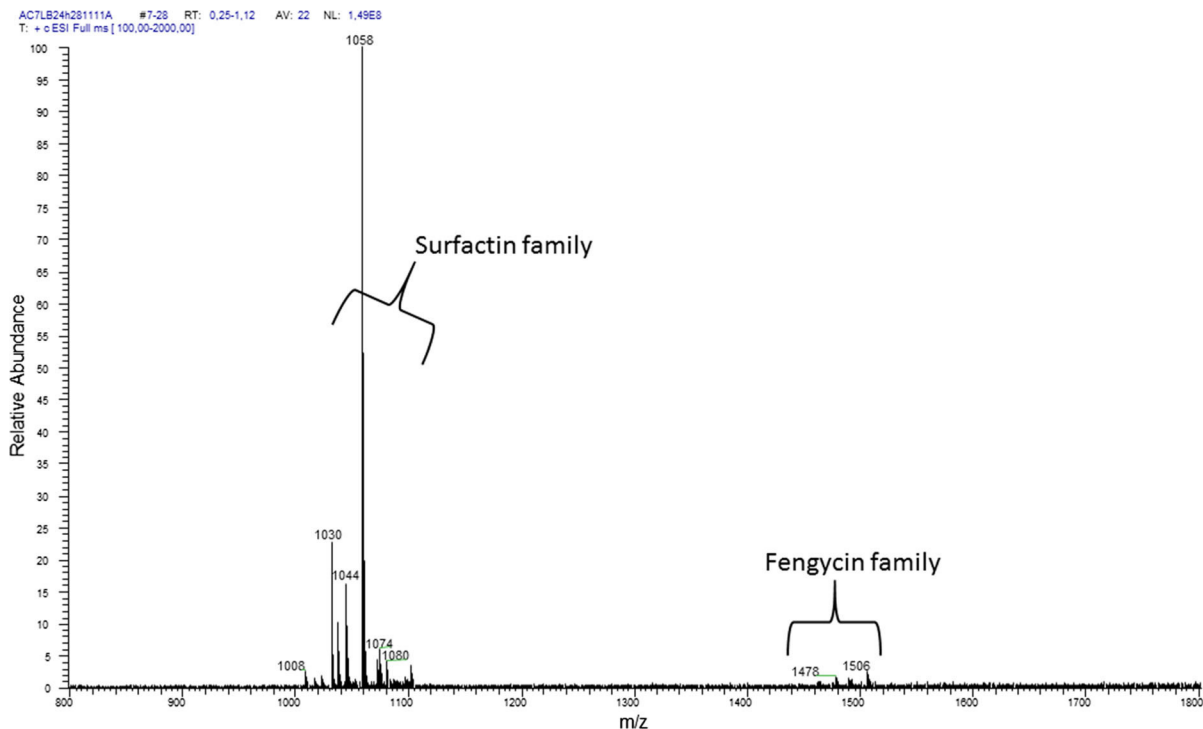


Fig. 2 (+) ESI-MS analysis (direct infusion) of lipopeptides produced by *B. subtilis* AC7. Two clusters of peaks revealed two sets of homologue molecules. The first set evidenced four main

signals corresponding to the $[M + Na]^+$ of surfactin family. The second set evidenced two main signals corresponding to the protonated molecules of fengycin family

457 CV is uniformly distributed on the surface whereas on
 458 pre-coated SEDs, the violet colour intensity and
 459 coverage area decrease with the increase of AC7 BS
 460 concentration with a maximum reduction observed at
 461 2 mg ml^{-1} , both at 1.5 and 24 h incubation. To
 462 quantify the CV staining, the disks were submerged in
 463 acetic acid, and the absorbance of the eluted stain
 464 measured. Figure 5 shows the OD_{570} as a function of
 465 the biosurfactant concentration.

466 In the co-incubation experiment, the adhesion and
 467 biofilm formation of the three *C. albicans* strains to
 468 SEDs (as measured by OD_{570}) were progressively
 469 reduced as a function of biosurfactant concentration,
 470 with a minimum reached at a concentration range
 471 between 1 and 2 mg ml^{-1} at time 1.5 h, and at
 472 concentration of 2 mg ml^{-1} at time 24 h (Fig. 5a, c).
 473 At the highest concentration (3 mg ml^{-1}), *C. albicans*
 474 adhesion and biofilm formation slightly increased.


475 Percentages of reduction of OD_{570} are reported in
 476 Table 2. In particular, the reduction at 2 mg ml^{-1}
 477 ranged (among the three strains) between 67 and 69 %
 478 at 1.5 h, and between 56 and 57 % at 24 h. Two-way

ANOVA showed that at time 1.5 h adhesion was
 significantly dependent on biosurfactant concentration
 (but not on the strain) while at time 24 h biofilm
 formation was significantly dependent on concentra-
 tion and on the strain. In particular, Tukey's HSD test
 revealed a significant reduction (both at time 1.5 h and
 at time 24 h) with a *P* value adjusted for multiple
 comparison of $<10^{-9}$.

In the pre-coating assay, the adhesion and biofilm
 formation of the three *C. albicans* strains to SEDs were
 progressively reduced as a function of biosurfactant
 concentration, with a minimum reached at the concentra-
 tion of 2 mg ml^{-1} both at 1.5 and 24 h incubation
 (Fig. 5b, d). As previously observed, at the highest
 concentration (3 mg ml^{-1}), adhesion and biofilm
 formation slightly increased. Percentages of reduction
 of OD_{570} are reported in Table 2. In particular,
 at 2 mg ml^{-1} the mean reduction ranged (among the
 three strains) between 59 and 63 % at 1.5 h, and
 between 47 and 50 % at 24 h. Two-way ANOVA
 showed that at 1.5 h adhesion was significantly
 dependent on AC7 BS concentration and also

479
 480
 481
 482
 483
 484
 485
 486
 487
 488
 489
 490
 491
 492
 493
 494
 495
 496
 497
 498
 499
 500

Fig. 3 Antifungal susceptibility testing against *C. albicans* planktonic cells and biofilms. AC7 BS activity at 24 h on **a** *C. albicans* 40, *C. albicans* 42 and *C. albicans* IHEM 2894 planktonic cells and **b** pre-formed biofilm, measured by OD₄₅₀ and OD₄₉₀, respectively. For each condition (concentration and strain) minimum, maximum median and interquartile range are illustrated using a box plot

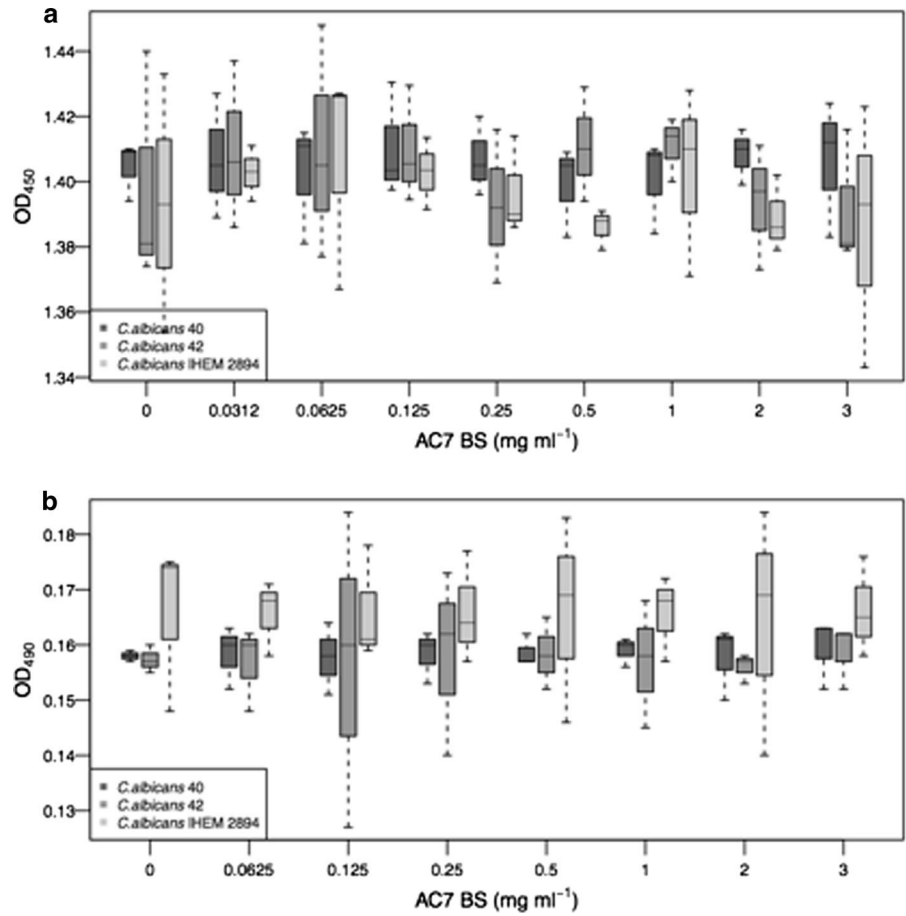

501 on the strain while at 24 h biofilm formation was
 502 significantly dependent on concentration (but not on
 503 the strain). In particular, Tukey’s HSD test revealed a
 504 significant reduction (both at time 1.5 h and at time
 505 24 h) with a *P* value adjusted for multiple comparison
 506 of $<10^{-9}$.

507 The effect of SEDs pre-coating with an AC7 BS
 508 concentration of 2 mg ml⁻¹ was further investigated
 509 by the viable cell counting method. Table 3 sum-
 510 marises the results obtained for the three *C. albicans*
 511 strains expressed as means and standard deviations for
 512 log₁₀ CFU/disk. In addition, the results of the Welch
 513 Two Sample t-test comparing AC7 BS treated and
 514 control samples are reported as *P* values and 95 %
 515 confidence intervals for the differences. The final
 516 column of Table 3 indicates the percentages of
 517 inhibition calculated as $(1-10^{\mu}) \times 100$, where μ is
 518 the difference in log₁₀ CFU/disk of AC7 BS treated
 519 and control samples. Fungal adhesion and biofilm
 520 formation on treated disks was significantly lower (at

both incubation times) than on untreated disks. The
 521 difference was more evident at time 1.5 h. It should be
 522 noted that, at time 1.5 h, fungal counts were very low
 523 compared to 24 h as *C. albicans* stains are in the initial
 524 phase of adhesion. With respect to controls, the
 525 adhesion of the three fungal stains to SEDs treated
 526 with 2 mg ml⁻¹ AC7 BS was significantly reduced in
 527 a range of 57.7–62.0 % at 1.5 h and biofilm formation
 528 was significantly inhibited in a range of 45.9–47.6 %
 529 after 24 h of incubation (*P* values in Table 3). Two-
 530 ways ANOVA confirmed that *C. albicans* viable
 531 counts were significantly dependent on the disk
 532 treatment (untreated or AC7 BS pre-coated) and on
 533 incubation time ($P < 10^{-15}$).
 534

Surface physicochemical characterisation 535

The static contact angle measurements showed that the
 536 PBS-treated SEDs, as well as the PBS-treated SEDs
 537 further incubated for 1.5 h in YNBD + 10 % FBS
 538

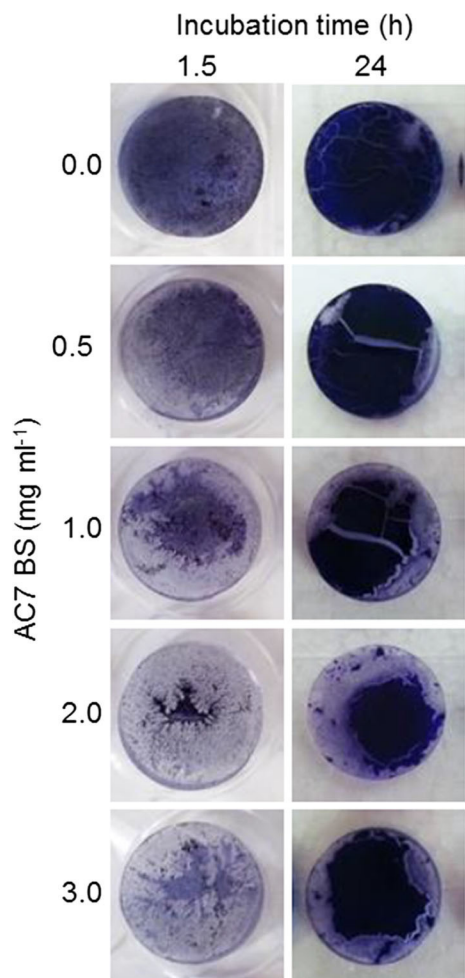


Fig. 4 CV stained SEDs, pre-coated with different concentrations of AC7 BS, after *C. albicans* IHEM 2894 adhesion (1.5 h) and biofilm formation (24 h)

539 (control SEDs of the simulated pre-coating assay),
 540 were hydrophobic ($110.6^\circ \pm 3.0^\circ$ and $112.0^\circ \pm 0.6^\circ$,
 541 respectively). AC7 BS pre-coated SEDs, as well as
 542 AC7 BS pre-coated SEDs further incubated for 1.5 h
 543 in YNBD + 10 % FBS (treated SEDs of the simulated
 544 pre-coating assay), were hydrophobic, although they
 545 showed a reduced average static contact angle com-
 546 pared to their respective control samples ($94.4^\circ \pm$
 547 10.0° and $103.8^\circ \pm 15.0^\circ$, respectively). The enhanced
 548 surface wettability was a consequence of AC7 BS
 549 surface adsorption. The wide standard deviation of the
 550 contact angle value of AC7 BS treated samples
 551 compared to the respective control samples suggested
 552 that surface coating by physical adsorption was
 553 uneven.

The FTIR-ATR spectra of each analysed SED 554
 showed the characteristic bands at $830\text{--}1110\text{ cm}^{-1}$ 555
 due to Si–O–Si stretching, at 1259.4 cm^{-1} due to CH_3 556
 symmetric stretching of $\text{Si}\backslash\text{CH}_3$, at 1412.4 cm^{-1} due 557
 to CH_3 asymmetric stretching of Si-CH₃, and at 558
 2962.8 cm^{-1} due to C–H stretching. AC7 BS physical 559
 absorption onto silicone disks did not alter the FTIR- 560
 ATR spectra suggesting that the surface amount of 561
 AC7 BS was below the detection limit of the FTIR- 562
 ATR technique. 563

Discussion 564

Candida albicans is one of the most important 565
 nosocomial pathogens frequently involved in 566
 implanted device-associated infection (Horn et al. 567
 2009) and represents a serious public health problem 568
 with important medical and economic consequences 569
 (Almirante et al. 2005; Lai et al. 2012). *C. albicans* 570
 biofilm formation is a complex, multicellular process 571
 in which adhesion of cells to materials or host cells is a 572
 primary prerequisite (Ramage et al. 2005). There is, 573
 therefore, a need for biomaterials with antimicrobial- 574
 coated surfaces for the inhibition of the microbial 575
 adhesion and the eradication of biofilms. The main 576
 drawbacks of antimicrobial coatings arise from time 577
 limited effectiveness and potential toxicity towards 578
 human cells (de Sainte 2009; Hegstad et al. 2010). In 579
 this context, biosurfactants have recently emerged as a 580
 new generation of anti-adhesive and antimicrobial 581
 agents with enhanced biocompatibility and potential 582
 commercial application in pharmaceutical and 583
 biomedical fields (Cameotra and Makkar 2004; Frac- 584
 chia et al. 2015). Among biosurfactants, lipopeptides 585
 form the most widely reported class with antimicro- 586
 bial/antiadhesive activities due to their ability to 587
 disrupt phospholipid membranes and to affect cell- 588
 to-surface interactions by decreasing hydrophobicity 589
 and, thus, interfering with cell deposition processes 590
 and microbial adhesion (Rodrigues et al. 2006b). 591

Previous research about the activity of biosurfac- 592
 tants from endophytes and from a *Lactobacillus brevis* 593
 isolate against *C. albicans* biofilm formation reported 594
 significant reductions in biofilm cell number and 595
 biomass on polystyrene, denture resin and silicone 596
 elastomer (Fracchia et al. 2010; Cochis et al. 2012; 597
 Ceresa et al. 2015). In the present study, the activity of 598
 AC7 BS was investigated on two clinically relevant 599

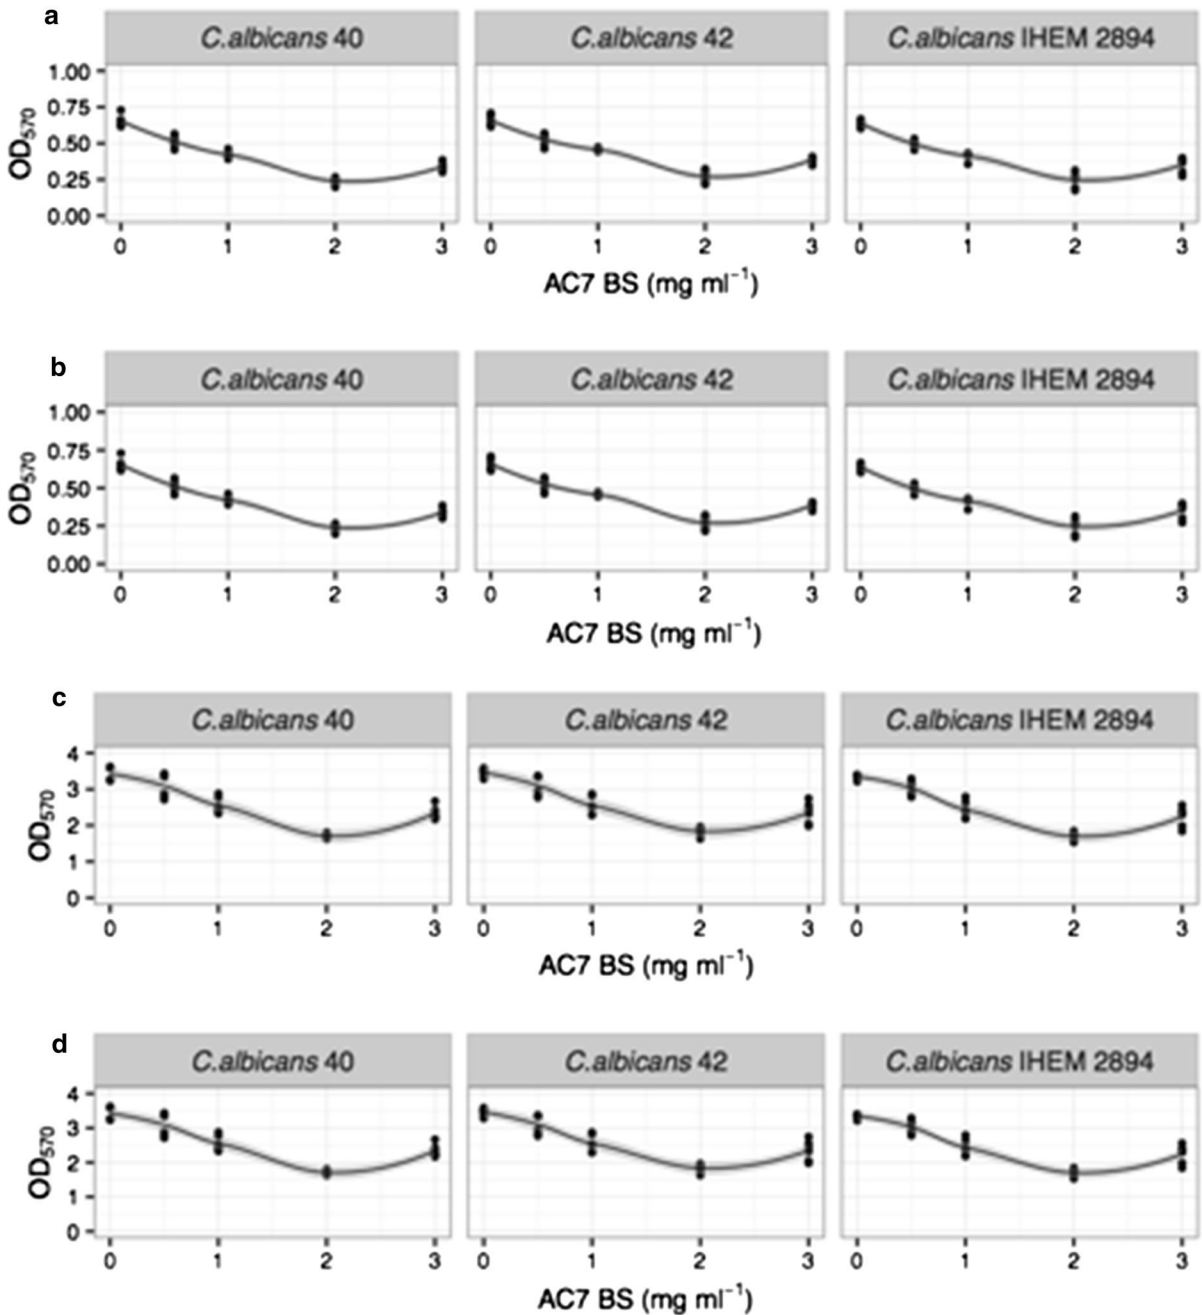


Fig. 5 AC7 BS activity against *C. albicans* adhesion and biofilm formation evaluated by the CV method. Inhibition of *C. albicans* 40, *C. albicans* 42 and *C. albicans* IHEM 2894 adhesion and biofilm formation on silicone disks by different concentrations of AC7 BS at 1.5 h, in co-incubation (a) and in pre-coating assays (b) and at 24 h, in co-incubation (c) and in

pre-coating assays (d). The inhibition of adhesion and biofilm formation is evaluated by means of the CV method and measured by OD₅₇₀. The different scales on the y-axes reflect the progression in biofilm formation with time. Each scatterplot includes a Loess curve (*local regression curve*) and a Loess confidence region (95 %)

600 wild strains of *C. albicans* and on a culture collection
601 strain. The experiments were carried out on industrially
602 produced medical-grade silicone disks, during the

603 initial phases of biofilm formation and a number of
604 different complementary methods (fungal biomass
605 staining, viable cell counting, and surface

Author Proof

Table 2 Percentages of inhibition of the *Candida albicans* strains adhesion (1.5 h) and biofilm formation (24 h)

Experimental condition	Strain	Time (h)							
		1.5				24			
		AC7 BS concentration (mg ml ⁻¹)							
		0.5	1	2	3	0.5	1	2	3
Co-incubation	<i>C. albicans</i> 40	35	63	69	51	26	47	57	49
	<i>C. albicans</i> 42	32	63	67	53	23	40	55	50
	<i>C. albicans</i> IHEM 2894	32	62	68	51	27	45	57	55
Pre-coating	<i>C. albicans</i> 40	22	36	63	48	10	26	50	32
	<i>C. albicans</i> 42	20	31	59	41	10	26	47	32
	<i>C. albicans</i> IHEM 2894	22	35	61	45	10	27	49	33

Table 3 AC7 BS inhibition of *Candida albicans* adhesion and biofilm formation in pre-coating assays

Time (h)	Strain	Control (C)		AC7 BS		95 % confidence interval (C-AC7 BS)	P value	Inhibition measures	
		Mean	SD ^a	Mean	SD			μ ^b	Percentage of inhibition (%) ^c
1.5	<i>C. albicans</i> 40	6.66	0.0489	6.24	0.0534	(0.371, 0.471)	3.76 × 10 ⁻¹²	-0.42	62.0
	<i>C. albicans</i> 42	6.66	0.0693	6.29	0.1130	(0.278, 0.469)	1.07 × 10 ⁻⁶	-0.37	57.7
	<i>C. albicans</i> IHEM 2894	6.67	0.0595	5.26	0.0757	(0.333, 0.470)	2.19 × 10 ⁻⁹	-0.4	60.3
24	<i>C. albicans</i> 40	7.63	0.0455	7.35	0.0918	(0.188, 0.384)	1.99 × 10 ⁻⁴	-0.29	48.3
	<i>C. albicans</i> 42	7.63	0.0408	7.36	0.0601	(0.206, 0.328)	1.36 × 10 ⁻⁶	-0.27	45.9
	<i>C. albicans</i> IHEM 2894	7.63	0.0508	7.35	0.0384	(0.222, 0.339)	1.45 × 10 ⁻⁶	-0.28	47.6

The table represents the mean *C. albicans* concentrations expressed as Log₁₀ CFU/disk (as calculated by the R package dupiR) recovered on silicone disks, 95 % confidence interval, P values and inhibition measures

^a SD standard deviation

^b μ = (log₁₀ CFU/disk_{AC7 BS} - log₁₀ CFU/disk_{Control})

^c Percentage of inhibition = (1 - 10^μ) × 100

606 physicochemical characterisation) were used, to
607 address the underlying mechanisms.

608 Chemical analysis of the AC7 BS crude extract
609 revealed the presence of surfactin and fengycin,
610 similar to other lipopeptide biosurfactants (Joshi
611 et al. 2008; Rivardo et al. 2009; Kim et al. 2010;
612 Pecci et al. 2010). Surface tension, CMC and emul-
613 sification capacity of AC7 BS were comparable to
614 those observed for other lipopeptide biosurfactants
615 (Lee et al. 2006; Nitschke and Pastore 2006). More-
616 over, AC7 BS showed a high stability to heat/cold
617 treatments and over a wide range of pH. In particular,
618 surface tension remained stable between pH 6 and 11,
619 with the maximum activity observed at pH 6. Similar

620 results were described by Kim et al. (1997) for the
621 lipopeptide biosurfactant from *B. subtilis* C9; by
622 Ghojavand et al. (2008) for the biosurfactant produced
623 by *B. subtilis* PTCC 1696; and by Rivardo et al. (2009)
624 for the lipopeptides V9T14 and V19T21. On the
625 contrary, surface tension and emulsification activity of
626 AC7 BS were affected by low pH values due to
627 biosurfactant precipitation in acidic conditions, as
628 reported for other biosurfactants (Rivardo et al. 2009;
629 Amani et al. 2010; Kanna et al. 2014; Elazzazy et al.
630 2015).

631 The efficacy of AC7BS to inhibit *C. albicans* 40, *C.*
632 *albicans* 42 and *C. albicans* IHEM 2894 biofilm
633 formation on SEDs was evaluated in co-incubation

634 experiments and after its absorption on the silicone
635 surface, in order to imitate a functional coating. The
636 assays were performed in combination with a pro-
637 teinaceous solution, i.e. FBS, to mimic blood contact
638 upon the silicone surface during clinical use. More-
639 over, FBS is known to promote the morphogenic
640 switching between yeast and filamentous states, an
641 important step for biofilm formation by *C. albicans*
642 (Chandra et al. 2008), that plays a significant role in
643 fungal infection (Thompson et al. 2011; Mayer et al.
644 2013). These stringent conditions were intended to
645 evaluate the activity of the biosurfactant in the
646 presence of a solution that stimulates the production
647 of biofilm.

648 AC7 BS treatments resulted in a significant reduc-
649 tion of the total adherent cells and biofilm biomass
650 compared to controls for all three *C. albicans* strains,
651 as evaluated by the CV method. The anti-adhesive and
652 anti-biofilm activity of AC7 BS was concentration-
653 dependent, with a maximum activity observed at about
654 2 mg ml⁻¹, both in the co-incubation and pre-coating
655 conditions. The effect of SEDs pre-coating with this
656 concentration of biosurfactant was, thus, further
657 investigated by the viable cell counting method. Cell
658 adhesion and biofilm formation were significantly
659 altered by AC7 BS treatment in terms of difference in
660 the number of log₁₀ CFU/disk. Notably, in pre-coating
661 assays, the percentages of reduction were almost
662 similar for the CV and viable cell counting biofilm
663 quantification assays (about 60 % reduction of adhe-
664 sion and 50 % reduction of biofilm formation for all
665 the three stains). In general, the highest performance
666 of AC7 BS was observed during the *C. albicans*
667 adhesion phase, whereas during the biofilm formation
668 phase, the inhibition was lower but still significant.

669 Research into the activity of lipopeptides against *C.*
670 *albicans* biofilm on silicone is scarce, as most
671 experiments have been conducted on polystyrene.
672 Janek et al. (2012) visually demonstrated that the
673 pretreatment of silicone urethral catheters with pseud-
674 ofactin II, a cyclic lipopeptide, and the inclusion of the
675 biosurfactant in the growth medium caused an
676 efficient reduction of *C. albicans* biofilm growth.
677 The same authors demonstrated that the pre-treatment
678 of polystyrene with pseudofactin II strongly inhibited
679 *C. albicans* adhesion (>90 %), whereas the post-
680 adhesion treatment dislodged biofilms grown on
681 untreated surfaces to a lower extent (29–39 %).
682 Rautela et al. (2014) evaluated the influence of

683 lipopeptides from *Bacillus amyloliquefaciens* strain
684 AR2 on *C. albicans* biofilm grown in polystyrene
685 plates. Biosurfactant exhibited concentration-depen-
686 dent fungal growth inhibition and fungicidal activity.
687 Moreover, when added to the growth media, biosur-
688 factant inhibited *C. albicans* biofilm formation in a
689 range of 46–100 % (depending on the concentration
690 and on *Candida* strains) and, less efficiently, dislodged
691 preformed biofilm from polystyrene plates. Very
692 recently, Biniarz et al. (2015) demonstrated that the
693 lipopeptide biosurfactants pseudofactin and surfactin
694 were able to limit fungal adhesion to polystyrene both
695 in co-incubation and in pre-coating conditions.

696 Surface wettability measurements showed that
697 AC7 BS coating by physical adsorption was success-
698 ful, as the average value of the static contact angle
699 decreased compared to control silicone disks. How-
700 ever, the wide standard deviation of the average
701 contact angle of AC7 BS coated disks suggested that
702 the biosurfactant was unevenly distributed on the
703 sample surface. This may explain why lower percent-
704 ages of inhibition of *C. albicans* adhesion and biofilm
705 formation were observed in pre-coating assays rather
706 than in co-incubation. Alternative coating methods are
707 being investigated include plasma pre-treatment of the
708 silicone disk surfaces (Ferreira et al. 2013) and AC7
709 BS physical adsorption and/or chemical grafting.

710 Finally, no antifungal activity towards *C. albicans*
711 40, *C. albicans* 42 and *C. albicans* IHEM 2894
712 planktonic cells and pre-formed biofilms was observed
713 at concentrations up to 3 mg ml⁻¹, suggesting that
714 AC7 BS inhibited pathogen adhesion without affect-
715 ing cell growth. Similarly, biosurfactants from *L.*
716 *brevis* CV8LAC (Fracchia et al. 2010) and from
717 *Bacillus licheniformis* V9T14 (Rivardo et al. 2011)
718 were reported to have anti-biofilm but not antimicro-
719 bial activity.

720 Our results indicate that AC7 BS can be used as a
721 coating agent to reduce efficiently *C. albicans* adhe-
722 sion and biofilm formation on medical device mate-
723 rials. To our knowledge, this is the first time that the
724 ability of lipopeptides to limit microbial adhesion on
725 silicone has been demonstrated at physiological con-
726 ditions and in the presence of FBS. However, further
727 investigations are in progress to develop coating
728 methodologies that will allow an even and stable dis-
729 tribution of the biosurfactant on the surface. In
730 conclusion, we suggest that biosurfactant AC7, thanks
731 to its anti-adhesive properties, could represent a

732 potential candidate to effectively limit colonisation of
733 medical devices and prevent *C. albicans* infections.

734 **Acknowledgments** This work was partially funded by
735 Regione Piemonte Grant POR-FESR Asse I—AGROBIOCAT
736 Project.

737 **Compliance with ethical standards**

738 **Conflict of interest** The authors declare that they have no
739 conflict of interest.

740 **References**

741 Almirante B, Rodriguez D, Park BJ et al (2005) Epidemiology
742 and predictors of mortality in cases of *Candida* blood-
743 stream infection: results from population-based surveil-
744 lance, Barcelona, Spain, from 2002 to 2003. *J Clin*
745 *Microbiol* 43:1829–1835
746 Amani H, Sarrafzadeh MH, Haghighi M, Mehrnia MR (2010)
747 Comparative study of biosurfactant producing bacteria in
748 MEOR applications. *J Pet Sci Eng* 75:209–214
749 Banat IM, Franzetti A, Gandolfi I et al (2010) Microbial bio-
750 surfactants production, applications and future potential.
751 *Appl Microbiol Biotechnol* 87:427–444. doi:10.1007/
752 s00253-010-2589-0
753 Biniarz P, Baranowska G, Feder-Kubis J, Krasowska A (2015)
754 The lipopeptides pseudofactin II and surfactin effectively
755 decrease *Candida albicans* adhesion and hydrophobicity.
756 *Antonie Van Leeuwenhoek* 108:343–353. doi:10.1007/
757 s10482-015-0486-3
758 Busscher HJ, van Hoogmoed CG, Geertsema-Doornbusch GI,
759 van der Kuijl-Booij M, van der Mei HC (1997) *Strepto-*
760 *coccus thermophilus* and its biosurfactants inhibit adhesion
761 by *Candida* spp. on silicone rubber. *Appl Environ Micro-*
762 *biol* 63:3810–3817
763 Cameotra SS, Makkar RS (2004) Recent applications of bio-
764 surfactants as biological and immunological molecules.
765 *Curr Opin Microbiol* 7:262–266
766 Ceresa C, Tessarolo F, Caola I (2015) Inhibition of *Candida*
767 *albicans* adhesion on medical-grade silicone by a *Lacto-*
768 *bacillus*-derived biosurfactant. *J Appl Microbiol*
769 118:1116–1125. doi:10.1111/jam.12760
770 Chandra J, Mukherjee PK, Ghannoum MA (2008) In vitro
771 growth and analysis of *Candida* biofilms. *Nat Protoc*
772 3:1909–1924. doi:10.1038/nprot.2008.192
773 Cochis A, Fracchia L, Martinotti MG, Rimondini L (2012)
774 Biosurfactants prevent in vitro *Candida albicans* biofilm
775 formation on resins and silicon materials for prosthetic
776 devices. *Oral Surg Oral Med Oral Pathol Oral Radiol*
777 113:755–761. doi:10.1016/j.oooo.2011.11.004
778 Comoglio F, Fracchia L, Rinaldi M (2013) Bayesian inference
779 from count data using discrete uniform priors. *PLoS One*.
780 doi:10.1371/journal.pone.0074388
781 Crump JA, Collignon PJ (2000) Intravascular Catheter-Asso-
782 ciated Infections. *Eur J Clin Microbiol Infect Dis* 19:1–8
783 de Sainte CP (2009) Degradation of PEO in the solid state: a
784 theoretical kinetic model. *Macromolecules* 42:3469–3482

Elazzazy AM, Abdelmoneim TS, Almaghrabi OA (2015) Iso-
785 lation and characterization of biosurfactant production
786 under extreme environmental conditions by alkali-halo-
787 thermophilic bacteria from Saudi Arabia. *Saudi J Biol Sci*
788 22:466–475
789 Espinel-Ingroff A, Canton E, Martin-Mazuelos E, Pemán J
790 (2009) Pharmacotherapy of *Candida* infections with
791 echinocandins. *Clin Med Insights Ther* 1:889–897
792 Falagas ME, Makris GC (2009) Probiotic bacteria and biosur-
793 factants for nosocomial infection control: a hypothesis.
794 *J Hosp Infect* 71:301–306. doi:10.1016/j.jhin.2008.12.008
795 Fanning S, Mitchell AP (2012) Fungal biofilms. *PLoS Pathog*.
796 doi:10.1371/journal.ppat.1002585
797 Ferreira AM, Carmagnola I, Chiono V et al (2013) Surface
798 modification of poly(dimethylsiloxane) by two-step
799 plasma treatment for further grafting with chitosan–Rose
800 Bengal photosensitizer. *Surf Coat Technol* 223:92–97
801 Fracchia L, Cavallo M, Allegrone G, Martinotti MG (2010) A
802 *Lactobacillus*-derived biosurfactant inhibits biofilm for-
803 mation of human pathogenic *Candida albicans* biofilm
804 producers. In: Méndez-Vilas A (ed) Current research,
805 technology and education topics in applied microbiology
806 and microbial biotechnology. Formatex Research Center,
807 Badajoz, pp 827–837
808 Fracchia L, Banat JJ, Cavallo M et al (2015) Potential thera-
809 peutic applications of microbial surface-active compounds.
810 *AIMS Bioeng* 2:144–162
811 Franzetti A, Gandolfi I, Raimondi C et al (2012) Environmen-
812 tal fate, toxicity, characteristics and potential applications of
813 novel bioemulsifiers produced by *Variovorax paradoxus*
814 7bCT5. *Bioresour Technol* 108:245–251. doi:10.1016/j.
815 biortech.2012.01.005
816 Ghojavand H, Vahabzadeh F, Roayaei E, Shahraki AK (2008)
817 Production and properties of a biosurfactant obtained from
818 a member of the *Bacillus subtilis* group (PTCC 1696).
819 *J Colloid Interface Sci* 324:17–26. doi:10.1016/j.jcis.2008.
820 05.001
821 Goldberg SP, Baddley JW, Aaron MF, Pappas PG, Holman WL
822 (2000) Fungal infections in ventricular assist devices.
823 *ASAIO J* 46:S37–S40
824 Guery B, Arendrup M, Auzinger G et al (2009) Management of
825 invasive candidiasis and candidemia in adult non-neu-
826 tropenic intensive care unit patients: part I. Epidemiology
827 and diagnosis. *Intensive Care Med* 35:55–62. doi:10.1007/
828 s00134-008-1338-7
829 Hawser SP, Douglas LJ (1994) Biofilm formation by *Candida*
830 species on the surface of catheter materials in vitro. *Infect*
831 *Immun* 62:915–921
832 Hegstad K, Langsrud S, Lunestad BT, Scheie AA, Sunde M,
833 Yazdankhah SP (2010) Does the wide use of quaternary
834 ammonium compounds enhance the selection and spread
835 of antimicrobial resistance and thus threaten our health?
836 *Microb Drug Resist* 16:91–104. doi:10.1089/mdr.2009.
837 0120
838 Horn DL, Neofytos D, Anaissie EJ et al (2009) Epidemiology
839 and outcomes of candidemia in 2019 patients: data from the
840 prospective antifungal therapy alliance registry. *Clin Infect*
841 *Dis* 48:1695–1703. doi:10.1086/599039
842 Janek T, Lukaszewicz M, Krasowska A (2012) Antiadhesive
843 activity of the biosurfactant pseudofactin II secreted by the
844

Author Proof

- 845 Arctic bacterium *Pseudomonas fluorescens* BD5. BMC
846 Microbiol. doi:10.1186/1471-2180-12-24
- 847 Joshi S, Bharucha C, Desai A (2008) Production of biosurfactant
848 and antifungal compound by fermented food isolate
849 *Bacillus subtilis* 20B. Bioresour Technol 99:4603–4608
- 850 Kanna R, Gummadi SN, Kumar GS (2014) Production and
851 characterization of biosurfactant by *Pseudomonas putida*
852 MTCC 2467. J Biol Sci 14:436–445
- 853 Karchmer AV (2000) Infections of prosthetic valves and
854 intravascular devices. In: Mandell G, Bennett JE, Dolin R
855 (eds) Principles and practice of infectious diseases. Churchill Livingstone, Elsevier, Philadelphia, pp 903–917
- 856 Kim HS, Yoon BD, Lee CH et al (1997) Production and prop-
857 erties of a lipopeptide biosurfactant from *Bacillus subtilis*
858 C9. J Ferment Bioeng 84:41–46. doi:10.1016/S0922-
859 338X(97)82784-5
- 860 Kim PI, Ryu J, Kim YH, Chi YT (2010) Production of biosur-
861 factant lipopeptides Iturin A, fengycin and surfactin A from
862 *Bacillus subtilis* CMB32 for control of *Colletotrichum*
863 *gloeosporioides*. J Microbiol Biotechnol 20:138–145
- 864 Kojic EM, Darouiche RO (2004) *Candida* infections on medical
865 devices. Clin Microbiol Rev 17:255–267. doi:10.1128/
866 CMR.17.2.255-267.2004
- 867 Kullberg BJ, Verweij PE, Akova M et al (2011) European expert
868 opinion on the management of invasive candidiasis in
869 adults. Clin Microbiol Infect 17:1–12. doi:10.1111/j.1469-
870 0691.2011.03615.x
- 871 Lai CC, Wang CY, Liu WL, Huang YT, Hsueh PR (2012) Time
872 to positivity of blood cultures of different *Candida* species
873 causing fungaemia. J Med Microbiol 61:701–704. doi:10.
874 1099/jmm.0.038166-0
- 875 Lazzell AL, Chaturvedi AK, Pierce CG, Prasad D, Uppuluri P,
876 Lopez-Ribot JL (2009) Treatment and prevention of *Cand-*
877 *ida albicans* biofilms with caspofungin in a novel central
878 venous catheter murine model of candidiasis. J Antimicrob
879 Chemother 64:567–570. doi:10.1093/jac/dkp242
- 880 Lee SC, Yoo JS, Kim SH et al (2006) Production and charac-
881 terization of lipopeptide biosurfactant from *Bacillus sub-*
882 *tilis* A8–8. J Microbiol Biotechnol 16:716–723
- 883 Maki DG, Tambyah PA (2001) Engineering out the risk for
884 infection with urinary catheters. Emerg Infect Dis
885 7:342–347
- 886 Mayer FL, Wilson D, Hube B (2013) *Candida albicans*
887 pathogenicity mechanisms. Virulence 4:119–128. doi:10.
888 4161/viru.22913
- 889 Nitschke M, Pastore GM (2006) Production and properties of a
890 surfactant obtained from *Bacillus subtilis* grown on cassava
891 wastewater. Bioresour Technol 97:336–341
- 892 Pecci Y, Rivardo F, Martinotti MG, Allegrone GJ (2010) LC/
893 ESI-MS/MS characterisation of lipopeptide biosurfactants
894 produced by the *Bacillus licheniformis* V9T14 strain. Mass
895 Spectrom 45:772–778. doi:10.1002/jms.1767
- 896 Ramage G, Saville SP, Thomas DP, López-Ribot JL (2005)
897 *Candida* biofilms: an update. Eukaryot Cell 4:633–638
- Rautela R, Singh AK, Shukla A, Cameotra SS (2014) 899
Lipopeptides from *Bacillus* strain AR2 inhibits biofilm 900
formation by *Candida albicans*. Antonie Van Leeuwen- 901
hoek 105:809–821 902
- Rivardo F, Turner RJ, Allegrone G, Ceri H, Martinotti MG 903
(2009) Anti-adhesion activity of two biosurfactants pro- 904
duced by *Bacillus* spp. prevents biofilm formation of 905
human bacterial pathogens. Appl Microbiol Biotechnol 906
83:541–553. doi:10.1007/s00253-009-1987-7 907
- Rivardo F, Martinotti MG, Turner RJ, Ceri H (2011) Synergistic 908
effect of lipopeptide biosurfactant with antibiotics against 909
Escherichia coli CFT073 biofilm. Int J Antimicrob Aging 910
37:324–331. doi:10.1016/j.ijantimicag.2010.12.011 911
- Rodrigues LR, Teixeira JA (2010) Biomedical and therapeutic 912
applications of biosurfactants. Adv Exp Med Biol 913
672:75–87 914
- Rodrigues L, Banat IM, Teixeira J, Oliveira R (2006a) Biosur- 915
factants: potential applications in medicine. J Antimicrob 916
Chemother 57:609–618 917
- Rodrigues LR, Banat IM, van der Mei HC, Teixeira JA, Oliveira 918
R (2006b) Interference in adhesion of bacteria and yeasts 919
isolated from explanted voice prostheses to silicone rubber 920
by rhamnolipid biosurfactants. J Appl Microbiol 921
100:470–480 922
- Rodriguez-Tudela JL, Arendrup MC, Barchiesi F et al (2008) 923
EUCAST definitive document EDef 7.1: method for the 924
determination of broth dilution MICs of antifungal agents 925
for fermentative yeasts. Clin Microbiol Infect 14:398–405 926
- Ruhnke M, Rickerts V, Cornely OA et al (2011) Diagnosis and 927
therapy of *Candida* infections: joint recommendations of the 928
German speaking mycological society and the paul- 929
ehrlich-society for chemotherapy. Mycoses 54:279–310. 930
doi:10.1111/j.1439-0507.2011.02040.x 931
- Seydlová G, Svobodová J (2008) Review of surfactin chemical 932
properties and the potential biomedical applications. Cent 933
Eur J Med 3:123–133 934
- Singh P, Cameotra SS (2004) Potential applications of microbial 935
surfactants in biomedical sciences. Trends Biotechnol 936
22:142–146 937
- Singh A, Van Hamme JD, Ward OP (2007) Surfactants in 938
microbiology and biotechnology: part 2. Application 939
aspects. Biotechnol Adv 25:99–121 940
- Thompson DS, Carlisle PL, Kadosh D (2011) Coevolution of 941
morphology and virulence in *Candida* species. Eukaryot 942
Cell 10:1173–1182. doi:10.1128/EC.05085-11 943
- van de Veerdonk FL, Netea MG, Joosten LA, van der Meer 944
JWM, Kullberg BJ (2010) Novel strategies for the pre- 945
vention and treatment of *Candida* infections: the potential 946
of immunotherapy. FEMS Microbiol Rev 34:1063–1075. 947
doi:10.1111/j.1574-6976.2010.00232.x 948
- Wisplinghoff H, Bischoff T, Tallent SM, Seifert H, Wenzel RP, 949
Edmond MB (2004) Nosocomial bloodstream infections in 950
US hospitals: analysis of 24,179 cases from a prospective 951
nationwide surveillance study. Clin Infect Dis 39:309–317 952
953