

Short-time dynamics of correlated magnetic moments in superparamagnetic Cu-Co melt spun alloys exhibiting giant magnetoresistance

*Original*

Short-time dynamics of correlated magnetic moments in superparamagnetic Cu-Co melt spun alloys exhibiting giant magnetoresistance / Allia, PAOLO MARIA EUGENIO ICILIO; P., Tiberto; F., Vinai. - In: JOURNAL OF APPLIED PHYSICS. - ISSN 0021-8979. - 81:(1997), pp. 4599-4601. [10.1063/1.365175]

*Availability:*

This version is available at: 11583/2498098 since:

*Publisher:*

AIP

*Published*

DOI:10.1063/1.365175

*Terms of use:*

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

*Publisher copyright*

AIP postprint/Author's Accepted Manuscript e postprint versione editoriale/Version of Record

(Article begins on next page)

## Short-time dynamics of correlated magnetic moments in superparamagnetic Cu–Co melt spun alloys exhibiting giant magnetoresistance

P. Allia, P. Tiberto, and F. Vinai

Citation: *Journal of Applied Physics* **81**, 4599 (1997); doi: 10.1063/1.365175

View online: <http://dx.doi.org/10.1063/1.365175>

View Table of Contents: <http://scitation.aip.org/content/aip/journal/jap/81/8?ver=pdfcov>

Published by the [AIP Publishing](#)

---

### Articles you may be interested in

[Coercivity extrema in melt-spun CuCo ribbons: Effects of the magnetic moment distribution](#)

*J. Appl. Phys.* **86**, 3010 (1999); 10.1063/1.371161

[Giant magnetoresistance and remanence in granular CoCu codeposited films](#)

*J. Appl. Phys.* **83**, 7007 (1998); 10.1063/1.367808

[Giant magnetoresistance in granular CuFeNi alloys](#)

*J. Appl. Phys.* **83**, 7001 (1998); 10.1063/1.367624

[Correlation between magnetic interactions and giant magnetoresistance in melt-spun Co 10 Cu 90 granular alloys](#)

*J. Appl. Phys.* **82**, 3047 (1997); 10.1063/1.366164

[Determination of the upper limit of the magnetic moment in the magneto-resistance by using its irreversible temperature and square magnetization dependences in \(Cu-rich\)-TM melt-spun systems](#)

*J. Appl. Phys.* **81**, 4596 (1997); 10.1063/1.365174

---

The logo for the Journal of Applied Physics (AIP) is displayed in a white font against an orange background. The background features a pattern of concentric, wavy lines that resemble a cross-section of a material or a magnetic field.

## Meet The New Deputy Editors



Christian  
Brosseau



Laurie  
McNeil



Simon  
Phillpot

# Short-time dynamics of correlated magnetic moments in superparamagnetic Cu–Co melt spun alloys exhibiting giant magnetoresistance

P. Allia

*Dipartimento di Fisica Politecnico di Torino and INFM, I-10129 Torino, Italy*

P. Tiberto and F. Vinai

*IEN Galileo Ferraris and INFM, I-10125 Torino, Italy*

Evidence for correlation among superparamagnetic particles in melt-spun  $\text{Cu}_{100-x}\text{Co}_x$  systems ( $x = 5-20$ ) exhibiting a giant magnetoresistance is obtained by plotting this quantity as a function of reduced magnetization. Two ranges,  $R_\theta(H_e)$  and  $R_\phi(H_e)$ , have been recently introduced to describe the extent of correlation among angles of tilt ( $\theta$ ) and of twist ( $\phi$ ) of superparamagnetic moments precessing around a local field axis. The angle of tilt appears to be spatially correlated over a distance larger by a factor of 3 than the angle of twist. This difference is explained by analyzing the short-time dynamics of magnetic moments in superparamagnetic granular systems with long-range interactions (of dipolar and the RKKY-like type). The typical time constants characterizing the process of scattering of conduction electrons by adjacent magnetic moments (electronic time of flight, relaxation times for  $\theta$  and  $\phi$ ) are discussed in detail. An explicit expression for  $R_\phi(H)$  is obtained by considering the competition between a magnetic interaction favoring parallel (or antiparallel) alignment or adjacent moments, and thermal disturbances resulting in a continuous loss of the phase coherence. © 1997 American Institute of Physics. [S0021-8979(97)69808-4]

Granular magnetic systems, where nanometer-sized, superparamagnetic particles of a ferromagnetic metal are dispersed in a nonmagnetic metal, developed in view of their prospective applications in magnetic recording, are still attracting considerable interest from the fundamentalist's viewpoint, owing to their isotropic giant magnetoresistance (GMR), often exhibited even at room temperature.<sup>1</sup> Among these materials, the  $\text{Cu}_{100-x}\text{Co}_x$  system plays a relevant role, because it can be easily obtained in ribbon form over a wide composition range ( $0 < x \leq 20$ ) by planar flow quenching on a rotating drum, followed by proper annealing.<sup>2,3</sup> Varying the annealing conditions and/or methods<sup>2,3</sup> brings about a variety of granular structures characterized by rather different average values of the particle sizes. On the other hand, the width of the particle-size distribution appears to be affected to a lesser extent by annealing.<sup>3</sup> These results, indirectly obtained from room-temperature magnetization curves,<sup>3</sup> have been recently confirmed by independent low-temperature magnetic-susceptibility measurements.<sup>4</sup>

Plots of GMR versus reduced magnetization  $m = M/M_s$  provide compelling evidence for magnetic correlation among superparamagnetic particles. In fact, the so-called reduced GMR,  $(\Delta R/R)_{\text{red}}$  (a quantity defined in Ref. 3 and obtained by properly rescaling the GMR data) always displays a definite nonparabolic behavior when plotted against  $m$ , in disagreement with the prediction for uncorrelated magnetic particles,  $(\Delta R/R)_{\text{red}} = 1 - m^2$ . The typical flattening of actual  $(\Delta R/R)_{\text{red}}$  vs  $m$  curves with respect to a parabola (see Fig. 1) has been explained by a phenomenological theory,<sup>3</sup> providing an expression for  $(\Delta R/R)_{\text{red}}$  in systems characterized by superparamagnetic particles of magnetic moment  $\mu$ :

$$\left(\frac{\Delta R}{R}\right)_{\text{red}} = 1 - \left\{ \bar{u}^2 + (\langle u^2 \rangle - \bar{u}^2) e^{-\lambda/R_\theta(H_e)} + \left[ 1 - \bar{u}^2 - \frac{\langle u^2 \rangle - \bar{u}^2}{1 - \bar{u}^2} (1 - \bar{u}^2 e^{-\lambda/R_\theta(H_e)}) \right] e^{-\lambda/R_\phi(H_e)} \right\}, \quad (1)$$

where  $u = \cos \theta$ ,  $\bar{u} \equiv m = L(x)$ ,  $L(x)$  is the Langevin's function, and  $x = \mu H_e / k_B T$ ,  $\langle u^2 \rangle = 1 - 2L(x)/x$ ,  $\lambda$  is an (effec-

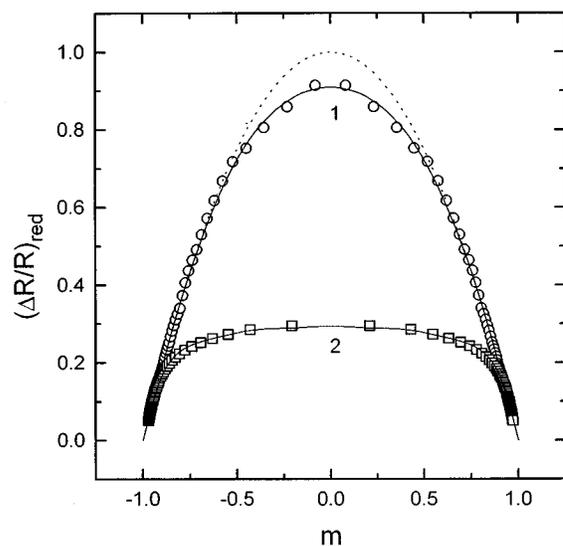


FIG. 1. Reduced GMR as a function of reduced magnetization  $m$  for  $\text{Cu}_{90}\text{Co}_{10}$  (joule-heated, electrical current density  $j = 4 \times 10^7 \text{ A/m}^2$  for 1 s; circles) and for  $\text{Cu}_{80}\text{Co}_{20}$  (joule-heated,  $j = 2 \times 10^7 \text{ A/m}^2$  for 1800 s; squares). Full lines: best fit according to Eq. (1). Dotted line: parabolic behavior.

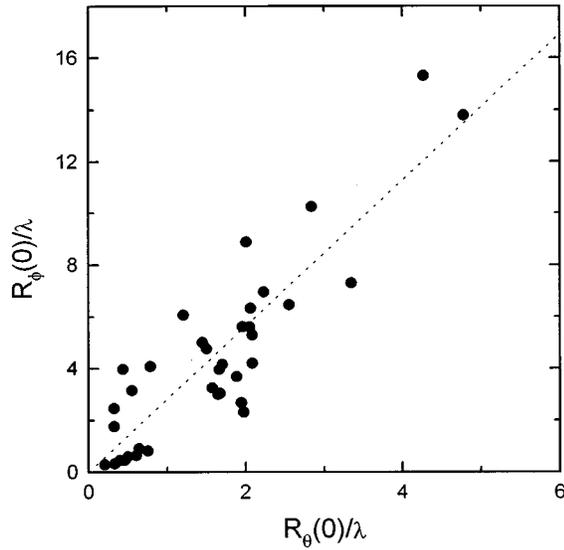


FIG. 2. Tilt-angle correlation length at zero external field,  $R_\theta(0)$  as a function of twist-angle correlation length at zero field,  $R_\phi(0)$ , for 34 alloys of the  $\text{Cu}_{100-x}\text{Co}_x$  system ( $5 \leq x \leq 20$ ) submitted to various annealing treatments.

tive) electronic mean free path.<sup>5</sup> A central role is played by the quantities  $R_\theta(H_e)$  and  $R_\phi(H_e)$ , i.e., the correlation lengths of tilt-angle and twist-angle fluctuations in the motion of magnetic moments around the local field axis, respectively. In spite of the success obtained applying Eq. (1) to fit actual  $(\Delta R/R)_{\text{red}}$  vs  $m$  curves (see Fig. 1), some aspects of this matter deserve further investigation.

First, the theory does not provide any explicit expression for  $R_\phi(H_e)$ , while  $R_\theta(H_e)$  is given by<sup>3</sup>

$$R_\theta(H) = \sqrt{\frac{\mu^2}{k_B T} \alpha L'(x)}, \quad (2)$$

where  $L'(x)$  is the first derivative of  $L(x)$  with respect to its argument, and  $\alpha = (1/3) \sum \lambda_{ik} r_{ik}^2$  contains the strength  $\lambda_{ik}$  of the coupling between particles  $i$  and  $k$ , where  $r_{ik}$  is the interparticle distance. For the sake of simplicity,  $R_\phi(H_e)$  was given in Ref. 3 the same functional dependence on  $H_e$  as  $R_\theta(H_e)$ , but without any attempt of justifying this assumption.

Second, collecting the  $R_\theta(0)/\lambda$  and  $R_\phi(0)/\lambda$  values obtained from best fit of a number of experimental GMR vs  $m$  curves, and plotting one correlation length against the other, a linear relationship is clearly found, although the data are slightly scattered [see Fig. 2, where the plotted data refer to 34 alloys of the system  $\text{Cu}_{100-x}\text{Co}_x$  ( $5 \leq x \leq 20$ ) and submitted to various annealing treatments<sup>3</sup>]. Note that the data reported here are comprehensive of the ones plotted in Fig. 16 of Ref. 3, where both scales were multiplied by a factor of  $\sqrt{3}$  with respect to the present plot; this discrepancy is, however, irrelevant to the following discussion. A ratio  $R_\theta(0)/R_\phi(0) \cong 3$  emerges from Fig. 2. Such a result has not been explained thus far.

The inadequacy of the model of independent moments can be related to two orders of reasons: First, the magnetic moments cannot be assumed as completely uncorrelated, owing to their long-range magnetic interactions; second, the

time scale of the sequential scattering of a conduction electron by two adjacent magnetic moments is much shorter than the characteristic relaxation times associated to the changes in the moments' directions by effect of random disturbances, so that the electrons are actually sensitive to the instantaneous angle between the considered moments. As a matter of fact, the time of flight of a conduction electron between adjacent scatterers may be estimated to be of the order of  $6 \times 10^{-15}$  s with a Fermi velocity of about  $10^8$  cm/s and an average intercluster distance of about  $6 \times 10^{-7}$  cm, as experimentally observed in the  $\text{Cu}_{100-x}\text{Co}_x$  system<sup>3</sup> (this is actually the distance between the borders of adjacent clusters; the average distance between centres is of the order of  $1 \times 10^{-6}$  m). On the other hand, the moments' directions in the superparamagnetic regime fluctuate in space by effect of both thermal and magnetic torques. Changes in the angle of tilt, involving changes in the local Zeeman energy, are related to the interaction between the localized moment and the thermal excitations of the lattice. Applying Néel's or Brown's models for the superparamagnetic relaxation,<sup>6</sup> and using the values  $K \approx 1 \times 10^6$  erg/cm<sup>3</sup> for the magnetic anisotropy energy,  $V \approx 7 \times 10^{-20}$  cm<sup>3</sup> for the average cluster volume, and a pre-exponential factor  $f_0 \approx 10^{10}$  s<sup>-1</sup>, a relaxation time  $\tau_1 = f_0^{-1} \exp(KV/k_B T)$  of the order of  $5 \times 10^{-10}$  s is found at room temperature. The angle of twist is more sensitive to the fluctuations in the local field acting on each localized moment, as in the case of paramagnetic resonance and relaxation. The relaxation time for the angle of twist,  $\tau_2$ , is of the order of  $(\gamma H_i)^{-1}$ , where  $\gamma$  is the gyromagnetic ratio and  $H_i$  is the rms magnetic field present on each site, arising from long-range interactions among moments, such as dipolar or RKKY-like interactions.<sup>7</sup> Using  $H_i \approx 5 \times 10^2$  Oe (a value to be justified later), one finds  $\tau_2 \approx 2 \times 10^{-10}$  s, not much smaller than  $\tau_1$ . These values should be intended as merely representative quantities. The spread in the cluster sizes may bring about significant local deviations from these average values.

An expression for  $R_\phi(H_e)$  can be obtained considering the short-time dynamics of magnetic moments. The main points of the theory follow: Let us consider a pair of magnetic moments  $(\mu_i, \mu_k)$ , initially rotating with the same phase angle around the local field axis (supposed to be the same for both moments). We admit the existence of a weak interaction of the type  $\epsilon_{ik} = -\lambda_{ik} \mu^2 \cos \theta_{ik}$ , favoring parallel (or antiparallel) alignment of moments, where  $\theta_{ik}$  is the instantaneous angle between  $\mu_i$  and  $\mu_k$  and  $|\lambda_{ik}| \approx 1/r_{ik}^3$  for both dipolar and RKKY-like interactions. If a change  $\eta_k$  in angle  $\phi_k$  suddenly occurs at  $t=0$ , angle  $\phi_i$  will relax toward the new  $\phi_k$  in order to reduce the coupling energy. However, the corresponding relaxation rate,  $\tau_{\text{rel}} = \gamma \lambda_{ik} \mu \sin \theta_i \sin \theta_k$ , where  $\theta_i, \theta_k$  are the tilt angles, is generally much smaller than  $\tau_2^{-1}$ , i.e., the rate at which the twist-angle coherence is lost. As a consequence, the relaxation process is continuously interrupted by new fluctuation events. Similar results are found considering the effect of  $z$  neighboring moments on the  $i$ th moment; a linear relation can be easily obtained between the twist-angle fluctuation  $\eta_i$  and the ones occurring at adjacent sites:

$$\eta_i = \gamma \mu \langle \sin^2 \theta \rangle \tau_2' \sum_k \lambda_{ik} \eta_k, \quad (3)$$

where  $\langle \dots \rangle$  means the expectation value,  $(\tau_2')^{-1}$  is the rate of loss of phase coherence between moment  $i$  and any of the  $z$  surrounding moments:  $\tau_2' \cong \tau_2/z$ ,  $\tau_2$  is usually referred to a single pair of adjacent moments. In the presence of an external field,  $\tau_2 \cong (\gamma H_i)^{-1}$ , with  $\mathbf{H}_i = \mathbf{H}_i + \mathbf{H}_e$ . As a consequence,

$$\eta_i \cong \frac{1}{z H_i} \mu \langle \sin^2 \theta \rangle \sum_k \lambda_{ik} \eta_k \quad (4)$$

at any time. Such a linear relation connecting fluctuations at neighboring sites allows one to write an expression for the correlation length  $R_\phi(H_e)$ :

$$R_\phi(H_e) \cong \left[ \frac{1}{z} \frac{\mu}{H_i} \frac{2L(x)}{x} \alpha \right]^{1/2}, \quad (5)$$

where  $\langle \sin^2 \theta \rangle$  has been rewritten as  $2L(x)/x$ . When  $H_e = 0$ ,  $R_\theta(0)$  and  $R_\phi(0)$  take the form

$$R_\phi(0) \cong \left[ \frac{1}{z} \frac{\mu}{H_i} \frac{2}{3} \alpha \right]^{1/2}, \quad R_\theta(0) \cong \left[ \frac{\mu^2}{k_B T} \frac{1}{3} \alpha \right]^{1/2}, \quad (6)$$

so that the ratio  $R_\theta(0)/R_\phi(0)$  is

$$\frac{R_\theta(0)}{R_\phi(0)} = \left( \frac{\mu H_i z}{k_B T} \right)^{1/2}. \quad (7)$$

Note that this ratio does not contain the parameter  $\alpha$ . The internal field  $H_i$  may be estimated (both for dipolar and RKKY-like interactions) as  $H_i \cong (2\mu^2 \sum_k 1/r_{ik}^6)^{1/2} \cong 2^{3/2} \mu/a^3$ , where  $a$  is the average interparticle distance.<sup>8</sup> Typical values of  $H_i$  for the  $\text{Co}_{100-x}\text{Cu}_x$  system are in the range  $2 \times 10^2 - 1 \times 10^3$  Oe, depending on  $\mu$  and  $a$  values. Taking values appropriate to the whole family of alloys studied ( $\mu \approx 10^{-16}$  emu,  $H_i \approx 3 \times 10^2$  Oe,  $k_B T \approx 4 \times 10^{-14}$  erg/atom,  $z \approx 25$ ), one gets  $R_\theta(0)/R_\phi(0) \approx 3$ , in excellent agreement with the experimental result. The value  $z \approx 25$  for the total number of magnetic particles effective in influencing the motion of the  $i$ th moment has been derived by comparing the values of all the parameters  $R_\theta(0)$  [obtained by fitting the  $(\Delta R/R)_{\text{red}}$  vs  $m$  curves to Eq. (1)] with the corresponding theoretical expression, which can be rewritten as  $R_\theta(0) \cong z^{1/2} [\mu^2/k_B T 1/(3a)]^{1/2} \cong z^{1/2} S$ , because  $\alpha \approx z/a$ . Using the values for  $\mu$  and  $a$  obtained from the fits of magnetization curves,<sup>3,4</sup> the quantity  $S$  is known for each alloy.

Plotting  $R_\theta(0)$  as a function of  $S$ , a linear relation of the type  $R_\theta(0) \cong 5 S$  is actually found.

Finally, two comments about the new expression for  $R_\phi(H_e)$  are needed. First, substituting Eq. (5) to the expression used in Ref. 3 [formally identical to the one for  $R_\phi(H_e)$ ] has only minor effects on the fits of experimental curves to Eq. (1). In particular, the values of  $R_\theta(0)$  and  $R_\phi(0)$  derived using Eq. (1) with the new functional dependence of  $R_\phi(H_e)$  always remain almost coincident with the ones obtained in Ref. 3. The second comment is about the different characters of the expressions for the two angular correlation ranges [Eqs. (2) and (5)]. In fact, twist-angle correlation occurs between instantaneous  $\phi$  values, while tilt-angle correlation is between expectation values of  $u \equiv \cos \theta$ , as evidenced by the presence of the  $L'(x)$  function. Such a difference reflects the fact that fluctuations in  $\theta$  and in  $\phi$  occur via quite different mechanisms. Thermal excitations are needed to induce changes in  $\theta$ , involving an exchange of energy between a magnetic moment and the environment. The effects of such excitations on adjacent moments are completely random, so that instantaneous tilt-angle fluctuations are essentially uncorrelated. A spatial correlation exists, therefore, only between expectation values of  $u$ . On the contrary, the local field  $\mathbf{H}_i(\mathbf{r}, t)$ , whose fast changes with time are responsible for twist-angle fluctuations, is weakly dependent on position over distances of the order of the interparticle distance, so that instantaneous fluctuations of  $\phi$  on adjacent moments may be substantially correlated, as shown in this paper.

This work was partially supported by CNR, Grants Nos. 115.25434 and 96.00262.CT02.

<sup>1</sup>A. E. Berkowitz, J. R. Mitchell, M. J. Carey, A. P. Young, S. Zhang, F. E. Spada, F. T. Parker, A. Hutten, and G. Thomas, *Phys. Rev. Lett.* **68**, 3745 (1992).

<sup>2</sup>J. Wecker, R. von Helmolt, L. Schultz, and K. Samwer, *Appl. Phys. Lett.* **62**, 1985 (1993); *IEEE Trans. Magn.* **29**, 3087 (1993).

<sup>3</sup>P. Allia, M. Knobel, P. Tiberto, and F. Vinai, *Phys. Rev. B* **52**, 15398 (1995).

<sup>4</sup>E. Agostinelli, P. Allia, R. Caciuffo, D. Fiorani, D. Rinaldi, A. M. Testa, P. Tiberto, and F. Vinai, *Mater. Sci. Forum* **235-238**, 705 (1997).

<sup>5</sup>P. Allia, P. Tiberto, and F. Vinai, *Philos. Mag.* (in press).

<sup>6</sup>A. Aharony, in *Magnetic Properties of Fine Particles*, edited by J. L. Dormann and D. Fiorani (North-Holland, Amsterdam 1993), p. 3.

<sup>7</sup>D. Altbir, J. d'Albuquerque e Castro, and P. Vargas, *Phys. Rev. B* **54**, 6823 (1996); P. Vargas and D. Altbir, *J. Magn. Magn. Mater.* (submitted).

<sup>8</sup>A. H. Morrish, *The Physical Principles of Magnetism* (Wiley, New York, 1966), p. 102.