

Lipopeptides from *Bacillus subtilis* AC7 inhibit adhesion and biofilm formation of *Candida albicans* on silicone

*Original*

Lipopeptides from *Bacillus subtilis* AC7 inhibit adhesion and biofilm formation of *Candida albicans* on silicone / Ceresa, Chiara; Rinaldi, Maurizio; Chiono, Valeria; Carmagnola, Irene; Allegrone, Gianna; Fracchia, Letizia. - In: ANTONIE VAN LEEUWENHOEK. - ISSN 0003-6072. - 109:(2016), pp. 1375-1388. [10.1007/s10482-016-0736-z]

*Availability:*

This version is available at: 11583/2649103 since: 2016-11-25T13:14:15Z

*Publisher:*

Springer Netherlands

*Published*

DOI:10.1007/s10482-016-0736-z

*Terms of use:*

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

*Publisher copyright*

Springer postprint/Author's Accepted Manuscript

This version of the article has been accepted for publication, after peer review (when applicable) and is subject to Springer Nature's AM terms of use, but is not the Version of Record and does not reflect post-acceptance improvements, or any corrections. The Version of Record is available online at: <http://dx.doi.org/10.1007/s10482-016-0736-z>

(Article begins on next page)

Dear Author,

Here are the proofs of your article.

- You can submit your corrections **online**, via **e-mail** or by **fax**.
- For **online** submission please insert your corrections in the online correction form. Always indicate the line number to which the correction refers.
- You can also insert your corrections in the proof PDF and **email** the annotated PDF.
- For fax submission, please ensure that your corrections are clearly legible. Use a fine black pen and write the correction in the margin, not too close to the edge of the page.
- Remember to note the **journal title**, **article number**, and **your name** when sending your response via e-mail or fax.
- **Check** the metadata sheet to make sure that the header information, especially author names and the corresponding affiliations are correctly shown.
- **Check** the questions that may have arisen during copy editing and insert your answers/corrections.
- **Check** that the text is complete and that all figures, tables and their legends are included. Also check the accuracy of special characters, equations, and electronic supplementary material if applicable. If necessary refer to the *Edited manuscript*.
- The publication of inaccurate data such as dosages and units can have serious consequences. Please take particular care that all such details are correct.
- Please **do not** make changes that involve only matters of style. We have generally introduced forms that follow the journal's style. Substantial changes in content, e.g., new results, corrected values, title and authorship are not allowed without the approval of the responsible editor. In such a case, please contact the Editorial Office and return his/her consent together with the proof.
- If we do not receive your corrections **within 48 hours**, we will send you a reminder.
- Your article will be published **Online First** approximately one week after receipt of your corrected proofs. This is the **official first publication** citable with the DOI. **Further changes are, therefore, not possible.**
- The **printed version** will follow in a forthcoming issue.

#### Please note

After online publication, subscribers (personal/institutional) to this journal will have access to the complete article via the DOI using the URL: [http://dx.doi.org/\[DOI\]](http://dx.doi.org/[DOI]).

If you would like to know when your article has been published online, take advantage of our free alert service. For registration and further information go to: <http://www.link.springer.com>.

Due to the electronic nature of the procedure, the manuscript and the original figures will only be returned to you on special request. When you return your corrections, please inform us if you would like to have these documents returned.

# Metadata of the article that will be visualized in OnlineFirst

**Please note: Images will appear in color online but will be printed in black and white.**

|                      |  |   |
|----------------------|--|---|
| ArticleTitle         | Lipopeptides from <i>Bacillus subtilis</i> AC7 inhibit adhesion and biofilm formation of <i>Candida albicans</i> on silicone |   |
| Article Sub-Title    |  |   |
| Article CopyRight    | Springer International Publishing Switzerland<br>(This will be the copyright line in the final PDF)                          |   |
| Journal Name         | Antonie van Leeuwenhoek  |   |
| Corresponding Author | Family Name  | <b>Fracchia</b>   |
|                      | Particle   |   |
|                      | Given Name   | <b>Letizia</b>  |
|                      | Suffix   |   |
|                      | Division   | Department of Pharmaceutical Sciences   |
|                      | Organization   | Università del Piemonte Orientale “A. Avogadro”   |
|                      | Address  | Largo Donegani 2, 28100, Novara, Italy  |
|                      | Email  | letizia.fracchia@uniupo.it  |
|                      | ORCID  | <a href="http://orcid.org/0000-0003-3505-1919">http://orcid.org/0000-0003-3505-1919</a> |
| Author               | Family Name  | <b>Ceresa</b>   |
|                      | Particle   |   |
|                      | Given Name   | <b>Chiara</b>   |
|                      | Suffix   |   |
|                      | Division   | Department of Pharmaceutical Sciences   |
|                      | Organization   | Università del Piemonte Orientale “A. Avogadro”   |
|                      | Address  | Largo Donegani 2, 28100, Novara, Italy  |
|                      | Email  |   |
|                      | ORCID  |   |
| Author               | Family Name  | <b>Rinaldi</b>  |
|                      | Particle   |   |
|                      | Given Name   | <b>Maurizio</b>   |
|                      | Suffix   |   |
|                      | Division   | Department of Pharmaceutical Sciences   |
|                      | Organization   | Università del Piemonte Orientale “A. Avogadro”   |
|                      | Address  | Largo Donegani 2, 28100, Novara, Italy  |
|                      | Email  |   |
|                      | ORCID  |   |
| Author               | Family Name  | <b>Chiono</b>   |
|                      | Particle   |   |
|                      | Given Name   | <b>Valeria</b>  |
|                      | Suffix   |   |
|                      | Division   | Department of Mechanical and Aerospace Engineering                                      |
|                      | Organization   | Politecnico di Torino   |

|                             |   |  |
|-----------------------------|---|--|
|                             | Address   | Corso Duca degli Abruzzi 24, 10129, Turin, Italy   |
|                             | Email   |  |
|                             | ORCID   |  |
| Author                      | Family Name   | <b>Carmagnola</b>                                  |
|                             | Particle  |  |
|                             | Given Name  | <b>Irene</b>                                       |
|                             | Suffix  |  |
|                             | Division  | Department of Mechanical and Aerospace Engineering |
|                             | Organization  | Politecnico di Torino                              |
|                             | Address   | Corso Duca degli Abruzzi 24, 10129, Turin, Italy   |
|                             | Email   |  |
|                             | ORCID   |  |
| Author                      | Family Name   | <b>Allegrone</b>                                   |
|                             | Particle  |  |
|                             | Given Name  | <b>Gianna</b>                                      |
|                             | Suffix  |  |
|                             | Division  | Department of Pharmaceutical Sciences              |
|                             | Organization  | Università del Piemonte Orientale “A. Avogadro”    |
|                             | Address   | Largo Donegani 2, 28100, Novara, Italy             |
|                             | Email   |  |
|                             | ORCID   |  |
| Schedule                    | Received  | 27 April 2016                                      |
|                             | Revised   |  |
|                             | Accepted  | 12 July 2016                                       |
| Abstract                    | <p><i>Candida albicans</i> is the major fungus that colonises medical implants, causing device-associated infections with high mortality. Antagonistic bacterial products with interesting biological properties, such as biosurfactants, have recently been considered for biofilm prevention. This study investigated the activity of lipopeptide biosurfactant produced by <i>Bacillus subtilis</i> AC7 (AC7 BS) against adhesion and biofilm formation of <i>C. albicans</i> on medical-grade silicone elastomeric disks (SEDs). Chemical analysis, stability, surface activities of AC7 BS crude extract and physicochemical characterisation of the coated silicone disk surfaces were also carried out. AC7 BS showed a good reduction of water surface tension, low critical micelle concentration, good emulsification activity, thermal resistance and pH stability. Co-incubation with 2 mg ml<sup>-1</sup> AC7 BS significantly reduced adhesion and biofilm formation of three <i>C. albicans</i> strains on SEDs in a range of 67–69 % and of 56–57 %, respectively. On pre-coated SEDs, fungal adhesion and biofilm formation were reduced by 57–62 % and 46–47 %, respectively. Additionally, AC7 BS did not inhibit viability of <i>C. albicans</i> strains in both planktonic and sessile form. Chemical analysis of the crude extract revealed the presence of two families of lipopeptides, principally surfactin and a lower percentage of fengycin. The evaluation of surface wettability indicated that AC7 BS coating of SEDs surface was successful although uneven. AC7 BS significantly prohibits the initial deposition of <i>C. albicans</i> and slows biofilm growth, suggesting a potential role of biosurfactant coatings for preventing fungal infection associated with silicone medical devices.</p> |  |
| Keywords (separated by '-') | Anti-adhesion - Biofilm - Medical device - Lipopeptide biosurfactant - Coating - <i>Candida albicans</i>  |  |
| Footnote Information        |   |  |

2 **Lipopeptides from *Bacillus subtilis* AC7 inhibit adhesion**  
3 **and biofilm formation of *Candida albicans* on silicone**

4 Chiara Ceresa · Maurizio Rinaldi · Valeria Chiono · Irene Carmagnola ·  
5 Gianna Allegrone · Letizia Fracchia 

6 Received: 27 April 2016 / Accepted: 12 July 2016  
7 © Springer International Publishing Switzerland 2016

8 **Abstract** *Candida albicans* is the major fungus that  
9 colonises medical implants, causing device-associated  
10 infections with high mortality. Antagonistic bacterial  
11 products with interesting biological properties, such as  
12 biosurfactants, have recently been considered for  
13 biofilm prevention. This study investigated the activity  
14 of lipopeptide biosurfactant produced by *Bacillus*  
15 *subtilis* AC7 (AC7 BS) against adhesion and biofilm  
16 formation of *C. albicans* on medical-grade silicone  
17 elastomeric disks (SEDs). Chemical analysis, stabil-  
18 ity, surface activities of AC7 BS crude extract and  
19 physicochemical characterisation of the coated sili-  
20 cone disk surfaces were also carried out. AC7 BS  
21 showed a good reduction of water surface tension, low  
22 critical micelle concentration, good emulsification  
23 activity, thermal resistance and pH stability. Co-  
24 incubation with 2 mg ml<sup>-1</sup> AC7 BS significantly  
25 reduced adhesion and biofilm formation of three *C.*  
26 *albicans* strains on SEDs in a range of 67–69 % and of  
27 56–57 %, respectively. On pre-coated SEDs, fungal  
28 adhesion and biofilm formation were reduced by

57–62 % and 46–47 %, respectively. Additionally, 29  
AC7 BS did not inhibit viability of *C. albicans* strains 30  
in both planktonic and sessile form. Chemical analysis 31  
of the crude extract revealed the presence of two 32  
families of lipopeptides, principally surfactin and a 33  
lower percentage of fengycin. The evaluation of 34  
surface wettability indicated that AC7 BS coating of 35  
SEDs surface was successful although uneven. AC7 36  
BS significantly prohibits the initial deposition of *C.* 37  
*albicans* and slows biofilm growth, suggesting a 38  
potential role of biosurfactant coatings for preventing 39  
fungal infection associated with silicone medical 40  
devices. 41

**Keywords** Anti-adhesion · Biofilm · Medical 42  
device · Lipopeptide biosurfactant · Coating · *Candida* 43  
*albicans* 44

**Introduction** 45

In recent years, a significant increase in the incidence 46  
of human fungal infections has been observed. *Can-* 47  
*dida* species are the major problem, especially in 48  
immunocompromised patients (Espinel-Ingroff et al. 49  
2009; van De Veerdonk et al. 2010; Ruhnke et al. 50  
2011), representing the fourth most common cause of 51  
nosocomial bloodstream infections (Wisplinghoff 52  
et al. 2004). Invasive candidiasis presents a high 53

A1 C. Ceresa · M. Rinaldi · G. Allegrone · L. Fracchia (✉)  
A2 Department of Pharmaceutical Sciences, Università del  
A3 Piemonte Orientale “A. Avogadro”, Largo Donegani 2,  
A4 28100 Novara, Italy  
A5 e-mail: letizia.fracchia@uniupo.it

A6 V. Chiono · I. Carmagnola  
A7 Department of Mechanical and Aerospace Engineering,  
A8 Politecnico di Torino, Corso Duca degli Abruzzi 24,  
A9 10129 Turin, Italy

54 global mortality rate, ranging from 36 to 63 % in  
55 different patient groups (Guery et al. 2009; van De  
56 Veerdonk et al. 2010) and represents a significant  
57 problem in terms of patient management and health-  
58 care costs in the public health system (Kullberg et al.  
59 2011).

60 Among the *Candida* species isolated from humans,  
61 *Candida albicans* is frequently associated with the  
62 formation of biofilms on a wide variety of medical  
63 devices (Crump and Collignon 2000; Goldberg et al.  
64 2000; Karchmer 2000; Maki and Tambyah 2001). *C.*  
65 *albicans* biofilms consist of structured surface-associ-  
66 ated cell communities embedded in an extracellular  
67 matrix that have distinct phenotypes compared to their  
68 planktonic cell counterparts (Fanning and Mitchell  
69 2012). The presence of the biofilm plays a key role on  
70 *C. albicans* pathogenesis, by protecting the microor-  
71 ganism from host defences and reducing significantly  
72 its susceptibility to antifungal agents (Hawser and  
73 Douglas 1994; Lazzell et al. 2009). Furthermore, the  
74 tenacity with which *C. albicans* infects indwelling  
75 medical devices necessitates, in almost all the cases,  
76 their removal (Kojic and Darouiche 2004).

77 For these reasons, the development of new tech-  
78 nologies to counteract *C. albicans* biofilm growth  
79 represents a major challenge in clinical practice and  
80 preventive medicine. Among microbial metabolites,  
81 biosurfactants have gained importance thanks to their  
82 interesting biological properties, such as the ability to  
83 disrupt membranes and to affect the adhesion proper-  
84 ties of cells/microorganisms (Cameotra and Makkar  
85 2004; Singh and Cameotra 2004; Seydlová and  
86 Svobodová 2008; Rodrigues and Teixeira 2010).  
87 Biosurfactants are amphipathic compounds with both  
88 hydrophilic and hydrophobic moieties that exhibit  
89 surface activities at interfaces (Banat et al. 2010).  
90 Adsorption of biosurfactants to a substratum surface  
91 modifies its hydrophobicity, interfering with microbial  
92 adhesion and desorption processes (Rodrigues et al.  
93 2006a; Biniarz et al. 2015). Pre-coating catheters and  
94 other medical implantable materials with biosurfac-  
95 tants could represent a preventive strategy to inhibit  
96 pathogenic biofilm growth, thus reducing the use of  
97 pharmaceuticals and antibiotics (Rodrigues et al.  
98 2006b; Singh et al. 2007; Falagas and Makris 2009).

99 In this study, the ability of the lipopeptide biosur-  
100 factant AC7 produced by *Bacillus subtilis* (AC7 BS) to  
101 inhibit adhesion and biofilm formation of three *C.*  
102 *albicans* strains was evaluated by co-incubation and

pre-coating on silicone elastomer at physiological 103  
conditions. Lipopeptides activity was determined by 104  
means of the crystal violet staining and the viable cell 105  
counting methods. Moreover, AC7 BS was chemically 106  
characterised and its stability and surface activities 107  
measured. Surface physicochemical characterisations 108  
of the AC7 BS coated silicone were also carried out. 109

## 110 Materials and methods

### 111 Microorganisms and culture conditions

112 The endophytic biosurfactant-producing strain AC7 112  
was isolated from the inside of stems of *Robinia* 113  
*pseudoacacia* and was genotypically identified by 114  
complete 16S rDNA sequence analysis (DSMZ Iden- 115  
tification Service, Braunschweig, Germany) as *B.* 116  
*subtilis*. For biofilm assays, the strain *C. albicans* 117  
IHEM 2894 was purchased from The Belgian Co- 118  
ordinated Collections of Microorganisms (BCCM). *C.* 119  
*albicans* 40 (DSM 29204) and 42 (DSM 29205) are 120  
two wild strains (courtesy of Hospital “Maggiore della 121  
Carità”, Novara, Italy), clinically isolated from central 122  
venous catheter and urinary catheter, respectively, and 123  
deposited by the Authors in the DSMZ collection. 124  
Strain *B. subtilis* AC7 was stored at  $-80^{\circ}\text{C}$  in Luria– 125  
Bertani (LB) broth (Sigma-Aldrich) supplemented 126  
with 25 % glycerol and grown on LB agar plates for 127  
24 h at  $28^{\circ}\text{C}$ . *C. albicans* strains were stored at 128  
 $-80^{\circ}\text{C}$  in Sabouraud dextrose broth (Sigma-Aldrich) 129  
supplemented with 25 % glycerol and grown for 24 h 130  
at  $37^{\circ}\text{C}$  on Sabouraud Dextrose Agar (SDA) plates. 131

### 132 Critical micelle concentration, emulsification 133 index and stability study of AC7 BS

134 AC7 BS crude extract was obtained according to the 134  
method described by Rivardo et al. (2009). Surface 135  
tension of 0.5, 1.0 and  $2.0\text{ mg ml}^{-1}$  AC7 BS solutions 136  
in alkaline distilled water was measured by using a 137  
ring tensiometer (KSV Sigma 703D). Results for 138  
surface tension measurements were expressed as 139  
 $\text{mN m}^{-1}$  and compared with alkaline distilled water. 140  
Critical micelle concentration (CMC) was determined 141  
on serially diluted biosurfactant solutions in alkaline 142  
distilled water (from  $0.01$  to  $0.5\text{ mg ml}^{-1}$ ). Surface 143  
tension of each dilution was determined in triplicate. 144  
The CMC was assessed from the intercept of two 145

straight lines extrapolated from the concentration-dependent and concentration-independent sections of a curve plotted between biosurfactant concentration and surface tension values.

The heat/cold stability of 0.5, 1.0 and 2.0 mg ml<sup>-1</sup> AC7 BS solutions was evaluated by measuring the emulsification index at 24 h E<sub>24</sub> (%) (Franzetti et al. 2012) and surface tension after treatment at 100 °C for 1 h, at 121 °C for 15 min and at -80 °C for 24 h. To study pH stability, the pH of the AC7 BS solutions (0.5, 1.0, 2.0 mg ml<sup>-1</sup>) was adjusted to different pH values (3–11) with 1 M NaOH or 1 M HCl. Afterwards, the surface tension and the E<sub>24</sub> were measured. Assays were carried out in triplicate.

## Chemical characterisation of AC7 BS

The chemical characterisation of the crude extract was performed according to the method described by Pecci et al. (2010), with and slight modifications. An aliquot of the biosurfactant extract was dissolved in methanol/ acetonitrile (50/50 v/v) to obtain a 1000 µg ml<sup>-1</sup> stock solution. Freshly prepared working solutions were made by diluting the stock solution with methanol/water (50/50 v/v) to 10 µg ml<sup>-1</sup> solutions. Mass spectrometry analyses were done on a LCQ DECA XP Plus (Thermo Finnigan, San Jose, CA, USA) IonTrap mass instrument equipped with an ESI source. Samples (10 µg/ml solutions) were injected with a syringe at 5 µl min<sup>-1</sup> flow rate. Source voltage and capillary voltage were at 4.80 kV and 23 V in positive mode. The capillary temperature was maintained at 350 °C and nitrogen was used as nebulising gas at 30 arbitrary units. Data were acquired in positive MS total ion scan mode (mass scan range  $m/z$  100–2000) and MS/MS product ion scan mode with normalised collision energy (nce %) optimised for each precursor ion selected:  $m/z$  1030, 38 %; 1044 and 1058, 39 %; 1478 and 1506, 35 %.

## Antifungal susceptibility testing against *Candida albicans* planktonic cells

AC7 BS antifungal activity towards planktonic cells of *C. albicans* strains was assessed according to EUCAST guidelines (Rodriguez-Tudela et al. 2008). Briefly, 100 µl of AC7 BS solutions (from 0.06 to 6 mg ml<sup>-1</sup>) were added in a 96-well microtiter plate (Bioster). In control wells (no biosurfactant added),

100 µl of sterile PBS were used. *C. albicans* suspensions at a concentration ranging from 1 to 5 × 10<sup>5</sup> colony-forming units (CFU) ml<sup>-1</sup> were prepared in sterile double-strength Roswell Park Memorial Institute (RPMI) 1640 medium (Sigma-Aldrich) buffered with 3-(*N*-morpholino)propanesulfonic acid buffer (MOPS) (Sigma-Aldrich) and supplemented with D-glucose (2 % final concentration), pH 7.0. Subsequently, 100 µl of the *Candida* suspensions were added to each well, to obtain final concentrations of AC7 BS ranging from 0.03 to 3 mg ml<sup>-1</sup>, and to the control wells. Blank wells were prepared by mixing 100 µl double-strength RPMI with 100 µl of the biosurfactant solutions (from 0.06 to 6 mg ml<sup>-1</sup>) or PBS. The plate was incubated at 37 °C for 24 h in static conditions. Finally, OD<sub>450</sub> was measured for each well using a Ultramark Microplate Imaging System (Bio-Rad). The data were normalised with respect to the value of the corresponding blank wells. Assays were carried out in triplicate.

## Medical-grade silicone elastomeric disks preparation

Medical-grade silicone elastomeric disks (SEDs) (TECNOEXTR Srl, Italy) used in the study were 15 mm in diameter and 1.5 mm in thickness for experiments in 12-well tissue culture plates, and 10 mm in diameter and 1.5 mm in thickness for experiments in 24-well tissue culture plates. Cleaning and sterilisation of SEDs was carried out according to the method described by Busscher et al. (1997). Briefly, disks were immersed in 200 ml of distilled water supplemented with 1.4 % (v/v) of RBS<sup>TM</sup> 50 solution (Sigma-Aldrich), sonicated for 5 min at 60 kHz using Elma S30H (Elmasonic, VWR International) and rinsed in 1 l of MilliQ water twice. Then, disks were submerged in 20 ml of methanol (99 %) (Sigma-Aldrich), rinsed twice and autoclaved for 15 min at 121 °C.

## Antifungal susceptibility of *Candida albicans* biofilms

*Candida albicans* cells were cultivated for 24 h at 37 °C on SDA plates. Cells were then suspended in Phosphate Buffered Saline (PBS) solution with 10 % Fetal Bovine Serum (FBS) and standardised to 1 × 10<sup>7</sup> CFU ml<sup>-1</sup>. One milliliter of this fungal



|     |  |     |
|-----|--|-----|
| 236 | suspension was used to submerge silicone disks                             | 281 |
| 237 | previously inserted in a 24-well plate (Greiner bio-                       | 282 |
| 238 | one). After incubation in static conditions at 37 °C for                   | 283 |
| 239 | 1.5 h (adhesion phase), disks were transferred into a                      | 284 |
| 240 | new 24-well plate and submerged in 1 ml of Yeast                           | 285 |
| 241 | Nitrogen Base with 50 mmol l <sup>-1</sup> Dextrose (YNBD)                 | 286 |
| 242 | medium with 10 % of FBS and incubated at 37 °C for                         | 287 |
| 243 | 24 h at 90 rpm (biofilm growth phase). Mature                              | 288 |
| 244 | biofilms were then treated with different concentra-                       | 289 |
| 245 | tions of AC7 BS in YNBD + 10 % FBS (ranging                                | 290 |
| 246 | from 0.06 to 3 mg ml <sup>-1</sup> ) and incubated for an                  | 291 |
| 247 | additional 24 h at 37 °C in static conditions. As                          | 292 |
| 248 | controls, mature biofilms were submerged in 1 ml                           | 293 |
| 249 | YNBD + 10 % FBS. The antifungal activity of AC7                            | 294 |
| 250 | BS was evaluated by the {2,3-bis (2-methoxy-4-nitro-                       |     |
| 251 | 5-sulfophenyl)-5-[(phenylamino) carbonyl]-2H-tetra-                        |     |
| 252 | zolium hydroxide} (XTT) (Sigma-Aldrich) colorimet-                         |     |
| 253 | ric assay. Disks were transferred into new plates and                      |     |
| 254 | submerged in 1 ml of PBS containing 12.5 µl of XTT                         |     |
| 255 | solution (1 mg ml <sup>-1</sup> ) and 1 µl of 1 mmol l <sup>-1</sup> mena- |     |
| 256 | dione solution (Sigma-Aldrich). Blank disks (disks                         |     |
| 257 | without biofilm), submerged in the XTT/menadione                           |     |
| 258 | mixture were also prepared. Plates were covered with                       |     |
| 259 | an aluminum foil and incubated at 37 °C for 5 h at                         |     |
| 260 | 90 rpm. Finally, 150 µl were collected from each well                      |     |
| 261 | and transferred to a 96-well plate for OD <sub>490</sub> measure-          |     |
| 262 | ment using an Ultramark microplate imaging system                          |     |
| 263 | (Bio-Rad Laboratories Srl, Segrate MI, Italy). The                         |     |
| 264 | data were normalised with respect to the value of                          |     |
| 265 | blanks (background). All assays were carried out in                        |     |
| 266 | triplicate.  |     |
| 267 | Anti-adhesion and anti-biofilm assays against                              |     |
| 268 | <i>C. albicans</i> strains   |     |
| 269 | <i>Co-incubation assays</i>  |     |
| 270 | Five hundred microliters of <i>C. albicans</i> suspensions                 |     |
| 271 | (2 × 10 <sup>7</sup> CFU ml <sup>-1</sup> ) in PBS + 20 % FBS, were        |     |
| 272 | added to each well of a 24-well plates (Greiner bio-                       |     |
| 273 | one) containing a silicone disk together with either                       |     |
| 274 | 500 µl of 2 × AC7 BS solutions (1, 2, 4 and                                |     |
| 275 | 6 mg ml <sup>-1</sup> ) (test groups) or PBS (control group).              |     |
| 276 | After 1.5 h of incubation ( <i>C. albicans</i> adhesion                    |     |
| 277 | phase), the disks were transferred into a new plate                        |     |
| 278 | and placed in either 1 ml of YNBD + 10 % FBS with                          |     |
| 279 | 0 mg ml <sup>-1</sup> (control group) or 0.5, 1, 2, 3 mg ml <sup>-1</sup>  |     |
| 280 | AC7 BS (test groups) and incubated for 24 h at 37 °C                       |     |
|     | at 90 rpm. The reduction of adherent cells and biofilm                     |     |
|     | biomass was evaluated after 1.5 and 24 h by crystal                        |     |
|     | violet (CV) staining. The supernatants were discarded                      |     |
|     | and the disks were washed three times with PBS for                         |     |
|     | removal of non-adherent cells. Afterwards, disks were                      |     |
|     | dried at 37 °C for 2 h and submerged into 1 ml of a                        |     |
|     | 0.2 % CV solution for 10 min. The CV solution was                          |     |
|     | removed by washing with distilled water and the disks                      |     |
|     | air-dried. Finally, bound CV was released by adding                        |     |
|     | 2 ml of 33 % acetic acid (Sigma-Aldrich) and OD <sub>570</sub>             |     |
|     | was measured using a Ultramark microplate imaging                          |     |
|     | system (Bio-Rad Laboratories Srl, Segrate MI, Italy).                      |     |
|     | Assays were carried out in triplicate and the experi-                      |     |
|     | ments were repeated two times.   |     |
|     | <i>Pre-coating assays</i>  |     |
|     | SEDs were dipped in 2 ml of AC7 BS solution at                             |     |
|     | concentrations ranging from 0.5 to 3 mg ml <sup>-1</sup> (test             |     |
|     | groups) or in PBS only (control group) and incubated                       |     |
|     | at 37 °C for 24 h at 140 rpm. Disks were then placed                       |     |
|     | in 12-well plates containing two milliliters of <i>C.</i>                  |     |
|     | <i>albicans</i> suspensions, standardised to 1 × 10 <sup>7</sup>           |     |
|     | CFU ml <sup>-1</sup> . After 1.5 h of incubation (adhesion                 |     |
|     | phase), the disks were transferred into 2 ml                               |     |
|     | YNBD + 10 % FBS and incubated at 37 °C with                                |     |
|     | gentle shaking for 24 h. The reduction of adherent                         |     |
|     | cells and biofilm biomass were evaluated after 1.5 and                     |     |
|     | 24 h with CV staining method as indicated previously.                      |     |
|     | Furthermore, the anti-adhesion and anti-biofilm                            |     |
|     | activity of silicone disks pre-coated with AC7 BS at a                     |     |
|     | concentration of 2 mg ml <sup>-1</sup> was evaluated by means              |     |
|     | of the viable-cell counting method. Silicone disks and                     |     |
|     | <i>C. albicans</i> suspensions were prepared as described                  |     |
|     | previously. After 1.5 h and 24 h of incubation, the                        |     |
|     | supernatants were discarded and the disks were                             |     |
|     | washed three times with PBS to remove non-adherent                         |     |
|     | cells. Then, the disks were inserted into 50 ml tubes                      |     |
|     | containing 10 ml PBS and subjected to four cycles of                       |     |
|     | sonication (30 s) and stirring (30 s) for cells detach-                    |     |
|     | ment. The disrupted biofilm cells were serially diluted                    |     |
|     | in PBS and 1 ml of each dilution was incorporated into                     |     |
|     | melted SDA using the pour-plate method.                                    |     |
|     | Agar plates were incubated at 37 °C for 24 h and                           |     |
|     | colonies were then enumerated. Assays were carried                         |     |
|     | out in triplicate and experiments were repeated two                        |     |
|     | times. Results were expressed as mean log <sub>10</sub> CFU/               |     |
|     | disk ± standard deviations.  |     |



# Surface physicochemical characterisation

For the physicochemical characterisation, a set of six AC7 BS pre-coated and six control (PBS treated) SEDs was prepared as described previously. In order to simulate a pre-coating assay, three of the AC7 BS pre-coated and three of the control SEDs were subjected to the same procedures as described in the previous section (up to the three washing steps with PBS after 1.5 h of incubation) with the only difference that sterile YNBD + 10 % FBS was added to the disks instead of the *C. albicans* suspensions.

The wettability of SEDs was evaluated by water contact angle measurements using a CAM 200 KSV Instrument (Biolin Scientific), equipped with Tetha software. Static water contact angle was measured using the sessile drop 1 Milli-Q water drops) at room temperature. The static contact angle method was calculated as the average value from five measurements.

The surface chemical properties of SEDs were analysed by infrared spectroscopy in an IR Perkin-Elmer Frontier spectrophotometer equipped with an attenuated total reflectance (ATR-FTIR) device using a Germanium crystal. Spectra were recorded with a resolution of 4 cm<sup>-1</sup> and averaged over 36 scans.

## Statistical analysis of data


Statistical analysis and graphs were elaborated by means of the statistical program R, 3.1.2 (R Development Core Team, <http://www.R-project.org>). Two-way ANOVA was used to compare optical densities of planktonic cells and pre-formed biofilm at different AC7 BS concentrations for the three *C. albicans* strains. Tukey's Honest Significant Difference (HSD) method was used as ANOVA post hoc test. The Welch Two Sample *t* test was performed to investigate the effect of AC7 BS on the three *Candida* stains adhesion and biofilm formation in pre-coating assays, carried out by means of the viable cell counting method. Results were considered to be statistically significant when *P* < 0.05. To estimate log<sub>10</sub> CFU/disk from colony counts, the R package dupiR was used (Coglioglio et al. 2013). This package allows estimation, from a set of counts, the population size and its uncertainty using a Bayesian approach under minimal information on the distributions; this is particularly helpful in situations where one faces with low counts.

## Results

### Critical micellar concentration and stability study of AC7 BS

Critical micellar concentration (CMC) was evaluated for the AC7 BS crude extract. An AC7 BS solution at a concentration of 0.5 mg ml<sup>-1</sup> reduced the surface tension of alkaline distilled water from 72.4 to 31.4 mN m<sup>-1</sup> (Fig. 1). Serial dilutions of this solution showed a gradual increase of surface tension up to 38.2 mN m<sup>-1</sup> at the concentration of 62.5 µg ml<sup>-1</sup>. Then, surface tension rapidly increased to 54.9 mN m<sup>-1</sup> at the concentration of 7.8 µg ml<sup>-1</sup>. The CMC value for AC7 BS was 31.9 µg ml<sup>-1</sup>.

Studies on the pH stability of AC7 BS, carried out at 0.5, 1.0 and 2.0 mg ml<sup>-1</sup>, demonstrated that it was stable over a wide pH range (Table 1). At pH ranging from 6 to 11, the surface tension was preserved without large deviations at all of the three concentrations tested. In particular, the highest surface activity of AC7 BS solutions at 0.5, 1.0 and 2.0 mg ml<sup>-1</sup> was found at pH 6.0 with values of 28.45, 28.53 and 29.26 mN m<sup>-1</sup>, respectively. At pH 11.0 the values were 30.76, 30.91 and 30.92 mN m<sup>-1</sup>. At pH ≤ 5, the surface tension of the three AC7BS solutions increased and reached, at pH 3, values of 49.01, 40.64 and 37.20 mN m<sup>-1</sup>. The mean emulsification index at 24 h (E<sub>24</sub>) of AC7 BS solutions was not altered at pH from 7 to 11 (about 60 % at all three concentrations tested), but it was absent when the pH

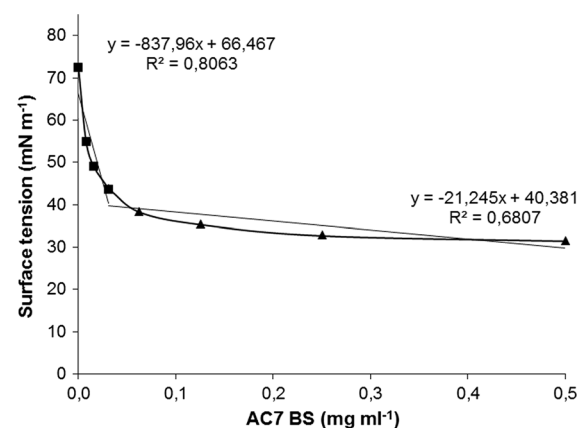

**Fig. 1** A plot of surface tension as a function of concentration of AC7 BS after purification. Standard deviation was ranging between ±0.3 mN m<sup>-1</sup>

**Table 1** Surface tension and emulsification index at 24 h ( $E_{24}$ ) of AC7 BS solutions as a function of pH

| pH   | 0.5 mg ml <sup>-1</sup>               |                 |               | 1 mg ml <sup>-1</sup>                 |      |               | 2 mg ml <sup>-1</sup>                 |      |               |
|------|---------------------------------------|-----------------|---------------|---------------------------------------|------|---------------|---------------------------------------|------|---------------|
|      | Surface tension (mN m <sup>-1</sup> ) |                 | $E_{24h}$ (%) | Surface tension (mN m <sup>-1</sup> ) |      | $E_{24h}$ (%) | Surface tension (mN m <sup>-1</sup> ) |      | $E_{24h}$ (%) |
|      | Mean                                  | SD <sup>a</sup> |               | Mean                                  | SD   |               | Mean                                  | SD   |               |
| 3.0  | 49.01                                 | 0.35            | 0             | 40.64                                 | 0.17 | 0             | 37.20                                 | 0.13 | 0             |
| 4.0  | 49.40                                 | 0.29            | 0             | 36.54                                 | 0.25 | 0             | 35.42                                 | 0.08 | 0             |
| 5.0  | 37.53                                 | 0.39            | 0             | 31.32                                 | 0.17 | 0             | 30.74                                 | 0.28 | 0             |
| 6.0  | 28.45                                 | 0.10            | 0             | 28.53                                 | 0.36 | 0             | 29.26                                 | 0.43 | 0             |
| 7.0  | 30.50                                 | 0.17            | 60.5          | 30.49                                 | 0.22 | 60            | 30.36                                 | 0.17 | 60            |
| 8.0  | 30.95                                 | 0.18            | 60.5          | 30.45                                 | 0.17 | 60            | 30.64                                 | 0.06 | 60            |
| 9.0  | 30.96                                 | 0.14            | 60.5          | 30.47                                 | 0.30 | 60            | 30.84                                 | 0.44 | 60            |
| 10.0 | 31.13                                 | 0.22            | 60.5          | 30.82                                 | 0.27 | 60            | 30.62                                 | 0.31 | 60            |
| 11.0 | 30.76                                 | 0.32            | 60.5          | 30.91                                 | 0.30 | 60            | 30.92                                 | 0.14 | 60            |

Surface tension of alkaline distilled water was 72.4 mN m<sup>-1</sup>

<sup>a</sup> SD standard deviation

was reduced. At pH 7 (the condition used in the anti-adhesion and anti-biofilm assays reported here), AC7 BS solutions showed an  $E_{24}$  of about 60 % and a mean surface tension value of 30.45 mN m<sup>-1</sup>.

The studies on the effect of heat/cold treatment on AC7 BS solutions at 0.5, 1.0 and 2.0 mg ml<sup>-1</sup> demonstrated no evident changes in surface tension and  $E_{24}$ . In particular, the treatment at 100 °C for 1 h, at 121 °C for 15 min and at -80 °C for 24 h did not alter the ability of AC7 BS solutions to decrease water surface tension and its emulsification property; moreover, the emulsions remained indefinitely stable.

#### Chemical characterisation of AC7 BS


The positive ESI-MS analysis of the crude extract showed the presence of homologues of two lipopeptide families, surfactin and fengycin, respectively (Fig. 2). The surfactin family member was composed mainly of C13, C14 and C15 surfactin homologues, whose structures were confirmed by the product ion spectra of the sodiated molecules  $[M + Na]^+$  at  $m/z$  1030, 1044 and 1058. The fengycin family member was composed of two main fengycin isoforms corresponding to C17 fengycin A and C17 fengycin B, whose structures were confirmed by the product ion spectra of the protonated molecules  $[M + H]^+$  at  $m/z$  1478 and 1506, respectively. The relative amount of the two families in the crude extract was about 98 % surfactin and 2 % fengycin.

#### Antifungal susceptibility testing against *Candida albicans* planktonic cells and biofilms

AC7 BS susceptibility testing was carried out on *C. albicans* strains 40, 42 and IHEM 2894 planktonic cells and pre-formed biofilms by means of EUCAST and XTT methods, respectively. Optical densities at 450 nm and at 490 nm versus the biosurfactant concentration are shown in Fig. 3. Two-way ANOVA analysis indicated that both OD<sub>450</sub> and OD<sub>490</sub> were not significantly associated with biosurfactant concentrations, showing that no antifungal activity against planktonic cells or biofilms was detected for any of the strains. For biofilm formation, OD<sub>490</sub> was significantly different among the three strains ( $P = 0.006371$ ). Tukey's HSD post hoc test showed that OD<sub>490</sub> was significantly higher for *C. albicans* IHEM 2894 suggesting that this strain is a stronger biofilm producer.

#### Anti-adhesion and anti-biofilm activity of AC7 BS against *Candida albicans* strains

The anti-adhesion and anti-biofilm activity of AC7 BS concentrations ranging from 0.5 to 3 mg ml<sup>-1</sup> in co-incubation and in pre-coating conditions were evaluated by the CV method, which stains total biofilm biomass (cells and extracellular matrix). Figure 4 shows how uncoated and AC7 BS coated SEDs appeared after treatment with CV. On uncoated SEDs,

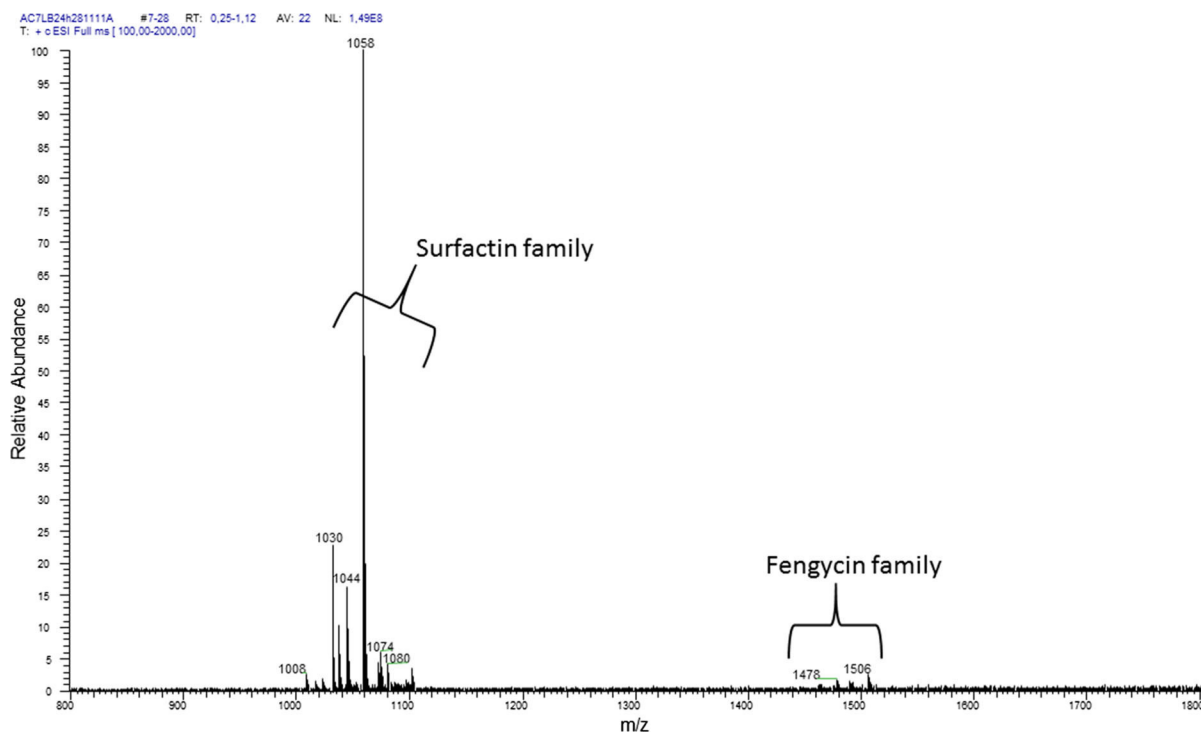

**Fig. 2** (+) ESI-MS analysis (direct infusion) of lipopeptides produced by *B. subtilis* AC7. Two clusters of peaks revealed two sets of homologue molecules. The first set evidenced four main

signals corresponding to the  $[M + Na]^+$  of surfactin family. The second set evidenced two main signals corresponding to the protonated molecules of fengycin family

CV is uniformly distributed on the surface whereas on pre-coated SEDs, the violet colour intensity and coverage area decrease with the increase of AC7 BS concentration with a maximum reduction observed at  $2 \text{ mg ml}^{-1}$ , both at 1.5 and 24 h incubation. To quantify the CV staining, the disks were submerged in acetic acid, and the absorbance of the eluted stain measured. Figure 5 shows the  $OD_{570}$  as a function of the biosurfactant concentration.


In the co-incubation experiment, the adhesion and biofilm formation of the three *C. albicans* strains to SEDs (as measured by  $OD_{570}$ ) were progressively reduced as a function of biosurfactant concentration, with a minimum reached at a concentration range between 1 and  $2 \text{ mg ml}^{-1}$  at time 1.5 h, and at concentration of  $2 \text{ mg ml}^{-1}$  at time 24 h (Fig. 5a, c). At the highest concentration ( $3 \text{ mg ml}^{-1}$ ), *C. albicans* adhesion and biofilm formation slightly increased.

Percentages of reduction of  $OD_{570}$  are reported in Table 2. In particular, the reduction at  $2 \text{ mg ml}^{-1}$  ranged (among the three strains) between 67 and 69 % at 1.5 h, and between 56 and 57 % at 24 h. Two-way

ANOVA showed that at time 1.5 h adhesion was significantly dependent on biosurfactant concentration (but not on the strain) while at time 24 h biofilm formation was significantly dependent on concentration and on the strain. In particular, Tukey's HSD test revealed a significant reduction (both at time 1.5 h and at time 24 h) with a *P* value adjusted for multiple comparison of  $<10^{-9}$ .

In the pre-coating assay, the adhesion and biofilm formation of the three *C. albicans* strains to SEDs were progressively reduced as a function of biosurfactant concentration, with a minimum reached at the concentration of  $2 \text{ mg ml}^{-1}$  both at 1.5 and 24 h incubation (Fig. 5b, d). As previously observed, at the highest concentration ( $3 \text{ mg ml}^{-1}$ ), adhesion and biofilm formation slightly increased. Percentages of reduction of  $OD_{570}$  are reported in Table 2. In particular, at  $2 \text{ mg ml}^{-1}$  the mean reduction ranged (among the three strains) between 59 and 63 % at 1.5 h, and between 47 and 50 % at 24 h. Two-way ANOVA showed that at 1.5 h adhesion was significantly dependent on AC7 BS concentration and also

**Fig. 3** Antifungal susceptibility testing against *C. albicans* planktonic cells and biofilms. AC7 BS activity at 24 h on **a** *C. albicans* 40, *C. albicans* 42 and *C. albicans* IHEM 2894 planktonic cells and **b** pre-formed biofilm, measured by OD<sub>450</sub> and OD<sub>490</sub>, respectively. For each condition (concentration and strain) minimum, maximum median and interquartile range are illustrated using a box plot

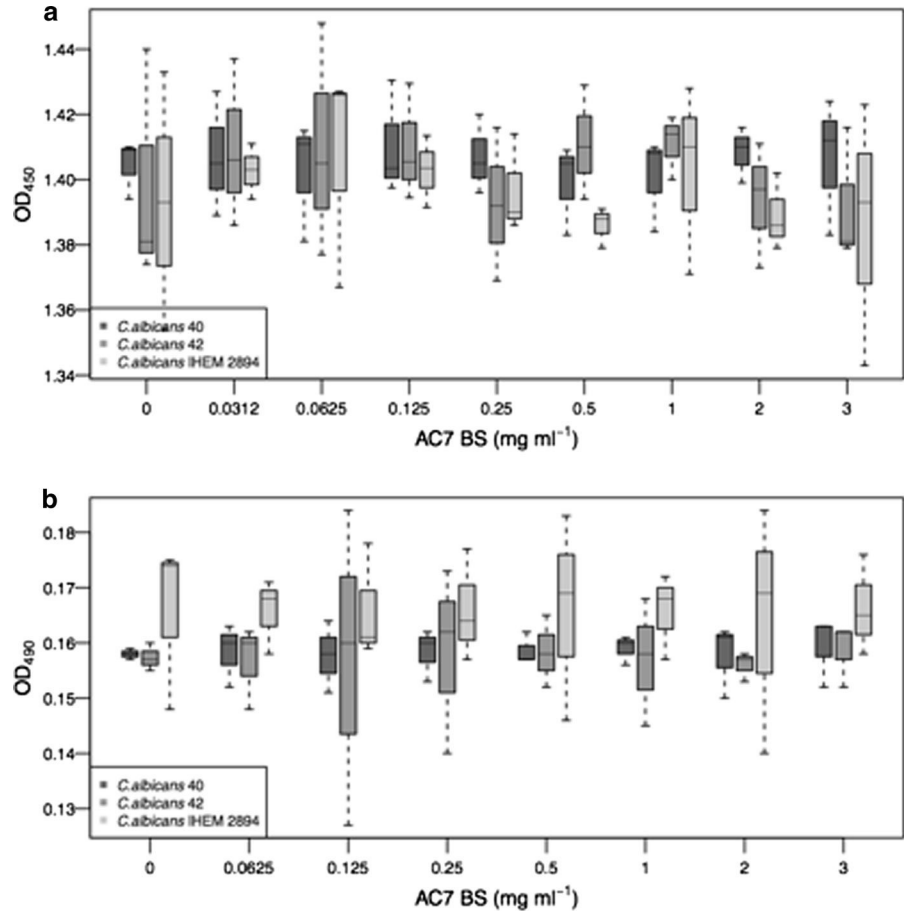


on the strain while at 24 h biofilm formation was significantly dependent on concentration (but not on the strain). In particular, Tukey's HSD test revealed a significant reduction (both at time 1.5 h and at time 24 h) with a *P* value adjusted for multiple comparison of  $<10^{-9}$ .

The effect of SEDs pre-coating with an AC7 BS concentration of 2 mg ml<sup>-1</sup> was further investigated by the viable cell counting method. Table 3 summarises the results obtained for the three *C. albicans* strains expressed as means and standard deviations for log<sub>10</sub> CFU/disk. In addition, the results of the Welch Two Sample t-test comparing AC7 BS treated and control samples are reported as *P* values and 95 % confidence intervals for the differences. The final column of Table 3 indicates the percentages of inhibition calculated as  $(1-10^{\mu}) \times 100$ , where  $\mu$  is the difference in log<sub>10</sub> CFU/disk of AC7 BS treated and control samples. Fungal adhesion and biofilm formation on treated disks was significantly lower (at

both incubation times) than on untreated disks. The difference was more evident at time 1.5 h. It should be noted that, at time 1.5 h, fungal counts were very low compared to 24 h as *C. albicans* stains are in the initial phase of adhesion. With respect to controls, the adhesion of the three fungal stains to SEDs treated with 2 mg ml<sup>-1</sup> AC7 BS was significantly reduced in a range of 57.7–62.0 % at 1.5 h and biofilm formation was significantly inhibited in a range of 45.9–47.6 % after 24 h of incubation (*P* values in Table 3). Two-ways ANOVA confirmed that *C. albicans* viable counts were significantly dependent on the disk treatment (untreated or AC7 BS pre-coated) and on incubation time ( $P < 10^{-15}$ ).

#### Surface physicochemical characterisation

The static contact angle measurements showed that the PBS-treated SEDs, as well as the PBS-treated SEDs further incubated for 1.5 h in YNBD + 10 % FBS

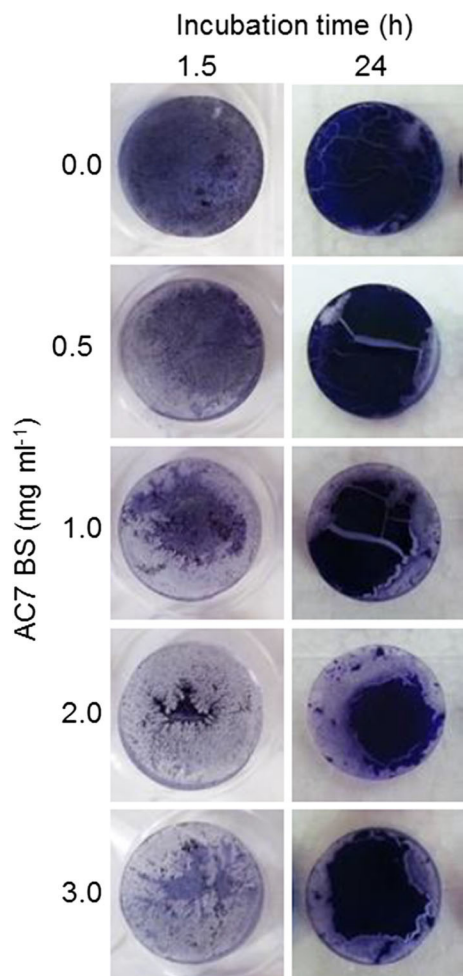

**Fig. 4** CV stained SEDs, pre-coated with different concentrations of AC7 BS, after *C. albicans* IHM 2894 adhesion (1.5 h) and biofilm formation (24 h)

(control SEDs of the simulated pre-coating assay), were hydrophobic ( $110.6^\circ \pm 3.0^\circ$  and  $112.0^\circ \pm 0.6^\circ$ , respectively). AC7 BS pre-coated SEDs, as well as AC7 BS pre-coated SEDs further incubated for 1.5 h in YNBD + 10 % FBS (treated SEDs of the simulated pre-coating assay), were hydrophobic, although they showed a reduced average static contact angle compared to their respective control samples ( $94.4^\circ \pm 10.0^\circ$  and  $103.8^\circ \pm 15.0^\circ$ , respectively). The enhanced surface wettability was a consequence of AC7 BS surface adsorption. The wide standard deviation of the contact angle value of AC7 BS treated samples compared to the respective control samples suggested that surface coating by physical adsorption was uneven.


The FTIR-ATR spectra of each analysed SED showed the characteristic bands at  $830\text{--}1110\text{ cm}^{-1}$  due to Si–O–Si stretching, at  $1259.4\text{ cm}^{-1}$  due to  $\text{CH}_3$  symmetric stretching of  $\text{Si}\backslash\text{CH}_3$ , at  $1412.4\text{ cm}^{-1}$  due to  $\text{CH}_3$  asymmetric stretching of  $\text{Si-CH}_3$ , and at  $2962.8\text{ cm}^{-1}$  due to C–H stretching. AC7 BS physical absorption onto silicone disks did not alter the FTIR-ATR spectra suggesting that the surface amount of AC7 BS was below the detection limit of the FTIR-ATR technique.

## Discussion

*Candida albicans* is one of the most important nosocomial pathogens frequently involved in implanted device-associated infection (Horn et al. 2009) and represents a serious public health problem with important medical and economic consequences (Almirante et al. 2005; Lai et al. 2012). *C. albicans* biofilm formation is a complex, multicellular process in which adhesion of cells to materials or host cells is a primary prerequisite (Ramage et al. 2005). There is, therefore, a need for biomaterials with antimicrobial-coated surfaces for the inhibition of the microbial adhesion and the eradication of biofilms. The main drawbacks of antimicrobial coatings arise from time limited effectiveness and potential toxicity towards human cells (de Sainte 2009; Hegstad et al. 2010). In this context, biosurfactants have recently emerged as a new generation of anti-adhesive and antimicrobial agents with enhanced biocompatibility and potential commercial application in pharmaceutical and biomedical fields (Cameotra and Makkar 2004; Fracchia et al. 2015). Among biosurfactants, lipopeptides form the most widely reported class with antimicrobial/antiadhesive activities due to their ability to disrupt phospholipid membranes and to affect cell-to-surface interactions by decreasing hydrophobicity and, thus, interfering with cell deposition processes and microbial adhesion (Rodrigues et al. 2006b).

Previous research about the activity of biosurfactants from endophytes and from a *Lactobacillus brevis* isolate against *C. albicans* biofilm formation reported significant reductions in biofilm cell number and biomass on polystyrene, denture resin and silicone elastomer (Fracchia et al. 2010; Cochis et al. 2012; Ceresa et al. 2015). In the present study, the activity of AC7 BS was investigated on two clinically relevant



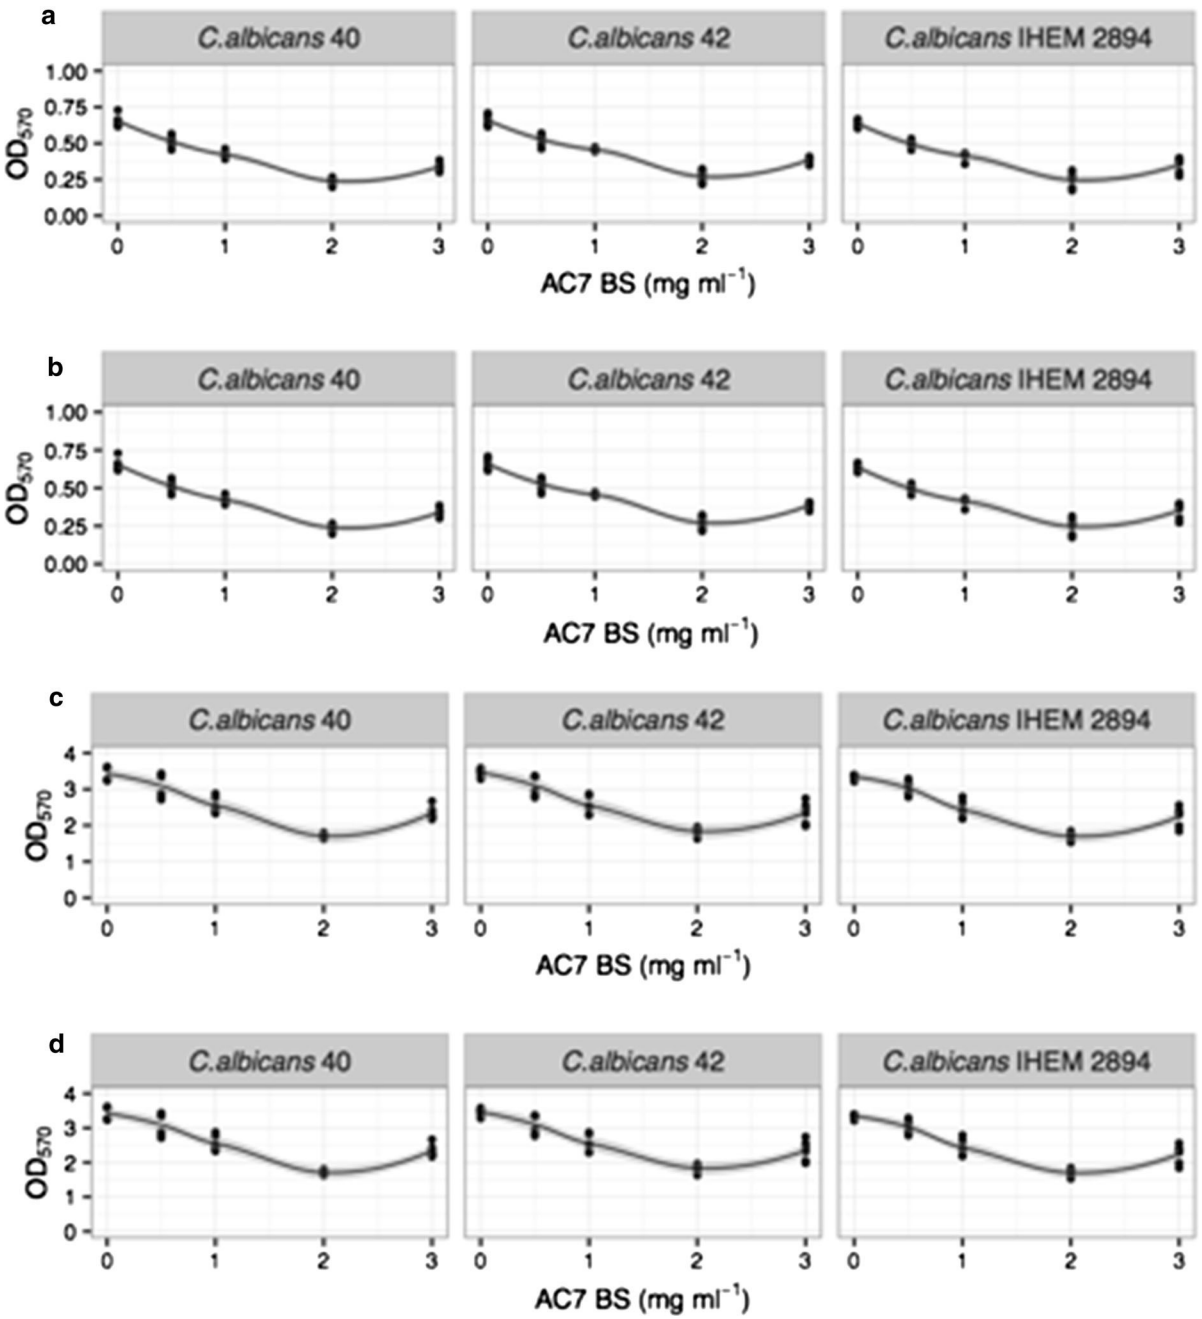

**Fig. 5** AC7 BS activity against *C. albicans* adhesion and biofilm formation evaluated by the CV method. Inhibition of *C. albicans* 40, *C. albicans* 42 and *C. albicans* IHEM 2894 adhesion and biofilm formation on silicone disks by different concentrations of AC7 BS at 1.5 h, in co-incubation (a) and in pre-coating assays (b) and at 24 h, in co-incubation (c) and in

pre-coating assays (d). The inhibition of adhesion and biofilm formation is evaluated by means of the CV method and measured by OD<sub>570</sub>. The different scales on the y-axes reflect the progression in biofilm formation with time. Each scatterplot includes a Loess curve (local regression curve) and a Loess confidence region (95 %)

wild strains of *C. albicans* and on a culture collection strain. The experiments were carried out on industrially produced medical-grade silicone disks, during the

initial phases of biofilm formation and a number of different complementary methods (fungal biomass staining, viable cell counting, and surface

**Table 2** Percentages of inhibition of the *Candida albicans* strains adhesion (1.5 h) and biofilm formation (24 h)

| Experimental condition | Strain                       | Time (h)                                    |    |    |    |     |    |    |    |
|------------------------|------------------------------|---|----|----|----|-----|----|----|----|
|                        |                              | 1.5   |    |    |    | 24  |    |    |    |
|                        |                              | AC7 BS concentration (mg ml <sup>-1</sup> ) |    |    |    |     |    |    |    |
|                        |                              | 0.5   | 1  | 2  | 3  | 0.5 | 1  | 2  | 3  |
| Co-incubation          | <i>C. albicans</i> 40        | 35  | 63 | 69 | 51 | 26  | 47 | 57 | 49 |
|                        | <i>C. albicans</i> 42        | 32  | 63 | 67 | 53 | 23  | 40 | 55 | 50 |
|                        | <i>C. albicans</i> IHEM 2894 | 32  | 62 | 68 | 51 | 27  | 45 | 57 | 55 |
| Pre-coating            | <i>C. albicans</i> 40        | 22  | 36 | 63 | 48 | 10  | 26 | 50 | 32 |
|                        | <i>C. albicans</i> 42        | 20  | 31 | 59 | 41 | 10  | 26 | 47 | 32 |
|                        | <i>C. albicans</i> IHEM 2894 | 22  | 35 | 61 | 45 | 10  | 27 | 49 | 33 |

**Table 3** AC7 BS inhibition of *Candida albicans* adhesion and biofilm formation in pre-coating assays

| Time (h) | Strain                       | Control (C) |                 | AC7 BS |        | 95 % confidence interval (C-AC7 BS) | P value                | Inhibition measures |   |
|----------|------------------------------|-------------|-----------------|--------|--------|-------------------------------------|------------------------|---------------------|---|
|          |                              | Mean        | SD <sup>a</sup> | Mean   | SD     |                                     |                        | μ <sup>b</sup>      | Percentage of inhibition (%) <sup>c</sup> |
| 1.5      | <i>C. albicans</i> 40        | 6.66        | 0.0489          | 6.24   | 0.0534 | (0.371, 0.471)                      | $3.76 \times 10^{-12}$ | -0.42               | 62.0                                      |
|          | <i>C. albicans</i> 42        | 6.66        | 0.0693          | 6.29   | 0.1130 | (0.278, 0.469)                      | $1.07 \times 10^{-6}$  | -0.37               | 57.7                                      |
|          | <i>C. albicans</i> IHEM 2894 | 6.67        | 0.0595          | 5.26   | 0.0757 | (0.333, 0.470)                      | $2.19 \times 10^{-9}$  | -0.4                | 60.3                                      |
| 24       | <i>C. albicans</i> 40        | 7.63        | 0.0455          | 7.35   | 0.0918 | (0.188, 0.384)                      | $1.99 \times 10^{-4}$  | -0.29               | 48.3                                      |
|          | <i>C. albicans</i> 42        | 7.63        | 0.0408          | 7.36   | 0.0601 | (0.206, 0.328)                      | $1.36 \times 10^{-6}$  | -0.27               | 45.9                                      |
|          | <i>C. albicans</i> IHEM 2894 | 7.63        | 0.0508          | 7.35   | 0.0384 | (0.222, 0.339)                      | $1.45 \times 10^{-6}$  | -0.28               | 47.6                                      |

The table represents the mean *C. albicans* concentrations expressed as Log<sub>10</sub> CFU/disk (as calculated by the R package dupiR) recovered on silicone disks, 95 % confidence interval, P values and inhibition measures

<sup>a</sup> SD standard deviation

<sup>b</sup>  $\mu = (\log_{10} \text{CFU/disk}_{\text{AC7 BS}} - \log_{10} \text{CFU/disk}_{\text{Control}})$

<sup>c</sup> Percentage of inhibition =  $(1 - 10^{\mu}) \times 100$

physicochemical characterisation) were used, to address the underlying mechanisms.

Chemical analysis of the AC7 BS crude extract revealed the presence of surfactin and fengycin, similar to other lipopeptide biosurfactants (Joshi et al. 2008; Rivardo et al. 2009; Kim et al. 2010; Pecci et al. 2010). Surface tension, CMC and emulsification capacity of AC7 BS were comparable to those observed for other lipopeptide biosurfactants (Lee et al. 2006; Nitschke and Pastore 2006). Moreover, AC7 BS showed a high stability to heat/cold treatments and over a wide range of pH. In particular, surface tension remained stable between pH 6 and 11, with the maximum activity observed at pH 6. Similar

results were described by Kim et al. (1997) for the lipopeptide biosurfactant from *B. subtilis* C9; by Ghosvandi et al. (2008) for the biosurfactant produced by *B. subtilis* PTCC 1696; and by Rivardo et al. (2009) for the lipopeptides V9T14 and V19T21. On the contrary, surface tension and emulsification activity of AC7 BS were affected by low pH values due to biosurfactant precipitation in acidic conditions, as reported for other biosurfactants (Rivardo et al. 2009; Amani et al. 2010; Kanna et al. 2014; Elazzazy et al. 2015).

The efficacy of AC7BS to inhibit *C. albicans* 40, *C. albicans* 42 and *C. albicans* IHEM 2894 biofilm formation on SEDs was evaluated in co-incubation



experiments and after its absorption on the silicone surface, in order to imitate a functional coating. The assays were performed in combination with a proteinaceous solution, i.e. FBS, to mimic blood contact upon the silicone surface during clinical use. Moreover, FBS is known to promote the morphogenic switching between yeast and filamentous states, an important step for biofilm formation by *C. albicans* (Chandra et al. 2008), that plays a significant role in fungal infection (Thompson et al. 2011; Mayer et al. 2013). These stringent conditions were intended to evaluate the activity of the biosurfactant in the presence of a solution that stimulates the production of biofilm.

AC7 BS treatments resulted in a significant reduction of the total adherent cells and biofilm biomass compared to controls for all three *C. albicans* strains, as evaluated by the CV method. The anti-adhesive and anti-biofilm activity of AC7 BS was concentration-dependent, with a maximum activity observed at about 2 mg ml<sup>-1</sup>, both in the co-incubation and pre-coating conditions. The effect of SEDs pre-coating with this concentration of biosurfactant was, thus, further investigated by the viable cell counting method. Cell adhesion and biofilm formation were significantly altered by AC7 BS treatment in terms of difference in the number of log<sub>10</sub> CFU/disk. Notably, in pre-coating assays, the percentages of reduction were almost similar for the CV and viable cell counting biofilm quantification assays (about 60 % reduction of adhesion and 50 % reduction of biofilm formation for all the three stains). In general, the highest performance of AC7 BS was observed during the *C. albicans* adhesion phase, whereas during the biofilm formation phase, the inhibition was lower but still significant.

Research into the activity of lipopeptides against *C. albicans* biofilm on silicone is scarce, as most experiments have been conducted on polystyrene. Janek et al. (2012) visually demonstrated that the pretreatment of silicone urethral catheters with pseudofactin II, a cyclic lipopeptide, and the inclusion of the biosurfactant in the growth medium caused an efficient reduction of *C. albicans* biofilm growth. The same authors demonstrated that the pre-treatment of polystyrene with pseudofactin II strongly inhibited *C. albicans* adhesion (>90 %), whereas the post-adhesion treatment dislodged biofilms grown on untreated surfaces to a lower extent (29–39 %). Rautela et al. (2014) evaluated the influence of

lipopeptides from *Bacillus amyloliquefaciens* strain AR2 on *C. albicans* biofilm grown in polystyrene plates. Biosurfactant exhibited concentration-dependent fungal growth inhibition and fungicidal activity. Moreover, when added to the growth media, biosurfactant inhibited *C. albicans* biofilm formation in a range of 46–100 % (depending on the concentration and on *Candida* strains) and, less efficiently, dislodged preformed biofilm from polystyrene plates. Very recently, Biniarz et al. (2015) demonstrated that the lipopeptide biosurfactants pseudofactin and surfactin were able to limit fungal adhesion to polystyrene both in co-incubation and in pre-coating conditions.

Surface wettability measurements showed that AC7 BS coating by physical adsorption was successful, as the average value of the static contact angle decreased compared to control silicone disks. However, the wide standard deviation of the average contact angle of AC7 BS coated disks suggested that the biosurfactant was unevenly distributed on the sample surface. This may explain why lower percentages of inhibition of *C. albicans* adhesion and biofilm formation were observed in pre-coating assays rather than in co-incubation. Alternative coating methods are being investigated include plasma pre-treatment of the silicone disk surfaces (Ferreira et al. 2013) and AC7 BS physical adsorption and/or chemical grafting.

Finally, no antifungal activity towards *C. albicans* 40, *C. albicans* 42 and *C. albicans* IHEM 2894 planktonic cells and pre-formed biofilms was observed at concentrations up to 3 mg ml<sup>-1</sup>, suggesting that AC7 BS inhibited pathogen adhesion without affecting cell growth. Similarly, biosurfactants from *L. brevis* CV8LAC (Fracchia et al. 2010) and from *Bacillus licheniformis* V9T14 (Rivardo et al. 2011) were reported to have anti-biofilm but not antimicrobial activity.

Our results indicate that AC7 BS can be used as a coating agent to reduce efficiently *C. albicans* adhesion and biofilm formation on medical device materials. To our knowledge, this is the first time that the ability of lipopeptides to limit microbial adhesion on silicone has been demonstrated at physiological conditions and in the presence of FBS. However, further investigations are in progress to develop coating methodologies that will allow an even and stable distribution of the biosurfactant on the surface. In conclusion, we suggest that biosurfactant AC7, thanks to its anti-adhesive properties, could represent a

potential candidate to effectively limit colonisation of medical devices and prevent *C. albicans* infections.

**Acknowledgments** This work was partially funded by Regione Piemonte Grant POR-FESR Asse I—AGROBIOCAT Project.

# Compliance with ethical standards

**Conflict of interest** The authors declare that they have no conflict of interest.

## References

- Almirante B, Rodriguez D, Park BJ et al (2005) Epidemiology and predictors of mortality in cases of *Candida* bloodstream infection: results from population-based surveillance, Barcelona, Spain, from 2002 to 2003. *J Clin Microbiol* 43:1829–1835
- Amani H, Sarrafzadeh MH, Haghighi M, Mehrnia MR (2010) Comparative study of biosurfactant producing bacteria in MEOR applications. *J Pet Sci Eng* 75:209–214
- Banat IM, Franzetti A, Gandolfi I et al (2010) Microbial biosurfactants production, applications and future potential. *Appl Microbiol Biotechnol* 87:427–444. doi:10.1007/s00253-010-2589-0
- Biniarz P, Baranowska G, Feder-Kubis J, Krasowska A (2015) The lipopeptides pseudofactin II and surfactin effectively decrease *Candida albicans* adhesion and hydrophobicity. *Antonie Van Leeuwenhoek* 108:343–353. doi:10.1007/s10482-015-0486-3
- Busscher HJ, van Hoogmoed CG, Geertsema-Doornbusch GI, van der Kuijl-Booij M, van der Mei HC (1997) *Streptococcus thermophilus* and its biosurfactants inhibit adhesion by *Candida* spp. on silicone rubber. *Appl Environ Microbiol* 63:3810–3817
- Cameotra SS, Makkar RS (2004) Recent applications of biosurfactants as biological and immunological molecules. *Curr Opin Microbiol* 7:262–266
- Ceresa C, Tessarolo F, Caola I (2015) Inhibition of *Candida albicans* adhesion on medical-grade silicone by a *Lactobacillus*-derived biosurfactant. *J Appl Microbiol* 118:1116–1125. doi:10.1111/jam.12760
- Chandra J, Mukherjee PK, Ghannoum MA (2008) In vitro growth and analysis of *Candida* biofilms. *Nat Protoc* 3:1909–1924. doi:10.1038/nprot.2008.192
- Cochis A, Fracchia L, Martinotti MG, Rimondini L (2012) Biosurfactants prevent in vitro *Candida albicans* biofilm formation on resins and silicon materials for prosthetic devices. *Oral Surg Oral Med Oral Pathol Oral Radiol* 113:755–761. doi:10.1016/j.oooo.2011.11.004
- Comoglio F, Fracchia L, Rinaldi M (2013) Bayesian inference from count data using discrete uniform priors. *PLoS One*. doi:10.1371/journal.pone.0074388
- Crump JA, Collignon PJ (2000) Intravascular Catheter-Associated Infections. *Eur J Clin Microbiol Infect Dis* 19:1–8
- de Sainte CP (2009) Degradation of PEO in the solid state: a theoretical kinetic model. *Macromolecules* 42:3469–3482
- Elazzazy AM, Abdelmoneim TS, Almaghrabi OA (2015) Isolation and characterization of biosurfactant production under extreme environmental conditions by alkali-halophilic bacteria from Saudi Arabia. *Saudi J Biol Sci* 22:466–475
- Espinel-Ingroff A, Canton E, Martin-Mazuelos E, Pemán J (2009) Pharmacotherapy of *Candida* infections with echinocandins. *Clin Med Insights Ther* 1:889–897
- Falagas ME, Makris GC (2009) Probiotic bacteria and biosurfactants for nosocomial infection control: a hypothesis. *J Hosp Infect* 71:301–306. doi:10.1016/j.jhin.2008.12.008
- Fanning S, Mitchell AP (2012) Fungal biofilms. *PLoS Pathog.* doi:10.1371/journal.ppat.1002585
- Ferreira AM, Carmagnola I, Chiono V et al (2013) Surface modification of poly(dimethylsiloxane) by two-step plasma treatment for further grafting with chitosan–Rose Bengal photosensitizer. *Surf Coat Technol* 223:92–97
- Fracchia L, Cavallo M, Allegrone G, Martinotti MG (2010) A *Lactobacillus*-derived biosurfactant inhibits biofilm formation of human pathogenic *Candida albicans* biofilm producers. In: Méndez-Vilas A (ed) Current research, technology and education topics in applied microbiology and microbial biotechnology. Formatex Research Center, Badajoz, pp 827–837
- Fracchia L, Banat JJ, Cavallo M et al (2015) Potential therapeutic applications of microbial surface-active compounds. *AIMS Bioeng* 2:144–162
- Franzetti A, Gandolfi I, Raimondi C et al (2012) Environmental fate, toxicity, characteristics and potential applications of novel bioemulsifiers produced by *Variovorax paradoxus* 7bCT5. *Bioresour Technol* 108:245–251. doi:10.1016/j.biortech.2012.01.005
- Ghojvand H, Vahabzadeh F, Roayaei E, Shahraki AK (2008) Production and properties of a biosurfactant obtained from a member of the *Bacillus subtilis* group (PTCC 1696). *J Colloid Interface Sci* 324:17–26. doi:10.1016/j.jcis.2008.05.001
- Goldberg SP, Baddley JW, Aaron MF, Pappas PG, Holman WL (2000) Fungal infections in ventricular assist devices. *ASAIO J* 46:S37–S40
- Guery B, Arendrup M, Auzinger G et al (2009) Management of invasive candidiasis and candidemia in adult non-neutropenic intensive care unit patients: part I. Epidemiology and diagnosis. *Intensive Care Med* 35:55–62. doi:10.1007/s00134-008-1338-7
- Hawser SP, Douglas LJ (1994) Biofilm formation by *Candida* species on the surface of catheter materials in vitro. *Infect Immun* 62:915–921
- Hegstad K, Langsrud S, Lunestad BT, Scheie AA, Sunde M, Yazdankhah SP (2010) Does the wide use of quaternary ammonium compounds enhance the selection and spread of antimicrobial resistance and thus threaten our health? *Microb Drug Resist* 16:91–104. doi:10.1089/mdr.2009.0120
- Horn DL, Neofytos D, Anaissie EJ et al (2009) Epidemiology and outcomes of candidemia in 2019 patients: data from the prospective antifungal therapy alliance registry. *Clin Infect Dis* 48:1695–1703. doi:10.1086/599039
- Janek T, Lukaszewicz M, Krasowska A (2012) Antiadhesive activity of the biosurfactant pseudofactin II secreted by the



- Arctic bacterium *Pseudomonas fluorescens* BD5. BMC Microbiol. doi:10.1186/1471-2180-12-24
- Joshi S, Bharucha C, Desai A (2008) Production of biosurfactant and antifungal compound by fermented food isolate *Bacillus subtilis* 20B. Bioresour Technol 99:4603–4608
- Kanna R, Gummadi SN, Kumar GS (2014) Production and characterization of biosurfactant by *Pseudomonas putida* MTCC 2467. J Biol Sci 14:436–445
- Karchmer AV (2000) Infections of prosthetic valves and intravascular devices. In: Mandell G, Bennett JE, Dolin R (eds) Principles and practice of infectious diseases. Churchill Livingstone, Elsevier, Philadelphia, pp 903–917
- Kim HS, Yoon BD, Lee CH et al (1997) Production and properties of a lipopeptide biosurfactant from *Bacillus subtilis* C9. J Ferment Bioeng 84:41–46. doi:10.1016/S0922-338X(97)82784-5
- Kim PI, Ryu J, Kim YH, Chi YT (2010) Production of biosurfactant lipopeptides Iturin A, fengycin and surfactin A from *Bacillus subtilis* CMB32 for control of *Colletotrichum gloeosporioides*. J Microbiol Biotechnol 20:138–145
- Kojic EM, Darouiche RO (2004) *Candida* infections on medical devices. Clin Microbiol Rev 17:255–267. doi:10.1128/CMR.17.2.255-267.2004
- Kullberg BJ, Verweij PE, Akova M et al (2011) European expert opinion on the management of invasive candidiasis in adults. Clin Microbiol Infect 17:1–12. doi:10.1111/j.1469-0691.2011.03615.x
- Lai CC, Wang CY, Liu WL, Huang YT, Hsueh PR (2012) Time to positivity of blood cultures of different *Candida* species causing fungaemia. J Med Microbiol 61:701–704. doi:10.1099/jmm.0.038166-0
- Lazzell AL, Chaturvedi AK, Pierce CG, Prasad D, Uppuluri P, Lopez-Ribot JL (2009) Treatment and prevention of *Candida albicans* biofilms with caspofungin in a novel central venous catheter murine model of candidiasis. J Antimicrob Chemother 64:567–570. doi:10.1093/jac/dkp242
- Lee SC, Yoo JS, Kim SH et al (2006) Production and characterization of lipopeptide biosurfactant from *Bacillus subtilis* A8–8. J Microbiol Biotechnol 16:716–723
- Maki DG, Tambyah PA (2001) Engineering out the risk for infection with urinary catheters. Emerg Infect Dis 7:342–347
- Mayer FL, Wilson D, Hube B (2013) *Candida albicans* pathogenicity mechanisms. Virulence 4:119–128. doi:10.4161/viru.22913
- Nitschke M, Pastore GM (2006) Production and properties of a surfactant obtained from *Bacillus subtilis* grown on cassava wastewater. Bioresour Technol 97:336–341
- Pecci Y, Rivardo F, Martinotti MG, Allegrone GJ (2010) LC/ESI-MS/MS characterisation of lipopeptide biosurfactants produced by the *Bacillus licheniformis* V9T14 strain. Mass Spectrom 45:772–778. doi:10.1002/jms.1767
- Ramage G, Saville SP, Thomas DP, López-Ribot JL (2005) *Candida* biofilms: an update. Eukaryot Cell 4:633–638
- Rautela R, Singh AK, Shukla A, Cameotra SS (2014) Lipopeptides from *Bacillus* strain AR2 inhibits biofilm formation by *Candida albicans*. Antonie Van Leeuwenhoek 105:809–821
- Rivardo F, Turner RJ, Allegrone G, Ceri H, Martinotti MG (2009) Anti-adhesion activity of two biosurfactants produced by *Bacillus* spp. prevents biofilm formation of human bacterial pathogens. Appl Microbiol Biotechnol 83:541–553. doi:10.1007/s00253-009-1987-7
- Rivardo F, Martinotti MG, Turner RJ, Ceri H (2011) Synergistic effect of lipopeptide biosurfactant with antibiotics against *Escherichia coli* CFT073 biofilm. Int J Antimicrob Aging 37:324–331. doi:10.1016/j.ijantimicag.2010.12.011
- Rodrigues LR, Teixeira JA (2010) Biomedical and therapeutic applications of biosurfactants. Adv Exp Med Biol 672:75–87
- Rodrigues L, Banat IM, Teixeira J, Oliveira R (2006a) Biosurfactants: potential applications in medicine. J Antimicrob Chemother 57:609–618
- Rodrigues LR, Banat IM, van der Mei HC, Teixeira JA, Oliveira R (2006b) Interference in adhesion of bacteria and yeasts isolated from explanted voice prostheses to silicone rubber by rhamnolipid biosurfactants. J Appl Microbiol 100:470–480
- Rodriguez-Tudela JL, Arendrup MC, Barchiesi F et al (2008) EUCAST definitive document EDef 7.1: method for the determination of broth dilution MICs of antifungal agents for fermentative yeasts. Clin Microbiol Infect 14:398–405
- Ruhnke M, Rickerts V, Cornely OA et al (2011) Diagnosis and therapy of *Candida* infections: joint recommendations of the German speaking mycological society and the paul-ehrlich-society for chemotherapy. Mycoses 54:279–310. doi:10.1111/j.1439-0507.2011.02040.x
- Seydlová G, Svobodová J (2008) Review of surfactin chemical properties and the potential biomedical applications. Cent Eur J Med 3:123–133
- Singh P, Cameotra SS (2004) Potential applications of microbial surfactants in biomedical sciences. Trends Biotechnol 22:142–146
- Singh A, Van Hamme JD, Ward OP (2007) Surfactants in microbiology and biotechnology: part 2. Application aspects. Biotechnol Adv 25:99–121
- Thompson DS, Carlisle PL, Kadosh D (2011) Coevolution of morphology and virulence in *Candida* species. Eukaryot Cell 10:1173–1182. doi:10.1128/EC.05085-11
- van de Veerdonk FL, Netea MG, Joosten LA, van der Meer JWM, Kullberg BJ (2010) Novel strategies for the prevention and treatment of *Candida* infections: the potential of immunotherapy. FEMS Microbiol Rev 34:1063–1075. doi:10.1111/j.1574-6976.2010.00232.x
- Wisplinghoff H, Bischoff T, Tallent SM, Seifert H, Wenzel RP, Edmond MB (2004) Nosocomial bloodstream infections in US hospitals: analysis of 24,179 cases from a prospective nationwide surveillance study. Clin Infect Dis 39:309–317