

Macrophage immunomodulation: An indispensable tool to evaluate the performance of wound dressing biomaterials

Original

Macrophage immunomodulation: An indispensable tool to evaluate the performance of wound dressing biomaterials / Varela, Patrícia; Sartori, Susanna; Viebahn, Richard; Salber, Jochen; Ciardelli, Gianluca. - In: JOURNAL OF APPLIED BIOMATERIALS AND FUNCTIONAL BIOMATERIALS. - ISSN 2280-8000. - 17:1(2019), pp. 1-10. [10.1177/2280800019830355]

Availability:

This version is available at: 11583/2727132.21 since: 2019-03-06T13:34:43Z

Publisher:

Sage

Published

DOI:10.1177/2280800019830355

Terms of use:

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

Publisher copyright

(Article begins on next page)

Macrophage immunomodulation: An indispensable tool to evaluate the performance of wound dressing biomaterials

Journal of Applied Biomaterials &
Functional Materials
January-March: 1–10
© The Author(s) 2019
Article reuse guidelines:
sagepub.com/journals-permissions
DOI: 10.1177/2280800019830355
journals.sagepub.com/home/jbf
 SAGE

Patrícia Varela^{1,2} , Susanna Sartori¹, Richard Viebahn²,
Jochen Salber² and Gianluca Ciardelli¹

Abstract

A major burden of the healthcare system resides in providing proper medical treatment for all types of chronic wounds, which are usually treated with dressings to induce a faster regeneration. Hence, to reduce healing time and improve the patient's quality of life, it is extremely important to select the most appropriate constituent material for a specific wound dressing. A wide range of wound dressings exist but their mechanisms of action are poorly explored, especially concerning the immunomodulatory effects that occur from the interactions between immune cells and the biomaterial. Tissue-resident and monocyte-derived recruited macrophages are key regulators of wound repair. These phagocytic immune cells exert specific functions during the different stages of wound healing. The recognition of the substantial role of macrophages in the outcome of the wound healing process requires specific understanding of the immunomodulatory effects of commercially available or newly developed wound dressings. For a precise intervention, it is necessary to obtain more knowledge on macrophage polarization in different phases of wound healing in the presence of the dressings. The main purpose of this review is to collect clinical cases in which macrophage immunomodulation was taken into consideration as an indicator of the performances of novel or mainstream wound dressing materials, including those provided with antimicrobial properties.

Keywords

Dressings, immunomodulation, macrophages, wound

Date received: 3 October 2018; revised: 3 December 2018; accepted: 16 January 2019.

Introduction

Wound healing is a complex process in which different cell types (e.g. macrophages) are involved, progression is strictly regulated, and different cellular activities overlap.¹ If an atypical progression takes place, a chronic wound may result, impacting the patient's quality of life and the economic cost to the healthcare system.²

Recent research has been focused on understanding the factors that influence the healing progress and new discoveries elucidating mechanisms of physiologic wound repair have been reported. The development of advanced wound dressing biomaterials, able to play an active role in wound repair, is also a key issue, which is attracting increasing attention.

Therefore, the main objective of this manuscript is to review established and recent concepts about wound repair, with a focus on chronic wounds, and to underline the importance of macrophages in this context, as well as

¹Department of Mechanical and Aerospace Engineering, Politecnico di Torino, Turin, Italy

²Chirurgische Klinik, Universitätsklinikum Knappschafts-Krankenhaus Bochum, Ruhr-University Bochum, Germany

Corresponding author:

Patrícia Varela, Zentrum für klinische Forschung (ZKF), Ruhr Universität Bochum, AG Medical Biomaterials, Universitätsstr. 150, Room 1.050, 44801 Bochum, Germany.
Email: patricia.varela@polito.it





Figure 1. Morphology of chronic wounds : (a) colonized diabetic foot ulcer at the heel; (b) infected venous leg ulcer; (c) colonized pressure ulcer of the right ischium.

the effect of different types of wound dressing biomaterials on macrophage function.

Chronic wounds

Chronic wounds: A never-ending nightmare

Non-healing wounds, also known as chronic wounds, of diverse etiologies, are a significant health problem worldwide, being a major cause of morbidity and mortality. Owing to the extent of its strong social impact, wounds have been described as a “silent epidemic.”² Concomitant with the increase of the obese population, increased diabetic patients, and prolongation of life expectancy, the number of chronic wound cases is ascending alarmingly. Accurate epidemiological analysis concerning chronic wounds is scarce; consequently, the determination of the precise cost of wound management is affected. Nevertheless, there is a body of evidence that the incidence of chronic wounds is increasing, becoming an economic burden in developed countries.^{2–4}

A wound is characterized by the disturbance of the tissue integrity and structural organization of body cells, with or without destroying them.⁵ If a wound fails to initiate its physiologic regeneration after 2–3 weeks and does not regain its structural and functional integrity (remaining open for 3 months), it is classified as a non-healing (chronic) wound.^{6–8} Examples of chronic wounds are diabetic foot ulcers (Figure 1(a)), venous leg ulcers (Figure 1(b)), and pressure ulcers (Figure 1(c)).⁹

Disruption of healing process by bacterial infection and persistent inflammation

Chronic wounds are associated with an increased risk of infection, since long-term cutaneous wounds are more susceptible, owing to the loss of the protective barrier of intact skin. In fact, one of the main causes of impaired wound healing is the presence of high bacterial contamination.¹⁰ The progression from contamination through colonization to infection on open wounds depends on the bacterial multiplication rate, crosstalk between different microorganisms,

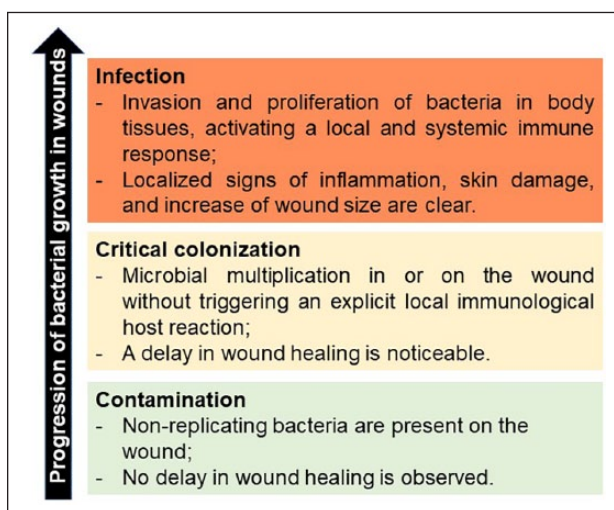


Figure 2. Description of cutaneous wounds by the establishment and growth of bacteria.¹³

and the initiation of the innate immune response, such as the disturbance of a successful recognition and ingestion of invading microorganisms, owing to the failure of the opsonization effect. This effect involves marking pathogens with antibodies and factors of the complement system, in order to attract phagocytes (e.g. macrophages) to the site of contamination and induce the elimination of the pathogens.^{11,12} Figure 2 describes the most common effects induced by the progression of bacterial growth in wounds. Starting from a contaminated state, in which no major negative signals are observed, the system evolves to a severe state (established infected wound), in which pathogens proliferate and an inflammatory response is clearly activated.

In the past years, there has been increasing evidence that bacteria exist in chronic wounds as organized communities, in which they are able to cooperate and communicate. These colonies are commonly defined as biofilms.^{10, 14,15} Biofilms are usually polymicrobial in nature and are surrounded by a self-produced extracellular polysaccharide matrix, which contains extracellular enzymes, plasmids, and signal molecules for chemical communication (quorum sensing).¹⁶ In wound biofilms, blood components may

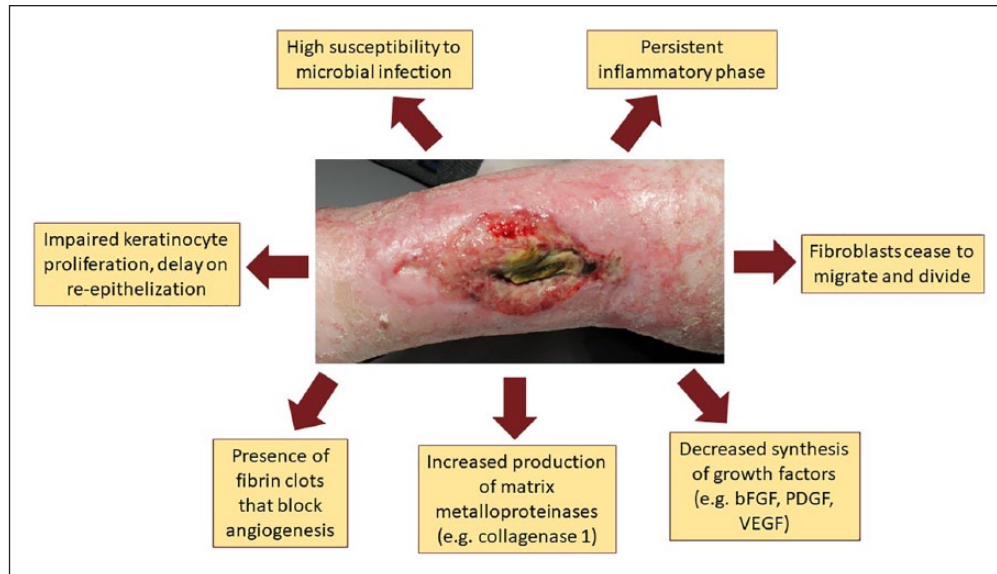


Figure 3. Abnormalities in the chronic wound environment.

bFGF: basic fibroblast growth factor; PDGF: platelet-derived growth factor; VEGF: vascular endothelial growth factor.

also be enclosed in the matrix.¹⁷ Moreover, bacteria show a higher tolerance to antibiotics and have a barrier protection against the host immune system.^{11,18}

Staphylococcus aureus is the most common bacterial species found in chronic wounds, followed by *Enterococcus faecalis*, *Pseudomonas aeruginosa*, coagulase-negative staphylococci, and anaerobic bacteria.^{19,20}

For successful removal of contaminating bacteria, inflammation is a crucial part of the normal wound healing process. However, when the microbial clearance is incomplete, the progression of bacterial growth on wounds reaches a critical colonization state and the immunologic inflammatory process will be prolonged.¹

The combination of the presence of bacteria (especially as a biofilm) and persistent inflammatory reaction involves the overexpression of pro-inflammatory cytokines (e.g. interleukin-1 (IL-1), tumor necrosis factor- α (TNF- α), chemokines (C-X-C motif ligand 9 (CXCL9), CXCL10, and CXCL11) and other signal molecules (e.g. signal transducer and activator of transcription 1 and nitric oxide synthase 2). This framework is the basis for the continuous non-healing status of chronic wounds.^{1,11}

Natural or synthetic antimicrobial wound dressing biomaterials can play an important role in preventing or decreasing the high bacterial contamination and provide a chance for the continuation of normal wound healing.²¹

Wound healing is a highly complex multicellular and regulated metabolic process. The normal wound healing stages, in timeline order, comprise four overlapping phases: hemostasis, inflammation, proliferation, and remodeling.^{22,23} In chronic wounds (Figure 3), bacterial critical colonization or infection is present and the inflammatory phase is persistent for a long period of time (from at least 4 weeks to several months).⁶ During this period,

several irregularities are present and, finally, no proper shift to the proliferation and remodeling phases occurs.²⁴

Macrophages in wound repair and regeneration

Recruited monocyte-derived macrophages and tissue-resident macrophages are essential key players in response to a tissue injury. After an injury, circulating neutrophils are the first to reach the site of damage. This is followed by the infiltration of monocytes, which differentiate into macrophages, joining tissue-resident macrophages with the mission of restoring integrity.²⁵ Macrophages are mononuclear leukocytes, part of the innate immune system, and are required for successful skin regeneration.²⁶ In fact, macrophages are involved in all phases of wound healing. Until recently, this immune cell population was considered a “background actor”, but during the last decade scientists’ attention exponentially increased, leading them to unveil macrophage immunomodulation, which is relevant in many diseases.²⁷ Wound healing research has revealed that plasticity, flexibility, and heterogeneity of macrophages have a crucial participation in obtaining successful cutaneous regeneration. Das et al. have compiled several studies that clearly prove the participative role of wound macrophages in scavenging, phagocytosis, efferocytosis, antigen presentation, promotion of repair, extracellular signaling, and angiogenesis.²⁸ Special attention has been given to the capacity of macrophages to remove debris from dead and dying cells, as a resolution of inflammation and a shift toward regeneration.²⁹

Using a very simplistic nomenclature, macrophages are able to polarize into two categories, depending on the environmental stimuli: classically activated M1 pro-inflammatory macrophages, which are involved in

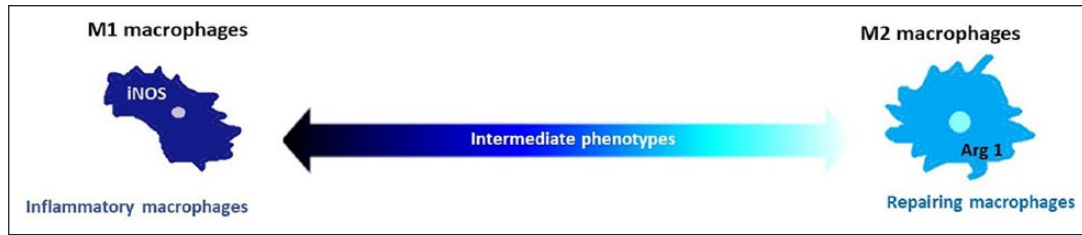


Figure 4. Macrophage polarization occurring in a spectrum between M1 and M2 macrophages. Arg 1: arginase 1; iNOS: inducible nitric oxide synthase.

Table 1. Most common characteristics of M2-like macrophages subtypes.^{23,32,38–41}

M2 subtype	Stimulation	Membrane receptors	Secretion		
			Cytokines	Chemokines	Signals
M2a	IL-4, IL-13	CD163, CD206	IL-10, IL-1RA	CCL17, CCL18, CCL22, CCL24	STAT-3, Arg1, TGF- β
M2b	IC, TLR/IL-1R ligands	CD86, MHC-II	TNF- α , IL-1 β , IL-6, IL-10	CCL1	SOCS3, COX-2
M2c	IL-10	CD86, CD163, CD206	IL-10	CCL16, CCL18, CXCL13	Arg 1, EGF, TGF- β , MMP-9
M2d	IL-6	CD14, CD16, CD68	TNF- α , IL-10, IL-12	CXCL10	TGF- β , VEGF

Arg1, arginase; CCL, C-C motif ligand; CCR, C-C chemokine receptor; CD, cluster of differentiation; COX, cyclooxygenase; CXCL, C-X-C motif ligand; EGF, epidermal growth factor; IC, immune complex; IGF, insulin-like growth factor; IL, interleukin; IL-1RA, IL-1 receptor antagonist; MHC, major histocompatibility complex; MMP, matrix metalloproteinase; SOCS, suppressor of cytokine signaling; STAT, signal transducer and activator of transcription; TGF, transforming growth factor; TLR, toll-like receptor; TNF, tumor necrosis factor; VEGF, vascular endothelial growth factor.

combating infections, or alternatively activated M2 tissue-healing macrophages, which are connected with tissue remodeling^{28,30,31} This polarization occurs as a continuous spectrum, in which macrophages shift and gain different metabolic and phenotypic characteristics (Figure 4).

During the inflammatory phase of cutaneous healing, M1 macrophages are predominant. These have an extremely important role in the phagocytosis of dead or dying cells and their components, besides orchestrating more macrophages immune cells at the site of injury.³² M1-like macrophages are known for their high production of nitric oxide, an antibacterial oxidative metabolite, and for being efficient antigen-presenting cells. Their stimulation is induced, for example, by lipopolysaccharides of the outer membrane of Gram-negative bacteria or interferon- γ (IFN- γ), and consequently its metabolism is activated toward producing high levels of pro-inflammatory cytokines, such as IL-1 β , IL-6, and TNF- α .³³ Additionally, this population is characterized by the release of reactive oxygen species, mainly derived from hydrogen peroxide (H₂O₂) and superoxide anions (O₂⁻).³⁴ Reactive oxygen species have been described as chemo-attractants of monocytes to the wound location.³⁵

Conversely, M2-like macrophages appear in greater quantities during the proliferation and remodeling phases

of wound healing, during which they express high levels of anti-inflammatory cytokines, such as IL-4 and IL-10, and the enzyme arginase-1, which is believed to be a main contributor to wound healing.²⁶ The classification of M2-like macrophages is still controversial and a subject of persistent study; hence, many types of subdivision are found in the literature, especially depending on specific diseases. It is not clear whether these intermediate phenotypes can be divided in such a strict categorized manner, owing to their plasticity through a continuous spectrum. However, it seems currently well accepted that M2-like macrophages are divided into four different subtypes (M2a, M2b, M2c, and M2d) in what concerning the wound healing process (Table 1).^{32,36,37}

Briefly, M2a macrophages release platelet-derived growth factors and stimulate fibroblasts to proliferate and secrete extracellular matrix, an essential factor for angiogenesis in wound repair.³³ M2b macrophages have been shown to have an important function in decreasing the inflammatory process by synthesizing high levels of the anti-inflammatory cytokine IL-10, despite the fact that these cells still produce pro-inflammatory cytokines (e.g. TNF- α).^{23,26} M2c macrophages are intervenient in vascular and matrix renovation, owing to the high production of extracellular matrix. Lastly, M2d macrophages are pro-angiogenic and produce high levels of vascular endothelial growth factor.³²

Macrophages: Dysfunction in chronic wounds

Non-healing wounds can be exacerbated because of improperly acting macrophages. In normal wound healing, macrophages induce an initial pro-inflammatory response and shift to a pro-repairing action. This inflammatory-to-regenerative shift is completely dependent on their capacity to perform phagocytosis of dead neutrophils and remaining debris.⁴² In healthy processes, M1 macrophages are partially converted to M2b macrophages to overcome inflammation; however, M1 macrophages can accumulate in chronic wounds, owing to environmental stimuli that do not allow the transition.³² As a consequence, a highly inflammatory environment is maintained, and wound closure is delayed, as proved by the increased levels of IL-1 and TNF- α (pro-inflammatory cytokines produced by M1-like macrophages) in chronic wound fluids.⁴³ Moreover, the fluid also contains higher levels of matrix metalloproteinases than those usually observed during the proliferation and remodeling phases, leading to protein and extracellular matrix degradation, and, as a consequence, impaired tissue regeneration.⁴⁴ Dysregulation of M2-like macrophages is also a big concern. Alteration of their typical phenotype and metabolic characteristics dictates the level of collagen deposition and scar formation.³² As an example, an overexpression of type-III collagen has been found in hypertrophic scars.⁴⁵

Wound dressings

The correct selection of wound dressing biomaterials is vital for a faster wound recovery of patients with non-healing cutaneous injuries. Hence, studies must provide information about biocompatibility, possible antibacterial efficacy, and material properties.⁴⁶

Such products as bandages and gauzes, of natural or synthetic origin, are commonly used to cover an acute wound to prevent contamination.⁴⁷ This type of dressing lacks many features for proper wound healing, such as maintaining wound hydration and preventing wound contamination. Modern wound dressings, based on polymers, can be made bioactive by the incorporation of antibiotics (e.g. gentamicin), metals (e.g. silver), or growth factors (e.g. fibroblast growth factor 1).⁴⁸

Unsurprisingly, the diverse surface morphologies and incorporated active components will induce an effect on the phenotype and metabolism of macrophages. Hence, it is extremely important to study the immunomodulatory effects of wound dressing biomaterials.

Wound healing biomaterials to the rescue: Are biomaterial–macrophage interactions friends or foes?

Countless wound dressings are commercially available, and a number of new dressings are under development, but

their mechanisms of action are poorly understood. Therefore, there is a great interest in exploring immune cell–biomaterial interactions. Owing to the importance of the effector functions of macrophages, it has become essential to obtain evidence about the polarization of macrophages and immunomodulation in the presence of different biomaterials.⁴⁹ As previously discussed, macrophages are dysregulated in non-healing wounds. Furthermore, a correlation between prolonged M1 cell populations and delayed wound repair has been demonstrated.⁵⁰ The importance of a wound dressing biomaterial that is able to stimulate the shift from M1 to M2 tissue-healing macrophages, or at least to avoid M1 pro-inflammatory phenotype perpetuation, is thus clearly evident. In the rest of this paper, relevant work describing the effect of non-commercially and commercially available wound dressing biomaterials on the immunomodulation of macrophages (Table 2) will be analyzed. To test their response to wound dressings, various techniques can be applied to macrophages after exposition to the biomaterial influence, such as gene up- or downregulation evaluation by polymerase chain reaction, determination of expressed membrane markers through flow cytometry, secretion of cytokines and other signal molecules by enzyme-linked immunosorbent assay, and evaluation of posttranslational proteins by proteomics.

Commercially available wound dressings. Alginate dressings are widely used in the treatment of exuding wounds and may enhance the healing process. Thomas and co-workers evaluated the capacity of interaction between alginates present in commercially available absorbent wound dressings with macrophages,⁴⁹ and observed that macrophages derived from the human histiocytic lymphoma cell line U937 in the presence of a calcium alginate dressing (Sorb-san) at 1 mg/mL stimulated the production of 302 ± 19 pg/mL of TNF- α and that the alginate calcium sodium dressing Kaltostat induced the production of 839 ± 36 pg/mL of TNF- α . Two other alginate dressings were also tested without significant differences. Thomas and co-workers concluded that alginate dressings have the potential to improve wound healing, owing to the ability to activate wound macrophages in producing TNF- α , a pro-inflammatory signal.⁴⁹ This cytokine has been found to be secreted by M2b and M2d macrophages but, contradictorily, it has been proved that prolonged expression of TNF- α contributes to a delayed wound healing, for example, in diabetic wounds.⁵¹

In a study conducted by Witherel and collaborators,⁵² the responses of monocyte-derived macrophages isolated from blood (one donor) to four currently applied wound dressing biomaterials were analyzed and compared. The four wound dressing biomaterials were:

- (a) *OASIS® Wound Matrix*. Extracellular matrix from porcine small intestinal mucosa;

Table 2. Selected studies that unravel alterations of macrophage phenotype or metabolism in the presence of wound dressing biomaterials.

	Type of biomaterial	Constitution of biomaterial	Loaded molecules	Testing model	Main alterations on macrophages phenotype/metabolism	Ref.
Commercially available wound dressing biomaterials	Natural	Calcium alginate dressing (Sorbsan)	None	Macrophages derived from human histiocytic lymphoma cell line U937 (basal state M0)	↑TNF- α secretion	49
		Alginate calcium sodium dressing (Kaltostat)				
		Extracellular matrix from porcine small intestinal mucosa OASIS®		Monocyte-derived macrophages isolated from human blood (basal state M0)	↓M2a anti-inflammatory markers CCL22 and TIMP3 and ↑M1 genes	52
		Fiber matrix of cross-linked bovine tendon type I collagen and chondroitin-6-sulfate INTEGRA™			↓M2a anti-inflammatory markers CCL22 and TIMP3	
Non-commercially available wound dressing biomaterials		Decellularized matrix composed of collagen and elastin AlloMend®			↑CD163 expression	
		Decellularized fetal bovine dermis with type I and II collagen PriMatrix®			↓genes CCL22 and TIMP3, and ↑pro-inflammatory cytokine TNF- α and expression of CD163 (M2c)	
		Composites produced from keratin, cellulose, and chitosan		THP-1 derived macrophages (basal state M0)	↑CD11b expression	53
	Synthetic	Polycaprolactone nanofibers	Curcumin	Mouse peritoneal macrophages (pro-inflammatory state M1)	↓ release of IL-6	58
		Polycaprolactone	Dimethyl-oxalylglycine	RAW264.7 macrophages (basal state M0)	↓ pro-inflammatory cytokines (IL-1, IL-6) and ↑ anti-inflammatory signals (IL-4, TGF- β) and growth factors (IGF, HB-EGF)	61
		Polycaprolactone	Polysaccharide-atorvastatin nano-reservoirs	THP-1 derived macrophages (pro-inflammatory state M1)	↓ pro-inflammatory cytokines TNF- α and IL-6	62
	Natural	Avian eggshell membrane particles	None		↓ IL-1, IL-6 and TNF- α secretion, ↑ anti-inflammatory IL-10 production, ↓ pro-inflammatory response receptors (e.g. toll-like receptor 4)	63
		Alginate	Aloe vera	Histologic samples with macrophages from mice	Modulate the inflammatory phase, with ↑ presence of macrophages	64

CCL, C-C motif ligand; CD, cluster of differentiation; EGF, epidermal growth factor; IGF, insulin-like growth factor; HB-EGF, heparin-binding EGF-like growth factor; IL, interleukin; TNF, tumor necrosis factor.

CCL, C-C motif ligand; CD, cluster of differentiation; EGF, epidermal growth factor; IGF, insulin-like growth factor; HB-EGF, heparin-binding EGF-like growth factor; IL, interleukin; M, macrophages; TGF, transforming growth factor; THP-1, human monocytic cell line; TIMP, tissue inhibitor of metalloproteinases; TNF, tumor necrosis factor.

- (b) *INTEGRA™ Bilayer Matrix*. Dermal layer made of porous fiber matrix of cross-linked bovine tendon type I collagen and chondroitin-6-sulfate, epidermal layer constituted of polysiloxane;
- (c) *AlloMend® Acellular Dermal Matrix*. Decellularized matrix composed mainly of collagen and elastin;
- (d) *PriMatrix® Dermal Repair Scaffold*. Decellularized fetal bovine dermis rich in type I and II collagen.

The expression of M2a anti-inflammatory markers CCL22 and TIMP3 in the presence of OASIS® and INTEGRA™ was downregulated; this suggests a possible inhibition of extracellular matrix secretion and fibrosis, which are key phenomena for wound closure. OASIS® was also responsible for the largest increase of expression of M1 genes; hence, Witherel and collaborators⁵² considered this product significantly pro-inflammatory. Although INTEGRA™ is constituted of collagen I and the anti-inflammatory chondroitin-6-sulfate, an opposite effect was observed and the reason might be the presence of glutaraldehyde in this dressing. OASIS® and INTEGRA™ seem to be a poor option for chronic wound cases.

In the case of PriMatrix®, a downregulation of the genes CCL22 and TIMP3 was also observed. Moreover, this wound dressing caused an overexpression of the pro-inflammatory cytokine TNF- α and increased the expression of CD163, associated with M2c, which is a less fibrotic phenotype.⁵² For last, AlloMend® only induced an effect of the upregulation of CD163, and it was considered the dressing with the lowest influence on macrophage response. Overall, this work shows that the dressings have a direct effect on macrophage immunomodulation, and give us a very important take home message, which is “the same wound dressing can have a dual effect promoting the polarization to M1- and M2-like macrophages”.

Non-commercially available materials for wound dressings. Composites produced from keratin, cellulose, and chitosan have shown bactericidal and anti-inflammatory properties.⁵³ For instance, chitosan is well known for its highly antimicrobial activity against fungi and bacteria.⁵⁴ As a result of these properties, chitosan is used in the production of commercial wound dressing products, such as Tegaserb® and KytoCel®, alone or in combination with synthetic polymers, such as poly(ϵ -caprolactone) and polyethylene oxide.^{55,56} Anti-inflammatory properties were detected on THP-1 derived macrophages in the presence of composites produced from keratin, cellulose, and chitosan.⁵³ Herein, the authors of these studies noticed that the composites induced an increase in the expression of CD11b on macrophages. As a support, it has been proven that the depletion of CD11b⁺ macrophages in a bacterial pathogen-induced inflammation model delayed inflammation resolution and antigen clearance, indicating its importance for proper wound healing.⁵⁷

In a study of Merrell and co-workers, curcumin-loaded poly(ϵ -caprolactone) (PCL) nanofibers were evaluated for wound healing applications.⁵⁸ PCL is a synthetic polymer utilized in wound dressing biomaterials⁵⁹; it possesses several advantages over other synthetic polymers, including stability, low cost, mechanical strength, and biocompatibility.⁶⁰ In combination with the anti-oxidant curcumin, these novel nanofibers reduced the anti-inflammatory reaction, proven by the low release of IL-6 observed in mouse monocyte-derived macrophages, which were previously polarized to the M1 state by lipopolysaccharides. *In vivo* studies showed a quicker wound healing rate on diabetic mice model wounds, proving the efficacy of curcumin-loaded nanofibers in chronic wounds.⁵⁸

Likewise, in a study in which the hydroxylase inhibitor dimethylxalylglycine was embedded in PCL, a similar anti-inflammatory modulation of macrophages was demonstrated.⁶¹ On RAW264.7 macrophages, Zhang et al.⁶¹ observed a decreased production of the pro-inflammatory cytokines (IL-1, IL-6) and an enhancement of anti-inflammatory signals (IL-4, TGF- β) and growth factors (insulin-like growth factor, heparin-binding epidermal-growth-factor-like growth factor).

Schwinté and colleagues produced electrospun PCL containing polysaccharide-atorvastatin nano-reservoirs by using complexes with poly-aminocyclodextrin.⁶² These membranes were tested on THP-1 stimulated by lipopolysaccharides. A pronounced decrease in the production of pro-inflammatory cytokines TNF- α and IL-6 (reductions of 60 and 80%, respectively) was verified for these M1-like macrophages. This strategy is very interesting to overcome the exacerbated inflammatory phase that occurs in non-healing injuries.

Natural biomaterials, such as avian eggshell membrane have been widely used on injured skin, especially in Asian countries. In a recent study, processed avian eggshell membrane particles have been found to contain collagen, hyaluronic acid, sulfated glycosaminoglycans, and *N*-glycans, which have anti-inflammatory properties and a high potential as a biological wound dressing biomaterial for chronic wounds.⁶³ After polarization of macrophages to an inflammatory state, particles were applied and a reduction of IL-1, IL-6, and TNF- α secretion occurred, while production of the anti-inflammatory IL-10 increased. Furthermore, the expression of important pro-inflammatory response receptors (e.g. toll-like receptor 4) were downregulated.⁶³

Other examples of non-commercial materials are the novel alginate dressings with aloe vera, which are able to modulate the inflammatory phase, promote angiogenesis, and stimulate type I collagen production.⁶⁴

Biomaterial–macrophage interactions: Main drawbacks

When a biomaterial is in contact within the human body, a series of events occur. These events include^{65,66}:

- Immediate protein adsorption on the biomaterial;
- Cell infiltration (i.e. neutrophils, monocytes, and platelets) and adhesion to the biomaterial surface;
- Production of chemokines and cytokines by adhered cells;
- Macrophage fusion forming multinucleated foreign body giant cells;
- Interaction between macrophages or foreign body giant cells and inflammatory or wound healing cells in general.

The formation of foreign body giant cells originates from fused variants of M1 macrophages in an attempted phagocytic response to eradicate a large foreign body.^{66–68} As a result of this effort, foreign body giant cells secrete reactive oxygen species and matrix metalloproteinases, provoking a failure to deposit extracellular matrix and the consequent local persistence of damage-associated molecular patterns and continuous activation of macrophages.^{69,70} Since regeneration is not achieved, tissue granulation occurs, finally forming a fibrous capsule.^{71,72} This is a very important effect in the cutaneous healing area, especially if a wound dressing biomaterial must be left in contact for a prolonged period.

This foreign body response also alters the material surface, leading to biomaterial degradation, inducing a continuous inflammatory response and consequent failure of injury repair, which finally has an undesirable impact on biocompatibility.⁷¹ Hence, the formation of foreign body giant cells is the “dark side” of macrophages in interaction with biomaterials.

Final remarks

Biomaterial–macrophage interactions are a “hot topic” nowadays. A beneficial macrophage response in contact with a biomaterial is therefore crucial for a successful overcome of the perpetual inflammatory phase that occurs in chronic wounds. Thus, biomaterials that induce the “M1–M2 shift” are ideal candidates for promoting wound closure and avoiding susceptibility to contamination from the early stages. Not only a huge effort has been given to develop newly synthesized biomaterials with anti-inflammatory properties, but also a deeper understanding of the selective impact on wound macrophage polarization of currently applied biomaterials is being explored. However, the field of macrophage immunomodulation and biomaterial–macrophage interaction is still “immature”. The progress that has been made in understanding macrophage polarization under physiological versus pathological wound conditions has given a boost to research in biomaterial science. The focus on immunomodulatory effects may lead to the establishment of a novel generation of immunomodulating biomaterials, able to influence the behavior of the wound healing key players, such as different macrophage phenotypes.

Declaration of conflicting interest

The authors declared no potential conflicts of interest with respect to the research, authorship, and/or publication of this article.

Funding

The authors disclosed receipt of the following financial support for the research, authorship, and/or publication of this article: This work was supported by the “Drug-Free Antibacterial Hybrid Biopolymers for Medical Applications” HyMedPoly project and the European Union’s Horizon 2020 research and innovation programme under the Marie Skłodowska-Curie Action MSCA-ITN-2014-EID: Marie Skłodowska-Curie Innovative Training Networks (grant number 643050).

ORCID iD

Patrícia Varela  <https://orcid.org/0000-0001-8358-1581>

Jochen Salber  <https://orcid.org/0000-0001-9738-2305>

References

1. Guo S and DiPietro LA. Factors affecting wound healing. *J Dent Res* 2010; 89(3): 219–229.
2. Sen CK, Gordillo GM, Roy S, et al. Human skin wounds: A major snowballing threat to public health and the economy. *Wound Repair Regen* 2009; 17(6): 763–771.
3. Heyer K, Herberger K, Protz K, et al. Epidemiology of chronic wounds in Germany: Analysis of statutory health insurance data. *Wound Repair Regen* 2016; 24(2): 434–442.
4. Guest JF, Ayoub N, McIlwraith T, et al. Health economic burden that wounds impose on the National Health Service in the UK. *BMJ Open* 2015; 5(12): e009283.
5. Kujath P and Michelsen A. Wounds—from physiology to wound dressing. *Dtsch Arztebl Int* 2008; 105(13): 239–248.
6. Han G and Ceilley R. Chronic wound healing: A review of current management and treatments. *Adv Ther* 2017; 34(3): 599–610.
7. Iqbal A, Jan A, Wajid MA, et al. Management of chronic non-healing wounds by hirudotherapy. *World J Plast Surg* 2017; 6(1): 9–17.
8. Werdin F, Tennenhaus M, Schaller H-E, et al. Evidence-based management strategies for treatment of chronic wounds. *Eplasty* 2009; 9: e19.
9. Lindholm C and Searle R. Wound management for the 21st century: Combining effectiveness and efficiency. *Int Wound J* 2016; 13: 5–15.
10. Leaper D, Assadian O and Edmiston CE. Approach to chronic wound infections. *Br J Dermatol* 2015; 173(2): 351–358.
11. Edwards R and Harding KG. Bacteria and wound healing. *Curr Opin Infect Dis* 2004; 17(2): 91–96.
12. Hiemstra P and Daha M. Opsonization. In: Delves PJ (ed.) *Encyclopedia of immunology*. London: Academic Press, 1998; pp. 1885–1888.
13. Gottrup F, Apelqvist J, Bjansholt T, et al. EWMA document: Antimicrobials and non-healing wounds. Evidence, controversies and suggestions. *J Wound Care* 2013; 22(5 Suppl.): S1–S89.
14. Burmølle M, Thomsen TR, Fazli M, et al. Biofilms in chronic infections—a matter of opportunity—monospecies biofilms in multispecies infections. *FEMS Immunol Med Microbiol* 2010; 59(3): 324–336.

15. Zhao G, Usui ML, Lippman SI, et al. Biofilms and inflammation in chronic wounds. *Adv Wound Care* 2013; 2(7): 389–399.
16. Ikuma K, Decho AW and Lau BLT. The extracellular basins of bacteria—a biofilm way of life. *Nat Educ Knowl* 2013; 4: 2–19.
17. Donlan RM. Biofilms: Microbial life on surfaces. *Emerg Infect Dis* 2002; 8: 881–890.
18. Flemming HC, Wingender J, Szewzyk U, et al. Biofilms: An emergent form of bacterial life. *Nat Rev Microbiol* 2016; 14(9): 563–575.
19. Ibberson CB, Stacy A, Fleming D, et al. Co-infecting microorganisms dramatically alter pathogen gene essentiality during polymicrobial infection. *Nat Microbiol* 2017; 2(5): 17079.
20. Gjødsbøl K, Christensen JJ, Karlsmark T, et al. Multiple bacterial species reside in chronic wounds: A longitudinal study. *Int Wound J* 2006; 3(3): 225–231.
21. Sarheed O, Ahmed A, Shouqair D, et al. Antimicrobial dressings for improving wound healing. *Intech Open* 2016; 17: 373–398.
22. Velnar T, Bailey T and Smrkolj V. The wound healing process: An overview of the cellular and molecular mechanisms. *J Int Med Res* 2009; 37(5): 1528–1542.
23. Krzyszczyk P, Schloss R, Palmer A, et al. The role of macrophages in acute and chronic wound healing and interventions to promote pro-wound healing phenotypes. *Front Physiol* 2018; 9(5): 419.
24. Demidova-Rice TN, Hamblin MR and Herman IM. Acute and impaired wound healing: Pathophysiology and current methods for drug delivery, Part 1: Normal and chronic wounds: Biology, causes, and approaches to care. *Adv Ski Wound Care* 2012; 25(7): 304–314.
25. Minutti CM, Knipper JA, Allen JE, et al. Tissue-specific contribution of macrophages to wound healing. *Semin Cell Dev Biol* 2017; 61: 3–11.
26. Ogle ME, Segar CE, Sridhar S, et al. Monocytes and macrophages in tissue repair: Implications for immunoregenerative biomaterial design. *Exp Biol Med* 2016; 241(10): 1084–1097.
27. Davies LC and Taylor PR. Tissue-resident macrophages: Then and now. *Immunology* 2015; 144(4): 541–548.
28. Das A, Sinha M, Datta S, et al. Monocyte and macrophage plasticity in tissue repair and regeneration. *Am J Pathol* 2015; 185: 2596–2606.
29. Khanna S, Biswas S, Shang Y, et al. Macrophage dysfunction impairs resolution of inflammation in the wounds of diabetic mice. *PLoS One* 2010; 5(3): e9539.
30. Biswas SK and Mantovani A. Orchestration of metabolism by macrophages. *Cell Metab* 2012; 15(4): 432–437.
31. Das A, Datta S, Roche E, et al. Novel mechanisms of Collagenase Santyl Ointment (CSO) in wound macrophage polarization and resolution of wound inflammation. *Sci Rep* 2018; 8(1): 1696.
32. Hesketh M, Sahin KB, West ZE, et al. Macrophage phenotypes regulate scar formation and chronic wound healing. *Int J Mol Sci* 2017; 18(7): E1545.
33. Novak ML and Koh TJ. Macrophage phenotypes during tissue repair. *J Leukoc Biol* 2013; 93(6): 875–881.
34. Bae YS, Lee JH, Choi SH, et al. Macrophages generate reactive oxygen species in response to minimally oxidized low-density lipoprotein: Toll-like receptor 4- and spleen tyrosine kinase-dependent activation of NADPH oxidase 2. *Circ Res* 2009; 104(2): 210–218.
35. Tan H-Y, Wang N, Li S, et al. The reactive oxygen species in macrophage polarization: Reflecting its dual role in progression and treatment of human diseases. *Oxid Med Cell Longev* 2016; 2016: 2795090.
36. Ferrante CJ and Leibovich SJ. Regulation of macrophage polarization and wound healing. *Adv Wound Care* 2012; 1(1): 10–16.
37. Grinberg S, Hasko G, Wu D, et al. Suppression of PLCβ2 by endotoxin plays a role in the adenosine A_{2A} receptor-mediated switch of macrophages from an inflammatory to an angiogenic phenotype. *Am J Pathol* 2009; 175(6): 2439–2453.
38. Brown BN and Badylak SF. Expanded applications, shifting paradigms and an improved understanding of host-biomaterial interactions. *Acta Biomater* 2013; 9(2): 4948–4955.
39. Röszer T. Understanding the mysterious M2 macrophage through activation markers and effector mechanisms. *Mediators Inflamm* 2015; 2015: 816460.
40. Weigel E, Smith C, Liu GP, et al. Macrophage polarization and its role in cancer. *J Clin Cell Immunol* 2015; 6: 338.
41. Rees PA, Greaves NS, Baguneid M, et al. Chemokines in wound healing and as potential therapeutic targets for reducing cutaneous scarring. *Adv Wound Care (New Rochelle)* 2015; 4(11): 687–703.
42. Koh TJ and DiPietro LA. Inflammation and wound healing: The role of the macrophage. *Expert Rev Mol Med* 2011; 13(7): e23.
43. Macleod AS and Mansbridge JN. The innate immune system in acute and chronic wounds. *Adv Wound Care (New Rochelle)* 2015; 5(2): 65–78.
44. Newby AC. Metalloproteinase expression in monocytes and macrophages and its relationship to atherosclerotic plaque instability. *Arter Thromb Vasc Biol* 2008; 28(12): 2108–2114.
45. Gauglitz GG, Korting HC, Pavicic T, et al. Hypertrophic scarring and keloids: Pathomechanisms and current and emerging treatment strategies. *Mol Med* 2011; 17(1–2): 113–125.
46. National Institute for Health and Care Excellence (NICE). Chronic wounds: Advanced wound dressings and antimicrobial dressings. Evidence summary ESMPB2. <https://www.nice.org.uk/advice/esmpb2/chapter/Key-points-from-the-evidence> (2016, accessed 21 July 2018).
47. Boateng JS, Matthews KH, Stevens HNE, et al. Wound healing dressings and drug delivery systems: A review. *J Pharm Sci* 2008; 97(8): 2892–2923.
48. Simões D, Miguel SP, Ribeiro MP, et al. Recent advances on antimicrobial wound dressing: A review. *Eur J Pharm Biopharm* 2018; 127: 130–141.
49. Thomas A, Harding KG and Moore K. Alginates from wound dressings activate human macrophages to secrete tumour necrosis factor-α. *Biomaterials* 2000; 21(17): 1797–1802.
50. Nassiri S, Zakeri I, Weingarten MS, et al. Relative expression of proinflammatory and antiinflammatory genes reveals differences between healing and nonhealing human chronic diabetic foot ulcers. *J Invest Dermatol* 2015; 135(6): 1700–1703.
51. Xu F and Graves DT. Abnormal cell responses and role of TNF-α in impaired diabetic wound healing abnormal cell responses and role of TNF-α in impaired diabetic wound healing. *Biomed Res Int* 2013; 2013: 754802.

52. Witherel CE, Graney PL, Freytes DO, et al. Response of human macrophages to wound matrices *in vitro*. *Wound Repair Regen* 2016; 24(3): 514–524.
53. Rosewald M, Hou FYS, Mututuvuri T, et al. Cellulose-chitosan-keratin composite materials: Synthesis, immunological and antibacterial properties. *ECS Trans* 2015; 64(4): 499–505.
54. Liakos I, Rizzello L, Scurr DJ, et al. All-natural composite wound dressing films of essential oils encapsulated in sodium alginate with antimicrobial properties. *Int J Pharm* 2014; 463(2): 137–145.
55. Miguel SP, Ribeiro MP, Coutinho P, et al. Electrospun polycaprolactone/aloe vera chitosan nanofibrous asymmetric membranes aimed for wound healing applications. *Polymers (Basel)* 2017; 9(5): 183.
56. Yuan TT, Jenkins PM, Digeorge Foushee AM, et al. Electrospun chitosan/polyethylene oxide nanofibrous scaffolds with potential antibacterial wound dressing applications. *J Nanomater* 2016; 2016: 25.
57. Kataru RP, Jung K, Jang C, et al. Critical role of CD11b⁺ macrophages and VEGF in inflammatory lymphangiogenesis, antigen clearance, and inflammation resolution. *Blood* 2012; 113(22): 5650–5659.
58. Merrell JG, McLaughlin SW, Tie L, et al. Curcumin-loaded poly(ϵ -caprolactone) nanofibres: Diabetic wound dressing with anti-oxidant and anti-inflammatory properties. *Clin Exp Pharmacol Physiol* 2009; 36(12): 1149–1156.
59. Teo EY, Ong SY, Chong MS, et al. Polycaprolactone-based fused deposition modeled mesh for delivery of antibacterial agents to infected wounds. *Biomaterials* 2011; 32(1): 279–287.
60. Hutmacher DW. Scaffolds in tissue engineering bone and cartilage. *Biomaterials* 2000; 21: 2529–2543.
61. Zhang Q, Oh JH, Park CH, et al. Effects of dimethylglycine-embedded poly(ϵ -caprolactone) fiber meshes on wound healing in diabetic rats. *ACS Appl Mater Interfaces* 2017; 9(9): 7950–7963.
62. Schwinté P, Mariotte A, Anand P, et al. Anti-inflammatory effect of active nanofibrous polymeric membrane bearing nanocontainers of atorvastatin complexes. *Nanomedicine (Lond)* 2017; 12(23): 2651–2674.
63. Vuong TT, Rønning SB, Suso HP, et al. The extracellular matrix of eggshell displays anti-inflammatory activities through NF- κ B in LPS-triggered human immune cells. *J Inflamm Res* 2017; 10: 83–96.
64. Koga AY, Pereira AV, Lipinski LC, et al. Evaluation of wound healing effect of alginate films containing aloe vera (*Aloe barbadensis* Miller) gel. *J Biomater Appl* 2018; 32(9): 1212–1221.
65. Sridharan R, Cameron AR, Kelly DJ, et al. Biomaterial based modulation of macrophage polarization: A review and suggested design principles. *Mater Today* 2015; 18(6): 313–325.
66. Anderson JM, Rodriguez A and Chang DT. Foreign body reaction to biomaterials. *Semin Immunol* 2008; 20: 86–100.
67. Sheikh Z, Brooks PJ, Barzilay O, et al. Macrophages, foreign body giant cells and their response to implantable biomaterials. *Materials (Basel)* 2015; 8(9): 5671–5701.
68. MacLauchlan S, Skokos EA, Meznarich N, et al. Macrophage fusion, giant cell formation, and the foreign body response require matrix metalloproteinase 9. *J Leukoc Biol* 2009; 85(4): 617–626.
69. Sorokin L. The impact of the extracellular matrix on inflammation. *Nat Rev Immunol* 2010; 10(10): 712–723.
70. Bygd HC, Forsmark KD and Bratlie KM. The significance of macrophage phenotype in cancer and biomaterials. *Clin Transl Med* 2014; 3(1): 62.
71. Boccafroschi F, Mosca C and Cannas M. Cardiovascular biomaterials: When the inflammatory response helps to efficiently restore tissue functionality? *J Tissue Eng Regen Med* 2014; 8(4): 253–267.
72. Anderson JM and McNally AK. Biocompatibility of implants: Lymphocyte/macrophage interactions. *Semin Immunopathol* 2011; 33(3): 221–233.