



POLITECNICO DI TORINO
Repository ISTITUZIONALE

Vinyl ethers and epoxides photoinduced copolymerization with perfluoropolyalkylether monomers

Original

Vinyl ethers and epoxides photoinduced copolymerization with perfluoropolyalkylether monomers / Trusiano, G.; Vitale, A.; Bonneaud, C.; Pugliese, D.; Dalle Vacche, S.; Joly-Duhamel, C.; Friesen, C. M.; Bongiovanni, R.. - In: COLLOID AND POLYMER SCIENCE. - ISSN 0303-402X. - ELETTRONICO. - (2020), pp. 1-13.

Availability:

This version is available at: 11583/2845991 since: 2020-09-17T14:49:22Z

Publisher:

Springer

Published

DOI:10.1007/s00396-020-04723-3

Terms of use:

openAccess

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

Publisher copyright

springer

Copyright Springer. The final publication is available at link.springer.com

(Article begins on next page)

Supporting Information

Vinyl ethers and epoxides photoinduced copolymerization with perfluoropolyalkylether monomers

Giuseppe Trusiano,^{†,} Alessandra Vitale,^{†,*} Céline Bonneaud,[‡] Diego Pugliese,[†] Sara Dalle Vacche[†],
Christine Joly-Duhamel,[‡] Chadron M. Friesen,[§] Roberta Bongiovanni[†]*

[†] Department of Applied Science and Technology , Politecnico di Torino, Corso Duca degli Abruzzi 24,
10129 Torino, Italy

[‡] Institut Charles Gerhardt Montpellier , University of Montpellier, CNRS, ENSCM, Cedex 5,
34296 Montpellier, France

[§] Department of Chemistry, Trinity Western University, 7600 Glover Road, V2Y 1Y1 Langley, BC, Canada

* Corresponding authors: giuseppe.trusiano@polito.it ; alessandra.vitale@polito.it

List of Figures

Fig. S1 ATR FT-IR spectra of the PFPAE-EGVE + TVE copolymer:.....	3
Fig. S2 ATR FT-IR spectra of the PFPAE-BGVE + TVE copolymer:	3
Fig. S3 ATR FT-IR spectra of the PFPAE-DEGVE + TVE copolymer:	4
Fig. S4 ATR FT-IR spectra of the PFPAE-MO + TGE copolymer:	4
Fig. S5 ATR FT-IR spectra of the PFPAE-EO + TGE copolymer:	5
Fig. S6 ATR FT-IR spectra of the PFPAE-PO + TGE copolymer:	5
Fig. S7 Water contact angle hysteresis measurements, on air and glass sides, of the UV-cured copolymers: ...	7

List of Tables

Table S1 Number of repeat units, average molecular weight (M_n), difunctional content, (from ^{19}F -NMR spectra) of the functionalized PFPAE monomers, and composition details and fluorine content of the investigated copolymers.	6
Table S2 Degradation temperatures of the UV-cured hydrogenated resins and copolymers.....	7

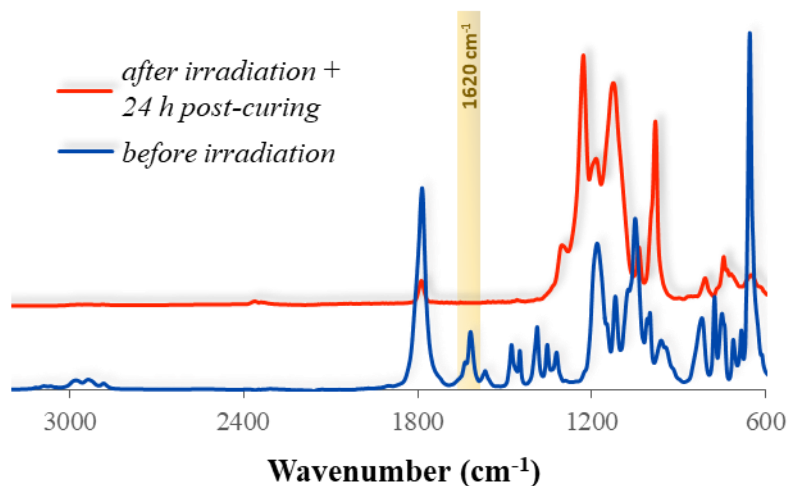


Fig. S1 ATR FT-IR spectra of the PFPAE-EGVE + TVE copolymer:

R_h: peak $\sim 1780\text{ cm}^{-1}$ C=O bond; $\sim 1620\text{ cm}^{-1}$ C=C; peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers;

R_f: peak $\sim 1240\text{ cm}^{-1}$ stretching C-F bond, and peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers;

Photoinitiator: peak $\sim 2950\text{ cm}^{-1}$ stretching C=C-H; peak $\sim 1780\text{ cm}^{-1}$ C=O bond; peak $\sim 1600\text{-}1320\text{ cm}^{-1}$ C₆H₆ bonds; peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers

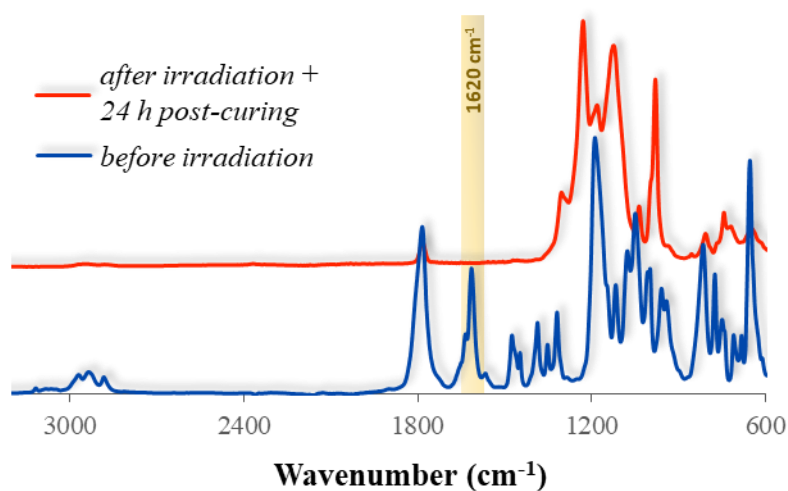


Fig. S2 ATR FT-IR spectra of the PFPAE-BGVE + TVE copolymer:

R_h: peak $\sim 1780\text{ cm}^{-1}$ C=O bond; $\sim 1620\text{ cm}^{-1}$ C=C; peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers;

R_f: peak $\sim 1240\text{ cm}^{-1}$ stretching C-F bond, and peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers;

Photoinitiator: peak $\sim 2950\text{ cm}^{-1}$ stretching C=C-H; peak $\sim 1780\text{ cm}^{-1}$ C=O bond; peak $\sim 1600\text{-}1320\text{ cm}^{-1}$ C₆H₆ bonds; peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers

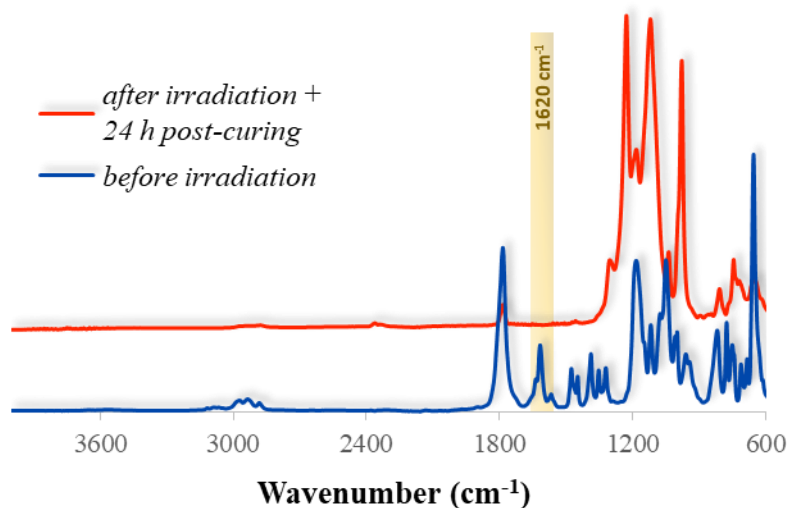


Fig. S3 ATR FT-IR spectra of the PFPAE-DEGVE + TVE copolymer:

R_h: peak $\sim 1780\text{ cm}^{-1}$ C=O bond; $\sim 1620\text{ cm}^{-1}$ C=C; peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers;

R_f: peak $\sim 1240\text{ cm}^{-1}$ stretching C-F bond, and peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers;

Photoinitiator: peak $\sim 2950\text{ cm}^{-1}$ stretching C=C-H; peak $\sim 1780\text{ cm}^{-1}$ C=O bond; peak $\sim 1600\text{-}1320\text{ cm}^{-1}$ C₆H₆ bonds; peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers

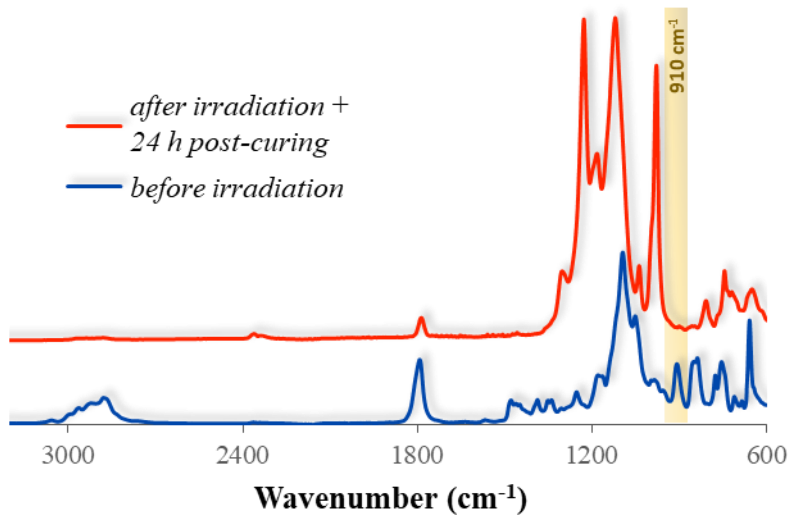


Fig. S4 ATR FT-IR spectra of the PFPAE-MO + TGE copolymer:

R_h: peak $\sim 1780\text{ cm}^{-1}$ C=O bond; $\sim 1620\text{ cm}^{-1}$ C=C; peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers; peak $\sim 910\text{ cm}^{-1}$ epoxides;

R_f: peak $\sim 1240\text{ cm}^{-1}$ stretching C-F bond, and peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers;

Photoinitiator: peak $\sim 2950\text{ cm}^{-1}$ stretching C=C-H; peak $\sim 1780\text{ cm}^{-1}$ C=O bond; peak $\sim 1600\text{-}1320\text{ cm}^{-1}$ C₆H₆ bonds; peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers

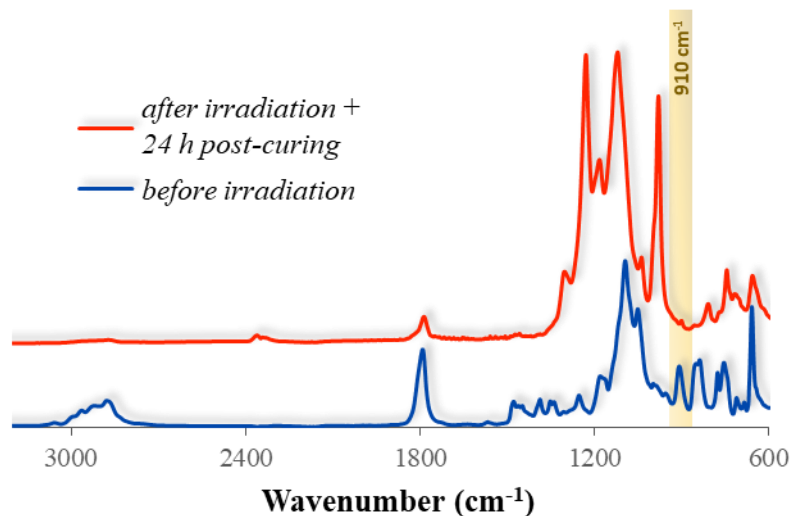


Fig. S5 ATR FT-IR spectra of the PFP AE-EO + TGE copolymer:

R_h: peak $\sim 1780\text{ cm}^{-1}$ C=O bond; $\sim 1620\text{ cm}^{-1}$ C=C; peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers; peak $\sim 910\text{ cm}^{-1}$ epoxides;

R_f: peak $\sim 1240\text{ cm}^{-1}$ stretching C-F bond, and peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers;

Photoinitiator: peak $\sim 2950\text{ cm}^{-1}$ stretching C=C-H; peak $\sim 1780\text{ cm}^{-1}$ C=O bond; peak $\sim 1600\text{-}1320\text{ cm}^{-1}$ C₆H₆ bonds; peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers

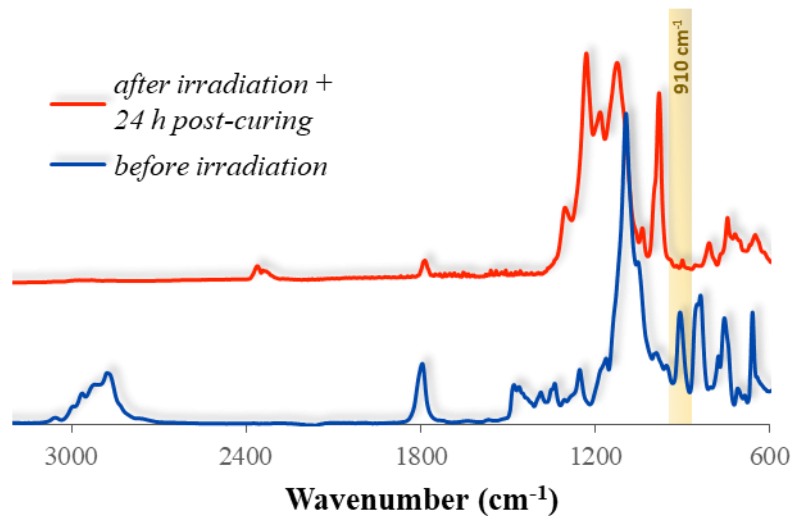


Fig. S6 ATR FT-IR spectra of the PFP AE-PO + TGE copolymer:

R_h: peak $\sim 1780\text{ cm}^{-1}$ C=O bond; $\sim 1620\text{ cm}^{-1}$ C=C; peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers; peak $\sim 910\text{ cm}^{-1}$ epoxides;

R_f: peak $\sim 1240\text{ cm}^{-1}$ stretching C-F bond, and peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers;

Photoinitiator: peak $\sim 2950\text{ cm}^{-1}$ stretching C=C-H; peak $\sim 1780\text{ cm}^{-1}$ C=O bond; peak $\sim 1600\text{-}1320\text{ cm}^{-1}$ C₆H₆ bonds; peak $\sim 1100\text{ cm}^{-1}$ C-O-C ethers

Table S1 Number of repeat units, average molecular weight (M_n), difunctional content, (from ^{19}F -NMR spectra) of the functionalized PFPAE monomers, and composition details and fluorine content of the investigated copolymers.

Copolymer	m	PFPAE molecular weight (g/mol)	PFPAE difunctional content (mol%)	PFPAE/Resin weight ratio	F content in copolymer (wt%)	F content in copolymer (mol%)
PFPAE-EGVE + TVE	6	1740	56	0.32	18.45	0.97
PFPAE-BGVE + TVE	8	2130	88	0.32	18.93	1.00
PFPAE-DEGVE + TVE	7	2000	43	0.32	16.46	0.87
PFPAE-MO + TGE	12	2720	63	0.32	17.06	0.90
PFPAE-EO + TGE	8	2130	41	0.32	16.06	0.85
PFPAE-PO + TGE	10	2530	58	0.32	16.08	0.85

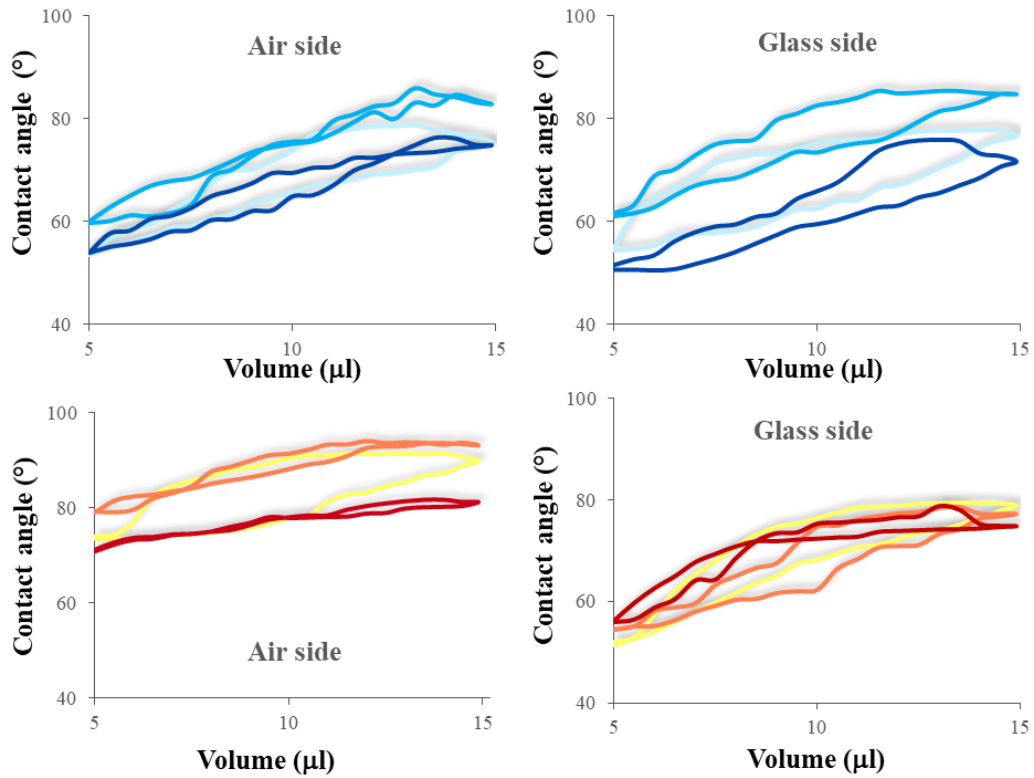


Fig. S7 Water contact angle hysteresis measurements, on air and glass sides, of the UV-cured copolymers:

— PFPAE-EGVE + TVE, — PFPAE-BGVE + TVE, — PFPAE-DEGVE + TVE,
 — PFPAE-MO + TGE, — PFPAE-EO + TGE, — PFPAE-PO + TGE.

Table S2 Degradation temperatures of the UV-cured hydrogenated resins and copolymers

System	T_{onset} (°C)	T_{max1} (°C)	T_{max2} (°C)	$T_{90\%}$ (°C)
TVE	188	-	398	428
PFPAE-EGVE + TVE	137	181	397	427
PFPAE-BGVE + TVE	150	192	366	429
PFPAE-DEGVE + TVE	136	182	375	429
TGE	185	-	378	405
PFPAE-MO + TGE	130	156	381	413
PFPAE-EO + TGE	132	159	361	410
PFPAE-PO + TGE	140	159	385	413