POLITECNICO DI TORINO Repository ISTITUZIONALE

Influence of different dry-mixing techniques on the mechanical, thermal, and electrical behavior of ultrahigh molecular weight polyethylene/exhausted tire carbon composites

Original

Influence of different dry-mixing techniques on the mechanical, thermal, and electrical behavior of ultra-high molecular weight polyethylene/exhausted tire carbon composites / Duraccio, Donatella; Arrigo, Rossella; Bartoli, Mattia; Paolo Capra, Pier; Malucelli, Giulio. - In: POLYMERS FOR ADVANCED TECHNOLOGIES. - ISSN 1042-7147. - ELETTRONICO. - (2022), pp. 1-10. [10.1002/pat.5637]

Availability:

This version is available at: 11583/2956078 since: 2022-09-08T15:58:13Z

Publisher: Wiley

Published

DOI:10.1002/pat.5637

Terms of use:

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

Publisher copyright

Wiley postprint/Author's Accepted Manuscript

This is the peer reviewed version of the above quoted article, which has been published in final form at http://dx.doi.org/10.1002/pat.5637.This article may be used for non-commercial purposes in accordance with Wiley Terms and Conditions for Use of Self-Archived Versions.

(Article begins on next page)

Fra

NEWTEAM

Influence of the Process Parameters on the Densification and Microstructure of Ni-based Superalloys with Different Amount of γ' Former Alloying Elements

Processed by SLM

Giulio Marchese^{1, 3}; Simone Parizia^{1, 3}; *Antonio Sivo*^{1,3}; Emilio Bassini^{1,3}; Flaviana Calignano^{2, 3}; Sara Biamino^{1, 3}; Daniele Ugues^{1, 3};

¹Department of Applied Science and Technology, Politecnico di Torino, Corso Duca degli Abruzzi 24, 10129 Torino, Italy; ²Department of Management and Production Engineering, Politecnico di Torino, Corso Duca degli Abruzzi 24, 10129 Torino, Italy; ³Consorzio Interuniversitario Nazionale per la Scienza e Tecnologia dei Materiali (INSTM), Via G. Giusti, 9,50121 Firenze, Italy

JOINT UNDERTAKING

Ni-based superalloys are characterized by high-temperature strength, oxidation and corrosion resistance making them excellent for several applications such as aerospace and chemical sectors. Additive manufacturing (AM) processes, in particular laser powder bed fusion, allow the fabrication of complex parts in a single step resulting attractive for Ni-based superalloys.

This work investigates the effect of different process parameters on the densification and microstructure of various Ni-based superalloys, Tab 1, characterized by increasing amounts of γ' former alloying elements, studying the balance between pores and cracks reduction and the resulting microstructure. The involved parameters are: laser power, scanning speed, hatching distance. The scanning strategy used is "stripes" as shown in Figure 1

	Tab. 1 Studied Ni-based superalloys composition [1]											
-	Alloy	Cr	Со	Мо	W	Та	Nb	Al	Ti	С	Hf	
-	CM247 LC	8	9.3	0.5	9.5	3.2		5.6	0.7	0.07	1.4	
	Renè 80	14	9	4	4			3	4.7	0.16	0.8	
	Inconel 939	22.4	19		2		1	1.9	3.7	0.15		

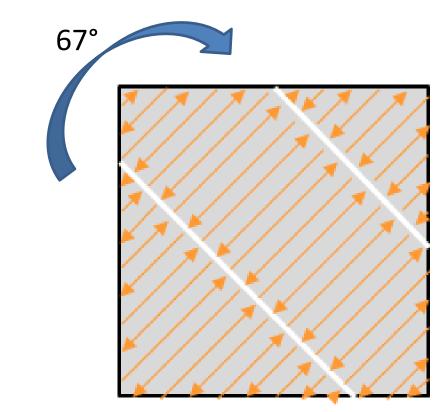


Fig. 1 Top view of the stripes scan strategy

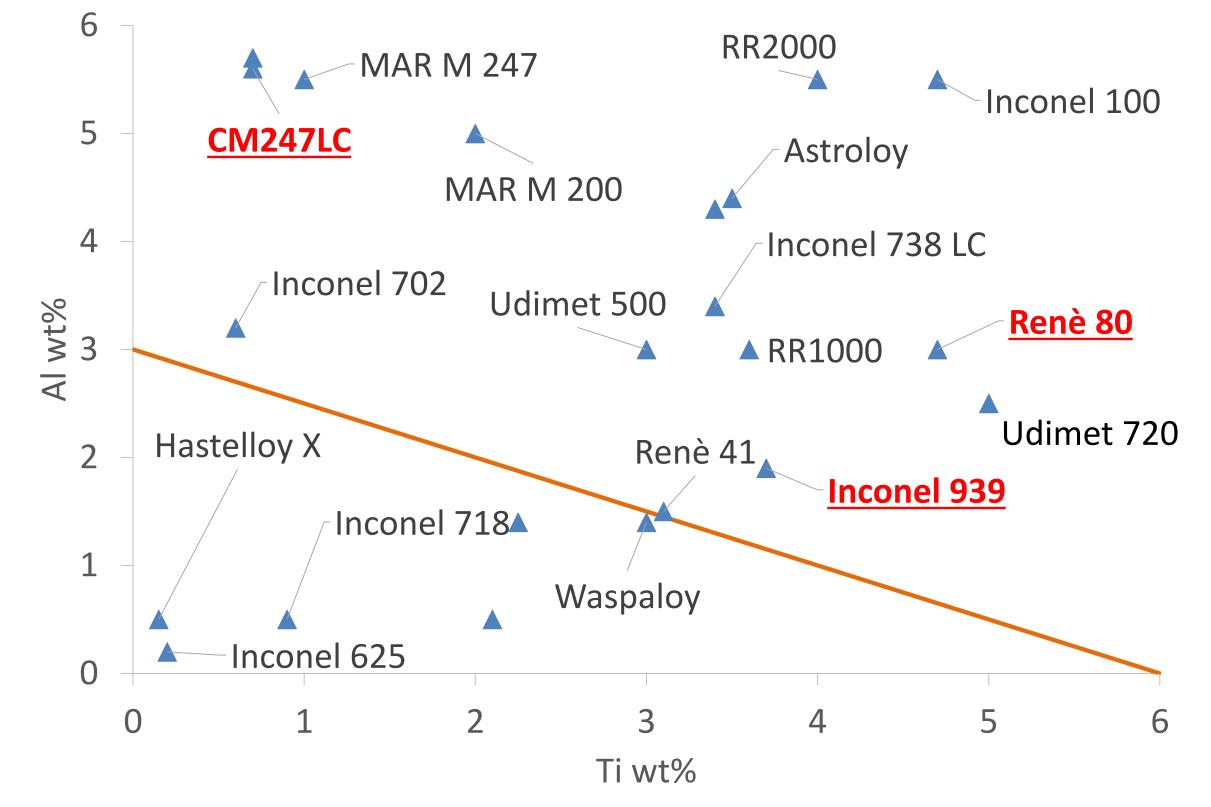
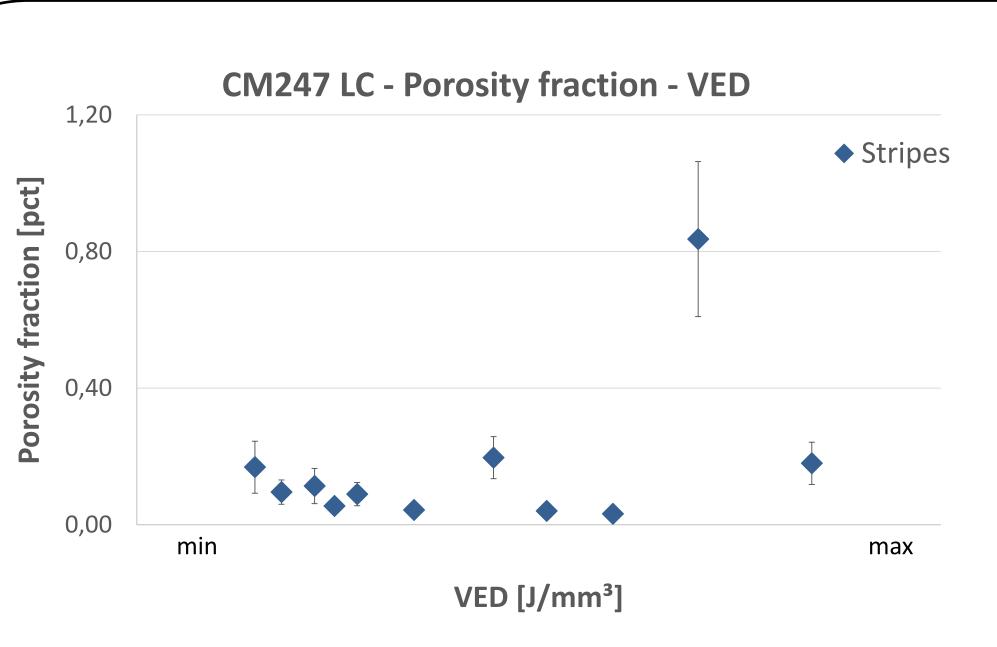
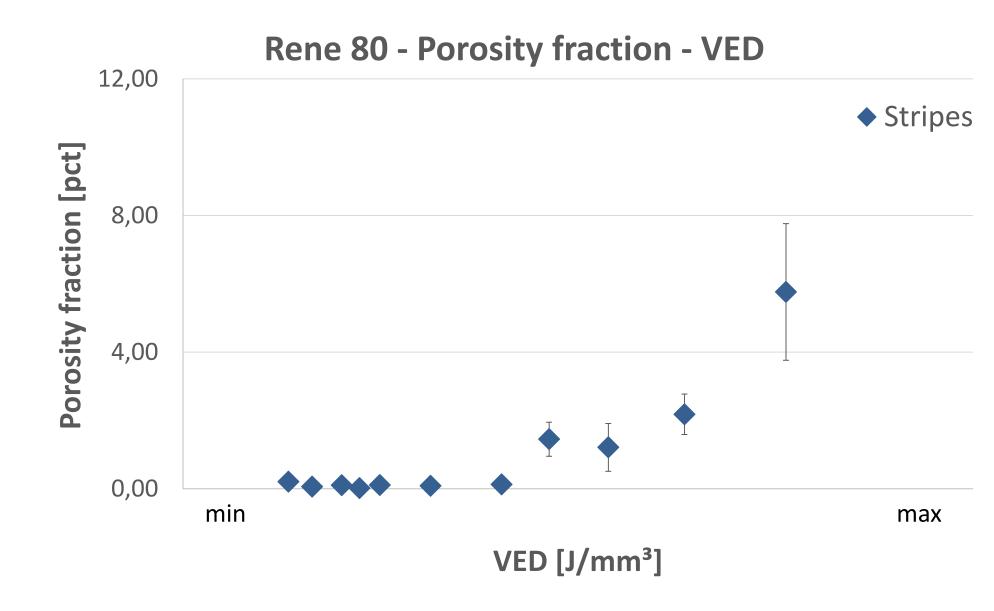


Figure 2. Theoretical weldability diagram according PWHT cracking mechanism [2]





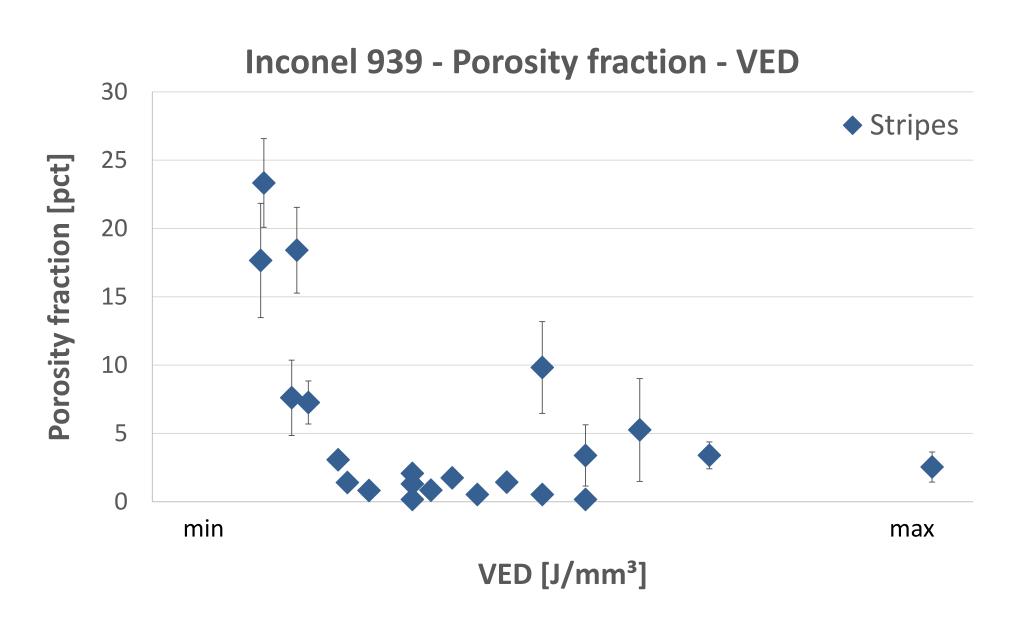
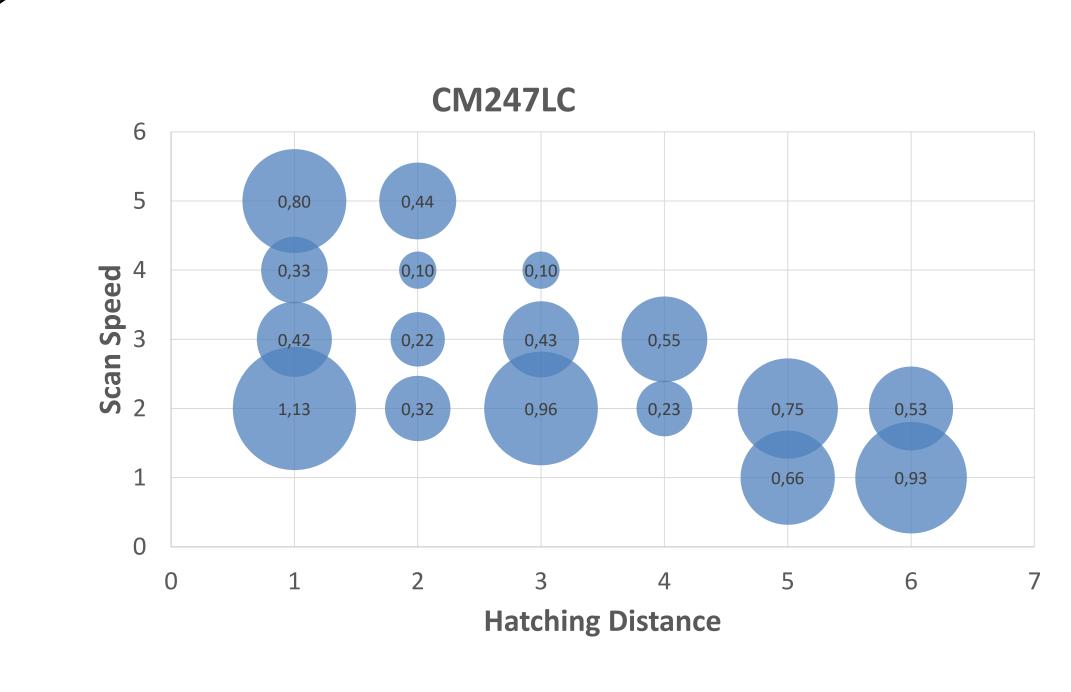
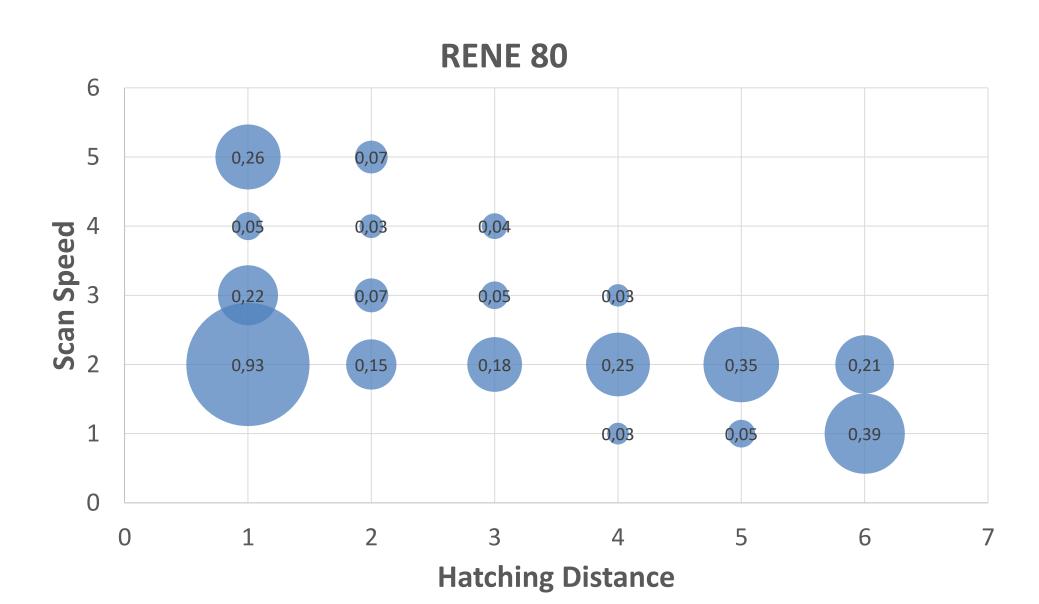


Figure 3. Show the effect of the VED on the pores fraction among the studied composition. From left to right, CM247LC, Rene80, Inconel 939

$$VED = \frac{P}{v \, hd \, t} \left[\frac{J}{mm^3} \right]$$





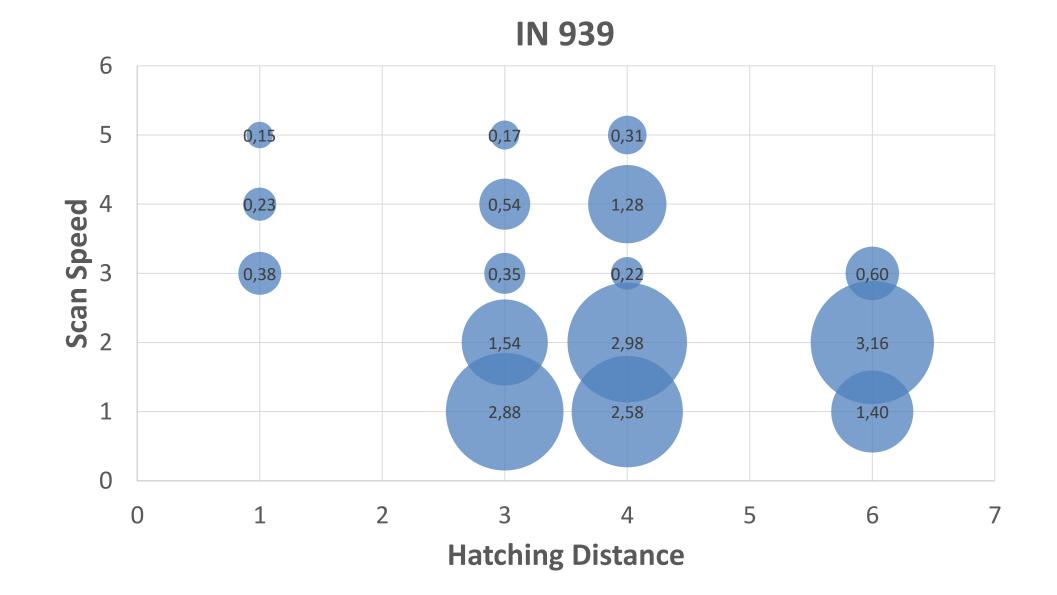


Figure 4. Effect of hatching distance and scans peed on the crack density, expressed in reduced values and keeping the power constant

SO imm

Figure 5. Macrostructure obtained after mixed acid etching. Shows the columnar grains, vertically oriented, the meltpool and the thermal cracks parallel to the grains

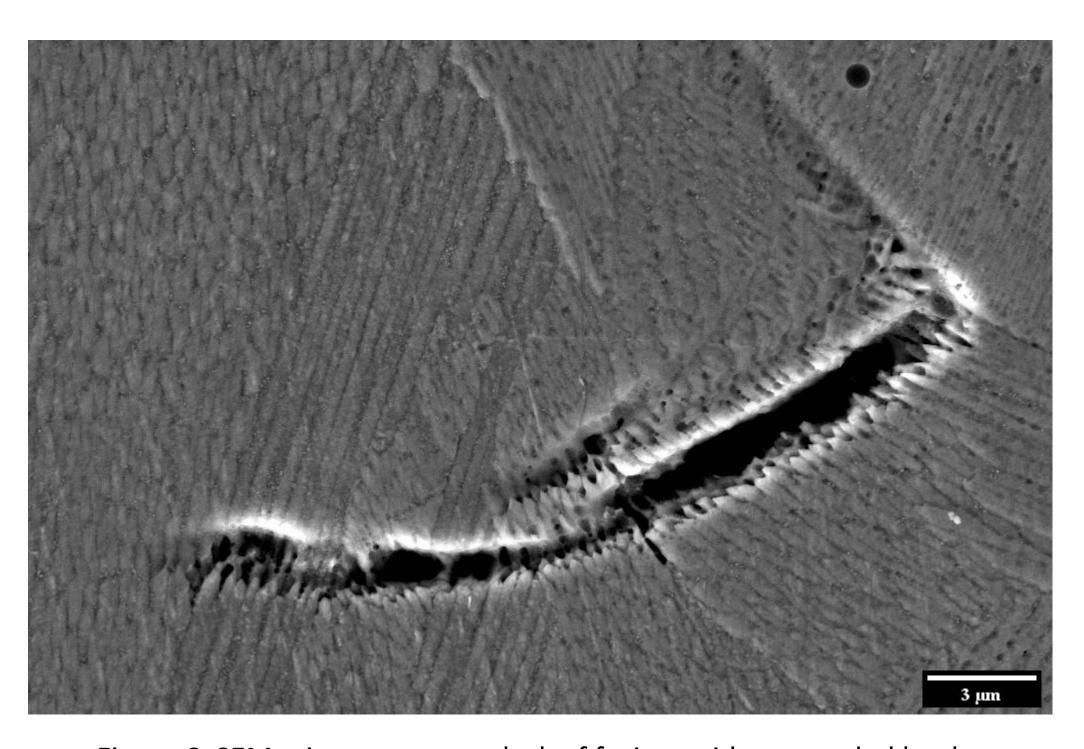


Figure 6. SEM microstructure a lack of fusion void surrounded by the typical pattern of the cellular structure that develops inside the grains

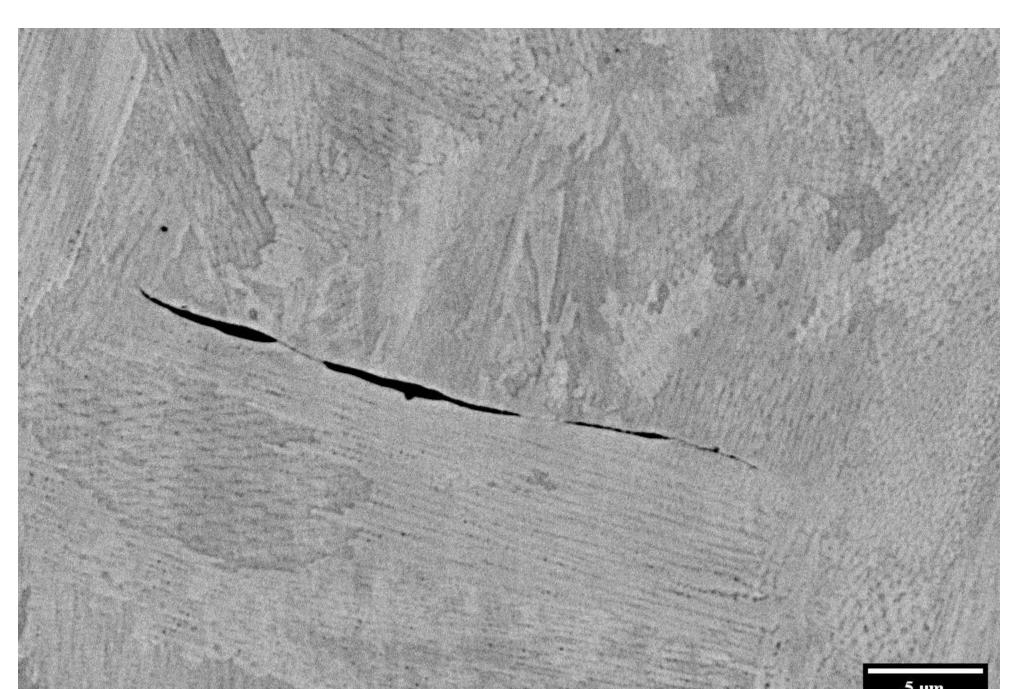


Figure 7. SEM microstructure of a thermal crack grown on a grain boundary.

References