

Functional characterization of L-PBF produced FeSi<sub>2.9</sub> Soft Magnetic Material

*Original*

Functional characterization of L-PBF produced FeSi<sub>2.9</sub> Soft Magnetic Material / Quercio, Michele; Galbusera, Francesco; Poskovic, Emir; Franchini, Fausto; Ferraris, Luca; Canova, Aldo; Gruosso, Giambattista; Demir, Ali Gokhan; Previtali, Barbara. - ELETTRONICO. - International Conference on Electrical Machines, ICEM:(2022), pp. 531-537. (Intervento presentato al convegno XXV International Conference on Electrical Machines- ICEM 2022 tenutosi a Valencia, Spain nel 5-8 September 2022) [10.1109/ICEM51905.2022.9910684].

*Availability:*

This version is available at: 11583/2972594 since: 2022-10-29T09:00:04Z

*Publisher:*

IEEE

*Published*

DOI:10.1109/ICEM51905.2022.9910684

*Terms of use:*

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

*Publisher copyright*

IEEE postprint/Author's Accepted Manuscript

©2022 IEEE. Personal use of this material is permitted. Permission from IEEE must be obtained for all other uses, in any current or future media, including reprinting/republishing this material for advertising or promotional purposes, creating new collecting works, for resale or lists, or reuse of any copyrighted component of this work in other works.

(Article begins on next page)

# Functional characterization of L-PBF produced FeSi<sub>2.9</sub> Soft Magnetic Material

Michele Quercio, Francesco Galbusera, Emir Pošković, Fausto Franchini, Luca Ferraris, Aldo Canova, Giambattista Grusso, Ali Gökhan Demir, Barbara Previtali

**Abstract** -- Additive manufacturing (AM) is a production technology attractive for various sectors such as aerospace, biomedical, and automotive. The advantages are various, including being able to create objects with complex geometry and through a careful study of topological optimization, reduce the weight while maintaining mechanical performance. The aim of the present work is to study the feasibility of producing ferromagnetic materials using AM technology for electrical application such as rotor for electrical machine or electromagnetic devices via Laser Powder Bed Fusion (L-PBF). L-PBF is shown to be effective to produce soft magnetic materials (SMMs) such as FeSi<sub>2.9</sub>. Dedicated test samples with various geometries have been manufactured for evaluating the electrical and magnetic performance under as-built conditions and after annealing.

**Index Terms**-- Additive manufacturing; Electromagnetic device; FeSi; Laser powder bed fusion; Soft magnetic materials.

## I. INTRODUCTION

Additive Manufacturing is a production technology created for rapid prototyping of nonstructural components, mainly for design purposes [1-3]. Around the end of 1990s, it evolved for the manufacture of structural components due to technological evolution [4,5]. The advantage of this technique is to create 3D objects by adding material where needed, following a CAD drawing. This saves material and avoids production waste. A further advantage comes from the fact that it is possible to produce complex or customized parts [6,7]. Through topological optimization, it is possible to reduce the weight of the objects while maintaining their mechanical properties [8-10]. The main technological drawbacks concern the production speed and the elevated costs that can be solved by improving the machine design and productivity [11-13]. Due to the high costs of both material and production (time-consumption), the sectors that first used this technology are aerospace and biomedical.

In the literature, there are numerous example cases of application in these sectors [14-17]. Among the most widely used AM technologies for metallic alloys, Laser Powder Bed Fusion (LPBF) is arguably the most developed one. This technique uses a laser beam to fuse the powder feedstock in a layer by layer fashion. The technique is well established for a limited number of metallic materials such as Ti6Al4V, AISI 316, AlSi10Mg, and CoCr alloys as well as their subsequent

heat treatments [18-20]. Recent works showed that L-PBF can be used to produce ferromagnetic material components, while the processability heavily relies on the alloy composition [21-23]. A few examples of the use of AM for the fabrication of ferromagnetic artifacts can be found in the literature where different alloy types such as Fe-Ni, Fe-Co, Fe-Si have been studied [24-26]. In this case, more studies should be conducted to investigate the optimal process parameters, the correct printing direction, and the effects of subsequent heat treatments on electrical, magnetic, and mechanical properties.

Compared to other widely discussed sectors (aerospace, and biomedical), soft magnetic materials produced with AM and their application in the electrical component manufacturing still require further exploration. With an increased demand in electrification especially in the mobility sector, the importance of newly designed components exploiting the geometric freedom of the AM processes with adequate electromagnetic properties become of great interest. Indeed, along with the processability issues the testing procedures of the produced parts and geometries require further attention. Accordingly, this work shows the L-PBF processing and extensive functional characterization of Fe-Si based electromagnetic components in as-built and annealed conditions. Because silicon steels are a very important class of materials for electromagnetic applications as they are widely used in transformers, cores, electric motors, and generators, for this purpose, FeSi<sub>2.9</sub> was chosen to be processed by L-PBF. For electrical and magnetic characterization, a rod to evaluate coercivity and a toroid to perform a ring test to evaluate the permeability of the material were produced. After discussing the properties before and after annealing, an example of application is also illustrated in the final paragraphs for completeness of the work.

## II. MATERIALS AND METHODS

### A. FeSi Powder

In the present investigation a low – silicon steel powder was processed. The feedstock was produced through powder atomization (m4p material solutions GmbH, Austria). The nominal chemical composition consists of 2.9 wt% Si and Fe bal. The powder had a spherical morphology with a declared granulometry comprised between 20 and 53  $\mu\text{m}$ .

---

M. Quercio, E. Pošković, F. Franchini, L. Ferraris, A. Canova are with the Energy Department, Politecnico di Torino, Torino, 10129, Italy (e-mail: [michele.quercio@polito.it](mailto:michele.quercio@polito.it), [emir.poskovic@polito.it](mailto:emir.poskovic@polito.it), [luca.ferraris@polito.it](mailto:luca.ferraris@polito.it), [aldo.canova@polito.it](mailto:aldo.canova@polito.it)).

F. Franchini is with the Energy Department, Politecnico di Torino, Alessandria Campus, 15121, Italy (e-mail: [fausto.franchini@polito.it](mailto:fausto.franchini@polito.it)).

Giambattista Grusso is with the Dipartimento di Elettronica ed Informazione, Politecnico di Milano, Italy (e-mail: [giambattista.grusso@polimi.it](mailto:giambattista.grusso@polimi.it)).

F. Galbusera, A.G. Demir, B. Previtali are with the Mechanical Department, Politecnico di Milano, Milano, 20156, Italy (e-mail: [francesco.galbusera@polimi.it](mailto:francesco.galbusera@polimi.it), [aligokhan.demir@polimi.it](mailto:aligokhan.demir@polimi.it), [barbara.previtali@polimi.it](mailto:barbara.previtali@polimi.it)).

## B. LPBF System

Samples for magnetic characterization were manufactured with an industrial grade LPBF system with open architecture (LLA150R, 3D-NT, Solbiate Olona, Italy). The system is equipped with a fiber laser source (Corona nLIGHT AFX 1000, nLIGHT Inc, Vancouver, Washington, USA), operating with a wavelength of 1070 nm ( $\pm 10$  nm), a maximum power of 1000W and a theoretical waist diameter of 47  $\mu\text{m}$  in the focus position. The laser source can operate either in Pulsed Wave (PW) or Continuous Wave (CW) emission by power modulation. Prior to manufacturing, the building chamber is filled with Ar in overpressure whereas the O<sub>2</sub> content is kept below 3000 ppm. Throughout the experimental activity, ferromagnetic samples were built upon stainless steel substrates.

## C. Production of components

The components have been realized starting from a CAD model. The drawing is sliced in several parts and the size of each slice is equal to the height of the layer. Next, the 200W fixed power laser was used continuously to melt the powder in a zig-zag pattern rotating the layers by 67° (Fig. 1). The direction of construction coincides with the axis of the produced part (Fig. 2), except for the toroid that was directed vertically (Fig. 3). The process parameters are listed in Table 1.

TABLE 1 - PROCESS PARAMETERS USED FOR THE FERROMAGNETIC SAMPLES MANUFACTURING.

PARAMETER	LEVEL
POWER, P, (W)	200
SCAN SPEED, V, (MM/S)	800
HATCH DISTANCE, H <sub>h</sub> , ( $\mu\text{M}$ )	70
LAYER THICKNESS, Z, ( $\mu\text{M}$ )	30

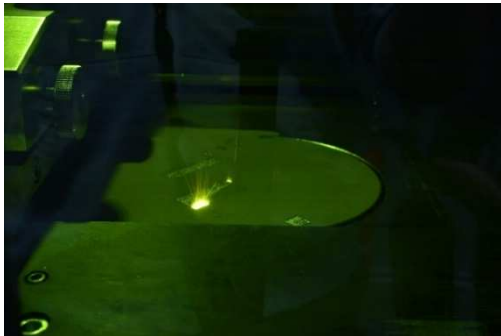


Fig. 1 - LPBF System

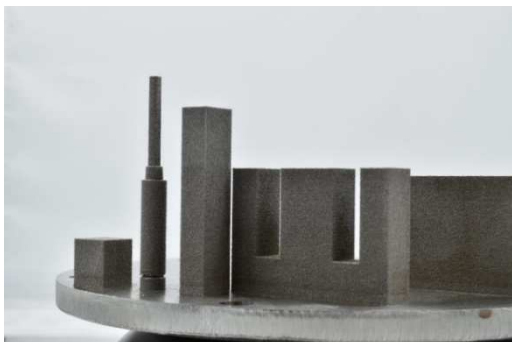


Fig. 2 - Components made of FeSi<sub>2.9</sub> material



Fig. 3 - FeSi<sub>2.9</sub> Toroidal Sample: outer diameter 13.35 mm, inner diameter 9.58 mm and thickness 2.25 mm

## III. MAGNETIC CHARACTERIZATION

The magnetic properties of produced components are detected to understand the possible relevant applications. The technique used to identify magnetic and energetic behavior are coercivity measurement and toroidal magnetic test. Also, the Single Sheet Tester (SST) can be applied, but the specimens require very high planarity. The used procedure is more similar to bulk or Soft Magnetic Composite (SMC) materials characterization instead of laminated steel [27]. Furthermore, the analysis has been conducted considering the measurement before and after heat treatment at 1200°C, 1h, in vacuum as suggested in [28].




### A. Coercivity Measurement

A very quick and reliable measurement could make evident the effects of the heat treatment on the magnetic hysteresis. The coercivity value (H<sub>c</sub>) measured in a very slow transient is highly related to the area of the hysteresis cycle. A controlled power supply, an excitation coil and two sensing coils are the main parts of the adopted coercimeter (Fig. 4). The maximum magnetic field value reached in the saturation phase is 100 kA/m, while the H<sub>c</sub> point is reached in 10 seconds, limiting most of the eddy current contribution. In Table 2 the results confirmed the expected material behavior: an important reduction is evident of the residual stresses due to the fast cooling cycles induced in LPBF process, as can be seen by the strongly reduced values of the thin and thick bars. The cylindrical rod showed a low coercivity value even before the treatment: this behavior should be better investigated in the future, as it can be related to the specimen shape or to the printing conditions of such a small diameter.



Fig. 4 - Specimen insertion in the coercimeter coil

TABLE 2 - COERCIVITY VALUES BEFORE AND AFTER THERMAL TREATMENT

Specimen Shape	No treatment (A/m)	Treatment at 1200°C in vacuum (A/m)
	212	85.6
	151.6	94.6
	87.7	69.1

**B. Toroidal Magnetic Test**

The tests involved the use of a soft material hysteresis graph operated at different frequencies between 10 Hz and 1 kHz. The measurements were limited to an excitation field peak of 6500 A/m or to a secondary voltage peak of 10 V.

The toroidal sample was equipped with two windings: the secondary one, thinner, directly on the sample surface and the primary one on top of the former, as shown in Fig. 5.

The toroid dimensions were somewhat too small if compared with the requirements of the IEC 60404 series standards, leading to a slight underestimation in the dynamic iron losses at the mid-low frequencies. The hysteresis contribution was always correct instead.

The comparison between the measurements conducted before and after the heat treatment shows different properties of the material, and helps to tune the next steps of the research activities. The main differences involve the maximum magnetic permeability and the total iron losses.

The magnetic permeability before the heat treatment is rather lower than expected for the adopted powder composition (Fig. 6), mainly showing a poorly relaxed state of the crystal lattices. Consequently, the magnetization curves are too narrow and smooth (Fig. 8). The maximum magnetic permeability value is 748 and magnetic induction does not exceed 1.1 T without the heat treatment.

The iron losses measured before the heat treatment show a rather low electrical resistivity, with the full cycles at 1 T losing their tips, but only at 500 Hz and 1 kHz. The hysteresis contribution is anyway rather high at all frequencies, as shown in Fig. 10 and Fig. 11.



Fig. 5 - FeSi2.9 Toroid: size and shape not fully compliant with the IEC 60404 series standards

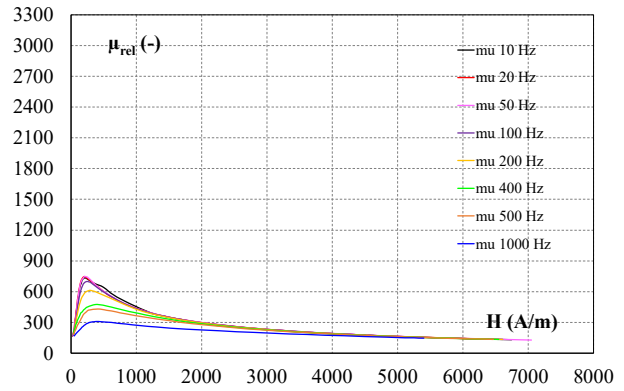


Fig. 6 - Magnetic permeability as a function of magnetic field H at different frequencies for FeSi2.9 toroid without treatment

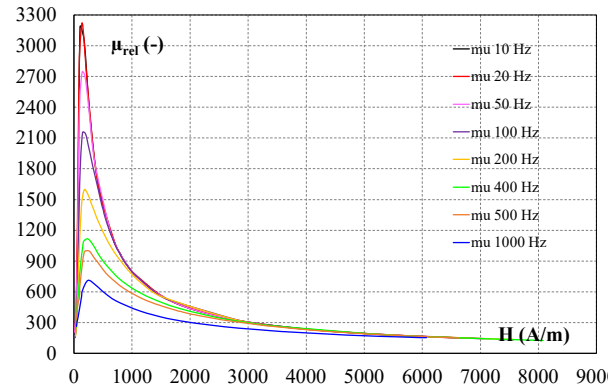


Fig. 7 - Magnetic permeability as a function of magnetic field H at different frequencies for FeSi2.9 toroid with the treatment at 1200°C

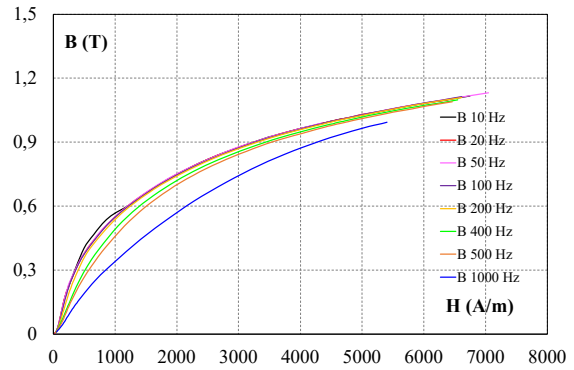


Fig. 8 - Magnetization curves at different frequencies for FeSi2.9 toroid without treatment

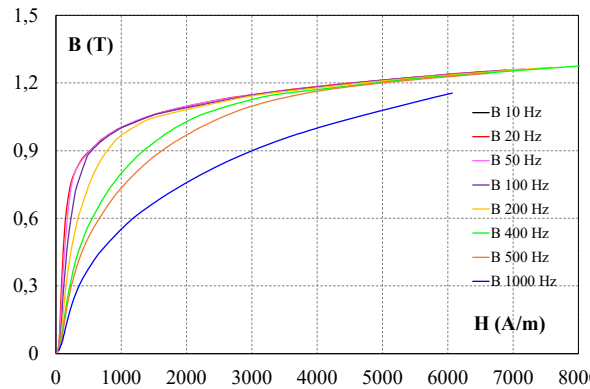


Fig. 9 - Magnetization curves at different frequencies for FeSi2.9 toroid with the treatment at 1200°C

The magnetic permeability raises consistently after the heat treatment (Fig. 7), bringing the hysteresis contribution to the iron losses at very low levels. The maximum magnetic permeability after the treatment corresponding to 3224 and magnetic induction show values greater than 1.2 T (Fig. 9).

The total iron losses after the heat treatment surprisingly decreased at all frequencies and for any peak induction value as reported in Fig. 12 and Fig. 13, showing that the heat treatment benefits fully compensate for the reduction in global electrical resistivity.

The hysteresis cycles before the treatment are reported in Fig. 14; it is possible to note the high presence of hysteresis losses together with the contribution of eddy currents. The full cycles at 1 T show a strongly reduced electrical resistivity, typical of a fully sintered internal structure (Fig. 15), in which the main part of the iron losses is dynamic and originates from the eddy currents.

The additional particular investigation concerns the maximum magnetic permeability as the function of the frequency, as shown in Fig. 16. The reduction is more pronounced after the heat treatment, and at 100 Hz the reached value is 50% compared to the maximum one. A similar percentage decrease is obtained at 400 Hz for no heat treatment. The iron losses @1T for various frequencies are shown in Fig. 17. The values for with and without heat treatment are very close to each other, where the values corresponding to heat treatment are slightly minor.

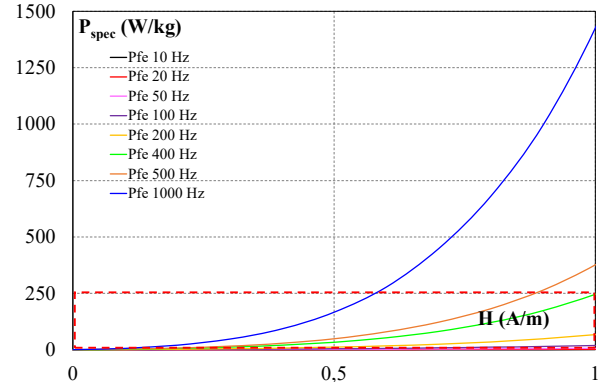


Fig. 12 - Specific iron losses as a function of magnetic induction at different frequencies for FeSi2.9 toroid with the treatment at 1200°C

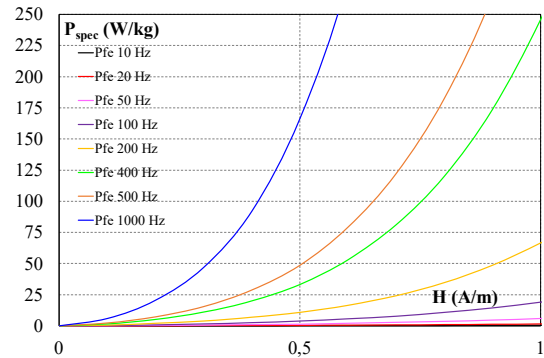


Fig. 13 - Specific iron losses as a function of magnetic induction at different frequencies for FeSi2.9 toroid with the treatment at 1200°C: restricted to 250 W/kg

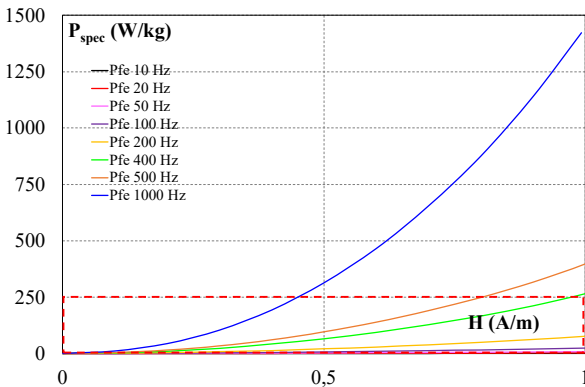


Fig. 10 - Specific iron losses as a function of magnetic induction at different frequencies for FeSi2.9 toroid without treatment

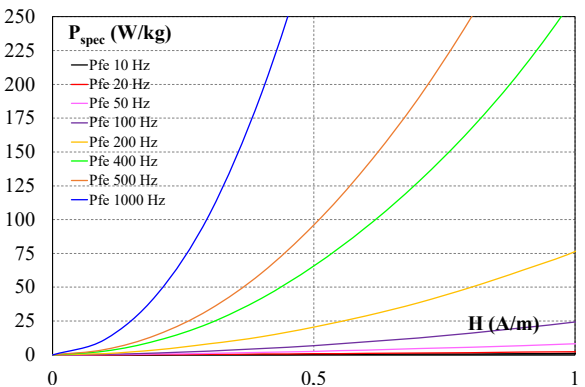


Fig. 11 - Specific iron losses as a function of magnetic induction at different frequencies for FeSi2.9 toroid without treatment: restricted to 250 W/kg

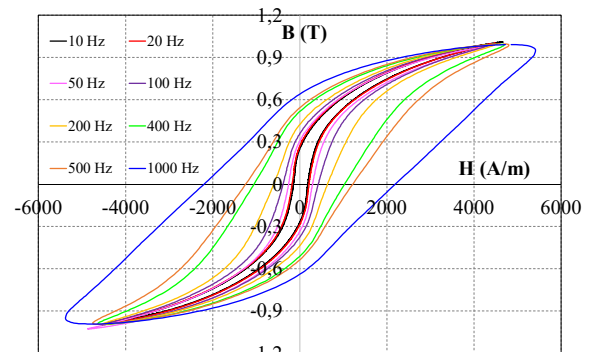


Fig. 14 - Hysteresis cycles at different frequencies for FeSi2.9 toroid without treatment

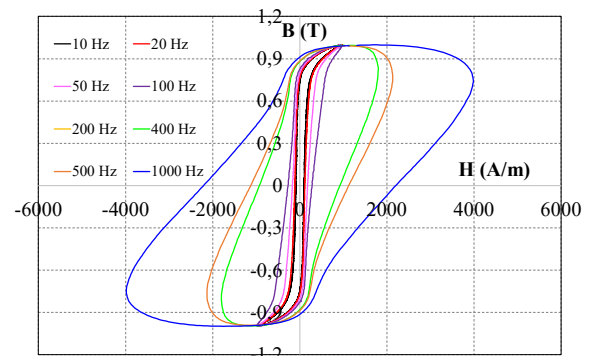


Fig. 15 - Hysteresis cycles at different frequencies for FeSi2.9 toroid with the treatment at 1200°C



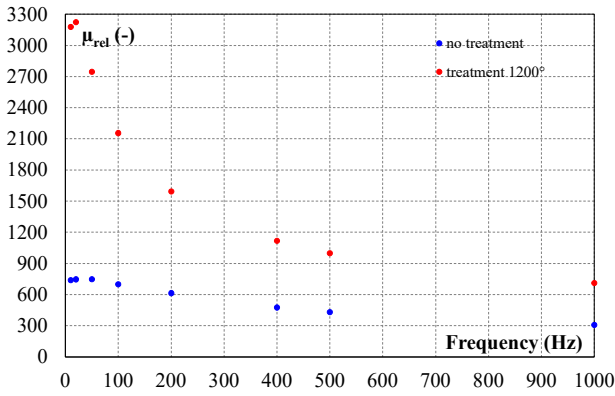


Fig. 16 - Comparison between magnetic permeability before and after thermal treatment as a function of frequency

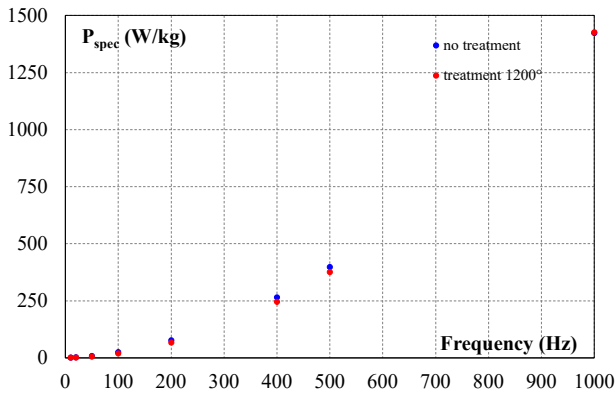


Fig. 17 - Comparison between specific iron losses before and after thermal treatment as a function of frequency

#### IV. APPLICATION

One of the produced FeSi samples fits as the cursor in a small magnetic piston. This device bases on a coil, magnetically pulling an inner solid cursor. The used model is of the single effect type, thus including a counteracting spring. The nominal voltage of the device is 12 Vdc.

After the LPBF process, the sample needed to be machined to obtain smooth surfaces and the thread for the end damper and nut (Fig. 18).

The tests on the device with the original and the newly produced rods, shown in Fig. 19, led to a direct electrical and mechanical comparison between the materials.

During the tests, a voltage step at the nominal level (12Vcd) caused the cursor movement until the natural stop position (Fig. 20). The recorded voltage and current waveforms are shown in the figures (Fig. 21, Fig. 22, and Fig. 23). Due to the reduced force on the FeSi cursor, the spring was not included in the setup and the initial cursor position was moved from the completely open one, to an intermediate one, so that the total stroke was in any case 10 mm.



Fig. 18 - Removal of front (a) and side (b) roughness



Fig. 19 - The original and FeSi2.9 plunger (a) and solenoid closing system (b)

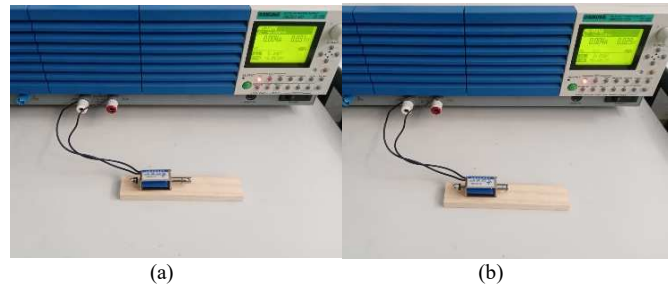


Fig. 20 - Plunger closing measurements: original (a) and FeSi2.9 (b)

In the first transient test, the coil had no cursor inside, so that only the electrical contribution to the current transient is visible (Fig. 21).

The presence of the cursor in the second and third tests changed the current waveform, clearly showing the cursor travel phase and the time at which, the movement completed. The latter can be easily detected as the last current slope inversion, after which the current completes the exponential transient following the higher final inductance value.

The main result is to show that the lower force acting on the FeSi rod causes a reduced acceleration (Fig. 23), with a longer travel time, with respect to the original rod (Fig. 22).

Future improvements to the test bench could lead to the measurement of the transient speed trend or of the force acting on the cursor at different positions.

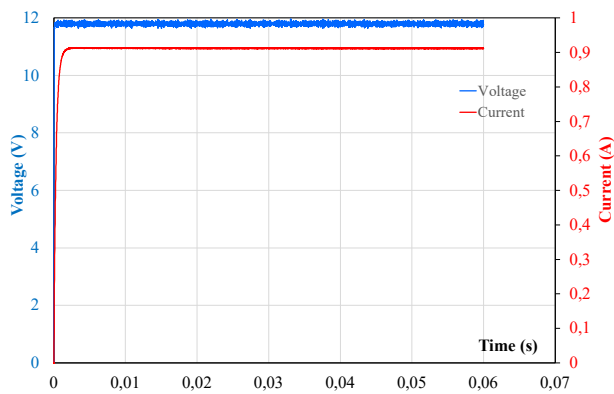


Fig. 21 - Initial current transient: Solenoid only

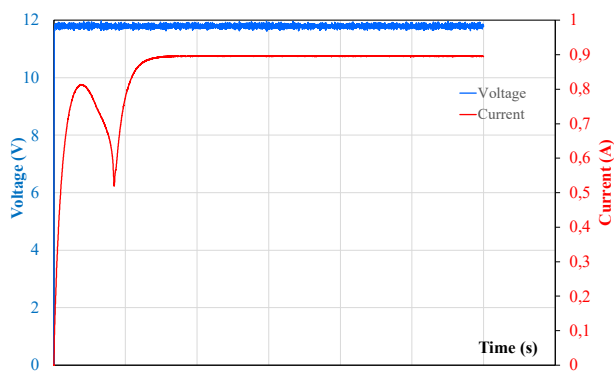


Fig. 22 - Initial current transient: Original small plunger

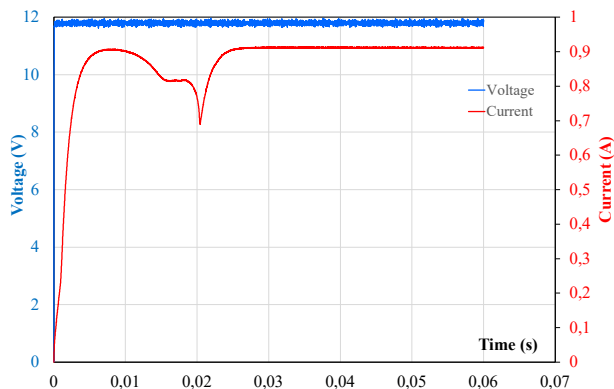


Fig. 23 - Initial current transient: FeSi<sub>2.9</sub> small plunger

## V. CONCLUSION

The above results are a beginning of investigation of the application of additive manufacturing to produce ferromagnetic components. As can be seen from the analyzes shown, the printing parameters and the type of heat treatment greatly affect the electrical and magnetic characteristics of the pieces produced. The electrical conductivity after heat treatment increases considerably, getting very close to the theoretical values for the alloy. For this reason, the lower losses due to hysteresis (narrower and longer cycle in B) are unfortunately compensated by greater losses due to eddy currents (mentioned in the text), which notoriously increase with the frequency, overall, hysteresis losses have been reduced. Future work will focus on the use of new

ferromagnetic alloys and on the possibility of making components with geometries that reduce the effects of eddy currents.

## VI. ACKNOWLEDGMENT

The Italian Ministry of Education, University and Research is acknowledged for the support provided through the Project "Department of Excellence LIS4.0 - Lightweight and Smart Structures for Industry 4.0".

## VII. REFERENCES

- [1] Campbell, I., Bourell, D. and Gibson, I. (2012), "Additive manufacturing: rapid prototyping comes of age", Rapid Prototyping Journal, Vol. 18 No. 4, pp. 255-258. <https://doi.org.ezproxy.biblio.polito.it/10.1108/13552541211231563>.
- [2] Gebhardt, Andreas. (2011). Understanding Additive Manufacturing - Rapid Prototyping, Rapid Tooling, Rapid Manufacturing - 1. Basics, Definitions, and Application Levels.
- [3] Touri, Maria, Fatemeh Kabirian, Mahdi Saadati, Seeram Ramakrishna, and Masoud Mozafari. "Additive Manufacturing of Biomaterials – The Evolution of Rapid Prototyping." Advanced Engineering Materials 21.2 (2019): 1800511-N/a.
- [4] Wong, Kaufui V., and Aldo Hernandez. "A review of additive manufacturing." International scholarly research notices 2012 (2012).
- [5] D. Gu, X. Shi, R. Poprawe, D. L. Bourell, R. Setchi, J. Zhu "Material-structure-performance integrated laser-metal additive manufacturing." Science 372.6545 (2021).
- [6] Ren, X., Shao, H., Lin, T., Zheng, H. (2016). 3D gel-printing—An additive manufacturing method for producing complex shape parts. Materials & Design, 101, 80-87.
- [7] Kumar, S. P., Elangovan, S., Mohanraj, R., Ramakrishna, J. R. (2021). Review on the evolution and technology of State-of-the-Art metal additive manufacturing processes. Materials Today: Proceedings, 46, 7907-7920.
- [8] Jihong, Z. H. U., Han, Z. H. O. U., Chuang, W. A. N. G., Lu, Z. H. O. U., Shangqin, Y. U. A. N., Zhang, W. (2021). A review of topology optimization for additive manufacturing: Status and challenges. Chinese Journal of Aeronautics, 34(1), 91-110.
- [9] Pham, T., Kwon, P., Foster, S. (2021). Additive manufacturing and topology optimization of magnetic materials for electrical machines— A review. Energies, 14(2), 283.
- [10] Ramadani, R., Pal, S., Kegl, M., Predan, J., Drstvenšek, I., Pehan, S., & Belšak, A. (2021). Topology optimization and additive manufacturing in producing lightweight and low vibration gear body. The International Journal of Advanced Manufacturing Technology, 113(11), 3389-3399.
- [11] Kumar, S. P., Elangovan, S., Mohanraj, R., & Ramakrishna, J. R. (2021). Review on the evolution and technology of State-of-the-Art metal additive manufacturing processes. Materials Today: Proceedings, 46, 7907-7920.
- [12] Schaible, J., Sayk, L., Schopphoven, T., Schleifenbaum, J. H., Häfner, C. (2021). Development of a high-speed laser material deposition process for additive manufacturing. Journal of Laser Applications, 33(1), 012021.
- [13] Sing, S. L., Kuo, C. N., Shih, C. T., Ho, C. C., Chua, C. K. (2021). Perspectives of using machine learning in laser powder bed fusion for metal additive manufacturing. Virtual and Physical Prototyping, 16(3), 372-386.
- [14] Blakey-Milner, B., Gradl, P., Snedden, G., Brooks, M., Pitot, J., Lopez, E., du Plessis, A. (2021). Metal additive manufacturing in aerospace: A review. Materials & Design, 209, 110008.
- [15] A. Canova, L. Giaccone, M. Quercio, "A proposal for performance evaluation of low frequency shielding efficiency," IEEE CIRED Conf., 2021, pp. 935-939.
- [16] Kumar, R., Kumar, M., Chohan, J. S. (2021). The role of additive manufacturing for biomedical applications: A critical review. Journal of Manufacturing Processes, 64, 828-850.
- [17] Salifu, S., Desai, D., Ogunbiyi, O., Mwale, K. (2022). Recent development in the additive manufacturing of polymer-based composites for automotive structures—a review. The International Journal of Advanced Manufacturing Technology, 1-15.

- [18] Yan, Lei, Yitao Chen, Frank Liou. "Additive Manufacturing of Functionally Graded Metallic Materials Using Laser Metal Deposition." *Additive Manufacturing* 31 (2020): 100901. Web.
- [19] Dzozbewu Thywill Cephas. "Additive Manufacturing of TiAl-based Alloys." *Manufacturing Review* (Ulis, France) 7 (2020): 35. Web.
- [20] Fousova, Michaela, Drahomir Dvorsky, Marek Vronka, Dalibor Vojtech, Pavel Lejcek. "The Use of Selective Laser Melting to Increase the Performance of AlSi<sub>9</sub>Cu<sub>3</sub>Fe Alloy." *Materials* 11.10 (2018): 1918. Web.
- [21] Garibaldi, Michele, Ian Ashcroft, Marco Simonelli, and Richard Hague. "Metallurgy of high-silicon steel parts produced using Selective Laser Melting." *Acta Materialia* 110 (2016): 207-216.
- [22] Goll, D., D. Schuller, G. Martinek, T. Kunert, J. Schurr, C. Sinz, T. Schubert, T. Bernthaler, H. Riegel, G. Schneider. "Additive Manufacturing of Soft Magnetic Materials and Components." *Additive Manufacturing* 27 (2019): 428-39. Web.
- [23] Chaudhary, V., S.A Mantri, R.V Ramanujan, R. Banerjee. "Additive Manufacturing of Magnetic Materials." *Progress in Materials Science* 114 (2020): 100688. Web.
- [24] Chaudhary, Varun, Nartu Mohan Sai Kiran Kumar Yadav, Srinivas Aditya Mantri, Sriswaroop Dasari, Abhinav Jagetia, R.V Ramanujan, R. Banerjee. "Additive Manufacturing of Functionally Graded Co-Fe and Ni-Fe Magnetic Materials." *Journal of Alloys and Compounds* 823 (2020): 153817. Web.
- [25] Schönrrath, H., M. Spasova, S.O Kilian, R. Meckenstock, G. Witt, J.T Seht, M. Farle. "Additive Manufacturing of Soft Magnetic Permalloy from Fe and Ni Powders: Control of Magnetic Anisotropy." *Journal of Magnetism and Magnetic Materials* 478 (2019): 274-78. Web.
- [26] Nakajima, Kenya, Marc Leparoux, Hiroki Kurita, Briac Lanfant, Di Cui, Masahito Watanabe, Takenobu Sato, Fumio Narita. "Additive Manufacturing of Magnetostrictive Fe-Co Alloys." *Materials* 15.3 (2022): 709. Web.
- [27] E. Pošković, F. Franchini, L. Ferraris, F. Carosio, M. Actis Grande, "Rapid Characterization Method for SMC Materials for a Preliminary Selection", *MDPI. Appl. Sci.*, vol. 11 (24), December 2021.
- [28] M. Garibaldi, I. Ashcroft, J.N. Lemke, M. Simonelli, R. Hague, Effect of annealing on the microstructure and magnetic properties of soft magnetic Fe-Si produced via laser additive manufacturing, *Scripta Materialia*, Vol.142,2018, <https://doi.org/10.1016/j.scriptamat.2017.08.042>.

## VIII. BIOGRAPHIES

**Michele Quercio** was born in Avola (SR), Italy, in 1994. He received the bachelor's and master's degrees in mechanical engineering from the Politecnico di Torino, Turin, Italy, in 2016 and 2018 respectively, where he is currently working toward the Ph.D. degree in electrical engineering in the Energy Department, since 2019, working in several fields: computation of electromagnetic fields, design of magnetic shields, implementation of computational algorithms, and renewable energy. He is also actually Convenor of the working group on non-destructive testing applied to the additive manufacturing sector of the Italian National Association of non Destructive Testing and Vice-Convenor of the same commission WG6 (<https://www.efndt.org/Organisation/Working-Groups/Working-Group-6-NDT-in-Additive-Manufacturing>) of the European Federation for Non Destructive Testing (EFNDT).

**Francesco Galbusera** was born in Lecco, Italy, in 1995. He received the bachelor's and master's degrees in mechanical engineering from Politecnico di Milano, Italy, in 2018 and 2020 respectively. He is currently working on his Ph.D. in mechanical engineering at Politecnico di Milano, working with novel LPBF processing techniques to enhance the processability of e-mobility alloys.

**Emir Pošković** was born in Sarajevo in Bosnia and Herzegovina, He studied and graduated from the Polytechnic of Turin, where he received B.S. and M.Sc. degree in electrical engineering in 2006 and in 2008, respectively. Also, he received a doctor's degree in electrical energy engineering from the University of Padova in 2020. He is an Assistant Professor with the Energy Department, Politecnico di Torino and a Key Researcher for the Magnetic Characterization Laboratory, Alessandria campus of Politecnico di Torino. His special fields of interest included soft and hard magnetic materials,

electrical machines, alternative and renewable energy (micro-hydro, fuel cell, PV-photovoltaic). He has published more than 50 scientific papers in conference proceedings and technical journals.

**Fausto Franchini** received the B.S. degree in electrical engineering from the Politecnico di Torino, Alessandria, Italy, in 2003. Since 2004, he has been a Technician with the Electrical Engineering Laboratory, Politecnico di Torino, Torino, Italy, where he has been responsible of the laboratory since 2007. His research interests include electromagnetic metrology, electromagnetic compatibility, data acquisition, control, and automation.

**Luca Ferraris** received the M.S. degree in electrical engineering from the Politecnico di Torino, Turin, Italy, in 1992. In 1995, he joined the Department of Electrical Engineering, Politecnico di Torino, where he is currently an Associate Professor of Electrical Machines and Drives and currently coordinates the experimental activities of the Electric and Electromagnetic Laboratories. He has published more than 120 technical papers in conference proceedings and technical journals. His research interests are the energetic behavior of machines, innovative magnetic materials for electromagnetic devices, electrical traction, electromagnetic compatibility, and renewable energies.

**Aldo Canova** was born in Biella, Italy, in 1967. He received the Laurea and Ph.D. degrees in electrical engineering from the Politecnico di Torino, Turin, Italy, in 1992 and 1996, respectively. In 1995, he became Researcher, then in 2003 Associate Professor and finally in 2017 Full Professor with the Energy Department "Galileo Ferraris" of Politecnico di Torino. He has authored/coauthored about 180 scientific publications in international conference proceedings and international journals and invented 8 patents. He is involved in research activities related to the numerical computation of electromagnetic fields in the area of power devices and magnetic shielding, energy system modelling and optimisation and non destructive testing. He has been a Member of the Comitato Elettrotecnico Nazionale (CEI) serving on Technical Committee CT106 (methods for the assessment of electric, magnetic and electromagnetic fields associated with human exposure), since 2004. He is also actually General Secretary of the Italian National Association of non Destructive Testing.

**Giambattista Groosso**, Senior Member, IEEE, was born in 1973. He received the B.S. and M.S. degrees in electrical engineering and the Ph.D. degree in electrical engineering from the Politecnico di Torino, Italy, in 1999 and 2003, respectively. From 2002 to 2011, he was an Assistant Professor with the Department of Electronics and Informatics, Politecnico di Milano, where he has been an Associate Professor, since 2011. He is the author of more than 80 papers on Journals and conferences on the topics. He does research in electrical engineering, electronic engineering, and industrial engineering. His main research interests include electrical vehicles transportation electrification, electrical power systems optimization, simulation of electrical systems, digital twins for smart mobility, factory and city, and how they can be obtained from data.

**Ali Gökhan Demir** was born in Istanbul, Turkey, in 1985. He completed his PhD in Mechanical Engineering at the Politecnico di Milano in collaboration with the University of Cambridge gaining a European PhD title in 2014. He has been an Associate Professor with the Department of Mechanical Engineering, Politecnico di Milano, since 2021. His current research interests include laser-based manufacturing processes, mainly, additive manufacturing, laser micromachining, and laser welding. Within his research, he gives emphasis to the light-material interaction mechanism in temporal, spatial, and wavelength domains to gather a greater understanding of both existing and new processes.

**Barbara Previtali** received her PhD degree in manufacturing and production system from the Politecnico di Milano in 2002. In 2016, she was appointed as Full Professor in the Mechanical Engineering Department, Politecnico di Milano. She leads the SITEC—Laboratory for Laser Applications and PromozioneL@ser with AITeM, which collects Italian laser users in industry and academia. Her current research interests include modeling, optimization and control of laser processes in their application in various fields. On these research subjects, she has authored or coauthored over 100 papers in refereed international journals and international conferences and several international patents.