

4D printing of light activated shape memory polymers with organic dyes

Original

4D printing of light activated shape memory polymers with organic dyes / Gastaldi, M.; Spiegel, C. A.; Vazquez-Martel, C.; Barolo, C.; Roppolo, I.; Blasco, E.. - In: MOLECULAR SYSTEMS DESIGN & ENGINEERING. - ISSN 2058-9689. - 8:3(2022), pp. 323-329. [10.1039/d2me00201a]

Availability:

This version is available at: 11583/2975715 since: 2023-03-16T15:41:30Z

Publisher:

RSC

Published

DOI:10.1039/d2me00201a

Terms of use:

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

Publisher copyright

(Article begins on next page)

ARTICLE

4D Printing of Light Activated Shape Memory Polymers with Organic Dyes

Received 00th January 20xx,
Accepted 00th January 20xx

Matteo Gastaldi,^{†,a} Christoph A. Spiegel,^{‡,b,c} Clara Vazquez-Martel,^{‡,b,c} Claudia Barolo,^{a,d} Ignazio Roppolo,^{*e} Eva Blasco^{*b,c}

DOI: 10.1039/x0xx00000x

Light based 3D printing technologies, such as digital light processing (DLP), allows for the additive manufacturing of complex 3D objects at fast speeds and with high resolution. Typical printable formulations for DLP consist of a (mixture) of monomer(s), a photoinitiator and very often, an organic dye absorbing at the printing wavelength in order to improve the resolution. Herein, we exploit the use of push-pull azobenzene (azo) dyes to not only enhance printing resolution but also to enable light response (fourth-dimension) of printed shape memory polymers (SMPs) employing DLP without the necessity of adding inorganic additives. In particular, a library of azo-dyes with different substituents in ortho-position have been synthesized and added as active dyes in the printing formulation. The light activated shape memory effect is demonstrated for all the printed structures including the dyes. Among all of them, the structures containing chlorine-substituted azo dyes show the best performance. Importantly, the desired effect is achieved with only 0.1 wt% of dye in the formulation. Furthermore, we demonstrate the potential of using visible light as stimulus for spatially resolved activation of complex structures on demand.

Introduction

Since its first conceptualization in 2013, four-dimensional (4D) printing has revolutionized the worlds of additive manufacturing and design.^[1,2] 4D printing relies on the combination of responsive materials with additive manufacturing technologies, enabling the fabrication of smart architectures able to evolve with time in response to external stimuli. Among the external stimuli reported - solvent^[3,4], pH^[5,6] or magnetic field^[7,8], temperature^[9-12] is certainly the most exploited one. Common thermoresponsive polymers include hydrogels^[12,13], liquid crystalline elastomers^[14-16] and shape memory polymers (SMPs)^[17-19]. The temperature activated morphism of the latter class – SMPs – is well-established and has found applications in everyday life^[20] as medical devices, smart fabrics or packaging.^[21]

In this context, the main approach to activate shape changes consists of heating a 3D printed structure either directly or using a thermal sink (such as water) to provide the desired temperature. Nevertheless, this strategy presents some drawbacks limiting its applicability: i) the necessity to heat the whole volume and thereby loss of any spatial control in terms of recovery and ii) material degradation that can take place due to applied high temperatures. Other approaches were proposed to improve localization and control of heating, such as use of current for Joule heating^[22] or magnetic field^[23]. Another suitable stimulus is irradiation. Light could be particularly attractive since its tunability of intensity, irradiation, irradiation time, polarization direction and wavelength allows precise spatial and temporal control.^[24-26] One strategy to achieve light response is the incorporation of an absorber, such as an inorganic filler, which can convert the absorbed light into heat, enabling shape recovery activation. In particular, gold^[27], silver^[28] and titanium^[29] nanoparticles as well as carbon fibers^[30], carbon black^[31], graphene^[32] and even rare earth complexes^[33] have been successfully incorporated in SMPs enabling light-induced shape-recovery. Organic dyes, such as azobenzene derivatives (azo-dyes), are an interesting alternative to inorganic fillers, which up to now have not been fully exploited in printable SMPs. The main advantages of azo-dyes are the straightforward preparation and functionalization, which enable to fine-tune their absorption properties, as well as their photostability on demand.^[34] The incorporation of these functional dyes in polymers, and more specifically in liquid crystalline materials, have been extensively investigated,

^a Department of Chemistry and NIS Interdepartmental Centre and INSTM Reference Centre, University of Torino, Via Pietro Giuria 7, 10125 Torino, Italy

^b Institute of Organic Chemistry, Heidelberg University, Heidelberg 69120, Germany
E-mail: eva.blasco@oci.uni-heidelberg.de

^c Institute for Molecular Systems Engineering and Advanced Materials, Heidelberg University, Im Neuenheimer Feld 225, 69120 Heidelberg, Germany

^d ICxT Interdepartmental Center, University of Turin, Lungo Dora Siena 100, 10153 Torino, Italy

^e Department of Applied Science and Technology, Politecnico di Torino, C.so Duca degli Abruzzi 24, 10129, Turin, Italy
E-mail: ignazio.roppolo@polito.it

[†]Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x

[‡]These authors contributed equally.

*Corresponding authors.

showing potential applications ranging from photoactuators, to photonic elements to biomedical devices.^[35–37] Furthermore, azo-dyes are widely used in photocurable resins in light-based 3D printing techniques, such as digital light processing (DLP)^[9,38,39]. Here, the use of dyes is crucial, due to their interactions with incident curing light, improving in this way control of the polymerization reaction, enabling higher precision, higher resolution (or smaller feature sizes) and consequently allowing the fabrication of more complex structures featuring fine structural details. Recently, the use of dyes has expanded over their conventional role, using them to impart functional properties to the 3D printed components.^[40] Based on our prior work on the design of a functional SMP ink system for DLP 3D printing utilizing a temperature stimulus,^[9] we attempt to expand the state-of-the-art of SMPs as printable materials and aim at the fabrication of complex 4D structures that can undergo spatially controlled shape changes. To achieve this, we employ azo-dyes as photoresponsive units to obtain 4D printed structures that offer at the same time high printing precision as well as light-induced programmable shape changes without the necessity of additional additives such as inorganic fillers. In this context, visible light irradiation will be used to locally increase the temperature and activate the SMP properties on demand (see Figure 1).

Results and discussion

Identification of a Functional System.

Push-pull azo-dyes were selected as ideal photoresponsive units. Their role here is two-fold: i) enhancing resolution during the 3D printing process and ii) enabling light-induced shape changes of the printed structures. Thus, a library of acrylate push-pull azo-dyes (see Figure 1) was first synthesized, introducing different functional groups in order to control the photochemical properties of the final molecules (see Supporting information) through electronic or steric effects.^[41] All the azo-dyes bear an acrylate moiety to enable covalent reaction during the 3D fabrication process and thus incorporation of the functional dyes into the polymeric network.^[42,43] Furthermore, all azo-dyes showed absorbance in the range of 400 nm to 600 nm (see absorbance spectra in Figure S1, Supporting information), not interfering with the 3D curing wavelength of 385 nm and allowing a later shape memory recovery actuation with light in the visible range.

4D printing of Light Activated SMPs.

In the next step, the synthesized azo-dyes were tested in SMP

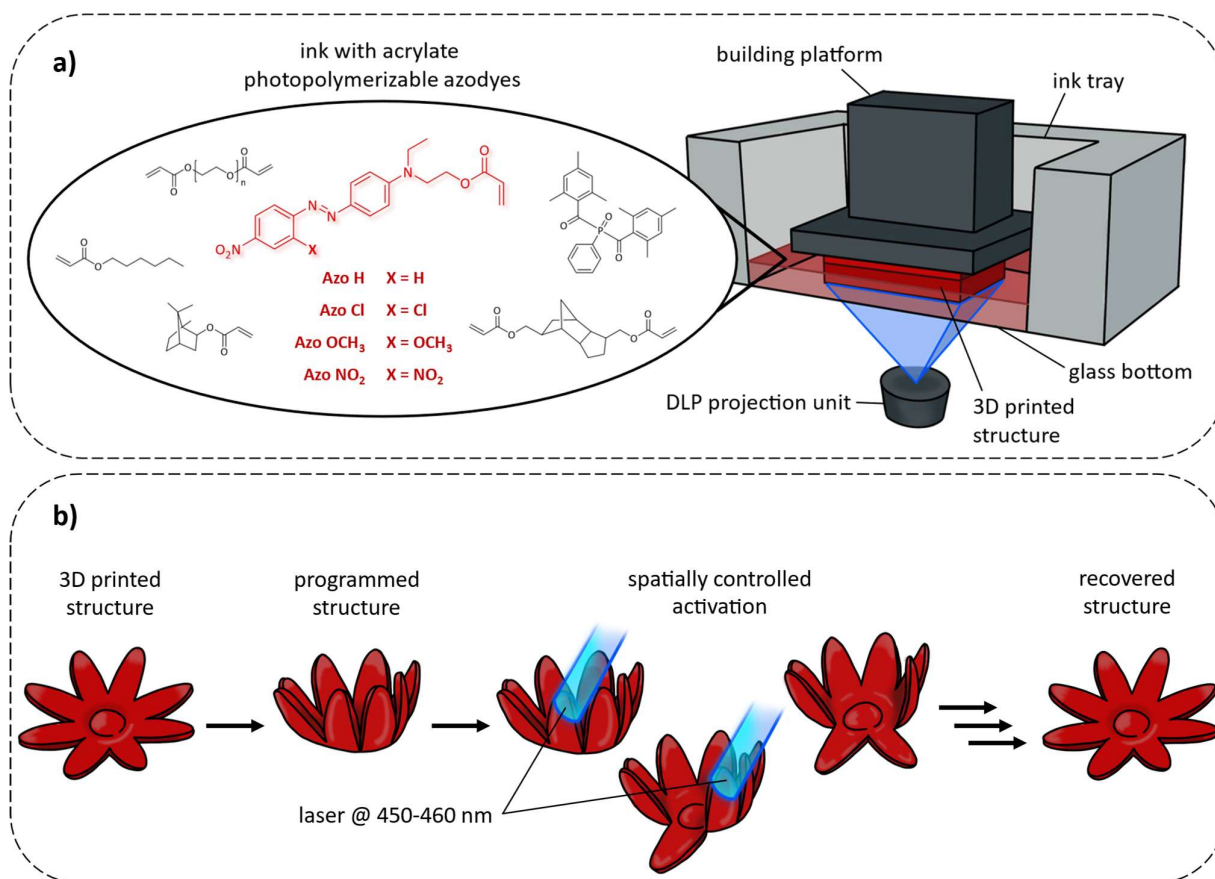


Figure 1. 4D Printing of Light Activated Shape Memory Polymers. a) Ink formulation based on acrylate monomer including photopolymerizable azo dyes and scheme of the DLP printer. b) Schematic representation of the shape memory cycle including the programming step followed by spatially controlled light induced recovery.

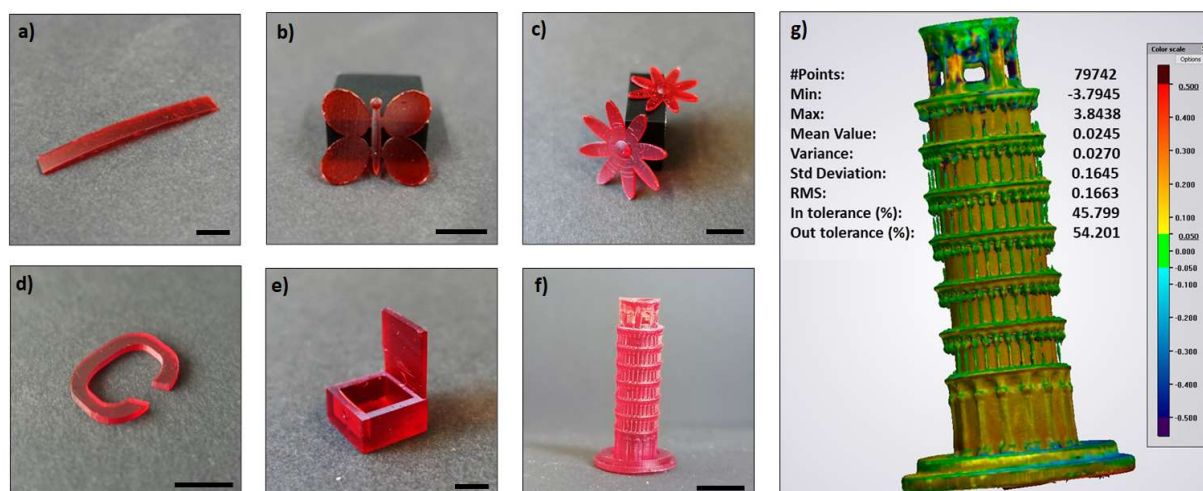


Figure 2. 3D printed structures using the formulation containing AzoCl: a) stripe, b) butterfly, c) flower, d) chain segment e) box, f) Pisa tower. g) Structural fidelity achieved demonstrated by the printed Pisa tower structure: Heat map illustrating deviations between the 3D scanned image of the printed structure with its STL file. Scale bar = 10 mm.

3D printable formulations, based on a previously optimized formulation of liquid components, exhibiting good printability by DLP fabrication as well as excellent shape memory properties.^[9] The SMP based ink is composed of isobornyl acrylate (IBA) as main component, and poly(ethylene glycol) diacrylate ($M_n = 575 \text{ g mol}^{-1}$, PEGDA) and tricyclo[5.2.1.0^{2,6}] decanedimethanol diacrylate (TCMDMA) as flexible and stiff crosslinkers, hexyl acrylate (HA), as well as phenylbis(2,4,6-trimethylbenzoyl)phosphine oxide (Irg819) as photoinitiator. The optimal concentration of azo-dye was experimentally evaluated for each sample by performing curing tests utilizing UV-LED irradiation in the range from 380 nm to 390 nm (same range as the DLP printer). In particular, we tested ink formulations with increasing amounts of azo-dye compounds AzoH, AzoCl, AzoOCH₃ and AzoNO₂ from 0.1 to 2.0 wt.% and determined the time required to achieve of the resin. The results are summarized in Table S1 in the Supporting information. As expected, it was observed that the higher is the azo-dye concentration, the longer time is required to achieve the photopolymerization. This is due to the competition of photon absorption between dye and photoinitiator. To not affect the efficiency of the printing process, an azo-dye concentration of 0.1 wt.% was set as optimal for all inks.

Afterwards, printing parameters for each ink were carefully optimized in terms of layer thickness and curing time, aiming an efficient and precise 3D fabrication process. Conducting material tests, Jacobs working curves were obtained at 10 mW cm^{-2} for each functional ink containing AzoH, AzoCl, AzoOCH₃, AzoNO₂ (see Figure S2, Supporting information). Critical energy values E_c were determined in the range of 3.1 to 4.3 mJ cm^{-2} and values for the light penetration depth D_p were calculated in the region of 70 to $80 \text{ }\mu\text{m}$. Setting the irradiation intensity to 10 mW cm^{-2} allowed structure fabrication with layer thicknesses of $50 \text{ }\mu\text{m}$ at short curing times between 1.5 s and 2.0 s , depending on the applied azo-dye (see Table S2, Supporting information). The printing performance was further investigated by 3D

manufacturing a range of geometries, starting from simple stripes, butterflies or flowers towards architectures featuring overhanging moieties such as the 3D box (see Figure 2a – e for ink containing AzoCl) and concluding with highly complex structures such as the Pisa Tower, allowing printability of even finest features (see Figure 2f). In case of the Pisa Tower structural fidelity of the printed geometry was further examined employing a 3D scanner. The obtained digital image was overlapped to the initial 3D model and the differences are plotted in a heat map (see Figure 2g) showing high structural fidelity. Importantly, the resolution was further evaluated quantitatively under the microscope showing good results down to $40 \text{ }\mu\text{m}$ for all the formulations (Figure S3, Supporting information).

Study of the Opto-thermo-mechanical Properties

Once the printed parameters were also optimized, we studied the opto-thermo-mechanical properties, in order to define the most effective dye to fabricate 4D devices. The activation of the shape memory process requires overcoming the glass transition temperature (T_g) by light induced heating.^[44,45] These values for T_g were obtained by dynamic mechanical analysis (DMA) (Figure 3a and Figure S4, Supporting information). We employed 3D printed flat specimens ($30 \times 10 \times 1 \text{ mm}^3$) from all formulations containing the different azo-dyes as well as from one without as reference (see Figure 3a, Figure S4 and Table S3, Supporting information). An intense peak is detected at about 80°C , which corresponds to the T_g of the major component (IBA monomer) in the generated network (all values are reported in Table S3). A second weaker transition temperature centred about 30°C was also observed, likely related to the aliphatic component. As expected, by comparing with the reference, no relevant modifications occur with the introduction of azo-dyes. In addition, the thermal stability of the fabricated structures was investigated using thermogravimetry (TGA) (see Figure S5,

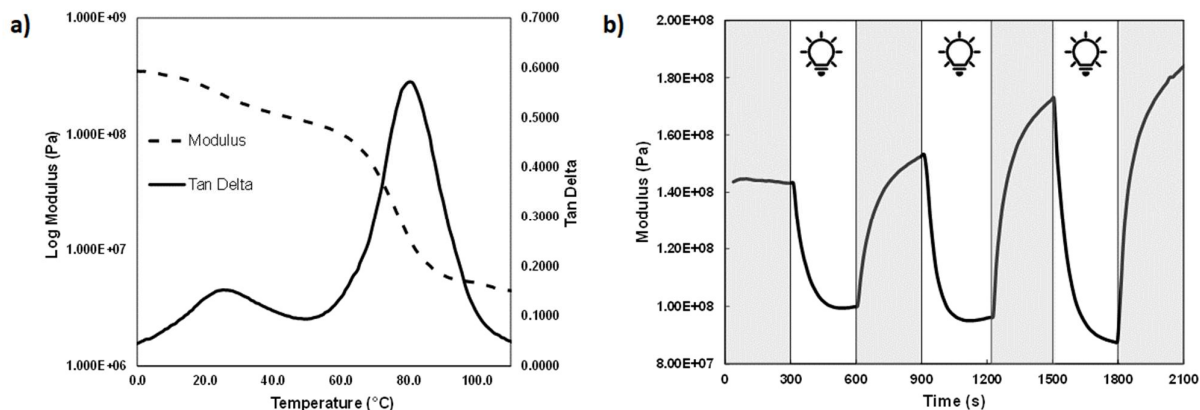


Figure 3. Thermo-mechanical and opto-mechanical characterization. a) DMA measurement of a stripe structure fabricated with functional ink based on AzoCl. b) DMA measurement under irradiation by 459 nm LED. Timeframes without a bulb define dark state (lamp switched off), whereas timeframes marked with a bulb define irradiated state (lamp switched on).

Supporting information). It was observed, that the incorporation of azo-dyes led to a decrease of the decomposition temperature. However, all the samples are stable until 130 °C without showing any degradation.

To gain more insight into opto-mechanical properties of the azo-containing printed materials, DMA measurements were conducted under LED irradiation of 459 nm wavelength. In particular, the variations of the storage modulus measured while switching on and off the light were monitored (see Figure 3b and Figure S6, Supporting information). Importantly, while the blank sample was not significantly affected, all azo-based samples exhibited a reduction in storage modulus (E') when irradiation by the light source was initiated due to the photothermal effect. Furthermore, this behaviour appears to be completely reversible when the light was turned off. Increasing the current of the LED power supply a faster response can be observed as well as more reduced values of storage modulus (E') were reached.

Light Activated Shape Memory Effect

Shape memory tests using the 4D printed flat strips containing the different azo-dyes were performed as next step. In these experiments the printed flat strips were deformed to a temporary (bent) shape using a pre-heated water bath (80 °C) and fixed using cold water at 15 °C. To activate the shape memory effect (recovery), the samples were irradiated using an LED (459 nm), which allows for local heating of the sample. To monitor the process, the recovery parameter α (recovered angle for bent strip) was measured as shown in Figure S7 (Supporting information) for each sample. For the samples containing azo-dyes AzoH and AzoOCH₃, the time required to complete the process is about 6 and 7 minutes, while for AzoCl and AzoNO₂ the process was faster, taking only 4 minutes to achieve 100% of shape recovery (Figure S8). Considering the results obtained, AzoCl resulted as the best dye to obtain 4D structures with a good light-activated shape memory effect along with its easy synthetical procedure and good printability.

Thus, the ink system containing azo-dye AzoCl was selected to carry out the next shape memory experiments on more complex 3D printed shapes. After programming the different shapes, the recovery was performed using a blue laser (450–460 nm) to demonstrated the light-activated SME. The temperature reached by laser irradiation was evaluated using 3D structures containing AzoCl and blank ink. For AzoCl structures temperatures above the higher T_g of the material and up to 125 °C were measured, despite of the low azo content, i.e., 0.1 wt% (see figure S9 and movie S01, Supporting information), whereas

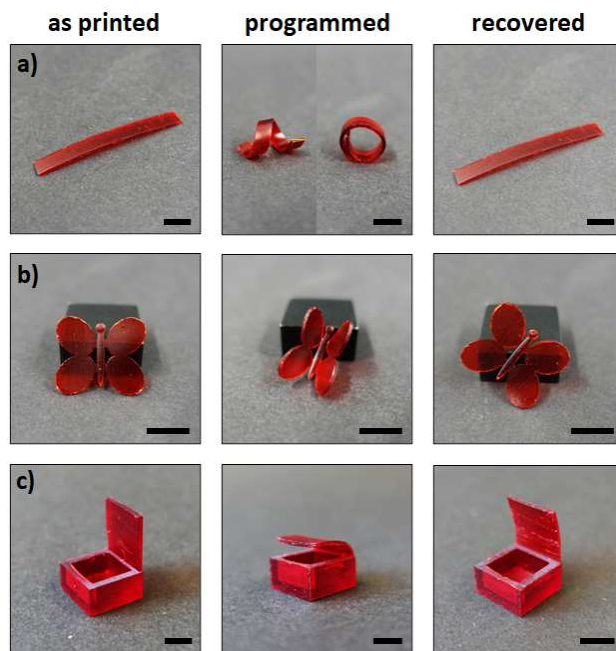


Figure 4. Shape memory test of DLP-printed structures. Initial (as printed), temporary and recovered shape of a) strip, b) butterfly, c) box. Programming was performed in hot water at 95 °C, followed by fixation in cold water at 15 °C. Successive shape memory recovery was initiated by blue laser light irradiation (450–460 nm) at 567 mW cm⁻². Scale bar = 10 mm

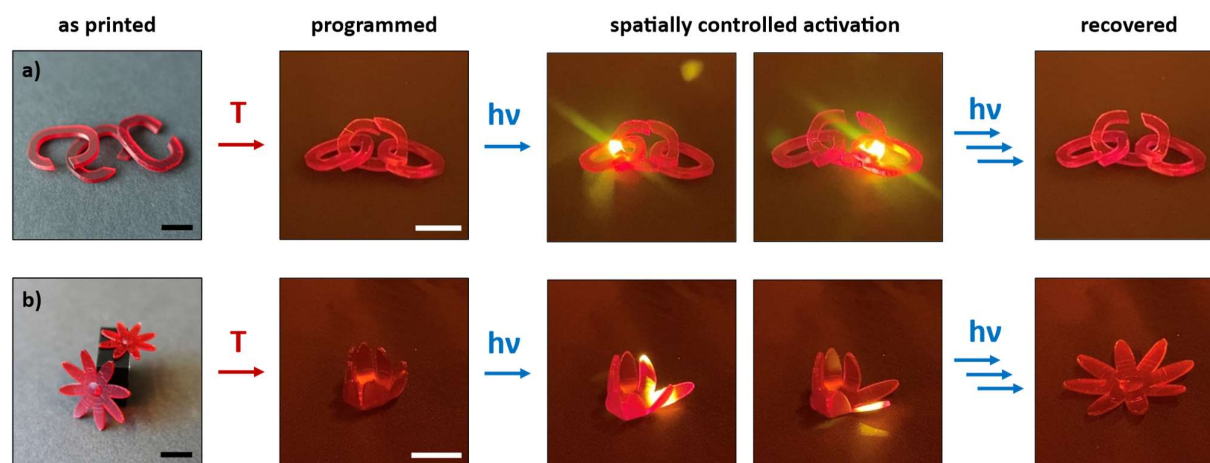


Figure 5. Spatially controlled recovery of the a) chain and b) flowers. Programming was performed in hot water at 95 °C, followed by fixation in cold water at 15 °C. Spatially controlled shape memory recovery was performed by irradiating the sample with blue laser light locally (450-460 nm) at 567 mW. Scale bar = 10 mm.

blank samples show no temperature increase (see figure S9 and movie S02, Supporting information). To further demonstrate the versatility and spatial control of the system, the flat strip was programmed and fixed in several shapes – e.g. a circular and a helical one – and recovered back to the initial shape by laser irradiation (see Figure 4a and movie S03 and movie S04, Supporting information). The programming and light induced shape recovery was also successfully evidenced utilizing complex 3D geometries such as a butterfly (see Figure 4b and movie S05, Supporting information), a flower (see Figure 5b and movie S06, Supporting information) and even “smart” box that can be opened on demand (see Figure 4c and movie S07, Supporting information).

Having demonstrated the light induced SME in different 3D printed structures, the potential of using light as stimulus was further exploited enabling spatially controlled activation and therefore, a finer manipulation of shape morphing. For visual demonstration, links and flowers were printed in the “open” state and programmed in a “closed” state. Here, the blue laser was employed to locally heat a specific region of the sample at temperatures above the T_g of the printed structure. Due to poor thermal conductivity of the polymer based material, the temperature increase is very local and the rest of the sample is barely affected allowing for a precise activation of the material in the targeted point. As a result, the recovery takes place only in the irradiated region enabling a partial recovery, and therefore new programmed shapes. For example, in the case of the three links, we were able to first selectively open the central segment without affecting of the two outer elements (see Figure 5a and movie S08, Supporting information), which could be open by focusing the laser (if desired). Furthermore, this effect can be also employed to enable even more “intermediate” states. As another example, the petals of the “closed” programmed flower can be selectively open individually on demand by focusing the laser in the intersection (see Figure 5b, movie S06, Supporting information).

Conclusions

In this study it has been demonstrated that push-pull azo dyes can be efficiently used to fabricate 4D printable objects. Different azo-dyes with different substituents in ortho position were synthesized and used as active dyes in a SM formulation suitable for light-activated 3D printing. All the dyes showed the ability to induce light activated shape memory behaviour. Furthermore, their presence helped the 3D printing process, increasing precision and structural fidelity. Among all the test dyes, the one modified with chlorine offered the best performance in terms of percentage and speed of recovery of the initial shape. Thermal tests performed on complex shape 3D printed objects evidenced a rapid increase of temperature induced by the presence of azo compounds. Furthermore, this temperature increase results localized in the irradiated area allowing for shape recovery with excellent spatial control. This was exploited in several 4D printed demonstrators, which showed light-induced spatial and time control over the shape memory properties. SME behaviour resulted also to be repeatable, indicating that despite temperature increase, dyes do not degrade, allowing to maintain the light-responsive property over time. Noteworthy, the light-controlled activation of shape memory behaviour is based on a component which is added at only 0.1 wt% of the ingredients. These findings can find multiple applications in soft robotics, advanced sensors, and biological studies.

Author Contributions

M.G., A.C.S and C.V-M.: data curation, methodology, investigation, software, formal analysis, visualization, writing – original draft. C.B., I.R. and E.B.: conceptualization, methodology, formal analysis, funding acquisition, resources, project administration, supervision, writing – review & editing.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

E.B. acknowledges the funding from the Deutsche Forschungsgemeinschaft (DFG, German Research Foundation) via the project BL-1604/2-1 and the Excellence Cluster “3D Matter Made to Order” (EXC-2082/1-390761711) and the Carl Zeiss Foundation through the “Carl-Zeiss-Foundation-Focus@HeiKA. C. V.-M. acknowledges the Fonds der Chemischen Industrie for the support during her PhD studies. The authors thank P. Kiefer (Karlsruhe Institute of Technology) for his help with the light microscope measurements. The authors also want to thank Y. Rahman (Karlsruhe Institute of Technology) for the fruitful discussions.

Notes and references

- P. Fu, H. Li, J. Gong, Z. Fan, A. T. Smith, K. Shen, T. O. Khalafallah, H. Huang, X. Qian, J. R. McCutcheon, L. Sun, *Prog. Polym. Sci.*, 2022, **126**, 101506.
- X. Kuang, D. J. Roach, J. Wu, C. M. Hamel, Z. Ding, T. Wang, M. L. Dunn, H. J. Qi, *Adv. Funct. Mater.*, 2019, **29**, 1805290.
- A. S. Gladman, E. A. Matsumoto, R. G. Nuzzo, L. Mahadevan, J. A. Lewis, *Nature Mater.*, 2016, **15**, 413.
- Z. Zhao, X. Kuang, C. Yuan, H. J. Qi, D. Fang, *ACS Appl. Mater. Interfaces*, 2018, **10**, 19932.
- Y. Hu, Z. Wang, D. Jin, C. Zhang, R. Sun, Z. Li, K. Hu, J. Ni, Z. Cai, D. Pan, X. Wang, W. Zhu, J. Li, D. Wu, L. Zhang, J. Chu, *Adv. Funct. Mater.*, 2020, **30**, 1907377.
- C. Garcia, A. Gallardo, D. López, C. Elvira, A. Azahti, E. Lopez-Martinez, A. L. Cortajarena, C. M. González-Henríquez, M. A. Sarabia-Vallejos, J. Rodríguez-Hernández, *ACS Appl. Bio Mater.*, 2018, **1**, 1337.
- S. Roh, L. B. Okello, N. Golbasi, J. P. Hankwitz, J. A.-C. Liu, J. B. Tracy, O. D. Velev, *Adv. Mater. Technol.*, 2019, **4**, 1800528.
- Y. Zhang, Q. Wang, S. Yi, Z. Lin, C. Wang, Z. Chen, L. Jiang, *ACS Appl. Mater. Interfaces*, 2021, **13**, 4174.
- C. A. Spiegel, M. Hackner, V. P. Bothe, J. P. Spatz, E. Blasco, *Adv. Funct. Mater.*, 2022, 2110580.
- K. Liu, Y. Zhang, H. Cao, H. Liu, Y. Geng, W. Yuan, J. Zhou, Z. L. Wu, G. Shan, Y. Bao, Q. Zhao, T. Xie, P. Pan, *Adv. Mater.*, 2020, **32**, 2001693.
- M. Hua, D. Wu, S. Wu, Y. Ma, Y. Alsaied, X. He, *ACS Appl. Mater. Interfaces*, 2021, **13**, 12689.
- M. Hippler, E. Blasco, J. Qu, M. Tanaka, C. Barner-Kowollik, M. Wegener, M. Bastmeyer, *Nat. Commun.*, 2019, **10**, 232.
- M. Champeau, D. Alves Heinze, T. Nunes Viana, E. Rodrigues de Souza, A. C. Chinellato, S. Titotto, *Adv. Funct. Mater.*, 2020, **30**, 1910606.
- Z. Guan, L. Wang, J. Bae, *Mater. Horiz.*, 2022, **9**, 1825.
- M. del Pozo, J. A. H. P. Sol, A. P. H. J. Schenning, M. G. Debije, *Adv. Mater.*, 2022, **34**, 2104390.
- A. Münchinger, V. Hahn, D. Beutel, S. Woska, J. Monti, C. Rockstuhl, E. Blasco, M. Wegener, *Adv. Mater. Technol.*, 2022, **7**, 2100944.
- J. Zhang, Z. Yin, L. Ren, Q. Liu, L. Ren, X. Yang, X. Zhou, *Adv. Mater. Technol.*, 2022, 2101568.
- Q. Ge, A. H. Sakhaei, H. Lee, C. K. Dunn, N. X. Fang, M. L. Dunn, *Sci. Rep.*, 2016, **6**, 31110.
- B. Zhang, H. Li, J. Cheng, H. Ye, A. H. Sakhaei, C. Yuan, P. Rao, Y.-F. Zhang, Z. Chen, R. Wang, X. He, J. Liu, R. Xiao, S. Qu, Q. Ge, *Adv. Mater.*, 2021, **33**, 2101298.
- M. Behl, A. Lendlein, *Mater. Today*, 2007, **10**, 20.
- Y. Xia, Y. He, F. Zhang, Y. Liu, J. Leng, *Adv. Mater.*, 2021, **33**, 2000713.
- A. Cortés, A. Cosola, M. Sangermano, M. Campo, S. González Prolongo, C. F. Pirri, A. Jiménez-Suárez, A. Chiappone, *Adv. Funct. Mater.*, 2021, **31**, 2106774.
- F. Zhang, L. Wang, Z. Zheng, Y. Liu, J. Leng, *Compos. - A: Appl. Sci. Manuf.*, 2019, **125**, 105571.
- M. Herath, J. Epaarachchi, M. Islam, L. Fang, J. Leng, *Eur. Polym. J.*, 2020, **136**, 109912.
- E. Pantuso, G. D. Filpo, F. P. Nicoletta, *Adv. Opt. Mater.*, 2019, **7**, 190025.
- R. Klajn, *Chem. Soc. Rev.*, 2014, **43**, 148.
- H. Zhang, Y. Zhao, *ACS Appl. Mater. Interfaces*, 2013, **5**, 13069.
- N. Yenpech, V. Intasanta, S. Chirachanchai, *Polymer*, 2019, **182**, 121792.
- S. Ishii, K. Uto, E. Niiyama, M. Ebara, T. Nagao, *ACS Appl. Mater. Interfaces*, 2016, **8**, 5634.
- H. M. C. M. Herath, J. A. Epaarachchi, M. M. Islam, W. Al-Azzawi, J. Leng, F. Zhang, *Compos. Sci. Technol.*, 2018, **167**, 206.
- Y. Liu, G. Zhu, W. Liu, H. Liu, Y. Huo, T. Ren, X. Hou, *Smart Mater. Struct.*, 2018, **27**, 095008.
- J. Loomis, X. Fan, F. Khosravi, P. Xu, M. Fletcher, R. W. Cohn, B. Panchapakesan, *Sci. Rep.*, 2013, **3**, 1900.
- L. Fang, S. Chen, T. Fang, J. Fang, C. Lu, Z. Xu, *Compos. Sci. Technol.*, 2017, **138**, 106.
- P. Weis, W. Tian, S. Wu, *Chem. Eur. J.*, 2018, **24**, 6494.
- H. Zeng, P. Wasylczyk, C. Parmeggiani, D. Martella, M. Buresi, D. S. Wiersma, *Adv. Mater.*, 2015, **27**, 3883.
- D. Martella, S. Nocentini, D. Nuzhdin, C. Parmeggiani, D. S. Wiersma, *Adv. Mater.*, 2017, **29**, 1704047.
- M. del Pozo, J. A. H. P. Sol, A. P. H. J. Schenning, M. G. Debije, *Adv. Mater.*, 2022, **34**, 2104390.
- S. Deng, J. Wu, M. D. Dickey, Q. Zhao, T. Xie, *Adv. Mater.*, 2019, **31**, 1903970.
- D. Ahn, L. M. Stevens, K. Zhou, Z. A. Page, *ACS Cent. Sci.*, 2020, **6**, 1555.
- M. Gastaldi, F. Cardano, M. Zanetti, G. Viscardi, C. Barolo, S. Bordiga, S. Magdassi, A. Fin, I. Roppolo, *ACS Materials Lett.*, 2021, **3**, 1.
- J. V. Accardo, J. A. Kalow, *Chem. Sci.*, 2018, **9**, 5987.
- M. Gillono, I. Roppolo, F. Frascella, L. Scaltrito, C. F. Pirri, A. F. Chiappone, *App. Mater. Today*, 2020, **18**, 100470.
- I. Roppolo, A. Chiappone, A. Angelini, S. Stassi, F. Frascella, C. F. Pirri, C. Ricciardi, E. Descrovi, *Mater. Horiz.*, 2017, **4**, 396.
- R. Suriano, R. Bernasconi, L. Magagnin, M. Levi, *J. Electrochem. Soc.*, 2019, **166**, B3274.
- A. P. Piedade, *J. Funct. Biomater.*, 2019, **10**, 9.