

Effects of Bioactive Glasses (BGs) on Exosome Production and Secretion: A Critical Review

*Original*

Effects of Bioactive Glasses (BGs) on Exosome Production and Secretion: A Critical Review / Gorgani, S.; Hosseini, S. A.; Wang, A. Z.; Bairo, F.; Kargozar, S.. - In: MATERIALS. - ISSN 1996-1944. - ELETTRONICO. - 16:11(2023).  
[10.3390/ma16114194]

*Availability:*

This version is available at: 11583/2984034 since: 2023-11-23T14:08:52Z

*Publisher:*

MDPI

*Published*

DOI:10.3390/ma16114194

*Terms of use:*

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

*Publisher copyright*

(Article begins on next page)

## Review

# Effects of Bioactive Glasses (BGs) on Exosome Production and Secretion: A Critical Review

Sara Gorgani <sup>1</sup> , Seyed Atefe Hosseini <sup>2</sup>, Andrew Z. Wang <sup>3</sup>, Francesco Baino <sup>4,\*</sup>  and Saeid Kargozar <sup>1,3,\*</sup>

<sup>1</sup> Tissue Engineering Research Group (TERG), Department of Anatomy and Cell Biology, School of Medicine, Mashhad University of Medical Sciences, Mashhad 917794-8564, Iran; sara.gorgani70n@gmail.com

<sup>2</sup> Department of Medical Biotechnology and Nanotechnology, Faculty of Medicine, Mashhad University of Medical Sciences, Mashhad 917794-8564, Iran; atefehosseini20@gmail.com

<sup>3</sup> Department of Radiation Oncology, Simmons Comprehensive Cancer Center, UT Southwestern Medical Center, 5323 Harry Hines Blvd, Dallas, TX 75390, USA; andrew.wang2@utsouthwestern.edu

<sup>4</sup> Institute of Materials Physics and Engineering, Department of Applied Science and Technology, Politecnico di Torino, Corso Duca degli Abruzzi 24, 10129 Torino, Italy

\* Correspondence: francesco.baino@polito.it (F.B.); saeid.kargozar@utsouthwestern.edu (S.K.)

**Abstract:** There is an increasing trend toward the application of bioactive glasses in different areas of biomedicine, including tissue engineering and oncology. The reason for this increase is mostly attributed to the inherent properties of BGs, such as excellent biocompatibility, and the ease of tailoring their properties by changing, for example, the chemical composition. Previous experiments have demonstrated that the interactions between BGs and their ionic dissolution products, and mammalian cells, can affect and change cellular behaviors, and thereby govern the performance of living tissues. However, limited research exists on their critical role in the production and secretion of extracellular vesicles (EVs) such as exosomes. Exosomes are nanosized membrane vesicles that carry various therapeutic cargoes such as DNA, RNA, proteins, and lipids, and thereby can govern cell–cell communication and subsequent tissue responses. The use of exosomes is currently considered a cell-free approach in tissue engineering strategies, due to their positive roles in accelerating wound healing. On the other hand, exosomes are known as key players in cancer biology (e.g., progression and metastasis), due to their capability to carry bioactive molecules between tumor cells and normal cells. Recent studies have demonstrated that the biological performance of BGs, including their proangiogenic activity, is accomplished with the help of exosomes. Indeed, therapeutic cargoes (e.g., proteins) produced in BG-treated cells are transferred by a specific subset of exosomes toward target cells and tissues, and lead to a biological phenomenon. On the other hand, BGs are suitable delivery vehicles that can be utilized for the targeted delivery of exosomes to cells and tissues of interest. Therefore, it seems necessary to have a deeper understanding of the potential effects of BGs in the production of exosomes in cells that are involved in tissue repair and regeneration (mostly mesenchymal stem cells), as well as in those that play roles in cancer progression (e.g., cancer stem cells). This review aims to present an updated report on this critical issue, to provide a roadmap for future research in the fields of tissue engineering and regenerative medicine.

**Keywords:** bioactive glasses (BGs); ion release; drug delivery; exosomes; tissue engineering; wound healing



**Citation:** Gorgani, S.; Hosseini, S.A.; Wang, A.Z.; Baino, F.; Kargozar, S. Effects of Bioactive Glasses (BGs) on Exosome Production and Secretion: A Critical Review. *Materials* **2023**, *16*, 4194. <https://doi.org/10.3390/ma16114194>

Academic Editor: Valeria Cannillo

Received: 11 April 2023

Revised: 30 May 2023

Accepted: 1 June 2023

Published: 5 June 2023



**Copyright:** © 2023 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

## 1. Introduction

Exosomes are nanosized biological structures that are secreted by different types of mammalian cells into physiological fluids in the body. They are generally categorized as a subfamily of extracellular vesicles (EVs). Although exosomes were first considered as the “waste bags” of living cells, experimental studies have revealed their critical roles in the cell signaling pathways of the body [1]. They are involved in local (autocrine and paracrine) and distant (endocrine) signaling via transferring their contents. Nowadays, it

is well-understood that every single alteration in tissue condition (e.g., cell proliferation, apoptosis, angiogenesis) is associated with cell–cell or cell–extracellular matrix (ECM) communications. Thus, exosomes have been found to occupy a unique place in governing tissue performance in the body. In fact, exosomes can carry biomolecular cargoes (e.g., proteins, nucleic acids, lipids) between different cells and tissues. It is stated that almost all mammalian cells, both normal and cancerous, may secrete their specific exosomes with a determined biochemical component. For example, exosomes have been proven to play a substantial role in cancer progression, survival, and metastasis [2,3]. Therefore, they can be considered and tracked as biomarkers for different healthy and unhealthy tissues [4]. As they have the ability to establish biochemical communication, biosafe exosomes are utilized as suitable delivery vehicles for various biomolecule and drug cargoes in medicine. While several clinical trials have demonstrated the satisfactory therapeutic capacity of exosomes in wound healing, their limited production, and the problems that remain regarding their isolation, still limit their wide-spread use in clinics [5]. Therefore, the stimulation of cells by the activation of special proteins and signaling pathways has been proposed in order to achieve higher yields of exosomes.

With their exceptional regenerating potential, bioactive glasses (BGs) have gained a special place in tissue-engineering approaches [6,7]. These synthetic biocompatible materials were first utilized for managing hard-tissue diseases and disorders; however, they have been found to be beneficial for managing soft tissues as well [8–11]. The reason for this is attributed to the great compositional versatility of BGs, which can be properly designed to achieve various physico-chemical, mechanical, and biological characteristics [12]. In addition to their chemical composition, other aspects of BGs, including morphology and surface characteristics, may affect cellular behaviors, and thereby potentially promote tissue repair and regeneration. Despite all the aforementioned advantages of BGs in biomedicine, some issues should be considered when biocompatible glasses are used for the treatment of human diseases and disorders. These issues include the sharp increase in local pH, possible adverse effects on cells due to ion release, and the low mechanical strength and fracture-toughness of BGs and BG-based constructs [13]. However, the release of therapeutic ions from BG particles is recognized as the main factor in determining their biological performance [14,15]. Most reported studies have shown the possible effects of glass dissolution products on cell metabolism, growth, and proliferation, as well as gene and protein expression. Still, studies addressing the impact of BGs on the production and secretion of exosomes, either in normal cells or cancer cells, have been limited [16]. The few available experimental studies on this topic suggest that BGs can induce the secretion of exosomes in mesenchymal stem cells (MSCs) through the nSMases and the Rab family of small GTPases, which play a critical role in stimulating endothelial cells (ECs) to overexpress genes involved in angiogenesis (new-blood-vessel formation) [17]. To gather the information presented in this review, we applied the keywords of “exosome”, “extracellular vesicles”, “bioactive glass”, “bioglass”, “tissue engineering”, and “cancer research” to Google Scholar, Pub Med, Scopus, and Web of Science. To the best of our knowledge, this is the first article on the potential effects of BGs on the production and release of exosomes from mammalian cells, and their beneficial impact on tissue engineering and regenerative medicine.

## 2. Bioactive Glasses (BGs): A Unique Class of Materials in Medicine

Bioactive glasses (BGs) are categorized as the third generation of biomaterials that benefit from highly reactive surfaces. These biocompatible substances can trigger special biological activities once implanted into the body [18]. The first commercialized BG (45S5 Bioglass®) was developed by Larry Hench in 1969 at Florida University, with the aim of treating defective hard tissues [19]. The 45S5 Bioglass® is known as the parent of silicate BGs, with the chemical composition of 46.1% SiO<sub>2</sub>, 24.4% Na<sub>2</sub>O, 26.9 CaO, and 2.6% P<sub>2</sub>O<sub>5</sub> (mol %) [12]. Over time, two other categories of BGs were developed, phosphate and borate, which exhibit different properties compared to silicate glasses. Utilizing various synthesis

methods, mostly the melt-quench and sol-gel routes, it is feasible to produce BGs in different sizes and shapes (e.g., nanostructured powder, fibers), with tunable physico-chemical, mechanical, and biological properties. Compared to dense melt-quenched BG particles, sol-gel-derived BGs display a porous structure that makes them suitable substances for drug-delivery applications. Up to now, a broad range of natural and synthetic therapeutic substances have been loaded into, and delivered from, BGs, to desired sites in the body, with the aim of performing targeted treatments, such as cancer therapy [20]. BGs can be easily manufactured into 3D scaffolds with different architectures, for implantation into damaged tissues. Furthermore, BG particles, mostly nanosized particles, can be added to polymeric substrates to develop composite constructs (e.g., electrospun nanofibrous composites), also in the form of scaffolds with improved properties (e.g., biological performance) [21]. Currently, BG products with different compositions and shapes are available on the market for treating a wide range of tissue damages and injuries [22–25]. The capability of BGs to form rapid, powerful, and long-lasting bonds with living body tissues has led to their extensive application in tissue engineering and regenerative medicine [26,27]. It should be highlighted that the use of BGs in medicine is not limited to tissue-engineering strategies; specific formulations of BGs have been tested in cancer treatment as well. The anticancer effects of BGs can be improved by adding certain elements to their composition. For instance, tellurium-, magnesium-, and silver-doped BG nanoparticles have previously been synthesized and successfully tested against tumor cells [28–30]. There are several studies in the literature that indicate the usability of BGs in cancer hyperthermia, photothermal therapy, and anticancer drug delivery [31,32]. Anticancer BG compositions show promise in being more versatile, and even safer, materials for cancer therapy, compared with commonly used inorganic particles (e.g., iron oxide nanoparticles). However, no clinical trials have yet been conducted to investigate the anticancer potential of BGs *in vivo*.

Several experimental studies have shown that the therapeutic effects of BGs mainly depend on ion release from their structure into the physiological environment. Accordingly, a wide range of elements have been added to the basic composition of BGs to render specific biological features (e.g., promoted angiogenesis). For example, the release of cobalt ions ( $\text{Co}^{2+}$ ) from the glass network into biological environments can lead to the overexpression of a series of genes involved in hypoxia (e.g., hypoxia-inducible factor 1 $\alpha$  (HIF-1 $\alpha$ )), that can in turn improve angiogenesis, via enhancing extracellular matrix (ECM) degradation, as well as stalk-cell proliferation and migration [33]. Molecular biology techniques have allowed glass researchers and scientists to gain a deeper understanding of how BGs affect cell behaviors and tissue performance. In this regard, the influence of ionic dissolution products from BGs on the biosynthesis of exosomes may indeed be one of the most interesting topics in the field, since it can shed light upon the regenerative capacity of these biomaterials.

### 3. Exosomes: Multifunctional Nanovectors for Biodelivery

Exosomes represent biologic membrane bilayers, which are made and secreted into physiological fluids by all cell types (normal and tumor cells). While “exosome” and “extracellular vesicle (EV)” are often used interchangeably in the literature, it should be emphasized that EV is a general term used for micro-vesicles with different release mechanisms and sizes (diameter 100 to 1000 nm). Contrastingly, exosomes, as the smallest family of EVs, have a diameter between 40 and 150 nm [34]. In 1967, Wolf detected these structures, and described them as “platelet dusts”. Twenty years later, Rose Johnstone first named these bilayer membranes as exosomes [2,35]. Their simple structure is composed of biological molecules such as DNA, RNA (mRNA, tRNA, lncRNA, miRNA, and mtDNA) [36], proteins, lipids, cytokines, transcription factor receptors, and any other bioactive molecule that is present in the secreting cell [37]. The exact mechanism of exosome formation is still under discussion, but the classic formation of exosomes begins with an invagination of the plasma membrane, and continues with the accumulation of bioactive substances in the primary-formed vesicles, named “early stage endosomes” or


ESEs. ESEs are modified into endocytosis-sorting complexes, and form “late sorting endosomes” or LSEs, which in turn became “multivesicular bodies” or MVBs. The MVBs integrate with the plasma membrane, and eventually release the final products, exosomes (Figure 1) [4]. It should be mentioned that exosome formation can also occur directly, when the contents bud directly and immediately from the plasma membrane [38]. The best-understood pathway of exosome formation is called endosomal-sorting-complexes-required-for-transport-dependent (ESCRT-dependent). Its subcomplexes are the main cargo-sorting complexes in the cytoplasm, and they recognize the inwarded endosomes, and then guide them toward further modifications, in order to form MVBs and release them as exosomes. Other ESCRT-independent pathways include the ceramide and tetraspanin family-mediated pathways [39].

As mentioned above, mammalian cells can secrete different exosomes with distinct compounds (tissue-specific) as a representative of the cell-source phenotype. These small structures can facilitate paracrine communication between cells and, therefore, determine a different fate for recipient cells [34,40]. Exosomes are present in nearly all biological fluids (e.g., urine, breast milk, saliva, plasma), and their biogenesis and secretion can be induced or regulated in physiologic and pathologic conditions by proteins, by various signaling pathways, and also by engineered bioactive materials [4]. As previously mentioned, exosomes can be secreted by normal cells (e.g., mesenchymal stem cells (MSC), NK cells, T cells, B cells, macrophages, dendritic cells (DC)), as well as different tumor cell lines (e.g., metastatic colorectal cancer cells) [41]. Depending on their nature and origin, exosomes can proceed different biological processes by facilitating intercellular communication. MSC-derived exosomes are one of the most studied groups of exosomes with confirmed positive wound-healing impacts (e.g., skin scars, diabetes-induced cardiovascular injury) [42–46]. In addition to preclinical studies, there are several clinical trials in which exosomes have been successfully applied in the treatment of different ulcers (e.g., skin-related ulcers, diabetic foot ulcers, cesarean-section scars) [5,47,48]. Therefore, the use of exosomes, regardless of their source, has become very popular thanks to their therapeutic effects (e.g., anti-inflammatory and proangiogenic activities). Moreover, the low immune-system stimulation and nano-size, which helps them to pass through biological barriers, have established a novel branch of therapies called “cell-free therapy” [16]. In this approach, isolated exosomes can be administered as therapeutic cargoes via different routes (e.g., injection, inhalation). It should be noted that these isolated exosomes can contain natural biomolecules without any external manipulations, or carry certain types of biomolecules (e.g., mRNAs, miRNAs, drugs) which are added artificially using different methods (e.g., the cellular-nanoporation method), in order to induce a special biological process or deliver a drug to targeted cells [49]. In spite of all the positive aspects mentioned, the isolation and purification of exosomes are still recognized as a main unsolved challenge for medical applications. One reason is associated with the extensive variation in the size, content, and source of exosomes. Additionally, the similarity of exosomes to other biphasic biogenic structures (e.g., lipoproteins) make it even more difficult to precisely perform their purification.

Various methods are used for exosome isolation, including ultracentrifugation (UC) techniques [50], size-based isolation [51], immunoaffinity chromatography [52], and polymer precipitation [53]. UC is the most commonly used, and also the gold-standard method for isolation. With UC, exosomes are separated from other cell components according to size and density differences. This method comprises two steps: (I) removing cells and other large-sized exosomes through operating several low–medium-speed centrifuges, and (II) isolating exosomes at high-speed centrifugal force, and washing them with PBS to eliminate impurities (e.g., contaminating proteins) [54]. Different characterization methods should be performed in order to verify whether the isolated substances are actually exosomes or not. Morphology and size evaluations can be carried out by utilizing a transmission electron microscope (TEM), nanoparticle tracking analysis technology (NTA), and dynamic light scattering (DLS). Moreover, Western blotting and flow cytometry can be performed to identify exosome marker protein (e.g., membrane protein or lipid rafts) [55,56].



Another challenge is related to the limited capacity of cells to secrete exosomes. The cell type, viability, and surrounding microenvironment can affect the yield of exosome production. Therefore, obtaining large doses of exosomes for clinical use has remained a major challenge [57]. One proposed solution is to use specific biomaterials and scaffolds to stimulate cells toward a higher production of exosomes. In this regard, it has been previously shown that BG-based scaffolds can activate exosome production in mammalian cells by releasing specific ions into cell-culture media [17].

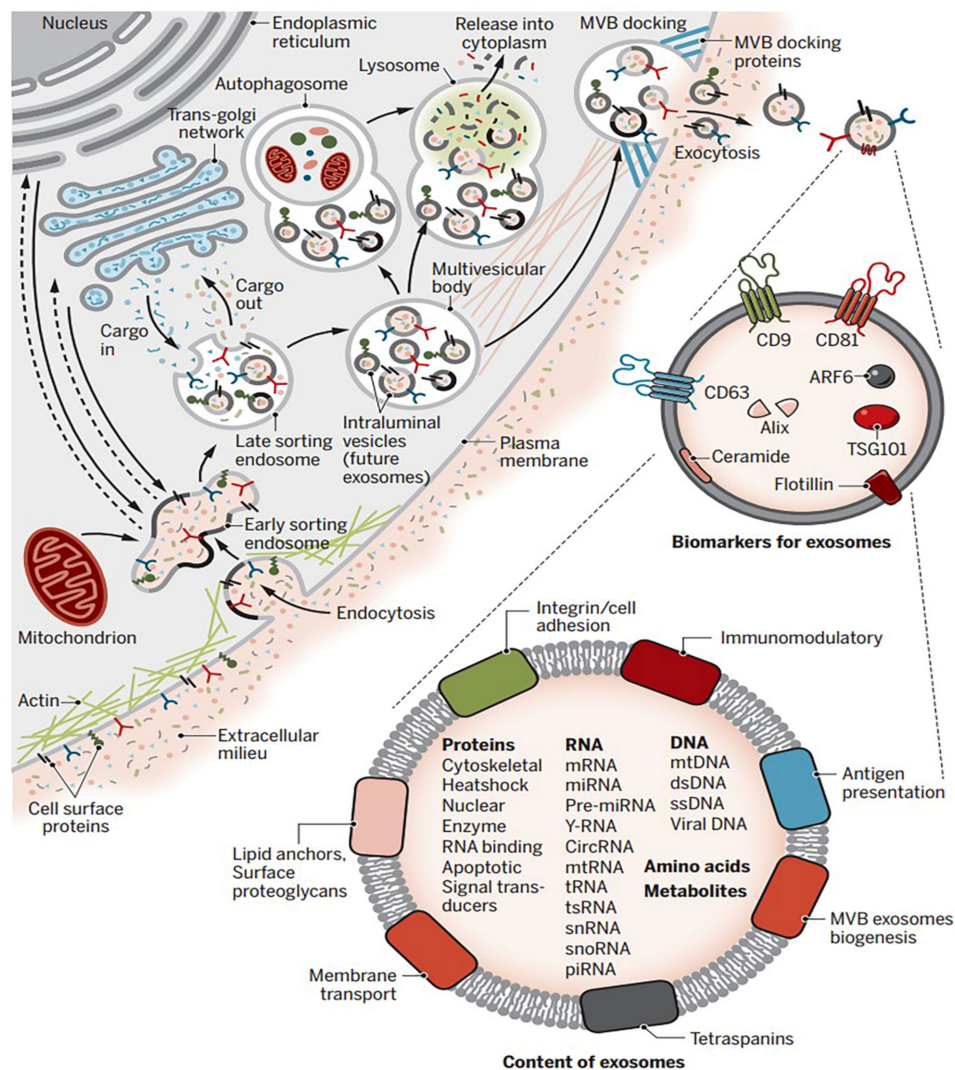

**Figure 1.** The schematic illustration of exosome biogenesis. In summary, the exosome formation starts with an intra-luminal invagination/endocytosis of the plasma membrane. The primary-formed vesicle is called an early sorting endosome (ESE), which then matures to a late sorting endosome (LSE). The multivesicular body (MVB), which contains future exosomes, is created because of secondary invaginations in the LSE. The MVB can undergo degradation by fusing to a lysosome, or releasing the exosomes to the extracellular space. Released exosomes have distinct compositions of surface markers, and may contain various types of bio-substances. Reproduced with permission from [58].

#### 4. Impact of BGs on Exosome Biogenesis


It is now well-acknowledged that multiple types of biomaterials can accelerate tissue repair and regeneration, through stimulating various cells (e.g., MSCs) to secrete specific kinds of exosomes. Exosome formation in cells can be stimulated by bioactive materials, through the activation of certain signaling pathways (autocrine, paracrine, and endocrine) that cause alterations in the behaviors of target cells. The composition of the applied

biomaterials directly affects the type and activity of the released exosomes [59]. Previous studies have confirmed that bioceramics can influence the production of specific types of exosomes in mammalian cells, which can lead to an improved tissue-healing process through the activation and enhancement of biological phenomena such as osteogenesis and angiogenesis [60–64]. In this regard, Lin et al. showed that strontium-substituted calcium silicates (Sr-CS) can promote neovascularization through the activation of human umbilical vein endothelial cells (HUVECs) to produce and secrete proangiogenic miR-146a-containing exosomes, and the inhibition of Smad4 and NF2 proteins [65].


The same scenario was reported regarding BGs. Recent experimental studies have clarified that BGs can impact the wound-healing process through the stimulation of cells to produce and secrete certain types of exosomes. This has provided a wider and clearer picture of the therapeutic effects of BGs in accelerating the wound-healing process.

The family of neural sphingomyelinases (nSMases), and the Rab family of small GTPases, are groups of well-identified proteins that are involved in the ESCRT-independent biosynthesis of exosomes from cells [66,67]. It has been reported that BG-dissolution products can affect these proteins in MSCs, in favor of tissue repair and regeneration. For example, Lu et al. showed that the ionic dissolution products of 45S5 Bioglass® can enhance the exosome release of MSCs. In fact, they found that the overexpression of nSMases and the Rab27 family in treated cells can enhance the nSMase and Rab GTPase pathways, respectively. Interestingly, the contents of exosomes released from the BG-treated MSCs were different from those that were secreted by the cells receiving no external stimulation. The treated MSCs secreted exosomes with a decreased level of microRNA-342-5p, and increased amounts of microRNA-1290 at the same time. These exosomes were confirmed to be internalized by endothelial cells (ECs), and led to the overexpression of angiogenesis-related genes, including vascular endothelial growth factor (VEGF), VEGF receptor 2 (KDR), and endothelial nitric oxide synthase (eNOS). Indeed, the *in vivo* administration of MSC-derived exosomes resulted in the generation of a significant number of micro-vessels in the injection region, compared with control groups (see Figure 2) [17].

Lithium-doped glass-ceramic (Li-BGC) scaffolds were prepared based on 45S5 BG, and their roles in the mediation of cell–cell communications between bone marrow stromal cells (BMSCs) and ECs were explored. The obtained results demonstrated that the release of Li<sup>+</sup> ions from BGCs can enhance neovascularization *in vitro* and *in vivo*. To elaborate: the Li<sup>+</sup> ions stimulated the secretion of specific BMSC-derived exosomes (BMSC-exo) containing proangiogenic miR-130a, which subsequently led to the downregulation of PTEN protein, and the activation of the AKT pathway. All these molecular phenomena resulted in elevated proliferation, migration, and tube formation of HUVECs *in vitro*. Moreover, the activation of the Wnt/ $\beta$ -catenin, AKT, and NF- $\kappa$ B signaling pathways was observed, and attributed to directly promoted new blood-vessel ingrowth *in vivo* [64]. Emphasizing the role of BGs in the treatment of bone-related diseases and disorders (e.g., osteoporosis), the nanosized BG particles (60SiO<sub>2</sub>-36CaO-4P<sub>2</sub>O<sub>5</sub> mol %) were examined for their capabilities in stimulating stem cells to secrete exosomes in favor of inhibiting bone loss in osteoporotic animals. In this regard, Yang et al. developed a co-culture system in which mouse BMSCs were treated with BG nanoparticles (1 mg/mL). This experiment indicated that BGs could significantly inhibit osteoclast differentiation in RAW264.7 cells, suggesting their possible role in preventing osteoporosis. Subsequent *in vivo* experiments demonstrated that BG treatment can lead to inhibition of bone resorption (i.e., bone loss) in an osteoporosis mouse model via lncRNA NRON enrichment (Figure 3). Indeed, BG nanoparticles can induce the expression of the lncRNA NRON (a long non-coding RNA) in BMSCs, and their subsequent secretion through exosomes. The lncRNA NRON-containing exosomes can then be internalized by osteoclasts, which leads to the inhibition of the nuclear transfer of NFATc, thereby prohibiting the differentiation of osteoclasts [16].

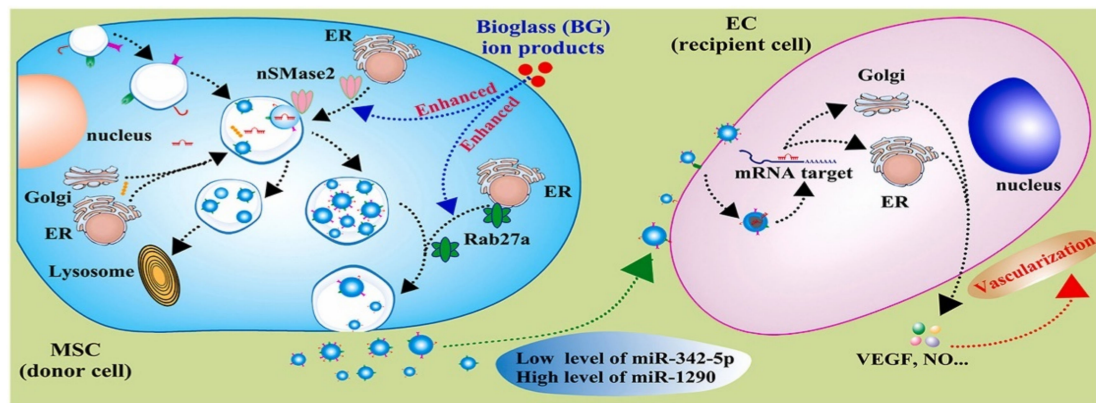


(A)

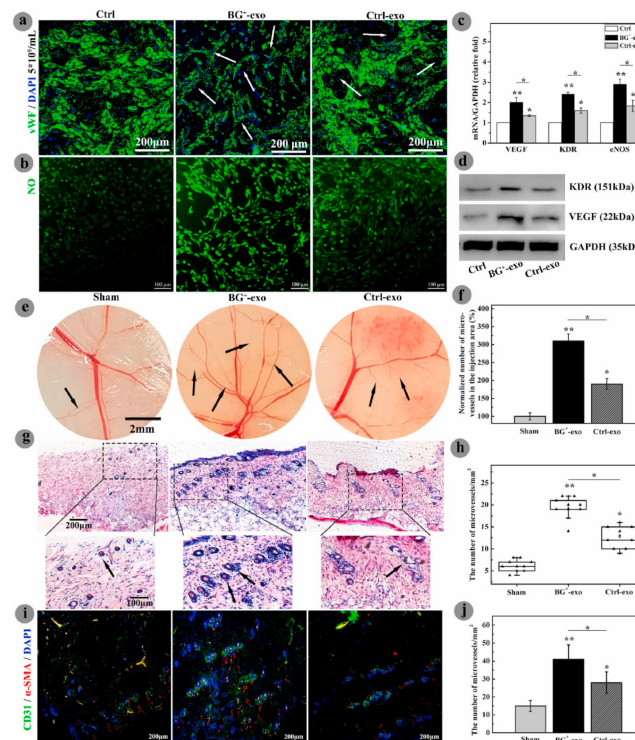

(B)

**Figure 2.** (A) A schematic representation of the potential effects of BGs on exosome production. As depicted, the ionic dissolution products released from BGs can stimulate the production and secretion of specific exosomes in MSCs, which can affect the behavior of endothelial cells (ECs) through defined signaling pathways in favor of promoted angiogenesis. (B) The effect of BGs in the enhancement of exosome production from MSCs, and the consequent promoted vascularization in vitro and in vivo: (a) vWF/DAPI staining, (b) NO staining, (c) expression of VEGF, KDR, and eNOS genes, (d) tracking of KDR and VEGF proteins in ECs co-cultured with MSC-derived exosomes in vitro for two days, (e,f) light-field images, and the quantitative analysis on observable micro-vessels, (g,h) H&E-stained skin samples at the injection area, and quantitative analysis of micro-vessel-like structures, and (i,j) the double-immunofluorescence images of skin samples stained with  $\alpha$ -SMA and CD31 at the injection area, and quantitative analysis of the tagged micro-vessels. \*  $p < 0.05$  and \*\*  $p < 0.01$  show the significant difference between the treatment groups and the corresponding sham/control group. (White and black arrows show capillary-like networks and blood vessels, “BG+” means BG stimulated MSC exosomes, and triangles indicate individual data points). Reproduced under CC license from [17].




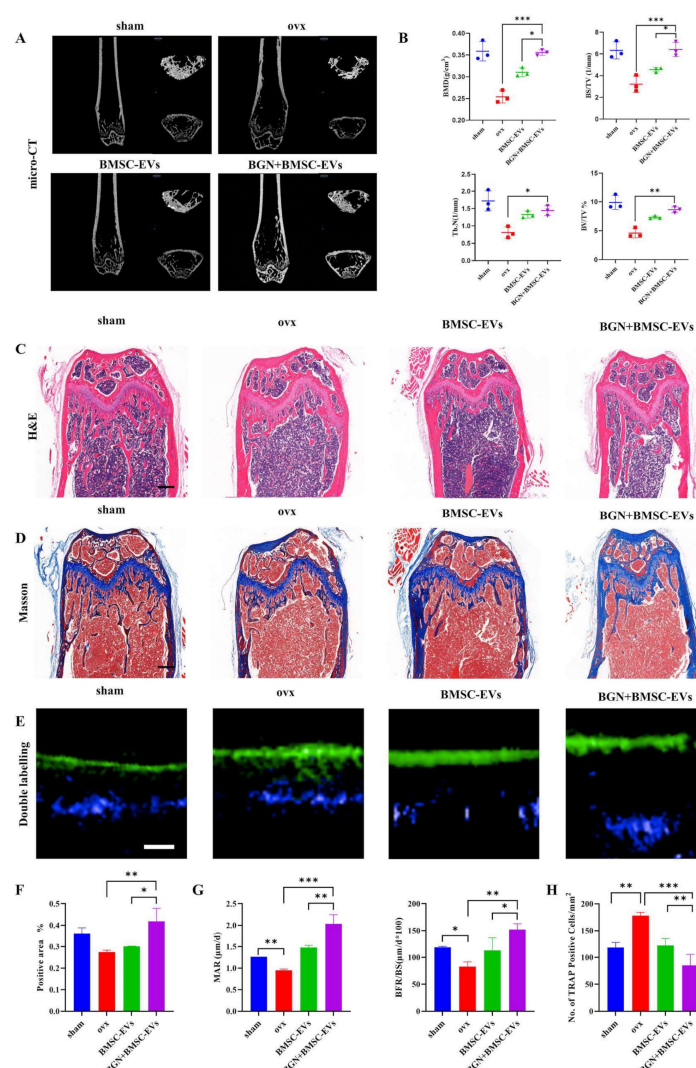

**Figure 3.** The inhibitory impact of BGN + BMSC-Evs on bone resorption in vivo: (A) micro-CT image of the femur, (B) Histomorphometry analysis of BMD, Tb. N, BS/TV, and BV/TV (symbols show scatter dot points) (C) H&E-staining images (scale bar, 500 µm), (D) Masson staining images (scale bar, 500 µm), (E) image of newly formed bones indicated by double labeling of tetracycline and calcein (scale bar, 20 µm), (F) volume fraction indicated from the collagen fiber analysis of the sham femurs, OVX, BGN + BMSC-EVs-treated OVX, and BMSC-EVs-treated OVX groups, (G) bone histomorphometric analysis of the MAR and BFR/BS in the femur of the treatment groups, and (H) histomorphometric analysis for counting osteoclasts in the samples. \*  $p < 0.05$ , \*\*  $p < 0.01$  and \*\*\*  $p < 0.001$  demonstrate the significant difference between the treatment groups and the corresponding sham/control group. Reproduced with permission from [16].

In another recently published study, human-adipose-tissue-derived MSCs were treated with diluted eluates from the ionic dissolution of 45S5 Bioglass® powders (particle size  $\sim 38$  µm), and EVs were then collected from treated cells (EV<sub>B</sub>) in order to investigate their effects in modulating macrophage polarization, angiogenesis, and tendon regeneration [68]. Compared to EVs isolated from untreated cells, the administration of the EV<sub>B</sub> resulted in the up-regulation of a therapeutic miRNA profile (including miR-199b-3p and miR-125a-5p) that could promote angiogenesis through facilitating the specific ring spatial distribution of anti-inflammatory M2 Mφs macrophages and CD31<sup>+</sup> ECs during tendon regeneration in vivo. The implantation of BG-elicited MSC-EV-laden GelMA hydrogels could improve tenogenesis, and reduce detrimental morphological changes, with no sign of heterotopic ossification in an acute rat Achilles-tendon-full-thickness rupture. From

a biomechanical point of view, an enhanced ultimate load, stiffness, and tensile elastic modulus were observed in the tendon of animals receiving the EVB. The authors have concluded that this method can be considered a next-generation therapy for improving the functional reconstruction of damaged tendons (see Figure 4) [68].

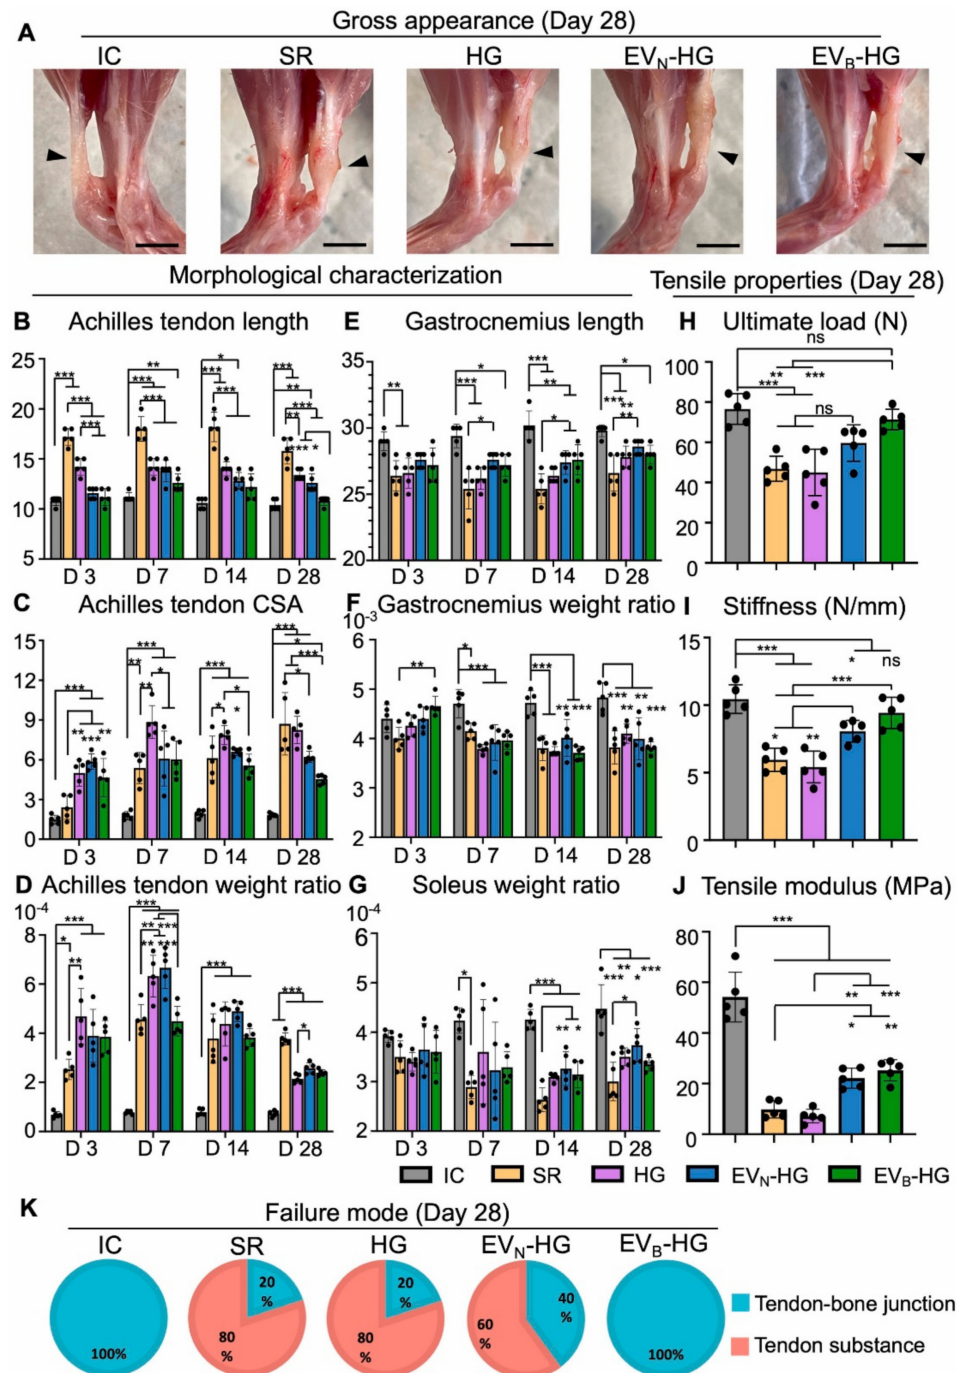

**Figure 4.** Morphological and biomechanical properties selectively enhanced in the calf-muscle–Achilles-tendon–calcaneus-bone complex by EV<sub>B</sub>-HG: (A) gross appearance of the Achilles tendon (showed by arrow) after 28 days (scale bar, 5 mm), (B) length of the Achilles tendon, (C) CSA of the Achilles tendon, (D) weight/body weight ratio of the Achilles tendon, (E) length of the Gastrocnemius muscle, (F) weight/body weight ratio of the Gastrocnemius muscle, (G) weight/body weight ratio of the soleus muscle, (H) ultimate load, (I) stiffness, (J) tensile modulus, and (K) failure mode. Data expressed as means  $\pm$  SD;  $n = 5$ ; \*  $p < 0.05$ ; \*\*  $p < 0.01$ ; \*\*\*  $p < 0.001$ , and “ns” = not significant. (Black dots show scatter points). Reproduced with permission from [68].

## 5. Conclusions and Future Perspectives

An understanding of the language through which cells communicate is a basis for clarifying the mechanisms of different biological processes. Several molecular players have been identified that modulate cell–cell and cell–ECM signaling, and among them, exosomes represent a specific class of inter-cellular signaling objects that can affect biological phenomena such as tissue healing. In fact, the molecular cargoes of exosomes can trigger a cascade of signaling pathways in target cells, and lead to a biological response. Recent experimental evidence suggests that BGs can stimulate cells (e.g., MSCs) to synthesize and secrete exosomes with specific therapeutic cargoes that can have a positive effect on tissue repair and regeneration. In this regard, the proangiogenic capacity of silicate BGs have been linked with their potential in modulating the cargoes of MSC-derived exosomes (a decreased level of microRNA-342-5p, along with an increased microRNA-1290 level). However, among the few available published studies, most have been performed on a limited set of compositions of silicate-based glasses (e.g., 45S5 BG). Therefore, it is necessary to evaluate whether other subfamilies of BGs; i.e., phosphate and borate glasses, can affect the exosome constituent secreted by cells, and if so, to what extent. Since BGs have shown a variety of biological activities (e.g., anti-inflammatory, antioxidant), the possible role of BGs in the production of defined types of exosomes may provide better insight into their therapeutic potential in tissue engineering, regenerative medicine, and cancer research. Furthermore, the loading and delivery of exosomes using mesoporous BGs or 3D glass-based constructs (scaffolds) can be considered a novel cell-free approach for enhancing desired outcomes.

In summary, BGs could perform a double function in the context of exosome applications for advanced therapy by: (i) acting as carriers for the release of previously secreted/produced exosomes, and (ii) producing a stimulatory effect on cells to produce exosomes through the release of appropriate ionic species. Of course, strategy (ii) potentially carries immeasurable advantages; for example: no longer requiring drugs, with their associated problems of high cost and side effects; and avoiding cells with problems relating to harvesting (if autologous cells), or immune rejection (if harvested from an external donor). Such an approach, although extremely fascinating, is nascent, and more studies are necessary to elucidate whether it is actually reproducible, safe, scalable from in vitro tests to animal studies and, eventually, to humans, and whether it can be relied on to achieve the desired action at a finely controllable level. Lastly, regulatory aspects, and the need for common protocols to be adopted in terms of the characterization and validation of its effects, will be key to the success of research in such a cross-disciplinary field.

**Author Contributions:** All authors contributed to the conceptualization, literature search, methodology, writing—original draft preparation, writing—review and editing. All authors have read and agreed to the published version of the manuscript.

**Funding:** This paper received no funding.

**Institutional Review Board Statement:** Not applicable.

**Informed Consent Statement:** Not applicable.

**Data Availability Statement:** This paper is a review; therefore, data are available in the source publications listed in the bibliography.

**Conflicts of Interest:** The authors declare no conflict of interest.

## References

1. Théry, C.; Zitvogel, L.; Amigorena, S. Exosomes: Composition, biogenesis and function. *Nat. Rev. Immunol.* **2002**, *2*, 569–579. [[CrossRef](#)] [[PubMed](#)]
2. Tkach, M.; Théry, C. Communication by Extracellular Vesicles: Where We Are and Where We Need to Go. *Cell* **2016**, *164*, 1226–1232. [[CrossRef](#)] [[PubMed](#)]
3. Zhang, H.-G.; Grizzle, W.E. Exosomes: A novel pathway of local and distant intercellular communication that facilitates the growth and metastasis of neoplastic lesions. *Am. J. Pathol.* **2014**, *184*, 28–41. [[CrossRef](#)] [[PubMed](#)]

4. Zhang, Y.; Bi, J.; Huang, J.; Tang, Y.; Du, S.; Li, P. Exosome: A Review of Its Classification, Isolation Techniques, Storage, Diagnostic and Targeted Therapy Applications. *Int. J. Nanomed.* **2020**, *15*, 6917–6934. [\[CrossRef\]](#)
5. Qin, H.; Zhu, X.; Zhang, B.; Zhou, L.; Wang, W. Clinical evaluation of human umbilical cord mesenchymal stem cell transplantation after angioplasty for diabetic foot. *Exp. Clin. Endocrinol. Diabetes* **2016**, *124*, 497–503. [\[CrossRef\]](#)
6. Batool, S.; Hussain, Z.; Liaqat, U. In Vitro and In Vivo Studies of Bioactive Glasses. In *Bioactive Glasses and Glass-Ceramics*; John Wiley: Hoboken, NJ, USA, 2022; pp. 397–429.
7. Baino, F.; Kargozar, S. *Bioactive Glasses and Glass-Ceramics: Fundamentals and Applications*; John Wiley & Sons: Hoboken, NJ, USA, 2022.
8. Fathi, A.; Kermani, F.; Behnamghader, A.; Banijamali, S.; Mozafari, M.; Baino, F.; Kargozar, S. Three-dimensionally printed polycaprolactone/multicomponent bioactive glass scaffolds for potential application in bone tissue engineering. *Biomed. Glasses* **2020**, *6*, 57–69. [\[CrossRef\]](#)
9. Li, C.; Wang, C.; Boccaccini, A.R.; Zheng, K. Sol-gel processing and characterization of binary P2O5-CaO and ternary P2O5-CaO-Li2O mesoporous phosphate bioactive glasses. *J. Non-Cryst. Solids X* **2023**, *17*, 100159. [\[CrossRef\]](#)
10. Kermani, F.; Nazarnezhad, S.; Mollaei, Z.; Mollazadeh, S.; Ebrahimzadeh-Bideskan, A.; Askari, V.R.; Oskuee, R.K.; Moradi, A.; Hosseini, S.A.; Azari, Z.; et al. Zinc- and Copper-Doped Mesoporous Borate Bioactive Glasses: Promising Additives for Potential Use in Skin Wound Healing Applications. *Int. J. Mol. Sci.* **2023**, *24*, 1304. [\[CrossRef\]](#)
11. Liverani, L.; Reiter, T.; Zheng, K.; Neščáková, Z.; Boccaccini, A.R. Copper-doped cotton-like malleable electrospun bioactive glass fibers for wound healing applications. *Mater. Lett. X* **2022**, *14*, 100133. [\[CrossRef\]](#)
12. Rahaman, M.N.; Day, D.E.; Bal, B.S.; Fu, Q.; Jung, S.B.; Bonewald, L.F.; Tomsia, A.P. Bioactive glass in tissue engineering. *Acta Biomater.* **2011**, *7*, 2355–2373. [\[CrossRef\]](#)
13. Fernandes, H.R.; Gaddam, A.; Rebelo, A.; Brazete, D.; Stan, G.E.; Ferreira, J.M.F. Bioactive Glasses and Glass-Ceramics for Healthcare Applications in Bone Regeneration and Tissue Engineering. *Materials* **2018**, *11*, 2530. [\[CrossRef\]](#)
14. Kargozar, S.; Baino, F.; Hamzehlou, S.; Hill, R.G.; Mozafari, M. Bioactive glasses entering the mainstream. *Drug Discov. Today* **2018**, *23*, 1700–1704. [\[CrossRef\]](#)
15. Kermani, F.; Vojdani-Saghir, A.; Beidokhti, S.M.; Nazarnezhad, S.; Mollaei, Z.; Hamzehlou, S.; El-Fiqi, A.; Baino, F.; Kargozar, S. Iron (Fe)-doped mesoporous 45S5 bioactive glasses: Implications for cancer therapy. *Transl. Oncol.* **2022**, *20*, 101397. [\[CrossRef\]](#)
16. Yang, Z.; Liu, X.; Zhao, F.; Yao, M.; Lin, Z.; Yang, Z.; Liu, C.; Liu, Y.; Chen, X.; Du, C. Bioactive glass nanoparticles inhibit osteoclast differentiation and osteoporotic bone loss by activating lncRNA NRON expression in the extracellular vesicles derived from bone marrow mesenchymal stem cells. *Biomaterials* **2022**, *283*, 121438. [\[CrossRef\]](#)
17. Wu, Z.; He, D.; Li, H. Bioglass enhances the production of exosomes and improves their capability of promoting vascularization. *Bioact. Mater.* **2021**, *6*, 823–835. [\[CrossRef\]](#)
18. Jones, J.R. Review of bioactive glass: From Hench to hybrids. *Acta Biomater.* **2013**, *9*, 4457–4486. [\[CrossRef\]](#)
19. Baino, F.; Hamzehlou, S.; Kargozar, S. Bioactive glasses: Where are we and where are we going? *J. Funct. Biomater.* **2018**, *9*, 25. [\[CrossRef\]](#)
20. Borges, R.; Pelosine, A.M.; de Souza, A.C.S.; Machado, J., Jr.; Justo, G.Z.; Gamarra, L.F.; Marchi, J. Bioactive Glasses as Carriers of Cancer-Targeted Drugs: Challenges and Opportunities in Bone Cancer Treatment. *Materials* **2022**, *15*, 9082. [\[CrossRef\]](#)
21. Saatchi, A.; Arani, A.R.; Moghanian, A.; Mozafari, M. Synthesis and characterization of electrospun cerium-doped bioactive glass/chitosan/polyethylene oxide composite scaffolds for tissue engineering applications. *Ceram. Int.* **2021**, *47*, 260–271. [\[CrossRef\]](#)
22. Qi, Q.; Zhu, Y.; Liu, G.; Yuan, Z.; Li, H.; Zhao, Q. Local intramyocardial delivery of bioglass with alginate hydrogels for post-infarct myocardial regeneration. *Biomed. Pharmacother.* **2020**, *129*, 110382. [\[CrossRef\]](#)
23. Kudo, K.; Miyasawa, M.; Fujioka, Y.; Kamegai, T.; Nakano, H.; Seino, Y.; Ishikawa, F.; Shioyama, T.; Ishibashi, K. Clinical application of dental implant with root of coated bioglass: Short-term results. *Oral Surg. Oral Med. Oral Pathol.* **1990**, *70*, 18–23. [\[CrossRef\]](#) [\[PubMed\]](#)
24. Stanley, H.R.; Hall, M.B.; Clark, A.E.; King, I.I.C.J.; Hench, L.L.; Berte, J.J. Using 45S5 bioglass cones as endosseous ridge maintenance implants to prevent alveolar ridge resorption: A 5-year evaluation. *Int. J. Oral Maxillofac. Implant.* **1997**, *12*, 95–105.
25. Gilchrist, T.; Glasby, M.; Healy, D.; Kelly, G.; Lenihan, D.; McDowall, K.; Miller, I.A.; Myles, L.M. In vitro nerve repair—In vivo. The reconstruction of peripheral nerves by entubulation with biodegradable glass tubes—A preliminary report. *Br. J. Plast. Surg.* **1998**, *51*, 231–237. [\[CrossRef\]](#) [\[PubMed\]](#)
26. Jung, S.; Day, D.; Day, T.; Stoecker, W.; Taylor, P. Treatment of non-healing diabetic venous stasis ulcers with bioactive glass nanofibers. In *Wound Repair and Regeneration*; Wiley-Blackwell Commerce Place: Malden, MA, USA, 2011.
27. Bitar, M.; Salih, V.; Mudera, V.; Knowles, J.C.; Lewis, M.P. Soluble phosphate glasses: In vitro studies using human cells of hard and soft tissue origin. *Biomaterials* **2004**, *25*, 2283–2292. [\[CrossRef\]](#) [\[PubMed\]](#)
28. Zhang, Y.; Hu, M.; Zhang, W.; Zhang, X. Construction of tellurium-doped mesoporous bioactive glass nanoparticles for bone cancer therapy by promoting ROS-mediated apoptosis and antibacterial activity. *J. Colloid Interface Sci.* **2022**, *610*, 719–730. [\[CrossRef\]](#)
29. Rahman, M.S.U.; Tahir, M.A.; Noreen, S.; Yasir, M.; Khan, M.B.; Mahmood, T.; Bahadur, A.; Shoaib, M. Osteogenic silver oxide doped mesoporous bioactive glass for controlled release of doxorubicin against bone cancer cell line (MG-63): In vitro and in vivo cytotoxicity evaluation. *Ceram. Int.* **2020**, *46*, 10765–10770. [\[CrossRef\]](#)



30. Shoaib, M.; Bahadur, A.; Iqbal, S.; Al-Anazy, M.M.; Laref, A.; Tahir, M.A.; Channar, P.A.; Noreen, S.; Yasir, M.; Iqbal, A.; et al. Magnesium doped mesoporous bioactive glass nanoparticles: A promising material for apatite formation and mitomycin c delivery to the MG-63 cancer cells. *J. Alloy. Compd.* **2021**, *866*, 159013. [\[CrossRef\]](#)
31. Danewalia, S.S.; Singh, K. Bioactive glasses and glass-ceramics for hyperthermia treatment of cancer: State-of-art, challenges, and future perspectives. *Mater. Today Bio* **2021**, *10*, 100100. [\[CrossRef\]](#)
32. Moeini, A.; Chinijani, T.H.; Khachatourian, A.M.; Fook, M.V.L.; Bairo, F.; Montazerian, M. A critical review of bioactive glasses and glass-ceramics in cancer therapy. *Int. J. Appl. Glass Sci.* **2023**, *14*, 69–87. [\[CrossRef\]](#)
33. Wu, C.; Zhou, Y.; Fan, W.; Han, P.; Chang, J.; Yuen, J.; Zhang, M.; Xiao, Y. Hypoxia-mimicking mesoporous bioactive glass scaffolds with controllable cobalt ion release for bone tissue engineering. *Biomaterials* **2012**, *33*, 2076–2085. [\[CrossRef\]](#)
34. Raposo, G.; Stoorvogel, W. Extracellular vesicles: Exosomes, microvesicles, and friends. *J. Cell Biol.* **2013**, *200*, 373–383. [\[CrossRef\]](#)
35. Johnstone, R.M. Revisiting the road to the discovery of exosomes. *Blood Cells Mol. Dis.* **2005**, *34*, 214–219. [\[CrossRef\]](#)
36. Jeppesen, D.K.; Fenix, A.M.; Franklin, J.L.; Higginbotham, J.N.; Zhang, Q.; Zimmerman, L.J.; Liebler, D.C.; Ping, J.; Liu, Q.; Evans, R.; et al. Reassessment of exosome composition. *Cell* **2019**, *177*, 428–445.e18. [\[CrossRef\]](#)
37. Stoorvogel, W.; Kleijmeer, M.J.; Geuze, H.J.; Raposo, G. The Biogenesis and Functions of Exosomes. *Traffic* **2002**, *3*, 321–330. [\[CrossRef\]](#)
38. Booth, A.M.; Fang, Y.; Fallon, J.K.; Yang, J.-M.; Hildreth, J.E.; Gould, S.J. Exosomes and HIV Gag bud from endosome-like domains of the T cell plasma membrane. *J. Cell Biol.* **2006**, *172*, 923–935. [\[CrossRef\]](#)
39. Wei, H.; Chen, Q.; Lin, L.; Sha, C.; Li, T.; Liu, Y.; Yin, X.; Xu, Y.; Chen, L.; Gao, W.; et al. Regulation of exosome production and cargo sorting. *Int. J. Biol. Sci.* **2021**, *17*, 163–177. [\[CrossRef\]](#)
40. Johnstone, R.M.; Adam, M.; Hammond, J.R.; Orr, L.; Turbide, C. Vesicle formation during reticulocyte maturation. Association of plasma membrane activities with released vesicles (exosomes). *J. Biol. Chem.* **1987**, *262*, 9412–9420. [\[CrossRef\]](#)
41. Wu, B.; Sun, D.; Ma, L.; Deng, Y.; Zhang, S.; Dong, L.; Chen, S. Exosomes isolated from CAPS1-overexpressing colorectal cancer cells promote cell migration. *Oncol. Rep.* **2019**, *42*, 2528–2536. [\[CrossRef\]](#)
42. Yin, S.; Ji, C.; Wu, P.; Jin, C.; Qian, H. Human umbilical cord mesenchymal stem cells and exosomes: Bioactive ways of tissue injury repair. *Am. J. Transl. Res.* **2019**, *11*, 1230–1240.
43. He, X.; Dong, Z.; Cao, Y.; Wang, H.; Liu, S.; Liao, L.; Jin, Y.; Yuan, L.; Li, B. MSC-Derived Exosome Promotes M2 Polarization and Enhances Cutaneous Wound Healing. *Stem Cells Int.* **2019**, *2019*, 7132708. [\[CrossRef\]](#)
44. A Canales-Aguirre, A.; E Reza-Zaldivar, E.; A Hernández-Sapiéns, M.; Gutiérrez-Mercado, Y.K.; Sandoval-Ávila, S.; Gomez-Pinedo, U.; Márquez-Aguirre, A.L.; Vázquez-Méndez, E.; Padilla-Camberos, E. Mesenchymal stem cell-derived exosomes promote neurogenesis and cognitive function recovery in a mouse model of Alzheimer’s disease. *Neural Regen. Res.* **2019**, *14*, 1626–1634. [\[CrossRef\]](#) [\[PubMed\]](#)
45. Lin, Y.; Zhang, F.; Lian, X.-F.; Peng, W.-Q.; Yin, C.-Y. Mesenchymal stem cell-derived exosomes improve diabetes mellitus-induced myocardial injury and fibrosis via inhibition of TGF- $\beta$ 1/Smad2 signaling pathway. *Cell. Mol. Biol.* **2019**, *65*, 123–126. [\[CrossRef\]](#) [\[PubMed\]](#)
46. Nassar, W.; El-Ansary, M.; Sabry, D.; Mostafa, M.A.; Fayad, T.; Kotb, E.; Temraz, M.; Saad, A.-N.; Essa, W.; Adel, H. Umbilical cord mesenchymal stem cells derived extracellular vesicles can safely ameliorate the progression of chronic kidney diseases. *Biomater. Res.* **2016**, *20*, 21. [\[CrossRef\]](#) [\[PubMed\]](#)
47. Fan, D.; Zeng, M.; Xia, Q.; Wu, S.; Ye, S.; Rao, J.; Lin, D.; Zhang, H.; Ma, H.; Han, Z.; et al. Efficacy and safety of umbilical cord mesenchymal stem cells in treatment of cesarean section skin scars: A randomized clinical trial. *Stem Cell Res. Ther.* **2020**, *11*, 244. [\[CrossRef\]](#) [\[PubMed\]](#)
48. Lee, S.E.; Lee, S.-J.; Kim, S.-E.; Kim, K.; Cho, B.; Roh, K.; Kim, S.C. Intravenous allogeneic umbilical cord blood-derived mesenchymal stem cell therapy in recessive dystrophic epidermolysis bullosa patients. *JCI Insight* **2021**, *6*, e143606. [\[CrossRef\]](#) [\[PubMed\]](#)
49. Yang, Z.; Shi, J.; Xie, J.; Wang, Y.; Sun, J.; Liu, T.; Zhao, Y.; Zhao, X.; Wang, X.; Ma, Y.; et al. Large-scale generation of functional mRNA-encapsulating exosomes via cellular nanoporation. *Nat. Biomed. Eng.* **2020**, *4*, 69–83. [\[CrossRef\]](#)
50. Livshits, M.A.; Khomyakova, E.; Evtushenko, E.G.; Lazarev, V.N.; Kulemin, N.A.; Semina, S.E.; Generozov, E.V.; Govorun, V.M. Isolation of exosomes by differential centrifugation: Theoretical analysis of a commonly used protocol. *Sci. Rep.* **2015**, *5*, 17319. [\[CrossRef\]](#)
51. Böing, A.N.; van der Pol, E.; Grootemaat, A.E.; Coumans, F.A.W.; Sturk, A.; Nieuwland, R. Single-step isolation of extracellular vesicles by size-exclusion chromatography. *J. Extracell. Vesicles* **2014**, *3*, 23430. [\[CrossRef\]](#)
52. Fitzgerald, J.; Leonard, P.; Darcy, E.; Sharma, S.; O’Kennedy, R. Immunoaffinity chromatography: Concepts and applications. *Protein Chromatogr.* **2017**, *1485*, 27–51.
53. Rider, M.A.; Hurwitz, S.N.; Meckes, D.G., Jr. ExtraPEG: A Polyethylene Glycol-Based Method for Enrichment of Extracellular Vesicles. *Sci. Rep.* **2016**, *6*, 23978. [\[CrossRef\]](#)
54. Théry, C.; Amigorena, S.; Raposo, G.; Clayton, A. Isolation and characterization of exosomes from cell culture supernatants and biological fluids. *Curr. Protoc. Cell Biol.* **2006**, *30*, 1–9. [\[CrossRef\]](#)
55. Maas, S.L.; de Vrij, J.; van der Vlist, E.J.; Geragousian, B.; van Bloois, L.; Mastrobattista, E.; Schiffelers, R.M.; Wauben, M.H.M.; Broekman, M.L.D.; Hoen, E.N.N. Possibilities and limitations of current technologies for quantification of biological extracellular vesicles and synthetic mimics. *J. Control. Release* **2015**, *200*, 87–96. [\[CrossRef\]](#)

56. Wu, Y.; Deng, W.; Klinke, I.I.D.J. Exosomes: Improved methods to characterize their morphology, RNA content, and surface protein biomarkers. *Analyst* **2015**, *140*, 6631–6642. [[CrossRef](#)]
57. Patel, D.B.; Luthers, C.R.; Lerman, M.J.; Fisher, J.P.; Jay, S.M. Enhanced extracellular vesicle production and ethanol-mediated vascularization bioactivity via a 3D-printed scaffold-perfusion bioreactor system. *Acta Biomater.* **2019**, *95*, 236–244. [[CrossRef](#)]
58. Kalluri, R.; LeBleu, V.S. The biology, function, and biomedical applications of exosomes. *Science* **2020**, *367*, eaau6977. [[CrossRef](#)]
59. Zhang, B.; Huang, J.; Liu, J.; Lin, F.; Ding, Z.; Xu, J. Injectable composite hydrogel promotes osteogenesis and angiogenesis in spinal fusion by optimizing the bone marrow mesenchymal stem cell microenvironment and exosomes secretion. *Mater. Sci. Eng. C* **2021**, *123*, 111782. [[CrossRef](#)]
60. Sun, Y.; Zhang, B.; Zhai, D.; Wu, C. Three-dimensional printing of bioceramic-induced macrophage exosomes: Immunomodulation and osteogenesis/angiogenesis. *NPG Asia Mater.* **2021**, *13*, 72. [[CrossRef](#)]
61. Liu, L.; Yu, F.; Li, L.; Zhou, L.; Zhou, T.; Xu, Y.; Lin, K.; Fang, B.; Xia, L. Bone marrow stromal cells stimulated by strontium-substituted calcium silicate ceramics: Release of exosomal miR-146a regulates osteogenesis and angiogenesis. *Acta Biomater.* **2021**, *119*, 444–457. [[CrossRef](#)]
62. Zhu, Y.; Li, Z.; Zhang, Y.; Lan, F.; He, J.; Wu, Y. The essential role of osteoclast-derived exosomes in magnetic nanoparticle-infiltrated hydroxyapatite scaffold modulated osteoblast proliferation in an osteoporosis model. *Nanoscale* **2020**, *12*, 8720–8726. [[CrossRef](#)]
63. Xu, J.; Li, D.; Cai, Z.; Sun, H.; Su, B.; Qiu, M.; Ma, R. Exosomal lncRNAs NONMMUT000375. 2 and NONMMUT071578. 2 derived from titanium particle treated RAW264. 7 cells regulate osteogenic differentiation of MC3T3-E1 cells. *J. Biomed. Mater. Res. Part A* **2020**, *108*, 2251–2262. [[CrossRef](#)]
64. Liu, L.; Liu, Y.; Feng, C.; Chang, J.; Fu, R.; Wu, T.; Yu, F.; Wang, X.; Xia, L.; Wu, C.; et al. Lithium-containing biomaterials stimulate bone marrow stromal cell-derived exosomal miR-130a secretion to promote angiogenesis. *Biomaterials* **2019**, *192*, 523–536. [[CrossRef](#)] [[PubMed](#)]
65. Lin, K.; Xia, L.; Li, H.; Jiang, X.; Pan, H.; Xu, Y.; Lu, W.W.; Zhang, Z.; Chang, J. Enhanced osteoporotic bone regeneration by strontium-substituted calcium silicate bioactive ceramics. *Biomaterials* **2013**, *34*, 10028–11004. [[CrossRef](#)] [[PubMed](#)]
66. Clarke, C.J.; Snook, C.F.; Tani, M.; Matmati, N.; Marchesini, N.; Hannun, Y.A. The extended family of neutral sphingomyelinases. *Biochemistry* **2006**, *45*, 11247–11256. [[CrossRef](#)]
67. Schimmoller, F.; Simon, I.; Pfeffer, S.R. Rab GTPases, directors of vesicle docking. *J. Biol. Chem.* **1998**, *273*, 22161–22164. [[CrossRef](#)]
68. Xu, H.; Zhu, Y.; Hsiao, A.W.-T.; Xu, J.; Tong, W.; Chang, L.; Zhang, X.; Chen, Y.-F.; Li, J.; Chen, W.; et al. Bioactive glass-elicited stem cell-derived extracellular vesicles regulate M2 macrophage polarization and angiogenesis to improve tendon regeneration and functional recovery. *Biomaterials* **2023**, *294*, 121998. [[CrossRef](#)]

**Disclaimer/Publisher’s Note:** The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.