

Testing novel multicomposite materials for electromethanogenesis

Original

Testing novel multicomposite materials for electromethanogenesis / Ghiara, Giorgia; Trasatti, Stefano; Goglio, Andrea; Cristiani, Pierangela. - In: E3S WEB OF CONFERENCES. - ISSN 2267-1242. - 334:(2022), pp. 1-6. (Intervento presentato al convegno 2021 European Fuel Cells and Hydrogen Piero Lunghi Conference, EFC 2021 tenutosi a online nel 16 December 2021 through 17 December 2021) [10.1051/e3sconf/202233408012].

Availability:

This version is available at: 11583/2985420 since: 2024-01-26T14:45:00Z

Publisher:

EDP Sciences

Published

DOI:10.1051/e3sconf/202233408012

Terms of use:

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

Publisher copyright

(Article begins on next page)

Testing novel multicomposite materials for electromethanogenesis

Giorgia Ghiara¹, Stefano Trasatti¹, Andrea Goglio², Pierangela Cristiani^{3*}

¹Università degli Studi di Milano, Department of Environmental Sciences and Policy, Milano, Italy

²Università degli Studi di Milano, Department of Agriculture and Environmental Sciences, Milano, Italy

³Ricerca sul Sistema Energetico - RSE S.p.A., 20134 Milano, Italy

Abstract. Electromethanogenesis is an innovative technology that uses a microbial electrochemical system to produce methane from CO₂, in a power-to-gas (BEP2G) concept. The results of experimental tests of new and cost-effective carbonaceous materials for electrode are presented here. The study aims at optimizing electromethanogenesis processes at laboratory level in mesothermic condition. As part of the experiments, hydrogenotrophic microorganisms (Family Metanobacteriaceae of Archaea domains) were selected from a mixed consortium taken from a biogas digestate and inoculated in double-chamber bioelectrochemical systems. The maximum amount of methane produced was 0.3 - 0.8 mol/m²g (normalized to the cathode area) with carbon cloth electrodes. Aiming at improving the methane productivity, innovative materials for the electrodes were now studied, creating porous high-surface composites, and studying nitrogen carbons doped with Cu and hydroxyapatite (Multicomposite Cu@/HAP/C), as chemical catalysts for CO₂ reduction (CO2RR). The description of the procedure for the Multicomposite Cu@/HAP/C production is reported in detail.

1 Introduction

Electromethanogenesis also called bioelectrochemical power-to-gas (BEP2G) is an innovative technology for storing renewable electricity in the form of methane, alternative to both biochemical methanogenesis and thermochemical methanation (Sabatier process) [1,2]. The process is supported by specific microorganisms selected FROM biogas plants or from natural anaerobic environments [3]. In BEP2G carbon dioxide (CO₂) and electrical energy are converted directly into methane (CH₄) on electrodes colonized by methanogenic microorganisms of the *Archea* domain [4,5]. In general, the mechanisms for the CH₄ production, in absence of electricity are different and depend on the metabolic pathways ascribed to the selected species. Two main pathways for methanogenesis are known: i) hydrogenotrophic; ii) acetoclastic. These metabolic processes start from two main types of molecules, respectively: i) carbonate ion; ii) acetate ion (or methanol). The values of Gibbs free energy at standard conditions (25 °C and pH 7) [6] differ by the nature of the substrate and the energy source used to produce CH₄ [7,8]. Among these, the most widespread and most metabolically efficient process for energy generation is the hydrogenotrophic one [9,10]

Using electricity, methanogenesis can be achieved using only carbon dioxide and bicarbonate as the only source of carbon and, it can be coupled to both the abiotic oxidation of water and the abiotic, or microbial, oxidation of organic

molecules [11-13]. According to this set-up, microorganisms catalyze the reduction of carbon dioxide introduced into the cathode chamber to methane on a polarized cathode, which donates electrons following reaction (1):



Furthermore, microbial electromethanogenesis can be effectively combined with the conventional anaerobic digestion (AD) process using CO₂-rich gases produced by biogas plants (methane up-grading) or using CO₂-rich industrial waste gases. However, it is a relatively recent technology, still mainly experimented at a laboratory level [1,2].

Lately, novel approaches have been proposed to solve technological problems and to make it a energy storage system more economically and industrially competitive [1,2]. Research on the optimization of the design and configuration of the bioreactors were carried out to reproduce the systems on a larger scale [2]. They mainly focused on the chamber set-up (i.e., single, or dual chamber), the applied cathode potential (~1 V), the choice of microorganisms, the cathode and/or anode feeding, the pH, etc... [14-17]. An alternative, relevant, approach is the study of different materials for the cathode. Electrodes must give large surfaces to maximize the interaction with microorganisms minimizing charge transfer resistance and diffususive mass transport [15]. Carbon-based materials are particularly suitable for electrochemical systems, especially biochar, which aroused great interest for such

* Corresponding author: Pierangela.Cristiani@rse-web.it

application [18,19]. In this study the authors present the first results of the use of an innovative composite carbon based electrocatalysts (e.g., biogenic carbon) functionalized with copper nanoparticles (Cu@) and hydroxyapatite (HAP) as a cathode material where reduce CO₂ (CO₂RR) to CH₄. The choice of a carbon of biological origin (biochar) as a support for both Cu@ and HAP was made according to the necessity to have suitable performances, in terms of porosity, conductivity, biocompatibility, mechanical resistance and resilience [20,21]. Furthermore, Cu@ is an active phase that directly promotes a further reduction of CO₂ (transfers > 2 e⁻) to a wide range of so-called higher order products (as CH₄, C₂ or C₃), while HAP enhances the selectivity towards CH₄ [22, 23]. The preparation of the electrode material (Cu@/HAP/C) is an important part of the experiment, and an innovative multi-phase protocol is introduced here.

2 Materials and methods

2.1 Biochar production

To obtain an electrically conductive material, giant cane (*Arundo Donax*, L., 1753) was employed. The canes were positioned in a quartz tube inside a horizontal furnace (Carbolite) and pyrolyzed accordingly. The pyrolysis procedure of the material was carried out according to the following protocol: 2 hours at 25 °C, slow heating (10 °C/min) up to 900 °C, 1 h held at 900 °C and cooling down to 25 °C according to [24]. During all the pyrolysis treatment, nitrogen flowed constantly at 1 NL/h. This type of procedure allows high temperatures to be reached in a short time and maximum treatment efficiency, without any heat loss.

2.2 Multicomposite Cu@/HAP/C production

The composite produced followed a multi-step protocol that involved the use of copper nanoparticles (SigmaAldrich, CAS 7440508, $\sigma = 25$ nm) and hydroxyapatite (produced at the University of Milan according to a procedure described elsewhere [25]). Firstly, biochar was pulverized using an agate mortar. The powder was subsequently used as a support for copper nanoparticles (Cu@) and hydroxyapatite (HAP). Approximately. 95 mg of biochar was dispersed in ca. 40 ml of isopropyl alcohol (IPA) (Figure 1a).

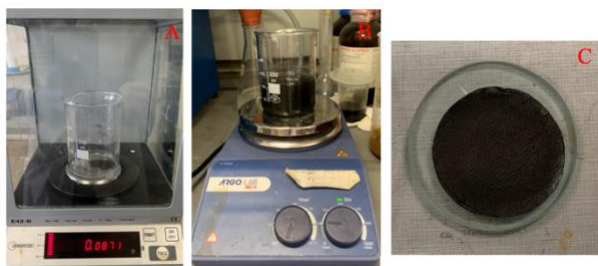


Fig. 1. Protocol to produce the multicomposite Cu@/HAP/C.

The pH of the suspension was adjusted to 10 by adding an aqueous solution of 0.1 M KOH. Similarly, approx. 5 mg of commercial Cu NP were dispersed in ca. 40 mL of IPA, adjusting the pH as indicated for the biochar suspension. Both mixtures were placed on ultrasound for 30 minutes to obtain an optimal suspension. Then, the Cu NP suspension was added one shot to the biochar suspension. The resulting mixture was stirred at room temperature for 48 hours (Figure 1b).

After the immobilization step, the powder was vacuum filtered on a 0.45 m Nylon membrane, washed with MilliQ water and dried at 110 °C for 45 minutes. The sample obtained was labeled Cu@/C. Approximately. 100 mg of Cu@/C were suspended in ca. 90 ml of MilliQ water. The pH of the suspension was brought to 7 by adding a 0.1 M aqueous solution of KOH. Similarly, ca. 7 mg of HAP were dispersed in ca. 20 mL of MilliQ water, adjusting the pH of the suspension to 7 by adding a 0.1 M KOH solution. Both mixtures were sonicated for 45 minutes. Then, the HAP suspension was added to the Cu@/C suspension in one shot; the resulting mixture was stirred for 72 h at room temperature. Finally, the powder was vacuum filtered on a 0.45m Nylon membrane, washed with MilliQ water and dried at 110 °C for 3 hours (Figure 1c). This sample obtained was labeled Cu@/HAP/C and the desired composition is presumed to be 5 wt. % Cu and 5 wt. % HAP.

2.3 Set-up of the bioelectrochemical cells

The dual chamber system was made with borosilicate (Pyrex) bottles. The anode and the cathode chambers, both characterized by a volume of 200 mL, were separated by a proton exchange membrane (PEM NAFION 417) (working surface: 7.0 cm²). CO₂ was fluxed at the cathode at the beginning of the experiment for 10 minutes. The catholyte solution consisted of the inoculum retrieved from an online biogas plant and stored at University of Milan, Bicocca. The inoculum was supplied with 2.54 g/L KH₂PO₄, 11.7 g/L Na₂HPO₄ * 12H₂O, 0.53 g/L NH₄Cl, 0.1 g/L Na₂SO₄, 5.0 g/L NaHCO₃, and vitamins. The anolyte consisted of a solution of 0.2M Na₂SO₄. The cathode was made of different materials and operated to verify, in comparison, the methane production.



Fig. 2. Set-up of the bioelectrochemical cell.

Three materials were used for the cathode: i) carbon cloth (CC); biochar (C); multicomposite Cu@/HAP/C. All electrodes had a comparable surface area of 100 cm². The anode was a Ti-mesh of a suitable area of 36 cm². Both anodic and cathodic collector wires were connected to a potentiostat (Amel S.r.l. Milan, Italy) that acted as a power supply. The recording of the potential imposed between the cell and the generated current was performed with an Agilent 4930 A data-logger. A reference electrode Ag/AgCl 3M was inserted in each cathodic compartment. The potential imposed on the cathode during the test was -1.2 V vs the reference electrode, corresponding to approximately -1V vs SHE (Standard Hydrogen Electrode). The duration of the experiments was 6 days and was replicated twice.

2.4 Analytical methods

To verify the morphology (i.e., pore size) of the pyrolyzed biochar and to characterize the multicomposite produced a Scanning Electron Microscopy analysis (SEM) coupled with Energy dispersive X-Ray measurements (EDS) was carried out at the Department of Earth Sciences of the University of Milan. The analyses were conducted at different magnifications and with an acceleration voltage of 20 KeV using secondary electrons (SE) detector.

The composition of biogas (CH₄, H₂, and CO₂) was analyzed using a gas chromatograph (GC) at the Department of Agriculture of the University of Milan. The sample for the GC was taken from the headspace of the bioreactor cathode chamber with flex-foil bags (1 and 5L) connected to the gas escape system. Numerous gas samplings were carried out on a weekly basis, lasting about 60 minutes. The quantity of CH₄ produced was expressed as a percentage of gas found. Furthermore, the pH was monitored on a three-day-basis.


3 Results

3.1 Biochar production

Firstly, A. Donax samples were weighted before and after pyrolysis to verify the success of the procedure. Figure 3 shows a sample before and after the treatment.

**Fig. 3.** Example of: A) pre pyrolyzed sample; B) pyrolyzed sample

Generally, a weight loss corresponding to approximately 75% of the initial weight was highlighted for all samples, consistent with the decomposition of the material in the absence of oxygen. During this process, the lignocellulosic components such as cellulose (C₆H₁₀O₅) n-hemicellulose and lignin undergo depolymerization reactions, fragmentation, and cross-linking [26]. It is in fact known from the literature that pyrolysis increases the porosity of the material and the surface area even by several orders of magnitude [26]. Porosity is formed because of the loss of water during the treatment. To define the size of the pores we proceeded with a SEM analysis. As can be seen from Figure 4, the material after pyrolysis maintained the same mechanical structure and highlighted an increasing number of pores on the surface, confirming the success of the treatment.

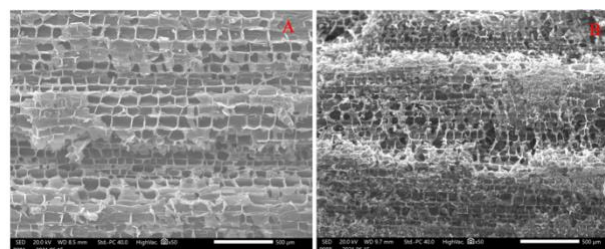**Fig. 4.** SEM-SE micrographs of: A) pre pyrolyzed sample; B) pyrolyzed sample

Generally, three types of pores can be distinguished followed by various applications of biochar: i) micropores (<2nm); ii) mesopores (2-50 nm); ii) macropores (> 50 nm). As displayed by the figure the material is composed of macropores, with average dimensions around 50 ± 10 μm. This is a promising result for its use as an electrode as the presence of macropores favors: i) the diffusion of gases (CO₂ and H₂) inside the material, also allowing for a good wettability by the H₂O; ii) the extracellular transfer of electrons by microbes that catalyze the direct production reaction of methane.

3.2 Multicomposite Cu@/HAP/C production

Figure 5 displays the qualitative results obtained by the EDS analysis on the powder.

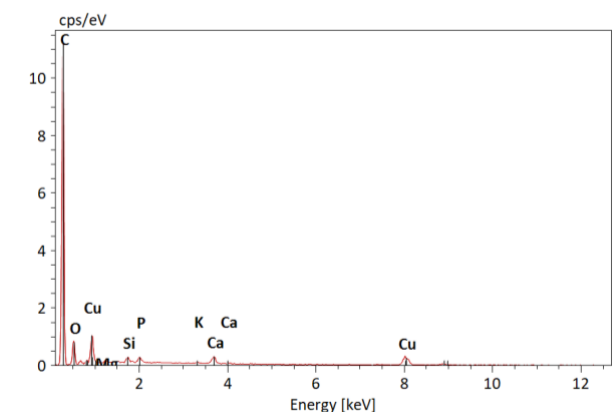


Fig. 5. EDS average spectrum of the Cu@/HAP/C multicomposite.

As expected, the spectrum indicated a high percentage of C on the surface, attributed to the biochar. However, the signals of Cu, Ca, O and P are detected, which implies the success of the methodology. In fact, hydroxyapatites bear generally the following stoichiometry: $Ca_{10}(PO_4)_6(OH)_2$. However, it was not possible to further quantify the overall percentage of the single components due to quantification limits connected to the massive presence of carbon. Further investigation will thus be dedicated to the study of the distribution of the Cu@ and HAP on the biochar and exact composition of this multicomposite material.

3.3 Bioelectrochemical cells

3.3.1 Current output

Figure 6 shows the trend of the cell current (I_{cell}) circulating for 140 h, considering the average. Red and blue arrows indicate gas and pH sampling, respectively. It should be noticed that the CO_2 dosing was carried out through a sparging method (materials and methods section) to allow all CO_2 to be consumed at the electrode and transformed into methane.

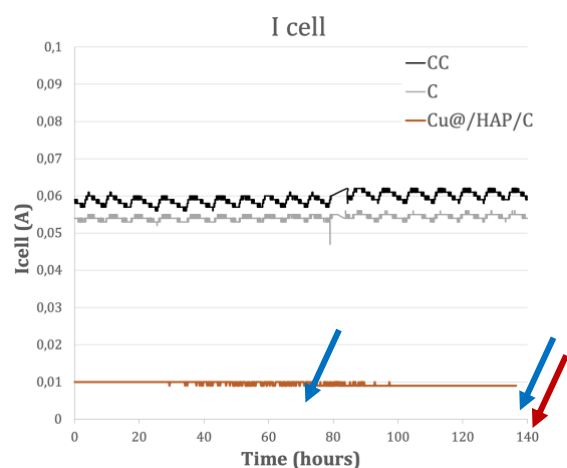


Fig. 6. Current circulating between the electrodes according to the material used. CC= carbon cloth; C= biochar.

As can be seen from the figure, the current produced is influenced by the type of material used as a cathode. An evident variability in the current output is noticed. Carbon cloth (CC) and biochar (C) exhibit higher currents than the multicomposite Cu@/HAP/C. These results are not surprising considering that with the same potential applied, the resistivity of the multicomposite is higher due to the presence of HAP.

The moles of H_2 that could ideally be produced by the system were also calculated, considering the charge supplied to be used exclusively for the H_2 production reaction. Table 1 summarizes the results obtained in moles of H_2 per day, averaging the currents as a function of the monitoring time.

Table 1. Ideal mmol of hydrogen produced daily by the polarization.

material	H_2 (mmol/d)
Carbon Cloth (CC)	23
Biochar (C)	23
Multicomposite Cu@/HAP/C	4

From the values obtained, the presence of the multicomposite catalyses the production of hydrogen at the electrode less easily, 6-times lower values of mmol produced per day.

The pH of the system varied according to the electrode used (as displayed by table 2) and it was expected to rise as a function of the hydrogen consumption due to the applied polarization.

Table 2. Measurements of pH during the experiment

material	pH		
	Day 1	Day 3	Day 6
Carbon Cloth (CC)	6.5	10	10
Biochar (C)	6.5	10	10
Multicomposite Cu@/HAP/C	6.5	6.5	7

As can be seen, a correction of the pH was necessary (0.1 M HCl each time) for both systems using carbon cloth and biochar due to the uptake of hydrogen ions from the solution. However, this trend seems not to interest the multicomposite system in which the pH results more stable, maintaining optimal conditions for the inoculum to produce methane.

3.3.2 Methane production

The gaseous methane was detected as a volumetric percentage contained within the 1 L flex-foil gasbags. The values that emerged from gas chromatography refer exclusively to the methane produced during sampling, which lasted about 60 minutes, for each experiment conducted. Figure 7 shows the results obtained from the gas chromatographic analyses at the end of the experiment.

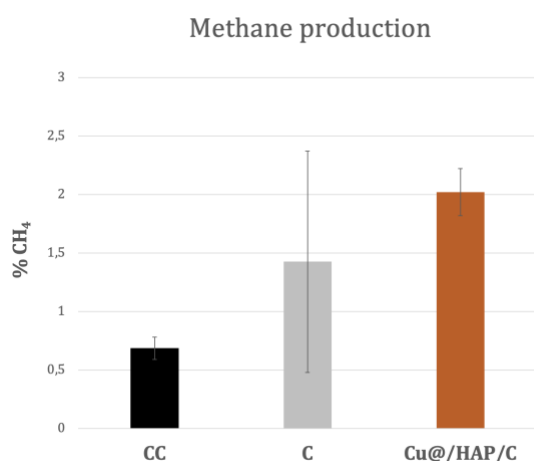


Fig. 7. CH₄ produced at the end of the experiment. CC= carbon cloth; C= biochar.

At first glance, the material effect on experimentation can be seen, characterized in general by an upward trend in methane production, showing a higher production in the presence of biochar. These results are also very promising since the highest methane production was found for the Cu@/HAP/C, in spite the current generated on the electrode was the lower one, suggesting a selectivity for

the direct reduction of CO₂ into methane in presence of the inoculum.

4 Conclusion

Comparing the results from the electrochemical and analytical point of view it the better performances of the Multicomposite Cu@/HAP/C than the other materials tested (carbon cloth and biochar) point out in an evident way.

This suggests the use of a different metabolic pathway to produce methane, probably associated with a direct passage of the electron from the electrode to the methanogens, avoiding a dispersion of hydrogen into the solution. Over time, the cell currents and the differences between the different materials remain constant.

An excessive enhancement of the pH suddenly occurs in the case of carbon cloth and biochar, in a few days, while the Multicomposite Cu@/HAP/C guarantee neutral values for longer time. The effect of pH stabilization can be adduced to the presence of HAP in the composite. This phenomenon, associated to the presence of Cu nanoparticle catalysts, can be responsible for the advantage in terms of the methane production process.

References

1. N. Aryal, T. Kvist, F. Amman, D. Pant, L. D. Ottosen, *Biores. Technol.*, **264**, (2018).
2. R. Blasco-Gomez, P. Batle-Vilanova, M. Villano, M. Balaguer, J. Colprin e S. Puig, *Int J. Mol Sci*, **18**, 32, (2017).
3. P. Clauwaert, *Water Sci. Technol.*, **57**, (2008).
4. P. Clauwaert, W. Verstraete, *Appl. Microbiol. Biotechnol.*, **82**, (2009).
5. P. Beese-Vasbender, *Bioelectrochem.*, **102**, (2015).
6. R. K. Thauer, K. Jungermann e K. Decker, *Bacteriol. Rev.*, **41**, (1977).
7. J.-L. Garcia, B. Patel, B. Ollivier, **6**, (2000).
8. Y. Liu, W. Whitman, *Ann. N. Y. Acad. Sci.*, **1125**, (2008).
9. M. Lever, *Trends Microbiol.*, **24**, 2, (2016).
10. F. Sousa, T. Thiergart, G. Landan, S. Nelson-Sathi, I. Pereira, J. Allen, N. Lane, W. Martin, *Philos. Trans. R. Soc. B: Biol. Sci.*, **368**, 1622, (2013).
11. S. Gajaraj, Y. Huang, P. Zheng, Z. Hu, *Biochem. Eng. J.*, **117**, (2017).
12. Q. Fu, Y. Kuramochi, N. Fukushima, H. Maeda, K. Sato, H. Kobayashi, *Environ. Sci. Technol.*, **49**, (2015).
13. D. E. A. Park, *Appl. Environ. Microbiol.*, **65**, (1999).
14. D. Liu, L. Zhang, S. Chen, C. Buisman A. ter Heijne, *Water Res.*, **99**, (2016).
15. Y. Dang, D. Holmes, Z. Zhao, T. Woodard, Y. Zhang, D. Sun, L.-Y. Wang, K. Nevin, D. Lovley, *Bioresour. Technol.*, **220**, (2016).
16. X. Guo, J. Liu, B. Xiao, *Int. J. Hydr. En.*, **38**, (2013).

17. M. Siegert, M. Yates, A. Spormann, B. Logan, *ACS Sustain. Chem. Eng.*, **3**, 2015.
18. A. Schievano, A. Goglio, C. Erckert, S. Marzorati, L. Rago, P. Cristiani, *Detritus*, **1** (2018)
19. S. Marzorati, A. Goglio, S. Fest-Santini D. Mombelli, F. Villa, P. Cristiani, A. Schievano, *Int. J Hydr. En.* **44** (2019)
20. C. Cruz Viggli, S. Simonetti, E. Palma, P. Pagliaccia, C. Braguglia, S. Fazi, S. Baronti, M. Navarra, I. Pettiti, C. Koch, F. Harnisch, F. Aulenta, *Biotechnol. Biofuels* **10**, (2017).
21. J. Mumme, F. Srocke, K. Heeg, M. Werner, *Bioresour. Technol.*, **164**, (2014).
22. A. Rendón-Calle, S. Builes, F. Calle-Vallejo, *Curr. Opin. Electrochem.*, **9**, (2018)
23. R. Chong, Y. Fan, Y. Du, L. Liu, Z. Chang, D. Li, *Int. J. Hydr. En.*, **3** (2018)
24. P. Cristiani, A. Goglio, S. Marzorati, S. Fest-Santini, A. Schievano, *Front. En. Res.* **8** (2020)
25. M. Ferri, S. Campisi, L. Polito, J. Shen, A. Gervasini, *J. Hazard. Mater.*, 2021, doi: 10.1016/j.jhazmat.2021.126656
26. P.R. Yaashika, P. Senthil Kumar, Sunita Varjani, A. Saravanan, *Biotechnol. Reports*, **28**, (2020)