

COMPREHENSIVE CHARACTERIZATION OF ANNEALED COATINGS: INVESTIGATING
ROUGHNESS AND WEAR PERFORMANCE THROUGH WEAR TESTING AND ANALYSIS

Original

COMPREHENSIVE CHARACTERIZATION OF ANNEALED COATINGS: INVESTIGATING ROUGHNESS AND WEAR PERFORMANCE THROUGH WEAR TESTING AND ANALYSIS / Sheibanian, N.; Sesana, R.; Dehghanpour Abyaneh, M.; Özbilen, S.; Lupoi, R.. - ELETTRONICO. - (2024), pp. 1-10. (Intervento presentato al convegno 53° congresso nazionale AIAS tenutosi a Napoli nel 5-7 Settembre 2024).

Availability:

This version is available at: 11583/2994101 since: 2024-11-02T08:53:05Z

Publisher:

AIAS

Published

DOI:

Terms of use:

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

Publisher copyright

(Article begins on next page)

Comprehensive Characterization of Annealed Coatings: Investigating Roughness and Wear Performance through Wear Testing and Analysis

N Sheibanian^{1,2*}, R Sesana¹, M Dehghanpour Abyaneh^{1,2}, S Özbilen³, R Lupoi³

¹ DIMEAS, Department of Mechanical and Aerospace Eng., Polytechnic of Turin, Corso Duca degli Abruzzi 24, 10129 Turin, Italy.

² TN ITALY, Central Laboratory, Corso Torino 378, 10064 Pinerolo, Torino, Italy.

³ Department of Mechanical, Manufacturing & Biomedical Engineering, Trinity College Dublin, the University of Dublin, Parsons Building, Dublin, D02, Ireland

*Corresponding author: nazanin.sheibanian@polito.it

Abstract. Surface coatings play a pivotal role in enhancing mechanical and functional properties of various materials. High Entropy Alloy (HEA) annealed coatings have garnered significant interest due to their potential to improve wear resistance and overall durability. This research presents a comprehensive study focused on the characterization of HEA annealed coatings. It focuses on evaluating their roughness and wear performance. In this research, a systematic approach is adopted to assess the effects of annealing on coating surface properties. The investigation begins with the deposition of the $Al_{0.1-0.5}CoCrCuFeNi$ and $MnCoCrCuFeNi$ coatings using a well-established cold spray (CS) technique, followed by a controlled annealing process. The coating surface roughness is analyzed using profilometry and microscopy techniques. This offers insights into the changes induced by annealing. The wear performance of the annealed coatings is evaluated through tribological tests. The data obtained from wear tests are correlated with surface roughness measurements. This provides a deeper understanding of the interplay between roughness and wear resistance.

1. Introduction

The development of metallurgical science has enabled alloys to demonstrate better and more tailored properties than single metals. However, traditional alloys are composed of a single main element, which limits the degree of freedom in the composition of an alloy. A new alloy concept proposed by J. W. Yeh, and B. Cantor is called "HEA" (High Entropy Alloy), which contains at least five major elements in an atomic percentage of 5-35% [1,2]. Secondary alloying elements are therefore characterized by atomic percentages of less than 5% [1-11]. Currently, the majority of knowledge is focused on alloys containing Al, Co, Cr, Cu, Fe, and Ni, and alloys derived from those alloys, obtained by adding other elements or substituting some of them. Many other alloys are still to be explored [3]. In terms of structural and functional applications, HEAs have a great deal of potential.

A high mixing entropy is found to promote the formation of solid solutions with simple microstructures [1,3]. High strains and stresses are associated with crystal lattices, as well as increasing strength and hardness, and a reduced sensitivity to temperature variations [1,2,3,10,11]. In many cases, HEAs can

demonstrate excellent properties due to their characteristic chemical composition, which consists of several main elements: high strength and hardness, considerable wear resistance, exceptional resistance to high temperatures, good structural stability, and excellent corrosion and oxidation resistance. HEAs do not require any special production techniques or facilities, so they can be manufactured using current technologies.

Due to the presence of multiple main elements within HEAs, there are "core effects" that are responsible for determining the microstructural characteristics and exceptional properties of the materials. As a result of these effects, there is a high mixing entropy, a severe distortion of the crystal lattice, sluggish diffusion, and a cocktail effect [1,2,3,6,7,10,11]. It was reported in [13] that samples of Al_{0.5}CoCrCuFeNi alloy quenched in water and cold rolled showed better performance than many conventional alloys, with fatigue strength limit values ranging from 540 to 945 MPa. It is evident from these results that the HEA of this system is potentially useful in future applications in which fatigue strength is an important consideration. The chemical composition of HEAs determines their tribological properties. By adding elements such as Al, Fe, and Nb, grains become refined and phases with a BCC structure are formed.

In addition, Mn and Cr play a significant role in the formation of hard phases. As C, N, B, and Si concentrations increase, carbides, silicates, and boron compounds are formed, or the phase transition from FCC to BCC/B2 occurs. A similar heat treatment to AISI 304 stainless steel increases the hardness of Mo better than those of AISI 304 stainless steel. In HEAs, wear resistance is determined by the type of phase present. The wear resistance of alloys made exclusively of simple and disordered phases ("SDPs") is generally not greater than that of conventional alloys with similar hardness. In contrast, if the prevailing phase is complex and ordered ("COPs"), the wear resistance of the alloy is often much greater than that of conventional alloys of similar hardness [3,13]. As a result, one of the major applications of HEAs is the creation of coatings with high wear resistance, which can be deposited using a variety of techniques. Coatings containing particles of ceramic materials dispersed in the metal matrix can increase the coating's overall hardness and, consequently, reduce the coating's wear rate [1,2,4,7-9,13-19].

The purpose of this paper is to describe annealed HEA coatings that have been cold sprayed and have been characterized with regards to dimensions and profiles as well as surface and microstructural characteristics, including roughness measurements and mechanical property determination of Cold Spray HEA coatings on Mg substrates. The wear performance of the annealed coatings is further evaluated by means of tribological tests. Annealing heat treatment is a practical way for adjusting the microstructures/properties and improvements in wear/corrosion/oxidation resistance of some light weight HEAs has been reported [3]. Compressively stressed cold sprayed (CS) HEA coatings can be recrystallized by annealing heat treatment to restore HEA coatings ductility and workability. The deformation via MA+CS and annealing behavior of a ductile HEA alloy, such as Al_{0.5}CoCrCuFeNi, with favorable properties like high work hardening, elevated temperature strength, wear/oxidation resistance were investigated to elucidate the phenomena exhibited in HEAs. The formation of two HEAs is investigated using Al_{0.1-0.5}CoCrCuFeNi and MnCoCrCuFeNi, as well as three deposition temperatures: 650°C, 750°C, and 850°C.

2. Experimental procedure

2.1. Materials and post-MA+CS vacuum annealing

Several pure elemental powders were used in this study, including Al, (Mn), Co, Cr, Cu, Fe, and Ni, all of which had high purity levels above 99.9%. A process known as mechanical alloying (MA) was used to create octonary high-entropy alloys (HEA): Al_{0.1-0.5}CoCrCuFeNi and MnCoCrCuFeNi. Refer to reference [20] for additional information regarding the steps involved in mechanical mixing (MM) and mechanical alloying (MA). According to Table I, calculations were performed using pure elemental powders of Al, Cu, Co, Cr, Fe, and Ni to achieve the desired compositions of Al_{0.1-0.5}CoCrCuFeNi and MnCoCrCuFeNi.

After mixing and homogenizing the materials, they were subjected to MA for 5.5 hours. In order to prevent contamination from the surrounding atmosphere, the MA powders were stored in airtight containers filled with argon gas until they were processed by Cold Spray (CS). Reference [20] provides a more detailed explanation of the impact of MA on powders.

During the cold spray deposition process, a magnesium (Mg) substrate was coated with High Entropy Alloys (HEAs) of $Al_{0.1-0.5}CoCrCuFeNi$ and $MnCoCrCuFeNi$ using various nitrogen gas temperatures, specifically at 650°C, 750°C, and 850°C. For this purpose, Trinity College, Dublin, Ireland, has made use of the Cold Spray deposition system as described in references [20], [21]. In both the MA and CS $Al_{0.5}HEA$ coatings, varying microstructures and properties were obtained by meticulously controlling the parameters of the cold spray process and the coating. In the cold spray process, nitrogen was used at a pressure of 30 bar, a type NZ1 nozzle with a standoff distance of 47mm, a powder feed rate of 9%, a nozzle speed of 15 millimeters per second, a beam distance of 2 millimeters, and four layers of coating were applied in a circular pattern. It was a 50mm x 50mm Mg substrate plate, and the powder feedstocks for the CS were -63 mm size fractions of MA $Al_{0.5}HEA$ powder. Furthermore, at 600°C for 1.0 hr under 0.05 bar pressure, vacuum annealing was carried out in a batch furnace at the National Heat Treatment Center, Kildare, Ireland. Tables 1 and 2 show the nominal chemical composition of coatings and samples denomination.

Table 1. Composition of HEA powders in nominal unit.

Samples Designation	Nominal chemical composition						
	Al	Cu	Cr	Co	Fe	Ni	
$Al_{0.1}CoCrCuFeNi$	At%	4.22	17.38	21.2	18.67	19.74	18.79
	Wt%	1.96	19.61	19.61	19.61	19.61	19.61
$Al_{0.2}CoCrCuFeNi$	At%	8.13	16.65	20.33	17.91	18.95	18.02
	Wt%	3.85	19.23	19.23	19.23	19.23	19.23
$Al_{0.5}CoCrCuFeNi$	At%	18.3	14.8	18.09	15.96	16.84	16.0
	Wt%	9.15	18.1	18.1	18.1	18.1	18.1
	At%	-	15.62	16.81	13.6	13.6	16.86
	Wt%	-	16.7	16.7	16.7	16.7	16.7

Table 2. $Al_{0.1-0.5}CoCrCuFeNi$ and $Al_{0.1}CoCrCuFeNi$ chemical composition samples prepared by cold spray.

$Al_{0.1}CoCrCuFeNi$	Cold spray-Temperature [°C] Denomination	650 A	750 B	850 C
$Al_{0.2}CoCrCuFeNi$	Cold spray-Temperature [°C] Denomination	650 D	750 E	850 F
$Al_{0.5}CoCrCuFeNi$	Cold spray-Temperature[°C] Denomination	650 G	750 H	850 I
$MnCoCrCuFeNi$	Cold spray-Temperature[°C]	650	750	850

2.2 Microstructure characterization

The details of sample preparation and microstructural characterization are provided in Ref. [22]. HEA coating and Mg substrate were intentionally removed (partially and entirely) in order to observe directly their interface from a plane-on perspective. An assessment of the coating microstructure was conducted by preparing cross-sectional samples according to standard metallographic procedures and polishing them with 0.06 mm colloidal silica. Using an energy-dispersive X-ray spectrometer (EDS) equipped with a scanning electron microscope (SEM), the coating elements were analyzed. In Figure 1, macro photos of annealed MA+CS $Al_{0.1-0.5}(Mn)CoCrCuFeNi$ HEA coatings have been taken at three process gas (N_2) temperatures, including 650, 750, and 850 degrees Celsius.

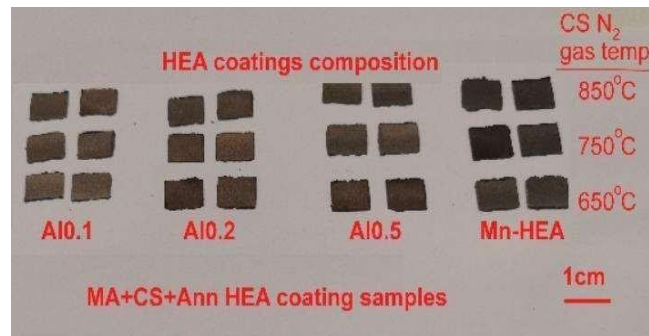


Figure 1. A macrophotograph of MA+CS $Al_{0.1-0.5}$ and Mn-HEA annealed coatings on magnesium.

2.3 Surface characterization measurement

The roughness was measured using an RTP80 roughness tester by SM-Instruments. Table 3 summarizes the measurement specifications. All specimen coatings were measured for surface roughness. Measurements were made in directions parallel to and perpendicular to the direction of deposition. The cut-off dimension was 0.25 mm, and the measuring length was 1.5 mm. Each coating sample was subjected to 5 roughness measurements. Each coating sample was subjected to three roughness measurements. Particularly: R_a , R_q , R_t . Standard definitions (UNI EN ISO 4287 (2011)) indicate that they are all parameters related to the amplitude of roughness, which is the distance between peaks and valleys. In terms of the assessed profile, R_a represents the arithmetical mean deviation; R_q represents the root square of the mean deviation and is an average amplitude measurement along the height direction. In relation to the total

height of the profile, R_t represents the height of the profile at its maximum height, which is the distance between its maximum peak and its minimum valley.

Table 3. Detailed specifications for the RTP80 roughness tester.

Characteristic	Description/value
Measuring range [μm]	± 500
Resolution [μm]	0.001
Cut-off length [mm]	0.25
Measuring length [mm]	1.5

2.4 Microhardness measurement

Innovatest Vickers microdurometers were used to measure the HV30 microhardness profiles of the coating samples with a 3 N preload and a 15 s indentation time. Firstly, annealed coatings were stuck onto Mg substrates with glue. Each specimen's microhardness was calculated by averaging the results of 3 indentations made on the polished side cross-section.

2.5 Tribological analysis

Wear tests are conducted under ambient conditions using a pin-on-disk tribometer (Anton Paar TriTec, TRB) at the Polytechnic University of Turin. A dedicated pin was developed to ensure a tight clamping of the samples during testing. The counterparts used during the wear tests are made of quenched 100Cr6 steel with a grinding surface. Figure 2 illustrates the experimental setup used during the wear tests. Table 4 illustrates the wear testing parameters.

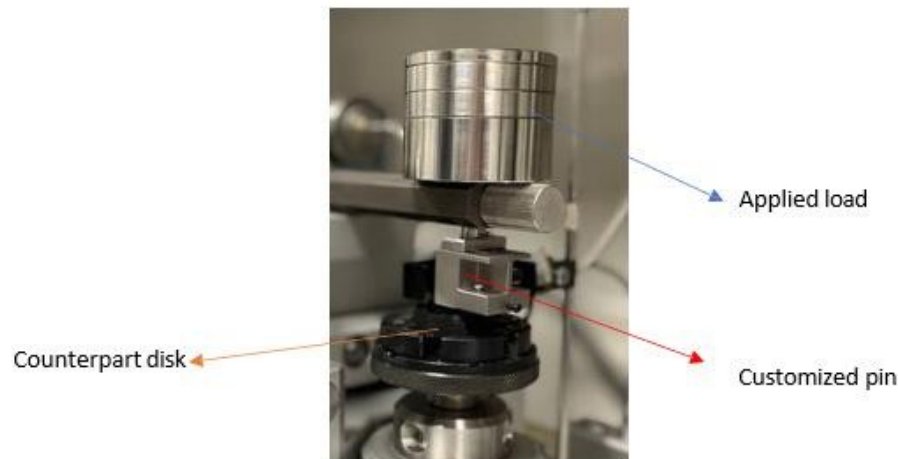


Figure 2. Experimental setup.

Table 4. Parameters of wear testing.

Wear testing parameters	
Rotational speed [rpm]	250
Normal load [N]	10
Sliding length [m]	200
Linear speed [mm/s]	235.6

3. Result and discussion

3.1 Result and discussion

Fig. 3a illustrates SEM-SE imaging of Al_{0.5} CS850°C annealed at 600° C. There is a similar level of roughness on the surface of the coating as in the MA+CS sample [23]. According to [23], the level of porosity is very low compared to the MA+CS sample. Surface roughness at the interface between the HEA coating and the Applied load Customized pin Counterpart disk magnesium substrate indicates a good level of bonding and adhesion. Figure 3b shows the same results for a 600°C annealed Mn-HEA CS850°C sample. The top surface roughness is also similar to that of the MA+CS counterpart. Porosity levels are also very low, interfaces are rough, and the first direct and plane on surface imaging (viewing) of the interface following mechanical removal of the Mg substrate from the HEA coating following annealing processes indicates the roughness of the interface that is responsible for its excellent bonding with the Mg substrate by the HEA coating

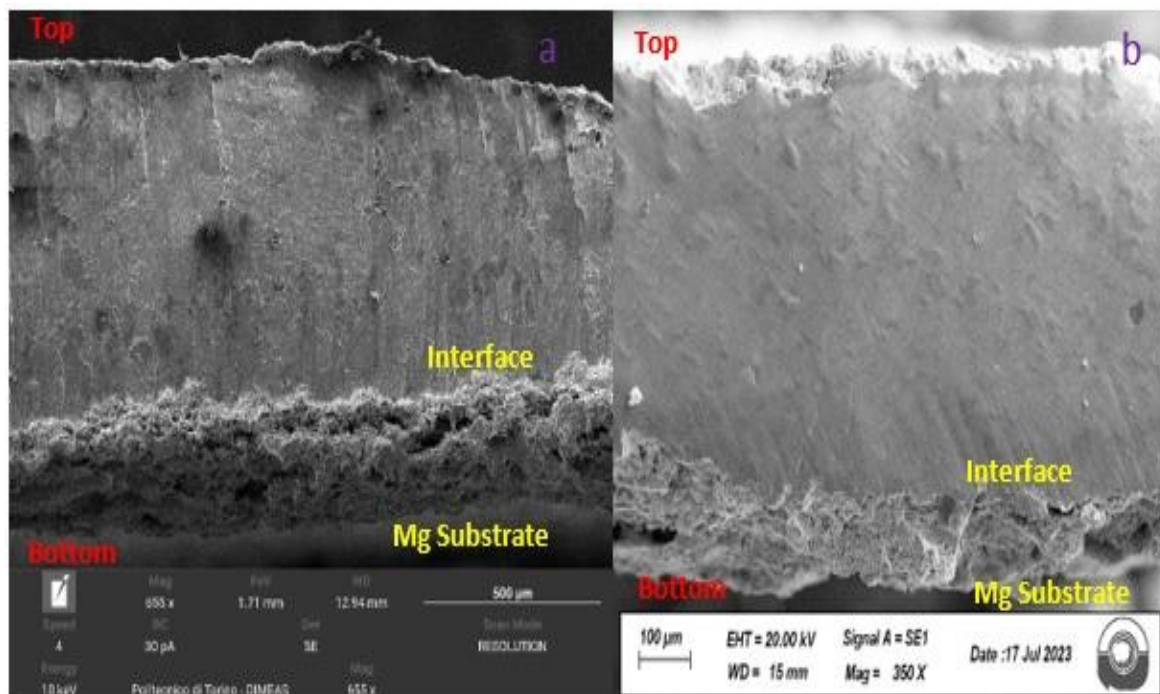


Figure 3. SEM micrograph: a) Al_{0.5} HEA CS 850°C b) Mn-HEA CS 850°C.

3.2 Surface characterization

3.2.1 Roughness measurements

An analysis of the roughness values obtained for samples with the same chemical composition at different deposition temperatures is presented in Figure 4. In Al_{0.1}CoCrCuFeNi, all roughness parameters decrease with increasing deposition temperature. As a result of experimental scattering, a monotonic relationship between roughness parameters and deposition temperature cannot be established for other specimens.

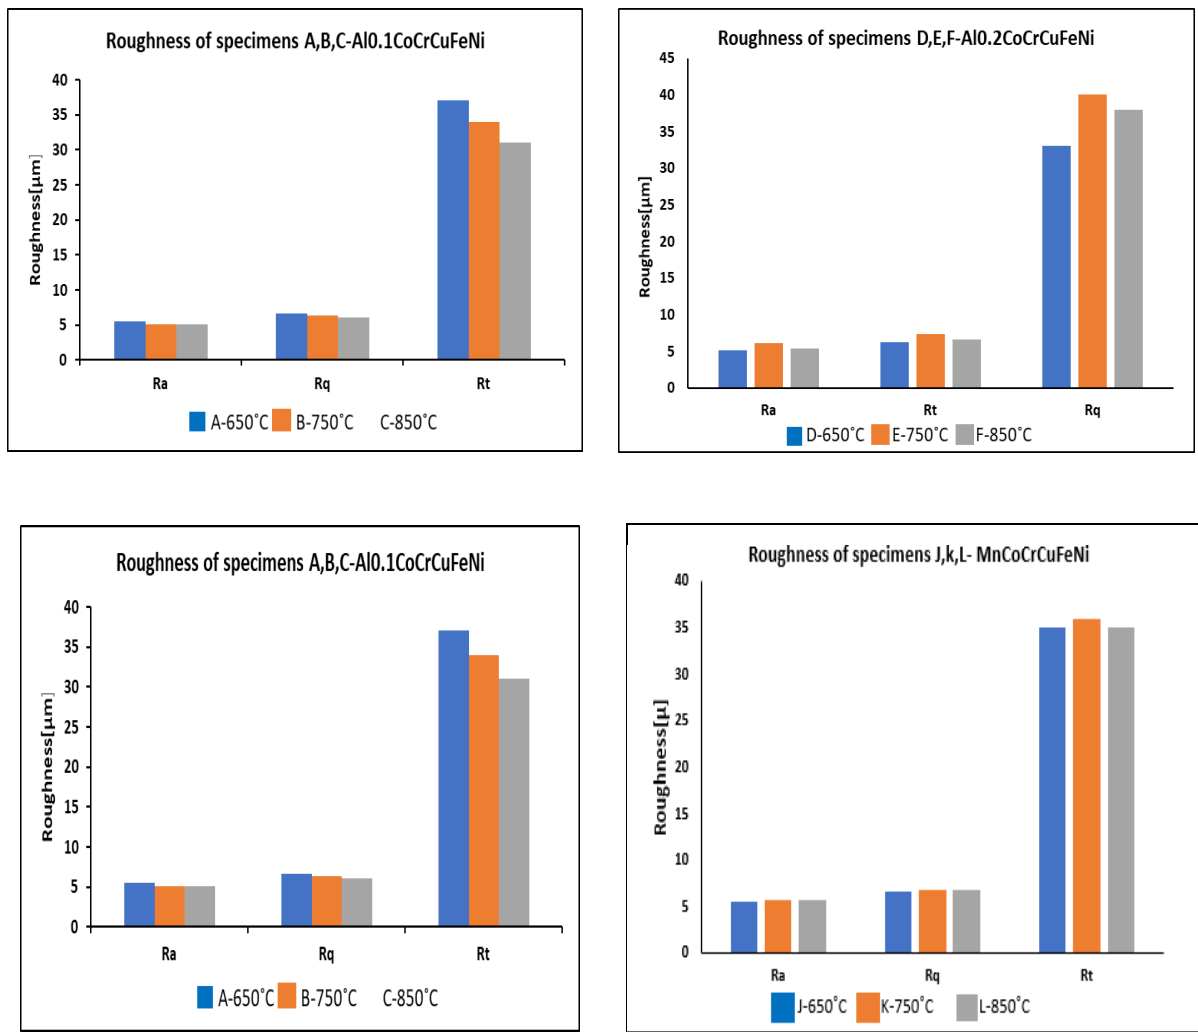


Figure 4. Roughness values.

3.3 Microhardness test

After careful polishing of the lateral surfaces of the samples, indentations were made at the interface close to the substrate. Based on three measurements, a mean value was calculated for each position. Table 5 indicates that the microhardness of a coating is highly dependent on its chemical composition. Microhardness averages for samples with Al_{0.1}CoCrCuFeNi composition (A-C) are the lowest, whereas

mean microhardness averages for samples with Al_{0.5}CoCrCuFeNi (G-I) composition are the highest.

Table 5. Vickers microhardness measurements for all compositions.

Coating			
Al _{0.1} CoCrCuFeNi	A (650 °C)	Average	113.26
		Std dev	4.55
	B (750 °C)	Average	79.48
Std dev		7.76	
C (850 °C)	Average	95.22	
	Std dev	9.42	
Al _{0.2} CoCrCuFeNi	D (650 °C)	Average	151.57
		Std dev	15.33
	E (750 °C)	Average	80.427
Std dev		14.73	
Al _{0.5} CoCrCuFeNi	F (850 °C)	Average	91.21
		Std dev	19.96
	G (650 °C)	Average	92.34
Std dev		4.76	
H (750 °C)	Average	171.49	
	Std dev	14.17	
	I (850 °C)	Average	131.96
MnCoCrCuFeNi	J (650 °C)	Average	91.8
		Std dev	18.56
	K (750 °C)	Average	84.123
Std dev		3.70	
L (850 °C)	Average	152.03	
	Std dev	13.09	

3.4 Wear test

Figure 5 depicts the average friction coefficient observed in each test. In the case of the Al 0.1-0.5 CoCrCuFeNi composition at 750°C, the friction coefficient is at its maximum. Conversely, for the MnCoCrCuFeNi composition, an increase in the cold spray temperature leads to a decrease in the friction coefficient.

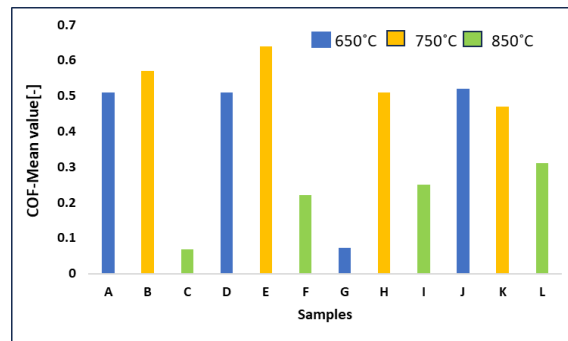


Figure 5. Coefficients of Friction (mean value) of coating samples.

4. Conclusion

The microstructure, roughness, hardness properties, and wear results of Al_{0.1}-0.5(Mn) CoCuCrFeNi High Entropy Alloy (HEA) coatings deposited on a magnesium substrate using nitrogen as the process gas at three different temperatures were examined. Vacuum annealing was conducted in a batch furnace at a pressure of 0.05 bar for a duration of 1.0 hour at a temperature of 600 degrees Celsius. The findings from this study allow for the following conclusions to be made. According to the experimental data collected, it cannot be inferred that the roughness of the coating is affected by the chemical composition of the high entropy alloy. The chemical composition of a coating has a notable impact on its microhardness. There is a clear trend of increasing microhardness as the aluminum content in the samples rises.

5. Acknowledgement

The research mentioned here is funded by the European Commission, REA through its Marie Skłodowska Curie European Individual Fellowship to one of the authors (SÖ), [Project No: 101018482] (Nov. 2021-Oct. 2023), which is gratefully acknowledged.

This publication is also part of the project PNRR-NGEU which has received funding from the MUR-DM117/2023 for one of the writers (MD), [Project No: MUR DM 117/Tsubaki Nakashima – Recovery, reuse and reduction of waste sludge in the production of balls and rolls for rolling bearings] (Nov. 2023-Oct. 2026), which is gratefully acknowledged.

This publication is finally part of the project PNRR-NGEU which has received funding from the MUR-DM352/2023 for one of the writers (NS), [Project No: MUR DM 352/TN Italy – Ceramic coatings for the production of balls for hybrid bearings] (Nov. 2022- Oct. 2025), which is gratefully acknowledged.

The following are also thanked for their contribution to the experimental part: Dr. Brendan Twamley of TSBI, TCD (XRD), Mr. John Fitzgerald of NHTC of Ireland, Robert Dunbar (OM, metallography, sample preparation), TCD workshop personnel (sample cutting, machining), Giacomo Cappelli (help in CS tests).

6. Reference

- [1] Raffaella S, Nazanin S, Luca C, Sedat Oz, Rocco L, Francesco A 2024 *Cold spray HEA coating surface microstructural characterization and mechanical testing* **21** 100540.
- [2] B.S. Murty, S. Ranganathan, J.W. Yeh 2014 *High-Entropy Alloys*, ButterworthHeinemann, Burlington, Web.
- [3] Ming-Hung Tsai, Jien-Wei Yeh, 2014 *High-entropy alloys: a critical review*, *Mater. Res. Lett.* **2** (3).
- [4] Shuo Yin, Wenya Li, Bo Song, Xingchen Yan, Min Kuang, Yaxin Xu, Kui Wen, Rocco Lupoi, 2019 *Deposition of FeCoNiCrMn high entropy alloy (HEA) coating via cold spraying*, *J. Mater. Sci. Technol.* **6** 1003–1007. Web.
- [5] Roghayeh Nikbakht, Mohammad Saadati, Taek-Soo Kim, Mohammad Jahazi, Hyoung Seop Kim, Jodoin Bertrand 2021 *Cold spray deposition characteristic and bonding of CrMnCoFeNi high entropy alloy*, *Surf. Coating. Technol* 127748. Web.
- [6] Jian Wu, Yujie Chen, Heguo Zhu 2022 *A review on the tribological performances of high-entropy alloys*, *Adv. Eng. Mater.* **8** 2101548. N/a. Web.
- [7] Dawei Luo, Qing Zhou, Zhuobin Huang, Yulong Li, Yulin Liu, Qikang Li, Yixuan He, Haifeng Wang 2022 *Tribological behavior of high entropy alloy coatings: a review*, *Coatings* **12** (10) 1428. Web.
- [8] Gifty, Oppong Boakye, et al. 2022 *Microstructural properties and wear resistance of FeCr-Co-Ni-Mo-based high entropy alloy coatings deposited with different coating techniques*, *Appl. Sci.* **12** (6) 3156.

- [9] Jiayi Xia, Dongqun Xin, Xizhang Chen, Heyang Xin 2022 *Investigation of the microstructure and friction mechanism of novel CoCrCu_{0.2}FeMox high-entropy alloy coating using plasma arc cladding*, *Met. Corros.*
- [10] D.B. Miracle, O.N. Senkov 2017 *A critical review of high entropy alloys and related concepts*, *Acta Mater.* **122** 448–511. Web.
- [11] Yong Zhang, Ting Ting Zuo, Zhi Tang, Michael C. Gao, Karin A. Dahmen, Peter K. Liaw, Zhao Ping Lu 2014 *Microstructures and properties of high-entropy alloys*, *Prog. Mater. Sci.* **61** 1–93. Web.
- [12] M.A. Hemphill, T. Yuan, G.Y. Wang, J.W. Yeh, C.W. Tsai, A. Chuang, P.K. Liaw 2012 *Fatigue behavior of Al_{0.5}CoCrCuFeNi high entropy alloys*, *Acta Mater.* **60** 5723–5734.
- [13] C.J. Tong, M.R. Chen, J.W. Yeh, et al. 2005 *Mechanical performance of the Al_xCoCrCuFeNi high-entropy alloy system with multiprincipal elements*, *Metall. Mater. Trans. A* **36** 1263–1271.
- [14] Yongming Zou, Zhaoguo Qiu, Chunjie Huang, Dechang Zeng, Rocco Lupoi, Nannan Zhang, Shuo Yin 2022 *Microstructure and tribological properties of Al₂O₃ reinforced FeCoNiCrMn high entropy alloy composite coatings by cold spray*, *Surf. Coat. Technol.* **434** 128205. Web.
- [15] Jien-Min Wu, Su-Jien Lin, Jien-Wei Yeh, Swe-Kai Chen, Yuan-Sheng Huang, HungCheng Chen 2006 *Adhesive wear behavior of Al_xCoCrCuFeNi high-entropy alloys as a function of aluminum content*, *Wear* **261** (5–6) 513-19. Web.
- [16] Jin-Kun Xiao, Hong Tan, Yu-Qing Wu, Juan Chen, Chao Zhang 2020 *Microstructure and wear behavior of FeCoNiCrMn high entropy alloy coating deposited by plasma spraying*, *Surf. Coat. Technol.* **385** 125430. Web.
- [17] Baosen Zhang, Yaqiu Yu, Shuaishuai Zhu, Zhijia Zhang, Xuwei Tao, Zhangzhong Wang, Bin Lu 2022 *Microstructure and wear properties of TiN–Al₂O₃–Cr₂B multiphase ceramics in-situ reinforced CoCrFeMnNi highentropy alloy coating*, *Mater. Chem. Phys.* **276** 125352. Web.
- [18] S.S. Liu, M. Zhang, G.L. Zhao, X.H. Wang, J.F. Wang 2022 *Microstructure, and properties of ceramic particle reinforced FeCoNiCrMnTi high entropy alloy laser cladding coating*, *Intermetallics* **140** 107402. Web.
- [19] Shuaishuai Zhu, Yaqiu Yu, Baosen Zhang, Zhijia Zhang, Xiao Yan, Zhangzhong Wang 2020 *Microstructure and wear behaviour of in-situ TiN–Al₂O₃ reinforced CoCrFeNiMn high-entropy alloys composite coatings fabricated by plasma cladding*, *Mater. Lett.* **272** 127870. Web.
- [20] S. Ozbilen, R. Lupoi 2023 *Al_{0.5} HEA Protective Coatings on Mg Based Parts by Mechanical Alloying, Cold Spraying and Argon Annealing*.
- [21] S. Yin, R. Lupoi, C. Chen 2019 *Property enhancement of cold sprayed Al-diamond MMC coating by using core-shelled diamond reinforcements*, *Proc. Int. Therm. Spray Conf* **2019** 469–475.
- [22] S. Ozbilen, J.F.B. Vasquez, W. Abbott, S. Yin, M. Morris, R. Lupoi 2023 *Mechanical milling, characterization, and phase prediction of Al_{0.1-0.5}(Mn)CoCrCuFeNi HEA powder feedstock for cold spray deposition processing*, under revision 1708