

The impregnation of mesoporous silica with diaminohexane by means of supercritical CO₂: A possible CO₂ solid sorbent

Original

The impregnation of mesoporous silica with diaminohexane by means of supercritical CO₂: A possible CO₂ solid sorbent / Gallo, Marta; Ronchetti, Silvia; Onida, Barbara; Manna, Luigi. - In: JOURNAL OF CO₂ UTILIZATION. - ISSN 2212-9820. - 101:(2025). [10.1016/j.jcou.2025.103207]

Availability:

This version is available at: 11583/3002550 since: 2025-08-25T21:10:41Z

Publisher:

Elsevier

Published

DOI:10.1016/j.jcou.2025.103207

Terms of use:

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

Publisher copyright

(Article begins on next page)



The impregnation of mesoporous silica with diaminoethane by means of supercritical CO₂: A possible CO₂ solid sorbent

Marta Gallo ^{*} , Silvia Ronchetti, Barbara Onida, Luigi Manna

Dipartimento di Scienza Applicata e Tecnologia, Politecnico di Torino, Corso Duca Degli Abruzzi, 24, Torino 10129, Italy

ARTICLE INFO

Keywords:

Sorbents
CO₂ capture
Supercritical CO₂
Amine
Silica

ABSTRACT

Among solid sorbents, silica is particularly interesting thanks to its stability and versatility. With this in mind, we developed a silica sorbent impregnated with amino groups to increase its ability to capture CO₂. A commercial mesoporous silica (type SBA-15) was impregnated with a diamine (diaminoethane) by using supercritical CO₂ as a green solvent. The so obtained sorbent was physico-chemically characterized and its adsorption behavior was investigated by means of volumetric isotherms at room temperature (and data were fitted by Langmuir models) and *in situ* Fourier Infrared Spectroscopy. The results prove that the impregnation with supercritical CO₂ is effective and the resulting material is able to capture CO₂. Although the CO₂ capture capacity value of the impregnated material is comparable to that of the pristine one (0.89 mmol/g and 0.94 mmol/g, respectively, at 25 °C), the impregnated sorbent is significantly more efficient in capturing CO₂ at low pressure. Chemisorption and, secondary, physisorption are observed. Both phenomena are reversible at room temperature, allowing an easy regeneration of the sorbent. The material, moreover, is stable also at higher temperature, proving to be compatible with thermal regeneration processes. Finally, Langmuir modeling indicates a dual-site behavior, with stronger adsorption sites attributed to amines, and weaker sites attributed to silica.

1. Introduction

As it is already well known, CO₂ is a greenhouse gas and its concentration has dramatically increased since the Industrial Revolution, passing from 280 ppm to more than 420 ppm in recent years [1]. The resulting climate changes are already affecting millions of people around the world, and the effects will be even more severe if the causes of climate change are not drastically reduced [2].

The envisaged long-term solutions include a drastic cut in CO₂ emissions, involving a radical change in many of the current paradigms (of production, of life...). In the meantime, transition solutions are sought for.

Among these, the recovery of CO₂ is widely investigated. The currently adopted strategy is the so-called wet-scrubbing with liquid amines, where amine solutions interact with gaseous CO₂ through acid-base reactions forming species highly soluble in solution, so depleting the gas stream of CO₂ [3]. This process is highly selective and effective; however, the regeneration of the amine solution is high energy demanding since it takes place at 100–140 °C [4]. If accidentally released, amines can cause adverse effects on human health and the

environment [5]. Moreover, amine solutions are highly corrosive, and their use induces elevated maintenance costs [6]. Finally, amines easily undergo oxidative degradation, a phenomenon that gradually decreases the efficiency of the wet-scrubbing process [6].

To overcome these limitations, alternative strategies are currently studied. A promising alternative is offered by solid sorbents, since these are easy to produce, to regenerate, and to handle. Among solid sorbents, the most studied ones are activated carbons, zeolites, metal-organic frameworks (MOF), and porous silica [7].

Although being efficient in CO₂ removal and requiring lower regeneration energies than liquid amines, also the solid sorbents present some drawbacks. In particular, activated carbons suffer from a strong variability of properties depending on their precursor material; moreover, their regeneration often requires high heat [8]. MOF are costly and difficult to produce on large scale [8]. Zeolites have an adsorption efficiency that decreases in the presence of moisture and impurities in gas feed [9], and have low selectivity [10]. Porous silica, being less prone to these limitations, represents a valid alternative. To increase the ability (kinetics, selectivity...) of silica to capture CO₂, a possible strategy is to functionalize it with functional groups that can chemically interact with

* Corresponding author.

E-mail address: marta.gallo@polito.it (M. Gallo).

<https://doi.org/10.1016/j.jcou.2025.103207>

Received 23 February 2025; Received in revised form 16 August 2025; Accepted 20 August 2025

Available online 23 August 2025

2212-9820/© 2025 The Author(s). Published by Elsevier Ltd. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

CO₂, such as amines.

In the present study, we used a commercial mesoporous silica (SBA-15) as a support and we selected a di-amine, diamino-hexane (DH), as functionalizing agent. It is worth mentioning that, based on the literature on amino-modified mesoporous silica [11], it is known that two amino groups are necessary to form carbamate species by interaction with one CO₂ molecule. In this sense, we selected on purpose a diamine with an alkyl chain long and flexible enough to fold and ideally interact with CO₂ with both its amine groups. In addition, previous studies report that the energy barrier for the reaction between CO₂ and amines, which is a key factor affecting CO₂ adsorption, is favorably lower for amines with longer alkyl chain (up to six carbon atoms, such as DH [12,13]). Finally, compared to other amines, DH has advantages such as lower price and higher boiling point [14]; moreover, DH solutions have been already proved promising for CO₂ capture [15]. Although these advantages, few studies are present in the literature about its use for CO₂ capture either in form of liquid amine solution [15] or as a functionalizing agent. The few examples of CO₂ sorbents functionalized with DH are limited to volcanic tuff [13], multi-walled carbon nanotubes (MWCNTs) [14] and silica [16]. However, in all these studies, the sorbent preparation requires the use of polluting solvents, such as methanol [16], and preliminary treatments, such as activation [13] or oxidation [14], which involve energy consumption (treatment at 50–90 °C [13, 14]) as well as time consumption (up to 24 h [14]).

The innovative approach presented in this work consists in using supercritical CO₂ (scCO₂) as a solvent for the functionalization process, thus avoiding the use of polluting organic solvents and offering a relatively simple alternative. To the authors' knowledge, this is the first time that a DH-functionalized silica sorbent is obtained by impregnation with scCO₂.

The DH-functionalized sorbent obtained by scCO₂ impregnation, as well as the reference pristine silica, were characterized in terms of physico-chemical properties and their efficacy in adsorbing CO₂ was studied by means of volumetric isotherms at room temperature. The so obtained data were regressed by Langmuir models (Single-Site and Dual-Site). Moreover, the interaction between the sorbent surface and CO₂ molecules was analyzed by means of *in situ* IR spectroscopy.

2. Materials and methods

For the synthesis and characterization of the samples the following chemicals were used (as received): mesoporous silica SBA-15 with pore size 8 nm (Sigma Aldrich, Burlington, MA, USA), 1,6-diamino-hexane (C₆H₁₆N₂, DH) in powder (Sigma Aldrich, Burlington, MA, USA), ethanol (absolute ethanol, for analysis, Merck, Darmstadt, Germany). According to the producer, the properties of DH are: MM = 116.20 g/mol, T_f = 39–42 °C, T_b = 199–204 °C, density = 0.83 cm³/g at 60 °C.

For the functionalization process, a physical mixture of DH (21 mg) and silica (200 mg) in a proportion of 50 mmol DH/mol SiO₂ (chosen on the base of a previous work [17]) was manually prepared. The mixture was poured in a package made of filter paper and placed in a glass vial disposed in a 40 mL stainless steel vessel (with an internal diameter of 14 mm). The vessel was filled with liquid CO₂; temperature and pressure were adjusted to 40 °C and 200 bar, to overcome the critical point of CO₂. In these conditions, CO₂ acted as a solvent dissolving DH. The mixture was kept at these temperature and pressure for 2 h to allow the dissolution of DH and its diffusion in the porosity of silica. Then, pressure was slowly release (around 5 mL/min) and CO₂ passed from supercritical to gaseous state; once below the critical point, the solubility of DH in CO₂ rapidly decreased and DH precipitated on the spot (i.e., inside the silica). Finally, the vessel was left to naturally cool down.

For comparison, a further adsorbent was obtained by traditional impregnation (incipient wetness impregnation). For this purpose, a solution of ethanol (1.5 mL) and DH (47 mg) was prepared; 0.66 mL of it were administered to 200 mg of silica (SBA-15 with pore size 8 nm). Then, the solvent was let to evaporate. At the end of the loading process,

21 mg of DH were theoretically added to 200 mg of silica.

The amine-impregnated samples, as well as the pristine silica (as a reference) were analyzed as follow.

Thermogravimetric (TGA) analyses were carried out using a Setaram TGA (Caluire, France) by heating the samples between 20 °C and 600 °C with a heating rate of 10 °C/min in air flow. An isotherm test was carried out for assessing the thermal stability of the specimens (inspired by [18]): samples were heated at 10 °C/min in air flow until they reached 120 °C and then they were left at a constant temperature of 120 °C for 1 h.

X-Ray diffraction (XRD) data were collected using an Empyrean (Cu K α radiation, Malvern Panalytical, Almelo, The Netherlands), at 40 kV and 40 mA, with a solid-state detector (PIXcel1D). Measurements were performed at low ($2\theta = 0.7^\circ$ – 5°) and high angles ($2\theta = 5^\circ$ – 60°).

FTIR spectra were recorded at a resolution of 2 cm⁻¹ on pelletized powders using an Equinox 55 spectrometer (Bruker, Billerica, MA, USA) after outgassing the sample at room temperature (residual pressure of 0.1 Pa).

Nitrogen adsorption-desorption isotherms were acquired using an ASAP 2020 Plus analyzer (Micromeritics, Norcross, GA, USA). Samples were outgassed at 70 °C in a nitrogen atmosphere at a pressure of 10 mmHg for 3 h. The surface area was calculated using the Brunauer–Emmett–Teller (BET) method [19], and pore volume using the Barrett–Joyner–Halenda (BJH) method [20], using desorption isothermal data.

Volumetric adsorption of CO₂ was evaluated with the same instrument used for nitrogen isotherms. In this case, samples were outgassed at 120 °C for 2 h and the measures were carried out at 25 °C. Two runs of measurement were carried out, with a 1 h outgassing at room temperature between the first and the second run.

In situ FTIR analyses were performed exposing the samples at different CO₂ equilibrium pressures at room temperature. The samples were outgassed beforehand at 120 °C for 2 h. At the end of the test the samples were outgassed at room temperature (under vacuum) for 5 min and a final FTIR spectrum was acquired.

3. Results

Fig. 1 reports FTIR spectra of the pristine silica, SBA_{ref}, and the sample functionalized with diamino-hexane, SBA_{DH}. The spectrum of the reference material presents bands typical of amorphous silica, i.e. a narrow band above 3700 cm⁻¹, mainly due to free terminal silanols, and a broad band between 3300 and 3600 cm⁻¹, due to silanols mutually interacting by H-bond. The spectrum of the functionalized sample is significantly different, with no band due to free terminal silanols. Moreover, the appearance of new bands is noted. Specifically, two peaks at about 3300 cm⁻¹, due to -NH₂ stretching modes, a band at about 1600 cm⁻¹, due to the -NH₂ bending mode, and two bands in the range

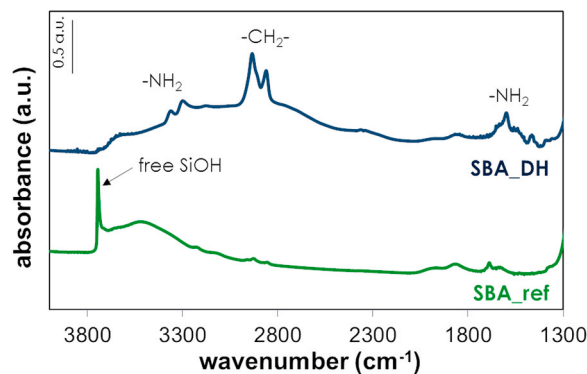


Fig. 1. FTIR spectra of the reference sample, SBA_{ref}, and the functionalized sample, SBA_{DH}.

2800–2900 cm⁻¹, ascribed to -CH₂- stretching modes [21]. Furthermore, a broad absorption between 2500 and 3600 cm⁻¹ is observed, to which the stretching modes of -NH₂ and -CH₂- are superimposed. This absorption is ascribed to the stretching mode of silanols engaged in H-bonding with -NH₂ groups of adsorbed diamino-hexane molecules [22].

The mass losses recorded by means of TGA are reported in Fig. 2. Below 150 °C SBA_ref loses 2.0 wt% due to evaporation of physisorbed water, while the mass loss between 150 °C and 600 °C is 1.3 wt% and can be ascribed to the condensation of silanols [23]. SBA_DH loses 4.5 wt% of water below 150 °C and 12.5 wt% between 150 °C and 600 °C. This latter mass variation can be attributed to the degradation of the incorporated amine and, at the same time, to the condensation of silanols. Considering the contribution due to silanols condensation equal to that measured on the pristine silica (1.3 wt%), the weight loss due to the amines degradation turns out to be 11.2 wt%.

Textural properties of the samples were assessed by nitrogen adsorption at 77 K. The main results are reported in Fig. 3 and Table 1. Both the reference and the functionalized sample present type IV isotherm, with H1 hysteresis loop typical of mesoporous materials with ordered and uniform cylindrical pores (Fig. 3A) [24]. This is confirmed by the narrow pore diameter distribution, obtained according to the BJH model [20] and reported in Fig. 3B. After functionalization, the specific surface area, the pore volume, and the average pore diameter decrease, as reported in Table 1, but the pore distribution remains narrow. These results are coherent with a uniform functionalization of the inner pore walls, without relevant pore blocking phenomena [25].

SBA_DH was compared to a sorbent obtained by a traditional impregnation technique (i.e., incipient wetness impregnation – IWI). The two samples were prepared using the same initial quantities of silica and DH, so to have the same nominal content of diamine. The textural properties and the measured DH-content of the sorbent obtained by IWI (Table A.1) were less apt to adsorption than those of SBA_DH, therefore the CO₂ adsorption tests were carried out only on the SBA_DH sample.

CO₂ adsorption performances were evaluated by volumetric adsorption isotherms at 25 °C (RT). For each sample two consecutive runs were performed; a 1-hour outgas at room temperature was carried out between the first and the second run to remove the species reversibly adsorbed. The resulting isotherms are reported in Fig. 4A and B for SBA_DH and SBA_ref, respectively. In both cases, the two runs are almost completely superimposed, suggesting that the adsorption phenomena are reversible on both samples.

A direct comparison of the first run on SBA_ref and SBA_DH is reported in Fig. 4C: although both curves reach roughly the same maximum adsorbed value (0.94 mmol/g for SBA_ref and 0.89 mmol/g for SBA_DH), they display a significantly different trend. The isotherm of SBA_DH is characterized by a downward concavity and a drastic increase of CO₂ adsorption in the lowest pressure range (Fig. 4D). Moreover, for pressures lower than approximately 700 mbar, SBA_DH shows

a higher CO₂ adsorption than SBA_ref at the same equilibrium pressure.

All experimental data were fitted to adsorption isotherm models using the least squares method. In the case of the pure silica sample, SBA_ref (Fig. 5B), the classical Single-Site Langmuir equation [26] provided an excellent fit to the experimental data, with an adjusted R-squared of 0.9997 and a percent Average Absolute Relative Deviation (AARD%) of 2.8 %. The equation applied was:

$$n_{\text{ads}} = (n_{\text{max}} \cdot K \cdot P) / (1 + K \cdot P) \quad (1)$$

where n_{ads} is the amount of CO₂ adsorbed (mol), n_{max} is the monolayer adsorption capacity (mol), K is the Langmuir equilibrium constant (mbar⁻¹), and P is the equilibrium pressure (bar).

For the functionalized sample, SBA_DH (Fig. 5A), the experimental data were fitted to several of the most widely used three- and four-parameter isotherm models reported in the literature. The three-parameter models of Sips [27], Redlich–Peterson [28], and Radke–Prausnitz [29], which describe intermediate adsorption behavior between the Langmuir and Freundlich isotherms, produced similar performance, each with an AARD% of approximately 5 %. The Toth model [30] yielded a slightly higher AARD% value of 7.7 %. Slight improvements were observed using the four-parameter Marczewski–Jaroniec model [31], which extends the Toth equation to account for broader energetic heterogeneity among adsorption sites, achieving an AARD% of approximately 5 %. The purely empirical four-parameter model proposed by Fritz–Schlunder [32] provided comparable results.

The best fit to the experimental data was obtained using a Dual-Site Langmuir model [26,33], which achieved an AARD% of 2.7 %. The applied equation is given as:

$$n_{\text{ads}} = (n_{\text{max}} \cdot K \cdot P) / (1 + K \cdot P) + (n'_{\text{max}} \cdot K' \cdot P) / (1 + K' \cdot P) \quad (2)$$

where n_{max} and K refer to the maximum adsorption capacity and equilibrium constant for the first type of adsorption site, and n'_{max} and K' refer to those for the second site.

It is worth noting that the Langmuir model is of particular interest, since it provides additional evidence regarding the properties of the material (i.e., number of adsorbing sites, strength of interaction).

As shown in Fig. 5, the fitted curves (light blue and light green lines in Figs. 5A and 5B, respectively) match the experimental data (dotted lines) very well. The corresponding values of the optimized parameters, adjusted R-squared, AARD%, and Root Mean Square Deviation (RMSD) between experimental and fitted data are summarized in Table 2.

The interaction between CO₂ and the samples was studied through *in situ* FTIR spectroscopy. Fig. 6 shows the difference spectra, related to increasing CO₂ equilibrium pressures, obtained by subtracting to each spectrum the one recorded prior to CO₂ adsorption (i.e., spectra reported in Fig. 1). Moreover, the spectrum recorded after outgassing (under vacuum) at room temperature to remove the adsorbed CO₂ is also reported (dashed curve, “degas”).

In the SBA_ref spectra, a peak appears at around 2340 cm⁻¹ and its intensity increases with increasing CO₂ pressure (Fig. 6). This peak is due to molecular CO₂ [34], which is physisorbed on the silica surface through weak interactions. When SBA_ref is outgassed at room temperature, this peak disappears (dashed line in Fig. 6), confirming that the physisorption phenomenon is completely reversible at room temperature.

At variance with SBA_ref, in the case of SBA_DH, besides the band due to molecular CO₂, new bands appear in the range 1500–1600 cm⁻¹ (inset in Fig. 6). These can be attributed to the formation of carbamates [11,35] caused by the chemical interaction between the basic amine groups of DH and the acid CO₂. Chemisorption of CO₂ forming carbamates is also reversible at room temperature and the outgassing is sufficient to desorb CO₂ (dashed line in the inset of Fig. 6).

Even though the adsorption of CO₂ was reversible at room temperature, for sake of completeness, in view of a possible thermal regeneration of the adsorbent, the thermal stability of the functionalised sample

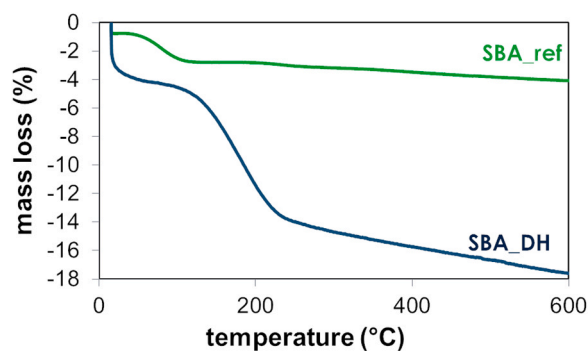


Fig. 2. Thermogravimetric curves of the reference sample, SBA_ref, and the functionalized sample, SBA_DH.

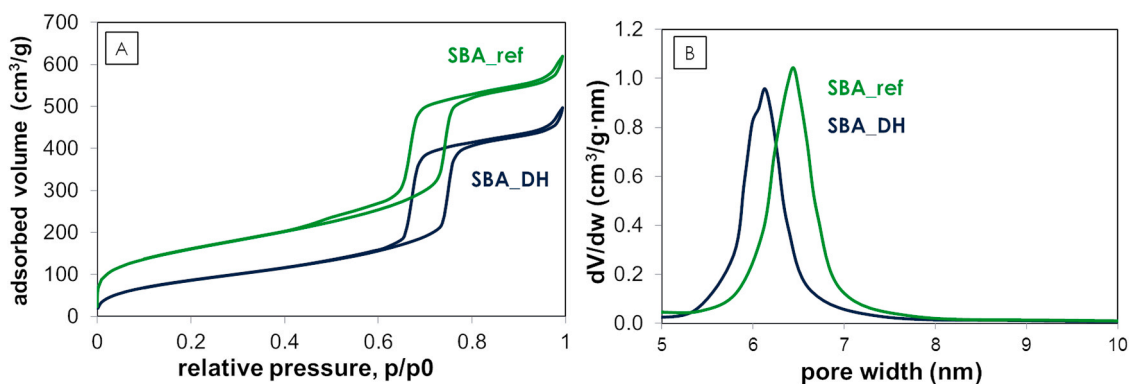


Fig. 3. Nitrogen adsorption isotherms (A) and pore size distribution (BJH model) (B) of the reference sample, SBA_ref, and the functionalized sample, SBA_DH.

Table 1

Textural properties of the reference sample, SBA_ref, and the functionalized sample, SBA_DH.

	SBA_ref	SBA_DH
Specific surface area (m ² /g)	570	330
Pore volume (cm ³ /g)	0.9	0.7
Average pore diameter – BJH (nm)	6.4	6.1

was assessed with an isothermal thermogravimetry test at 120 °C for 1 h. The results, reported in Fig. 7, reveal that, after an initial mass loss due to the desorption of physisorbed water, the sample is stable and only a negligible mass loss (0.5 wt%) takes place for the whole duration of the test.

4. Discussion

The characterization analyses prove that the amine is successfully incorporated by means of scCO₂ on the silica support. The presence of DH is testified by FTIR spectra (Fig. 1), where the functional groups typical of DH (-NH₂ and -CH₂-) are clearly visible. FTIR also suggests H-bond interactions between silica and DH (coherent with the broad band between 2500 and 3600 cm⁻¹). Together with data from nitrogen sorption isotherms, this evidence strongly suggests that DH molecules are homogeneously distributed on the silica surface of the inner pore wall. As expected, the SSA and the pore volume of the functionalized sample are lower than those of the reference specimen. Nevertheless, SBA_DH still presents an isotherm typical of mesoporous materials, with SSA, pore volume, and pore diameter suitable to the final application. The amount of DH experimentally measured by TGA (11.2 wt%, Fig. 2)

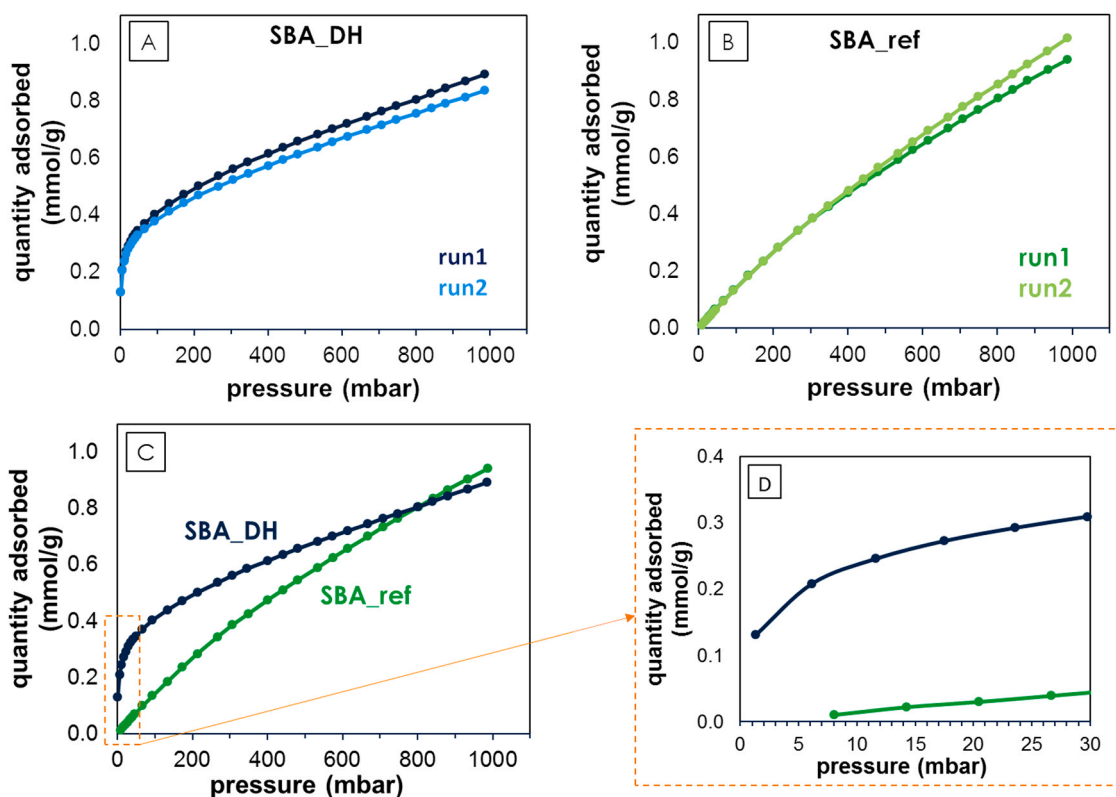


Fig. 4. Volumetric CO₂ adsorption isotherms at RT of the functionalized sample, SBA_DH (A), and the reference sample, SBA_ref (B), and the comparison of the two (C) with a zoom on the lowest pressures range (D).

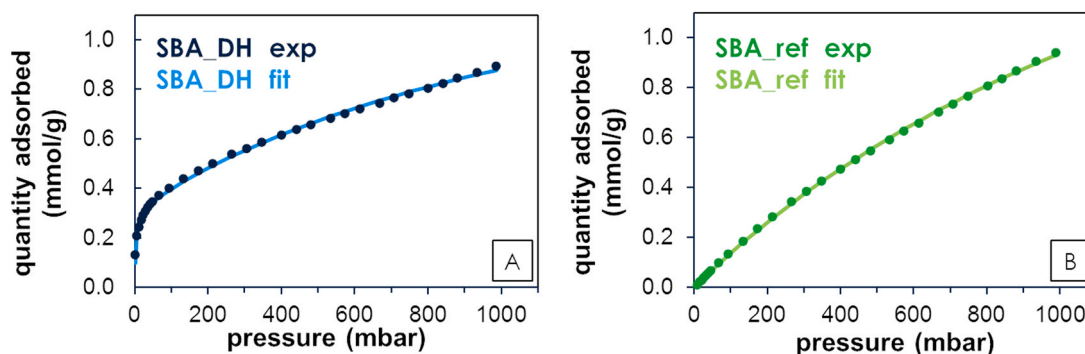


Fig. 5. Fitting of the volumetric CO₂ adsorption curves of the functionalized sample, SBA_DH (A), and the reference sample, SBA_ref (B).

Table 2

Fitting parameters of the volumetric CO₂ adsorption isotherms.

	n_{\max} (mmol/g)	K (mbar ⁻¹)	n'_{\max} (mmol/g)	K' (mbar ⁻¹)	adjusted R-squared	AARD% (%)	RMSD (mmol/g)
SBA_ref	2.69	$5.34 \cdot 10^{-4}$	-	-	0.9997	2.8	0.006
SBA_DH	1.35	$7.22 \cdot 10^{-4}$	0.315	0.332	0.9976	2.7	0.011

is very close to the nominal one (10 wt%), suggesting that the loading technique prevents loss of the functionalizing agent. On the overall, the physico-chemical properties of SBA_DH are more favorable than those of a similar sorbent obtained with a traditional impregnation technique (Table A.1), supporting the interest of the alternative approach proposed in this work.

Adsorption isotherms show that SBA_DH is able to adsorb CO₂ at room temperature. For high CO₂ pressure its adsorption capacity is comparable to that of the reference material (Fig. 4). However, it is worth underlining that, at low CO₂ pressure, the amount adsorbed by SBA_DH is significantly higher than that of SBA_ref: for example, at around 100 mbar SBA_ref adsorbs 0.1 mmol/g, while SBA_DH adsorbs 0.4 mmol/g (Fig. 4C). In particular, the concavity of the volumetric isotherms suggests a specific interaction between SBA_DH and CO₂ (Fig. 4A), which, however, is completely reversible at room temperature (since run 2 overlaps run 1 in volumetric measurements). These observations are confirmed by *in situ* FTIR measurements. When SBA_ref is in contact with increasing amounts of CO₂ it only interacts through weak interactions that result in the physisorption of molecular CO₂ on the silica surface. On the other hand, when SBA_DH is in contact with CO₂, the amine groups interact with CO₂ also through the formation of new chemical species (i.e., carbamates) inducing a chemisorption

phenomenon already at low pressure. Although the interaction between SBA_DH and CO₂ is due to chemical bonds (at least partially), the adsorption phenomenon is reversible at room temperature. It may be surprising, but, as reported in the literature, carbamate formation may be reversible even at room temperature in some conditions (such as when applying vacuum [36,37]). In the present case, indeed, an out-gassing at room temperature for a few minutes is sufficient for the adsorbent regeneration, coherently with what observed in the volumetric tests.

It is worth noting that the reversibility of the adsorption phenomena on SBA_DH is coherent with the lack of any CO₂ residue on the samples after the scCO₂ impregnation. This result further confirms the validity of the scCO₂ impregnation: after the impregnation process, the active sites are free, and no further treatments are necessary to make them available to interact with CO₂.

The fitting of the volumetric isotherms with a Langmuir model supports the outcomes of the *in situ* FTIR tests. In the case of SBA_ref a simple single-site Langmuir model well fits the experimental data, indicating that one type of interaction occurs between the surface of the silica and CO₂ molecules, i.e., the physisorption in the linear molecular form observed by *in situ* FTIR characterization (Fig. 6A). In the case of SBA_DH, instead, a Dual-Site Langmuir model is necessary: the weak interaction between silica and CO₂, as observed for SBA_ref, is represented by the first site (n_{\max} and K), while the amine groups, which interact with CO₂ forming carbamate species, are represented by the second site (n'_{\max} and K'). Indeed, the K parameters of the SBA_ref

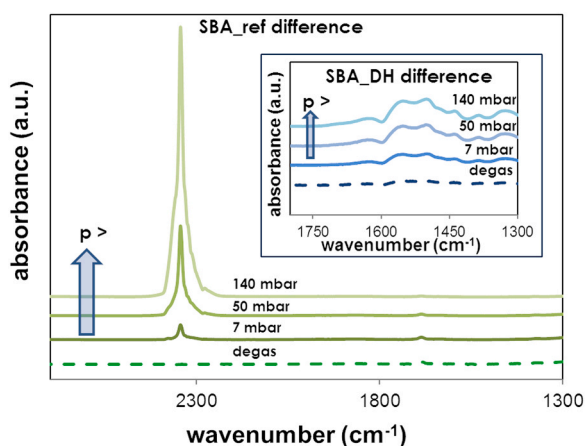


Fig. 6. *In situ* FTIR difference spectra at different CO₂ pressures for the reference sample, SBA_ref, and the functionalized sample SBA_DH (inset).

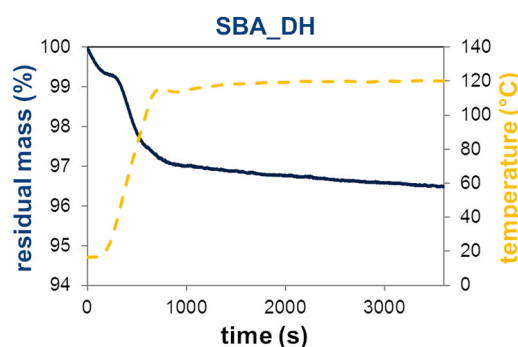


Fig. 7. Thermogravimetric curve of the functionalized sample, SBA_DH, for in isotherm treatment at 120 °C.

Table 3

Comparison of the CO₂ adsorption capabilities exhibited by SBA_DH and comparable materials.

sample	DH content (wt%)	Adsorption T (°C)	CO ₂ capture (mmol/g)	Reference
Volcanic tuff + DH	70	25	0.98	[13]
SBA + DH	30	45	1.24	[16]
SBA + DH	10	25	0.89	this work

Langmuir equation ($K = 5.34 \cdot 10^{-4} \text{ mbar}^{-1}$, Table 2) and of the first site of SBA_DH Dual-Site Langmuir equation ($K = 7.2 \cdot 10^{-4} \text{ mbar}^{-1}$, Table 2) are comparable, indicating that the strength of the interaction is similar for the two adsorbing sites. However, n_{max} for SBA_ref is higher than that of SBA_DH ($n_{\text{max}} = 2.69 \text{ mmol/g}$ and $n_{\text{max}} = 1.35 \text{ mmol/g}$, respectively, Table 2), coherently with its higher SSA (Table 1). Interestingly, the ratio between the two values, which represent the total amount of adsorbing sites, is very close to the ratio between the SSA values of the two adsorbents.

Regarding the second site obtained for SBA_DH by the Dual-Site Langmuir model, it is worth noting that its equilibrium constant, K' (0.33 mbar^{-1}), is significantly higher than that of the first site K ($7.2 \cdot 10^{-4} \text{ mbar}^{-1}$) coherently with the fact that this second site is responsible for the chemical interaction forming carbamate. The total amount of sites, n'_{max} , turns out to be 0.315 mmol/g from the Langmuir equation; this value can be compared to the total amount of DH in the adsorbent.

Considering the nominal value of DH content, which is 10 wt%, this corresponds to 0.830 mmol/g .

The nominal total amount of DH, expressed in mmol of DH per gram of adsorbent, is higher than n'_{max} , which, according to the Dual-Site Langmuir model, indicates the maximum amount adsorbed on the stronger adsorbing sites, which are considered responsible for the carbamate formation. This is not surprising if one takes into account at least two considerations. First, based on the literature [11], we should expect that both the amino groups of the DH molecule interact with one CO₂ molecule to form the carbamate species. This involves that the adsorbing DH molecule is in a suitable configuration, which cannot be the case for all the molecules on the silica surface. The second consideration regards the evidence of H-bonding between the surface silanols and the amino groups. It cannot be ruled out that this interaction, which involves the nitrogen of the amino group, may partially prevent the nucleophilic attack of the amino group to the CO₂ molecule. Finally, it is worth mentioning that if we consider a partial pressure low enough, such as 7 mbar, only carbamates are observed on SBA_DH by FTIR (Fig. 6). At this pressure, the quantity of CO₂ adsorbed by SBA_DH is 0.2 mmol/g (Fig. 4D) and this is in accordance with the maximum amount identified by the Dual-Site Langmuir model (n'_{max}).

The functionalization of the adsorbent has been obtained by impregnation, and DH molecules interact with the silica surface by means of intermolecular interactions, such as H-bonding and Van der Waals interactions. Nevertheless, the material is compatible with a regeneration through thermal treatment. When heated at a temperature suitable for the thermal regeneration of sorbents [18], such as 120 °C for 1 h, SBA_DH is stable, displaying a negligible mass loss (Fig. 7).

APPENDIX A

Wide-angle XRD patterns (Figure A.1) of both SBA_ref and SBA_DH are characterized by three reflections typical of the 2D hexagonal mesoporous silica SBA-15 [39], i.e. (100) at 2θ equal to 0.88° , (110) at 2θ equal to 1.55° and (200) at 2θ equal to 1.78° . XRD spectra at high angles (Figure A.1B) do not reveal the presence of any crystalline phase, as expected [40].

When comparing these results with those reported in the literature for similar sorbents (Table 3), it is worth noting that silica and tuff samples of previous studies have higher DH contents (30 wt% and 50–70 wt%, [13,16]), but result in adsorption capacities comparable to those obtained in this work ($0.98\text{--}1.24 \text{ mmol/g}$ compared to 0.89 mmol/g of this work). For the present work, an arbitrary amount of DH was incorporated, to prove the feasibility of the scCO₂-impregnation process; nevertheless, higher amounts of DH could be used for future studies. In addition, DH-functionalized sorbents reported in the literature require high-temperature regeneration ($90\text{--}100 \text{ °C}$ [13,14]) and not all of them (in particular MWCNTs) are thermally stable above 100 °C [14]. In conclusion, the material proposed here appears to be a promising starting point for the development of new CO₂ sorbents.

5. Conclusions

The results of this study show that supercritical CO₂ can be used as an alternative green solvent for the functionalization of silica with amino groups. This technique was successfully employed for the first time to the functionalization of silica with diamino-hexane. The final sorbent has a SSA of $330 \text{ m}^2/\text{g}$, an average pore diameter of 6.1 nm and a pore volume of $0.7 \text{ cm}^3/\text{g}$. The content of diamino-hexane is about 10 wt%. The functionalization appears to be homogeneous, and the sorbent is able to capture CO₂ through chemisorption and physisorption, both phenomena being reversible with a simple and rapid outgas at room temperature. The volumetric isotherm of CO₂ at RT is well described by a Dual-Site Langmuir model. Interestingly, the functionalized material is particularly effective in capturing CO₂ at low pressure, opening the way for possible applications in fields such as flue gas treatment and biogas enhancement [38]. Moreover, the sorbent appears to be compatible with thermal regeneration.

Finally, as future perspective, higher amounts of diamino-hexane could be used for functionalizing silica, to explore and better exploit all the capabilities of this new class of CO₂ sorbents.

CRedit authorship contribution statement

Silvia Ronchetti: Writing – review & editing, Validation, Supervision, Resources, Funding acquisition. **Barbara Onida:** Writing – review & editing, Validation, Supervision, Resources, Methodology, Funding acquisition, Conceptualization. **Marta Gallo:** Writing – original draft, Methodology, Investigation, Data curation, Conceptualization. **Luigi Manna:** Writing – review & editing, Resources, Funding acquisition.

Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgements

The authors would like to acknowledge Eng. Francesca Chiofalo for her contribution in the experimental work and Prof. Marco Armandi for the support given for the volumetric and *in situ* FTIR tests.

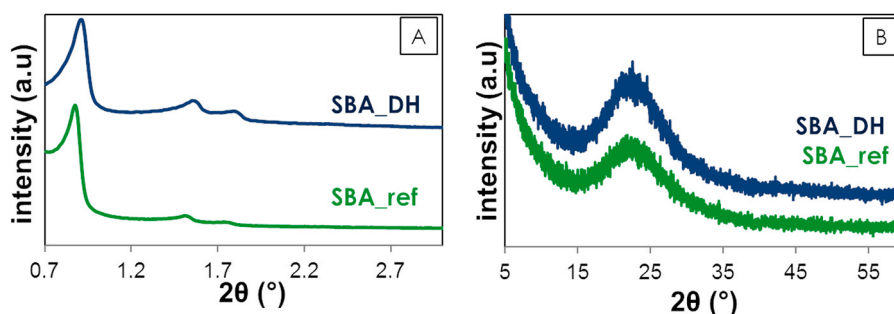


Figure A.1. XRD patterns at low (A) and high (B) angles of the reference sample, SBA_ref, and the functionalized sample, SBA_DH

The main properties of the sample impregnated by incipient wetness impregnation (SBA_DH_IWI) were obtained by nitrogen adsorption and TGA. These data are reported in Table A.1 with those of SBA_DH, as a comparison.

Table A.1

Textural properties and measured DH-content of the sample obtained by IWI, SBA_DH_IWI, and the scCO₂ functionalized sample, SBA_DH

	SBA_DH_IWI	SBA_DH
Specific surface area (m ² /g)	270	330
Pore volume (cm ³ /g)	0.5	0.7
Measured DH-content (%)	8.2	11.2

Data availability

Data will be made available on request.

References

- [1] NOAA (National Oceanic and Atmospheric Administration), Carbon dioxide now more than 50% higher than pre-industrial levels. (www.noaa.gov). 2022.
- [2] Intergovernmental Panel on Climate Change (IPCC), "Sixth Assessment Report (2023)", (<https://www.ipcc.ch/ar6-syr/>) (accessed 19/09/2024).
- [3] J. Hack, N. Maeda, D.M. Meier, Review on CO₂ capture using amine-functionalized materials, ACS Omega 7 (44) (2022) 39520–39530, <https://doi.org/10.1021/acsomega.2c03385>.
- [4] D.-M. D'Alessandro, B. Smit, J.-R. Long, Carbon dioxide capture: prospects for new materials, Angew. Chem. Int. Ed. 49 (2010) 6058, <https://doi.org/10.1002/anie.201000431>.
- [5] V. Gupta, P. Mobley, J. Tanthana, L. Cody, D. Barbee, J. Lee, R. Pope, M. Lail, J. Thornburg, R. Chartier, Aerosol emissions from water-lean solvents for post-combustion CO₂ capture, Int. J. Greenh. Gas. Control 106 (2021) 103284, <https://doi.org/10.1016/j.ijggc.2021.103284>.
- [6] F. Meng, Y. Meng, T. Ju, S. Han, L. Lin, J. Jiang, Research progress of aqueous amine solution for CO₂ capture: a review, Renew. Sustain. Energy Rev. 168 (2022) 112902, <https://doi.org/10.1016/j.rser.2022.112902>.
- [7] A. Samanta, A. Zhao, G.-K.-H. Shimizu, P. Sarkar, R. Gupta, Post-combustion CO₂ capture using solid sorbents: a review, Ind. Eng. Chem. Res. 51 (2012) 1438, <https://doi.org/10.1021/ie200686q>.
- [8] S. Kundu, T. Khandaker, M.A.A.M. Anik, M.K. Hasan, P.K. Dhar, S.K. Dutta, M. A. Latif, M.S. Hossain, A comprehensive review of enhanced CO₂ capture using activated carbon derived from biomass feedstock, RSC Adv. 14 (2024) 29693, <https://doi.org/10.1039/d4ra04537h>.
- [9] E. Pérez-Botella, S. Valencia, F. Rey, Zeolites in adsorption processes: state of the art and future prospects, Chem. Rev. 122 (24) (2022), <https://doi.org/10.1021/acs.chemrev.2c00140>.
- [10] L. Santamaría, S.A. Korili, A. Gil, Layered double hydroxides for CO₂ adsorption at moderate temperatures: synthesis and amelioration strategies, Chem. Eng. J. 445 (2023) 140551, <https://doi.org/10.1016/j.cej.2022.140551>.
- [11] A. Danon, P.C. Stair, E. Weit, FTIR study of CO₂ adsorption on amine-grafted SBA-15: elucidation of adsorbed species, J. Phys. Chem. C. 115 (23) (2011) 11540–11549.
- [12] P. Singh, J.P.M. Niederer, G.F. Versteeg, Structure and activity relationships for amine based CO₂ absorbents, Int J. Greenh. Gas. Control 1 (1) (2007) 5–10, [https://doi.org/10.1016/S1750-5836\(07\)00015-1](https://doi.org/10.1016/S1750-5836(07)00015-1).
- [13] G.-G. Kaya, Diamine functionalized volcanic tuff: a promising CO₂ adsorbent, J. Chem. Technol. Biotechnol. 98 (10) (2023) 2489, <https://doi.org/10.1002/jctb.7474>.
- [14] N.-S. Ardali, S. Riahi, M. Abbasi, N. Mohammadpour, Experimental investigation of carbon dioxide adsorption using functionalized MWCNTs with 1,6-diaminohexane, Fuel 338 (2023) 127213, <https://doi.org/10.1016/j.fuel.2022.127213>.
- [15] P. Singh, D.W.F. Brilman, M.-J. Groeneveld, Solubility of CO₂ in aqueous solution of newly developed absorbents, Energy Procedia 1 (1) (2009) 1257, <https://doi.org/10.1016/j.egypro.2009.01.165>.
- [16] E.-S. Sanz-Pérez, A. Arencibia, R. Sanz, G. Calleja, New developments on carbon dioxide capture using amine-impregnated silicas, Adsorption 22 (2016) 609, <https://doi.org/10.1007/s10450-015-9740-2>.
- [17] R. Girimonte, F. Testa, M. Turano, G. Leone, M. Gallo, G. Golemme, Amine-Functionalized mesoporous silica adsorbent for CO₂ capture in confined-fluidized bed: study of the breakthrough adsorption curves as a function of several operating variables, Processes 10 (2022) 422, <https://doi.org/10.3390/pr10020422>.
- [18] R. Girimonte, F. Testa, M. Gallo, R. Buscieti, G. Leone, B. Formisani, Adsorption of CO₂ on amine-modified silica particles in a confined-fluidized bed, Processes 8 (2020) 1531, <https://doi.org/10.3390/pr8121531>.
- [19] S. Brunauer, P.H. Emmett, E. Teller, Adsorption of gases in multimolecular layers, J. Am. Chem. Soc. 60 (1938) 309–319, <https://doi.org/10.1021/ja01269a023>.
- [20] E.P. Barrett, L.G. Joyner, P.P. Halenda, The determination of pore volume and area distributions in porous substances. I. Computations from nitrogen isotherms, J. Am. Chem. Soc. 73 (1951) 373–380, <https://doi.org/10.1021/ja01145a126>.
- [21] G. Socrates, Infrared and Raman characteristic group frequencies: tables and charts. 2001.
- [22] B. Onida, S. Fiorilli, L. Borello, G. Viscardi, D. Macquarrie, E. Garrone, Mechanism of the optical response of mesoporous silica impregnated with reichardt's dye to NH₃ and other gases, J. Phys. Chem. B 108 (2004) 16617–16620, <https://doi.org/10.1021/jp037094u>, s2-s2.0-8344259898.
- [23] Bergna H.E. The Colloid Chemistry of Silica. Comstock, J., Ed., Advances in Chemistry Series. 1994. 234. American Chemical Society, Washington DC. doi:10.1021/ba-1994-0234.
- [24] M. Thommes, K. Kaneko, A.V. Neimark, J.P. Olivier, F. Rodriguez-Reinoso, J. Rouquerol, K.S.W. Sing, Physisorption of gases, with special reference to the evaluation of surface area and pore size distribution (IUPAC Technical Report), Pure Appl. Chem. 87 (2015) 1051–1069, <https://doi.org/10.1515/pac-2014-1117>.
- [25] M. Castiglioni, L. Rivoira, M. Gallo, I. Ingrand, M. Del Bubba, B. Onida, M. C. Bruzzoniti, Removal of sugars from food and beverage wastewaters by amino-modified SBA-15, J. Clean. Prod. 324 (2021) 129236, <https://doi.org/10.1016/j.jclepro.2021.129236>.
- [26] H. Swenson, N.P. Stadie, Langmuir's theory of adsorption: a centennial review, Langmuir 35 (2019) 5409–5426, <https://doi.org/10.1021/acs.langmuir.9b00154>.
- [27] R. Sips, On the structure of a catalyst surface, J. Chem. Phys. 16 (5) (1948) 490–495, <https://doi.org/10.1063/1.1746922>.
- [28] O. Redlich, D.L. Peterson, A useful adsorption isotherm, J. Phys. Chem. 63 (6) (1959) 1024–10214, <https://doi.org/10.1021/j150576a611>.
- [29] C.J. Radke, J.M. Prausnitz, Thermodynamics of multi-solute adsorption from dilute liquid solutions, AIChE J. 18 (4) (1972) 761–768, <https://doi.org/10.1002/aic.690180418>.
- [30] J. Tóth, State equations of the solid-gas interface layers, Acta Chim. Acad. Sci. Hung. 69 (3) (1971) 311–317.
- [31] A.W. Marczewski, M. Jaroniec, A new isotherm equation for heterogeneous solid surfaces, Pol. J. Chem. 57 (1983) 1093–1103.

- [32] W. Fritz, E.U. Schlunder, Simultaneous adsorption equilibria of organic solutes in dilute aqueous solutions on activated carbon, *Chem. Eng. Sci.* 29 (5) (1974) 1279–1282, [https://doi.org/10.1016/0009-2509\(74\)85020-8](https://doi.org/10.1016/0009-2509(74)85020-8).
- [33] C. Zanzottera, M. Armandi, S. Esposito, E. Garrone, B. Bonelli, CO₂ adsorption on aluminosilicate Single-Walled nanotubes of imogolite type, *J. Phys. Chem. C* 116 (38) (2012) 20417–20425, <https://doi.org/10.1021/jp3061637>.
- [34] M. Pavani Organosilici a mesoporosità controllata per la cattura e la conversione dell'anidride carbonica". MS Thesis. Politecnico di Torino. 2013.
- [35] C. Knofel, C. Martin, V. Hornebecq, P. Llewellyn, Study of carbon dioxide adsorption on mesoporous aminopropylsilane-functionalized silica and titania combining microcalorimetry and in situ infrared spectroscopy, *J. Phys. Chem. C* 113 (2009) 21726–21734, <https://doi.org/10.1021/jp907054h>.
- [36] A.C. Forse, P.J. Milner, New chemistry for enhanced carbon capture: beyond ammonium carbamates, *Chem. Sci.* 12 (2021) 508–516, <https://doi.org/10.1039/D0SC06059C>.
- [37] S. Sircar, Pressure swing adsorption, *Ind. Eng. Chem. Res.* 41 (6) (2002) 1389–1392, <https://doi.org/10.1021/ie0109758>.
- [38] H.N.A. Halim, V. Rajiman, A.M. Shariff, A review on CO₂ absorption using chemical solvents at low and high CO₂ partial pressure conditions in a packed column, *Open Chem. Eng. J.* 16 (2022), <https://doi.org/10.2174/18741231-v16-e2204140>.
- [39] V. Meynen, P. Cool, E.F. Vansant, Verified syntheses of mesoporous materials, *Microporous Mesoporous Mater.* 125 (2009) 170–223, <https://doi.org/10.1016/j.micromeso.2009.03.046>.
- [40] M. Gallo, L. Serpella, F. Leone, L. Manna, M. Banchemo, S. Ronchetti, B. Onida, Piroxicam loading onto mesoporous silicas by supercritical CO₂ impregnation, *Molecules* 26 (2021) 2500, <https://doi.org/10.3390/molecules26092500>.