

Sensor placement strategies for the seismic monitoring of complex vaulted structures of the modern architectural heritage

*Original*

Sensor placement strategies for the seismic monitoring of complex vaulted structures of the modern architectural heritage / Lenticchia, E., Ceravolo, R., Antonaci, P.. - In: SHOCK AND VIBRATION. - ISSN 1070-9622. - STAMPA. - 2018:Article ID 3739690(2018). [10.1155/2018/3739690]

*Availability:*

This version is available at: 11583/2713221 since: 2018-09-17T17:57:59Z

*Publisher:*

Hindawi

*Published*

DOI:10.1155/2018/3739690

*Terms of use:*





This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

*Publisher copyright*

(Article begins on next page)

Review

# Unconventional Mining of End-of-Life Aircrafts: A Systematic Review

Silvia Zecchi <sup>1,2,\*</sup>, Giovanni Cristoforo <sup>1</sup>, Carlo Rosso <sup>3</sup>, Alberto Tagliaferro <sup>1,2</sup> and Mattia Bartoli <sup>2,4,\*</sup>

<sup>1</sup> Department of Applied Science and Technology, Politecnico di Torino, C.so Duca degli Abruzzi 24, 10129 Torino, Italy; giovanni.cristoforo@polito.it (G.C.); alberto.tagliaferro@polito.it (A.T.)

<sup>2</sup> Consorzio Interuniversitario Nazionale per la Scienza e Tecnologia dei Materiali (INSTM), Via G. Giusti 9, 50121 Firenze, Italy

<sup>3</sup> Department of Mechanical and Aerospace Engineering, Politecnico di Torino, C.so Duca degli Abruzzi 24, 10129 Torino, Italy; carlo.rosso@polito.it

<sup>4</sup> Center for Sustainable Future Technologies, Italian Institute of Technology, Via Livorno 60, 10144 Torino, Italy

\* Correspondence: silvia.zecchi@polito.it (S.Z.); mattia.bartoli@iit.it (M.B.); Tel.: +39-0110907347 (S.Z. & M.B.)

## Abstract

Advancements in material science have allowed us to exploit the potential of new era for aircraft production. High-performance composites and alloys have allowed us to improve the performance and durability of aircraft, but they have become more and more precious with time. These materials can provide significant advantages in use but are costly, energy-intensive to produce, and their recovery and reuse has become a critical step to be addressed. Accordingly, a new approach in which end-of-life aircrafts represent unconventional mines rather than a disposal challenge is becoming increasingly relevant, providing access to high-value strategic raw materials and aligning with circular economy principles including European Green Deal and the United Nations Sustainable Development Goals. The complexity of dismantling and processing hybrid structures composed of metal alloys, ceramics, and advanced composites requires multiple approaches able to integrate chemical, mechanical, and thermal recovery routes. Accordingly, this review critically discusses the state of the art of the routes of end-of-life aircraft treatments, evaluating the connections between technology and regulation, and positions material recycling and reuse as central pillars for advancing sustainability in aerospace. Furthermore, this review provides a comprehensive reference for addressing the technical, economic, and policy challenges of waste management in aviation, contributing to broader goals of resource circularity and environmental preservation set forth by international sustainability agendas.

**Keywords:** wastestreams; disassembling; mining; end-of-life aircrafts; sustainability



Academic Editor: Denis Rodrigue

Received: 21 August 2025

Revised: 23 September 2025

Accepted: 26 September 2025

Published: 29 September 2025

**Citation:** Zecchi, S.; Cristoforo, G.;

Rosso, C.; Tagliaferro, A.; Bartoli, M.

Unconventional Mining of End-of-Life Aircrafts: A Systematic Review.

*Recycling* **2025**, *10*, 187. <https://doi.org/10.3390/recycling10050187>

**Copyright:** © 2025 by the authors.

Licensee MDPI, Basel, Switzerland.

This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license


(<https://creativecommons.org/licenses/by/4.0/>).

## 1. Introduction

In recent years, global manufacturing sectors have faced increasing pressure to address environmental and climate issues. Relevant EU initiatives aimed at promoting sustainability include the European Green Deal and the Circular Economy Action Plan [1]. The Green Deal outlines a series of proposals with the goal to overcome the challenges of climate change and environmental degradation. Key targets include reducing net greenhouse gas emissions by at least 55% by 2030 and achieving net zero emissions by 2050. These proposals span multiple sectors, such as: climate change, energy, industry, transport, and research and innovation. Specifically, for the transport sector, the Green Deal aims to

reduce its greenhouse gas emissions by 90% [2–4]. The aerospace industry is responsible for approximately 2% of the total CO<sub>2</sub> emissions on the planet [5]. Therefore, in recent years, the aeronautical sector has been showing considerable interest in the topics of sustainability and circular economy [6,7].

Considering the number of commercial aircraft exceeds 28,000 units and is set to exceed 35,000 units in the next decade, the aviation sector has a considerable challenge to face. In the last five years, the number of aircraft annually retired from service is over 600 units [8]; consequently, the volume of material from end-of-life (EOL) airplanes that would become waste, contributing to global pollution if not properly recycled and recovered, has to be properly managed [9,10] as summarized in Figure 1.

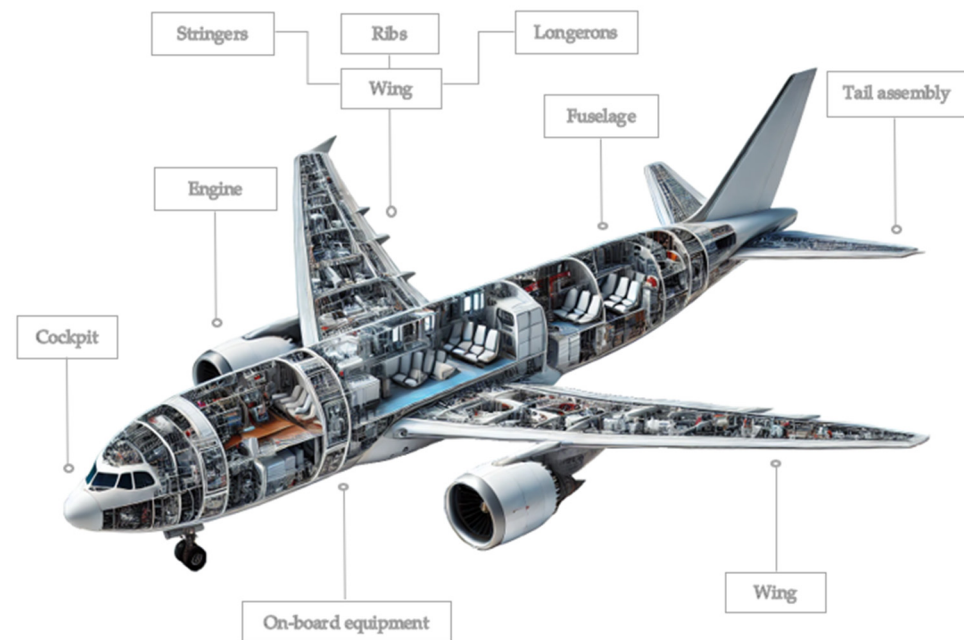

**Figure 1.** Main components of aircrafts.

With the development of efficient recycling and recovery technologies, the aircraft sector is able to reduce its environmental impact, both in terms of the lower demand for virgin raw material and the drastic reduction, or elimination, of aircrafts sent for landfill disposal [6,11,12]. A noteworthy first step in this direction is represented by the Process for Advanced Management of End-of-Life of Aircraft (PAMELA) project, funded by the European Union and led by Airbus in 2005 [13]. The main objective was to demonstrate that up to 85% of an aircraft's weight could be recycled, reused, or recovered, while establishing new standards for sustainable dismantling and recycling processes. The project provided significant benefits, including 90% energy saving in aluminum casting, the reuse of materials for aerospace applications, a 66% reduction in landfill waste, and enhanced safety and sustainability in resource management. Additionally, PAMELA ensured the safety and reliability of aerospace components while substantially reducing the environmental impact of end-of-life aircraft. Another project funded by the European Union is the Aircraft Metal Recycling (AiMeRe) CleanSky project [14]. Its primary objectives included enhancing the reutilization of high-grade alloys for industrial applications, ensuring the profitability of recycling practices, improving adherence to environmental regulations, and identifying new recycling pathways and opportunities. The project's scientific contributions provided a comprehensive overview of the current state of the aircraft recycling industry, detailing existing practices, legislative aspects, and aircraft composition in terms of valuable metals and hazardous waste. Additionally, it introduced economically and environmentally

optimized methods for dismantling, cutting, sorting, and processing materials, alongside exploring new applications for recycled metal alloys in both aerospace and other industries. The technical achievements included cartographic analyses of aircraft materials and waste, evaluations of enhanced recycling methods, studies on gold-containing components, and lifecycle assessments for aircraft metals recycling. The project also emphasized recommendations for design-for-environment practices and established dissemination activities to promote sustainable recycling approaches within the aerospace sector and beyond. The last noteworthy project is SUSTAINair [15], funded by the H2020 program, which integrates circular economy principles into all stages of an aircraft's lifecycle, from design to end-of-life. SUSTAINair aims to achieve several key outcomes: reducing weight and improving fuel efficiency through a multi-material design philosophy involving advanced metal alloys and composites; enhancing aerodynamic performance and safety by implementing onboard structural health-monitoring sensors for real-time damage diagnostics; introducing flexible wings with morphing capabilities; and minimizing waste during manufacturing and end-of-life processes through innovative recycling and upcycling methods for both metallic and composite materials. This includes developing solutions for carbon- and glass-fiber thermosets, as well as high-performance thermoplastic composites. Some projects have been launched to increase the recyclability of carbon waste. Indeed, Airbus has an ongoing project involving the recycling of carbon waste for bicycle production [16]. Boeing recycles composite materials from production waste to reuse them in cars and consumer goods [17].

Other projects focused on the alternative reutilization of end-of-life aircraft components into high-value products beyond the aerospace sector. A notable example is the "Eco-design of products" project, a collaboration between Bombardier, the University of Montreal, and the Consortium for Research and Innovation in Aerospace in Québec [18]. This initiative integrates end-of-life aircraft parts into conceptual designs using a lifecycle approach, focusing on the complexity of repurposing, environmental benefits, and public communication of sustainability impacts. The project demonstrated that alternative reuse often results in lower environmental impacts compared to recycling, with examples like bicycles, leather jackets, and wall clocks made from aircraft materials. When reusing aircraft components, the priority is to preserve their original form and function to maintain maximum value, as seen in cockpits repurposed as simulators and floor panels used for staging. If preserving form and function is not possible, the focus shifts to maintaining the material properties through upcycling.

The shared efforts of a large number of companies in such a complex and challenging field have led to progress in understanding and knowledge of the problem. A first example of innovation in this direction is the integration of disassembly planning during aircraft design [19].

In this review, we will discuss the three main material families that find application in aircraft construction: composites, metals, and polymers [20,21]. Moreover, we will focus on the state of the art of recycling and recovery techniques and their application to different materials. Furthermore, some considerations will be made about the advantages of one method rather than another, based on economic considerations, circularity, and when, instead, landfill disposal is the best choice.

## 2. Insight on Aircraft Materials and Their Components

The aviation sector relies on specialized materials to meet strict safety, durability, and performance standards, particularly given the industry's focus on lightweight, fuel-efficient aircraft. In recent years, the emergence of electric and hybrid aircrafts has driven the need for innovative materials that support efficient energy use and comply with stringent European regulations on critical raw materials (CRMs). The scarcity of certain metals

and minerals essential for manufacturing advanced aircraft components, especially those classified as CRMs by the European Union, poses unique challenges [22]. The European Union has identified materials crucial to its technological and economic sectors, and its 2023 Critical Raw Materials Act now lists 34 elements [23]. This regulation impacts the aviation industry, as many of these materials are essential for producing lightweight, high-strength parts.

The European Union's Critical Raw Materials list covers essential metals and minerals that are either scarce or whose supply chains are vulnerable [24]. These include cobalt, tungsten, rare-earth elements (such as neodymium, dysprosium, and praseodymium), and magnesium, all of which are used in the production of aircraft components. Due to limited sources and high import dependency, the EU has prioritized recycling, alternative sourcing, and minimizing waste. For example, cobalt, which is 100% imported into the EU, is integral to lithium-ion battery production, a core component in electric aircraft. The scarcity of cobalt presents a significant obstacle in the aerospace sector, where reliance on advanced battery technology is growing [25].

In addition to cobalt, neodymium, and praseodymium are crucial for manufacturing high-strength magnets used in electric motors and control systems [26]. Electric and hybrid aerotaxis, in particular, are dependent on high-efficiency motors and require neodymium-iron-boron (NdFeB) magnets, which deliver superior magnetic power with minimal weight [27]. According to EU directives, alternative sources and recycling processes are being investigated to limit dependency on imports from regions like China, which controls over 80% of the global rare-earth supply [28].

Tungsten is another critical element, often used for high-temperature applications due to its exceptional melting point and density. Tungsten is essential in aerospace components such as turbine blades, which must withstand high stress and heat. Tungsten carbide, which comprises approximately 2–3% of an aerotaxi's critical components, is used for parts that undergo intense mechanical stress, contributing to overall efficiency in propulsion and durability.

The EU's Critical Raw Materials Act promotes sustainable mining and processing of these materials, prioritizing local sources and exploring recycling options to secure their supply [29]. These efforts are crucial in light of the increased demand for lightweight, fuel-efficient aircraft. Approximately 40% of aircraft manufacturing materials are on the EU's CRM list, a considerable share highlighting the urgency for alternative sourcing or substitution strategies.

Beyond metals and rare-earth elements, polymers play a substantial role in aircraft manufacturing. While traditional plastics are often inadequate due to insufficient strength or heat resistance, advanced composites, and high-performance polymers have become integral to the aerospace industry. Carbon-fiber-reinforced plastics (CFRP) and glass-fiber-reinforced plastics (GFRP) account for a significant portion of these materials due to their high strength-to-weight ratios [30]. CFRPs are widely used in structural components like fuselage sections, wing structures, and control surfaces, representing roughly 50–70% of the primary structure in modern aircrafts. The fraction of plastics in total aircraft weight has grown as manufacturers focus on achieving lighter aircraft with increased fuel efficiency. Compared to metallic counterparts, CFRPs can reduce structural weight by up to 40%, directly contributing to energy savings and, in turn, reducing operational costs and emissions [31].

Thermosetting resins, such as epoxy, are common binding agents in these composites, providing strength and durability under high-stress conditions. In aerotaxis, where weight and efficiency are dominant, these polymers are essential for achieving competitive fuel efficiency and payload capacity. Epoxy resins are responsible for approximately 30–40% of

the total composite fraction, depending on the aircraft model and the extent to which CFRP is used [32].

Additionally, polyether ether ketone (PEEK) and polyimides are used in high-temperature areas like engine components, while polyamide-imide (PAI) provides excellent wear resistance and strength for interior components such as seating frames [33]. In aircraft applications, these plastics also contribute to noise reduction and passenger comfort, as they absorb vibrations better than metal. With the growing demand for these materials, recycling and alternative sourcing remain important considerations for sustainable manufacturing, particularly under EU regulations.

Metals and alloys are essential for aircraft construction, particularly for components that require high strength, durability, and resistance to environmental stress. The aerospace industry extensively uses aluminum, titanium, and nickel alloys due to their mechanical properties and relative lightness compared to steel.

Aluminum–lithium (Al–Li) alloys are a popular choice for aircraft due to their low density and high stiffness. Aluminum components represent approximately 40–50% of a traditional aircraft’s structural weight, though in newer aircraft this share may be lower due to increased CFRP usage [34]. The inclusion of lithium enhances the material’s resistance to fatigue and corrosion, providing a weight savings of approximately 7% over standard aluminum alloys. This makes it ideal for fuselage and wing components where strength-to-weight ratios are critical.

Titanium alloys (primarily Ti–6Al–4V) are commonly used in aircraft due to their high strength, low density, and resistance to corrosion and heat. Titanium is found in 10–15% of structural components, particularly in areas requiring high resistance to fatigue, such as landing gear, wing spars, and engine mounts [35]. Titanium’s high melting point allows it to maintain integrity under extreme heat and stress, a crucial property in areas exposed to high thermal loads.

Nickel-based superalloys, such as Inconel, are primarily used in turbine engines and areas exposed to high temperatures, where their resistance to oxidation and creep deformation is essential. Nickel alloys account for approximately 5–7% of an aircraft’s total structural weight [36]. These materials are indispensable for maintaining performance in high-stress environments, such as engine turbine blades.

The use of alloys in aircraft is guided by both performance and sustainability. For instance, replacing traditional steel components with high-strength aluminum or titanium alloys reduces weight and enhances fuel efficiency. However, many of these metals, such as titanium and nickel, are on the EU’s CRM list, necessitating careful management and recycling practices to ensure long-term availability [25].

With the rise in sustainable urban mobility solutions, aircrafts are becoming a central focus of innovation in aerospace. These vehicles aim to be highly efficient, eco-friendly, and lightweight, using advanced materials to meet strict weight and safety criteria [37]. Over time, there has been a significant shift in the percentages of materials used in aircraft manufacturing, driven by the goal of reducing weight and improving fuel efficiency. This evolution is evident in the comparison of materials used in various Airbus and Boeing aircraft models, spanning older to more recent designs, as shown in Figures 2 and 3.

For example, earlier models such as the Boeing 747 and Airbus A320 relied heavily on aluminum, making up 70–80% of their structural weight. In contrast, newer aircraft like the Boeing 787 and Airbus A350 feature a much higher percentage of carbon-fiber composites, which account for 50–53% of their structure, significantly reducing weight while maintaining strength [38,39].

Titanium and advanced alloys have also increased in use, particularly in areas where resistance to high temperatures and corrosion is critical. The trend towards lightweight

composite materials reflects the industry’s commitment to lowering fuel consumption, reducing emissions, and aligning with global sustainability goals.

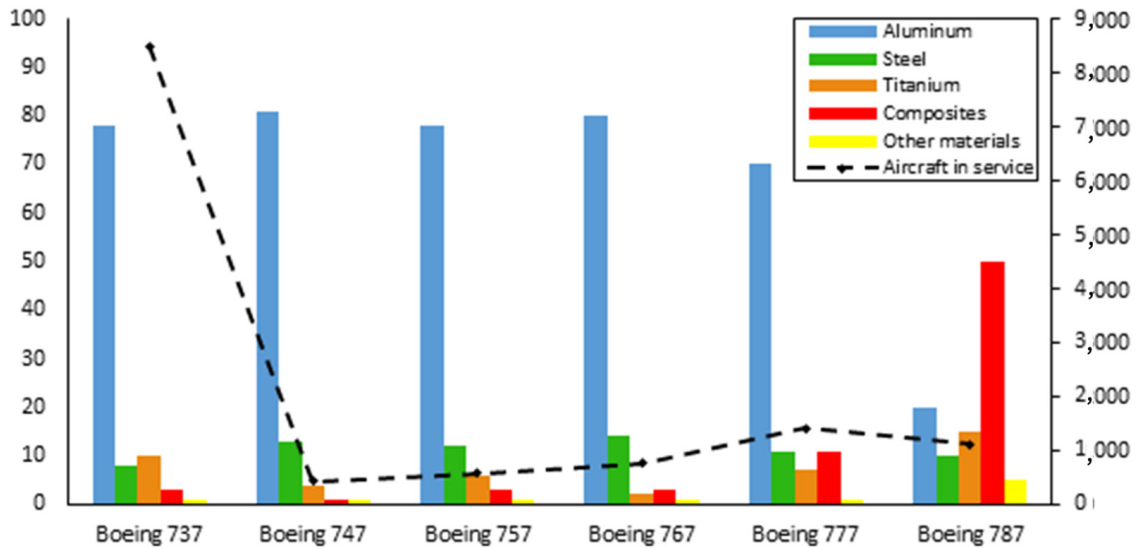


Figure 2. Material composition of the most important Boeing aircraft with the actual number of aircraft in service (2025) [40,41].

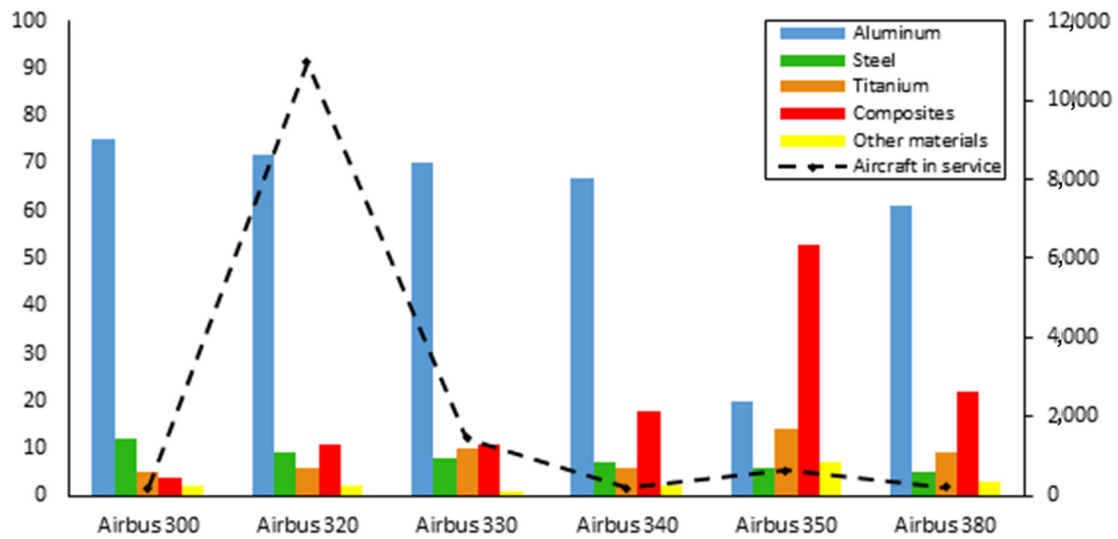


Figure 3. Material composition of the most important Airbus aircraft with the actual number of aircraft in service (2025) [42,43].

### 3. Strategy for Disposal and Recovery of End-of-Life Aircrafts

#### 3.1. Disassembling and Wastestreams

As reported in Figure 4, Aircraft dismantling constitutes the entry of aircraft parts and materials to the waste business, meaning that they cannot re-enter the aerospace business and fall under the general regulations covering waste treatment. The aircraft-dismantling industry emerged at the beginning of this century and involves various organizations, such as the official civil aviation agency, companies specialized in aircraft dismantling, aircraft manufacturers, maintenance, and waste-recycling companies [44]. Organizations like the International Civil Aviation Organization (ICAO), civil aviation authorities, and environmental protection agencies create rules and guidelines to ensure that dismantling and recycling are carried out safely and in an environmentally friendly manner. Associations

like the International Air Transport Association (IATA) and Aircraft Fleet Recycling Association (AFRA) work on creating manuals and procedures for aircraft dismantling and help standardize the industry. In addition, professional dismantling companies, such as AELS (Aircraft End-of-Life Solutions) in the Netherlands, not only handle aircraft dismantling but also focus on reusing materials from decommissioned aircraft.

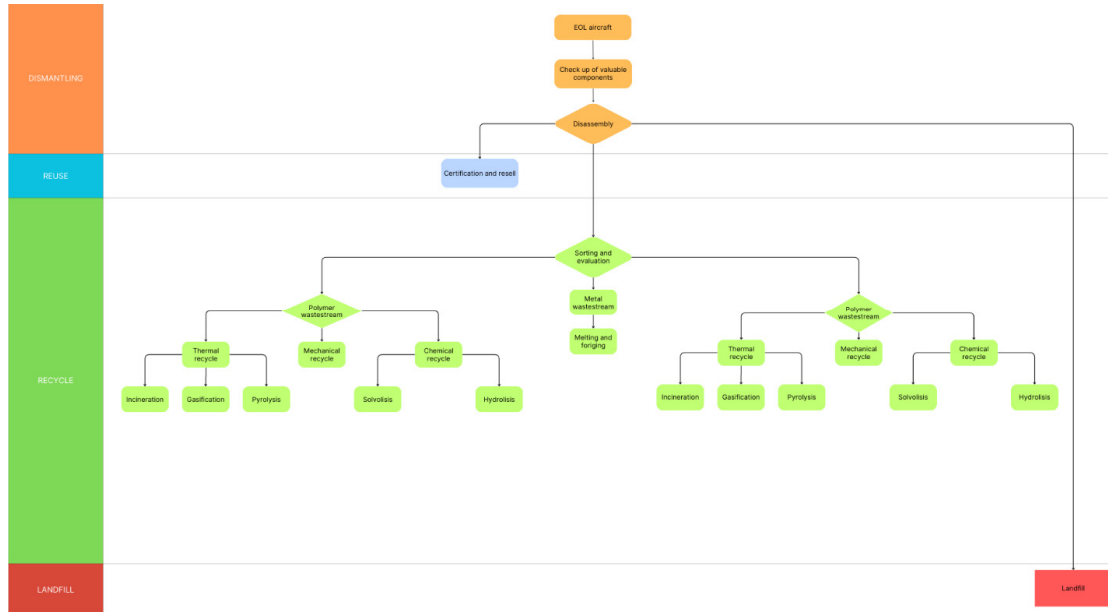


Figure 4. Scheme for disposal and recovery of EoL aircraft.

After excluding the possibility of passenger aircraft being converted to cargo aircraft, the procedure of dismantling involves the removal of components and materials for purposes such as reuse, recycling, recovery, or disposal [45]. The process gives economic value to the retired aircraft while promoting its environmental sustainability. In a typical aircraft-dismantling scenario (Figure 5), the process begins with the transportation of the aircraft to a certified facility, where a general inspection is carried out to assess the condition of its components.

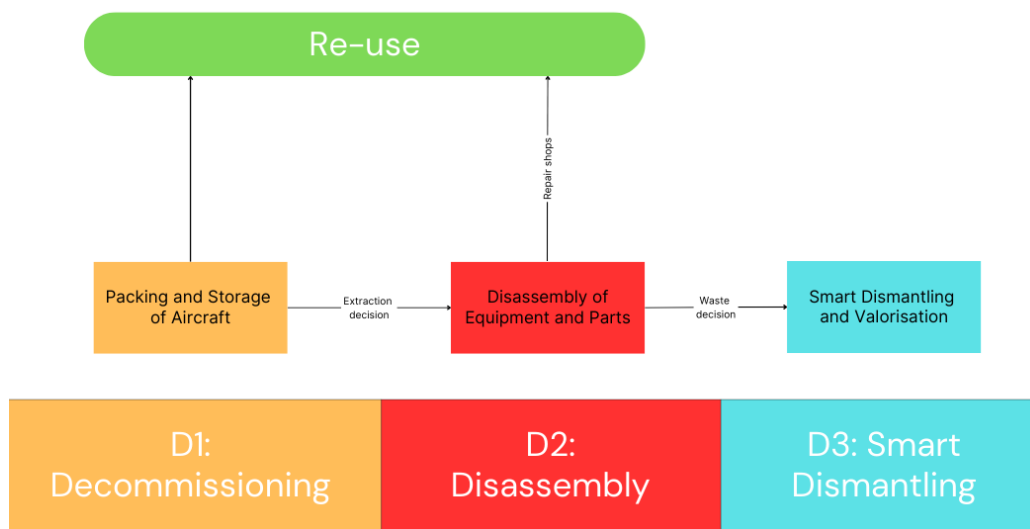


Figure 5. Airbus’s 3-D process for aircraft dismantling.

If the owner wishes to resell certain high-value parts, such as engines or avionics, these components undergo rigorous testing and certification before proceeding to the next stages. Certified components are either returned to the aviation market or sent for necessary repairs and overhauls by authorized units [46].

Once the certification process is completed, all fluids are removed from the aircraft, ensuring compliance with environmental safety standards. Subsequently, high-value components, such as engines and avionics, are carefully extracted for resale. These parts, which can account for 40–50% of the aircraft's total weight, play a significant role in the second-hand aviation materials market, offering a cost-effective alternative to new components [47]. The next step involves the removal of internal components, including seats, overhead bins, panels, and carpets, many of which are made of polymers [48,49]. These materials are classified based on polymer type and contamination level, such as mixed plastics, to determine their appropriate recycling path. The final stage involves processing the external structure. The fuselage, wings, and tail are segmented into manageable sections, and metal components are sorted based on their base metal matrix. Recyclable metals are directed toward recycling processes, while non-recyclable materials are prepared for disposal. The engine, accounting for over 60% of the aircraft's value, often receives special attention due to its high recyclability and resale potential [50]. A significant challenge in the dismantling process of EOL aircraft arises from the presence of various hazardous materials. For example, older military aircraft may contain asbestos, while fire extinguishers often contain bromotrifluoromethane [51]. Additionally, commercial aircraft frequently feature smoke detectors and emergency exit signs that contain radioactive elements. Hexavalent chromium is another concern, commonly found in aircraft paint primers. Proper handling and disposal of these hazardous materials add to the overall costs of dismantling. The presence of hexavalent chromium in aluminum scrap further complicates its reuse, particularly in industries like packaging [52]. While techniques exist to remove paint primers containing this substance, their economic feasibility and environmental impact require further investigation to determine their viability.

Through this structured process, a retired aircraft can yield up to 50,000 components, with approximately 20,000 parts being suitable for reuse in the aviation market after proper testing and certification [44]. Components not fit for aviation reuse may find applications in non-aerospace sectors, maximizing the value extracted from retired aircraft while minimizing waste. Logistical challenges further complicate aircraft recycling. To make this a scalable industry, it would be advantageous to concentrate recycling activities in global hubs where sufficient numbers of EOL aircraft can be processed. Alternatively, mobile dismantling units could address this issue by servicing remote locations, such as desert storage areas where EOL aircraft are often left to corrode. However, the recovered metals must still be transported to recycling facilities, making centralized dismantling and recycling locations more efficient. Aircraft could ideally perform a final flight to such facilities, streamlining the process.

Different strategies were carried out by the biggest aircraft producers. In 2006, the AFRA was established in order to look for a standard approach for aircraft disassembly [53]. Boeing, as a founding member, played a pivotal role in its development and growth. The organization aimed to create standardized practices for aircraft disassembly, develop efficient technologies for material recovery, and reduce the environmental impact of aircraft disposal. Thanks to the contributions of all participants taking part to the project, AFRA created a guide, known as Best Management Practices, as an approach to managing EOL aircraft [54]. The guide aims to create a standard for uniformity and safety in dismantling process, while maximizing the recovery of valuable parts that can re-enter the market. Moreover, it provides information for efficient recycling of materials such as metals and composites.

After advancements in knowledge and technology, the guidelines has undergone revision and updates; nowadays, the association counts a large number of members all over the world, with advanced facilities able to recover a significative amount of retired aircraft. An example of a fruitful collaboration is the agreement established in 2008 between Boeing and Alenia Aeronautica for the development of the first Italian center for the recovery of carbon-fiber composites (following the design of the Boeing 787 Dreamliner, in which the primary structure is made of this material) [55].

Due to the large number of aircraft close to their end of their life, in 2005 Airbus launched the PAMELA project, aiming to create a systematic and sustainable approach for aircraft dismantling and recycling [13]. The company selected a EOL Airbus A300 as a full-scale demonstration and developed a structured three-step process to manage its dismantling [56].

The first stage, known as *Decommissioning*, involves removing the aircraft from service and decontaminating it to ensure safety for subsequent steps [57]. This includes removing all operating fluids (e.g., fuel residues, technical fluids, wastewater) and hazardous substances, such as depleted uranium or explosive devices from army aircrafts, in accordance with existing regulations. Additional preparatory steps include the inspection, cleaning, and decontamination of components such as electronic devices, passenger equipment, and auxiliary systems. These initial processes also involve creating a detailed inventory of parts to be reused, enabling traceability throughout the aircraft's end-of-life phase [46]. The second stage, named *Disassembly*, focuses on systematically removing high-value components, such as engines, avionics, landing gears, and auxiliary power units. These components are selected based on market demand for spare parts and undergo inspection, repair, or certification to return them to service [58]. A detailed disassembly plan is created, which includes grouping components into families, determining disassembly sequences, and optimizing shop floor operations to enhance efficiency [59]. The final stage, *Dismantling*, involves recovering structural materials by grouping them according to type (e.g., aluminum alloys, stainless steel, composites) to optimize recycling. Advanced tools, such as plasma torches, hydraulic scissors, and water jets, are used to cut the aircraft into manageable sections. After initial sorting, materials are sent through dedicated recovery channels for further processing [60]. This stage ensures that up to 80% of the materials can be recycled, while the remaining non-recyclable waste is disposed of following standard procedures [61]. The PAMELA project achieved notable milestones: the project demonstrated an effective recovery rate of 85% of an aircraft, established a replicable model for the management of EOL aircraft, and reduced landfill disposal and greenhouse gas emissions (by recycling aluminum and other materials). Moreover, the project led to a new vision in designing aircraft, emphasizing the importance of a lifecycle approach for better recyclability in modern aircraft. Since the project was successfully concluded, Airbus decided to valorize it by founding in 2007, together with other partners, Tarmac Aerosave, a company specialized in the efficient recovery of EOL aircraft [62]. The company has developed its technology over the years, assuming a leading role in maintenance, the resale of high-added-value components and almost total recovery of EOL aircraft (up to 92% by weight). In 2024, Airbus, in collaboration with Tarmac Aerosave and the city of Chengdu, inaugurated the Airbus Lifecycle Services Centre, a multi-service facility aimed to offer solutions for the management of EOL aircraft, exploiting Tarmac Aerosave's expertise in the field [63].

### 3.1.1. Polymer Wastestreams

Aircraft tires are highly engineered products designed to endure extreme stresses, including heavy loads, rapid acceleration, and temperatures generated during takeoff and landing. They are essential for the safe operation of aircraft, yet their limited lifespan

contributes significantly to waste. Civil aviation tires typically last between 250 and 300 landings, while military aircraft tires often last only 20 to 50 landings [64]. With airlines like Southwest Airlines replacing nearly 40,000 tires annually, the disposal of end-of-life tires (ELTs) is a pressing issue. Larger aircraft exacerbate the challenge: a Boeing 777 uses 14 tires, an A380 requires 22, and the AN225 cargo aircraft has 32 tires [65].

The short service life of aircraft tires is partially offset by retreading, which allows tires to be reused up to seven times before they become non-viable. However, even with retreading, significant quantities of ELTs are generated, creating an opportunity to improve recycling and waste management practices [66]. Sustainable solutions are especially important given the materials used in tire production. Aircraft tires are predominantly made of rubber, including natural rubber (NR), Styrene–Butadiene Rubber (SBR), Polybutadiene Rubber (BR), and Isobutylene–Isoprene Rubber (IR), along with textiles and metals such as steel cords for reinforcement [67]. Additives such as sulfur compounds and other hazardous chemicals, including heavy metals and polycyclic aromatic hydrocarbons (PAHs), are also present in varying amounts depending on the manufacturer.

Two primary types of tires are used in aviation: bias-ply and radial. Bias-ply tires, known for their durability and retreadability, are commonly employed due to their robust construction. Radial tires, while lighter and offering reduced rolling resistance, provide higher performance with increased landing capacity [68]. Both types undergo rigorous testing to ensure they meet operational requirements, including tread designs tailored for traction under diverse runway conditions.

The environmental impact of aircraft tires stems from their short service life, complex composition, and hazardous materials. As air travel expands, driven by the rise in low-cost carriers and the demand for new aircraft, the number of ELTs requiring proper disposal will increase [69]. This underscores the necessity of advancing recycling technologies to recover valuable materials and minimize the environmental footprint of the aviation industry.

Scrap tire (ST) recycling can be broadly categorized into three main approaches: reuse, material recovery, and energy recovery. Reuse involves directly extending the tire's lifecycle, with retreading being a key method in this category. Material recovery transforms STs into new products or materials, employing technologies like shredding and grinding to produce rubber granulates or powders. Finally, energy recovery involves using STs as a fuel source, particularly in industries such as cement manufacturing, where tires are incinerated to generate energy.

Among these methods, retreading is a standout for its environmental and economic benefits. Retreading involves replacing the worn tread of a tire with a new one, allowing it to be reused multiple times while conserving resources and reducing waste. This process is particularly significant for truck and aircraft tires, which can undergo retreading up to three and twelve times, respectively. The process can be classified by the renewed surface: integral (tread and sidewall), semi-integral (tread and part of the sidewall), or tread-only [70]. Retreading can also be divided by adhesion system: hot retreading involves vulcanization at high temperatures (150–160 °C) [71], while cold retreading uses lower temperatures (98–125 °C) in autoclaves [72].

Retreading reduces raw material consumption by 30–50% and generates tires with comparable performance to new ones, making it a cost-effective and sustainable alternative. However, the process is contingent on the condition of the tire's casing, which must be intact and undamaged. Despite some limitations, such as the restricted number of possible retreads, this method significantly contributes to reducing the environmental impact of tire waste, particularly in regions with strong retread markets like Scandinavia, Germany, and Finland [73].

Aircraft interiors, including seats, overhead bins, and cabin linings, represent a significant source of polymer waste in the aviation sector [74]. These components are engineered to be lightweight, durable, and compliant with stringent safety and fire-resistance standards, making them highly specialized but challenging to recycle. The materials used in interiors range from thermoplastics and thermosetting polymers to polymer foams and fiber-reinforced composites, chosen for their balance between performance, weight, and cost [75].

Aircraft seats are among the most frequently replaced components within the cabin. They are constructed using a combination of lightweight metals for structural frames, polyurethane foams for cushioning, and synthetic materials like polyester or nylon for upholstery. In premium classes, advanced materials such as memory foam may also be incorporated to enhance passenger comfort. Thermoplastics such as polycarbonate, polyetherimide, and polyphenylene sulfide are used for seatbacks, tray tables, and armrests. A narrow-body aircraft seat typically weighs between 15 and 25 kg, while wide-body and premium-class seats can weigh significantly more. For instance, a fully equipped business-class seat may exceed 100 kg. On a Boeing 777, which has 396 seats, the combined weight can exceed 7500 kg.

Seats are typically replaced or refurbished every five to ten years, depending on usage, regulatory changes, or updates to airline branding. This results in substantial waste generation, with thousands of tonnes of materials discarded annually. Airlines with large fleets, such as Delta or Emirates, periodically refurbish or replace all their seating systems, contributing significantly to this wastestream.

Recycling seats is a complex process due to their multi-material construction. While metal frames are relatively straightforward to recycle, polymer foams and fabrics present challenges. Polyurethane foams, for example, are difficult to recycle mechanically and often end up in landfills. Additionally, adhesives and coatings used in seat assembly can hinder the separation and recovery of individual materials. For fiber-reinforced composites used in premium seating, recycling is even more difficult due to the nature of thermosetting polymers, which are not easily remoldable.

Recent advancements offer some solutions. Chemical recycling methods are being developed to break down polymers like polyurethane into reusable monomers, while mechanical recycling can transform thermoplastics into pellets for use in lower-grade applications [76]. In recent years, airlines have increasingly focused on reusing and repurposing interior components, particularly textiles and foams. Upholstery materials and fabrics removed from aircraft are often cleaned, repaired, and reused on other planes to extend their service life [77]. When direct reuse is not viable, these materials are sometimes upcycled into furniture, insulation panels, or decorative items for home and office applications, contributing to the growing trend of repurposing in aviation recycling. Non-metal parts such as textiles, insulation, mixed plastics, and rubber are typically processed at certified recycling centers, where they undergo separation and treatment to recover usable materials or convert them into new products. Despite these efforts, the recycling of seats remains a significant environmental challenge, highlighting the need for more sustainable materials and design practices.

In addition to seats, other cabin components such as overhead bins, interior linings, and flooring contribute substantially to polymer waste. These components are designed for high durability and compliance with fire safety standards and are typically made from materials such as glass-fiber-reinforced polymers, thermoplastics like polyetheretherketone and polyphenylene sulfide, and flame-retardant polycarbonates. Flooring and carpets, which are predominantly composed of nylon or polyester with fire-resistant treatments, also contribute to this wastestream. The interior panels of a narrow-body aircraft can weigh

around 1200 kg, while those in wide-body aircraft, such as the Airbus A380, may exceed 3000 kg. These components are replaced less frequently than seats, with a typical lifespan of 10 to 20 years, but their eventual disposal represents a significant environmental challenge.

The recycling of cabin linings and bins is hindered by their composite nature and the presence of flame retardants. However, thermoplastics used in these components are more easily recycled than thermosetting polymers. Remanufacturing programs, where airlines and manufacturers refurbish interior panels instead of replacing them entirely, are also emerging as an effective waste-reduction strategy. Additionally, research into bio-based and biodegradable polymers holds promise for future sustainability.

Aircraft interiors constitute a substantial wastestream, with significant environmental implications due to the volume of materials used and their extended replacement cycles. As the aviation industry continues to grow, with approximately 40,000 new aircraft expected to enter service by 2040, polymer waste from cabin interiors will increase unless proactive measures are adopted. Transitioning to recyclable materials, investing in advanced recycling technologies, and adopting circular design principles will be essential to mitigate the environmental impact of this waste.

Cables and wiring represent another substantial source of polymer waste in decommissioned aircraft. While the focus of recycling efforts often lies on the conductive metals within cables, such as copper, silver, and aluminum, the polymeric insulating layers also pose significant challenges. These insulators are typically made from thermoplastics or elastomers such as polyvinyl chloride (PVC), polyethylene (PE), or polytetrafluoroethylene (PTFE), chosen for their heat resistance, durability, and lightweight properties.

Modern aircraft can contain significant quantities of wiring. For example, a Boeing 777 has about 100 miles of cables, adding substantial weight and complexity to the aircraft [78]. Once removed, the metal and plastic components of cables are separated during recycling. Larger-scale wires are shredded and granulated, with separators used to distinguish metal particles from the polymeric insulation [79]. The recovered polymers are then melted and reprocessed into new materials for use in less critical applications.

Possible solutions involve a multi-pronged approach. Design-for-recycling strategies, such as modular construction and selective use of thermoplastics, can facilitate easier recovery. Advances in solvent-based chemical recycling show promise in selectively depolymerizing PEEK into reusable monomers while minimizing degradation. Hybrid recycling processes that combine mechanical and chemical routes may further enhance efficiency. Moreover, developing secondary markets for recycled PEEK—such as in automotive, electronics, or consumer goods—can improve economic viability, even if aerospace reuse is limited. Additionally, PEEK is often used matrix for together with carbon and glass fibers requiring environmental impacting procedures [80,81]. Furthermore, the aerospace industry certification standards make it difficult to reintroduce recycled PEEK into high-value applications, as even small changes in material properties can compromise safety compliance. As reported by McLauchlin et al. [82], in order to preserve the PEEK properties, a multistep rout should be followed and virgin PEEK should be added, even if only in small amounts.

For very thin cables, however, recycling becomes more complex due to the difficulty in separating the insulating polymers from the metals. In such cases, thermal processing may be used to burn off the plastic layers, though this method raises environmental concerns regarding the presence of toxic flame-retardant agents [83] including halogenated and heavy-metal-containing compounds [84]. The heat generated during burning can be captured and reused within the industry, enhancing energy efficiency and reducing waste.

### 3.1.2. Composite Wastestreams

In the aerospace field, composite materials are widely used due to their exceptional mechanical properties and lightweight characteristics [85]. These materials can be classified into three main categories based on their matrix type: metal-matrix composites (MMCs), ceramic-matrix composites (CMCs), and polymer-matrix composites (PMCs) [86]. Each category offers specific advantages, making them suitable for various aerospace applications, from structural components to thermal protection systems [87]. The properties and manufacturing costs of metal-matrix composites change significantly depending on material composition, processing techniques, and product quality [88]. The aerospace sector, for instance, demands materials with attributes like high weldability and a high specific modulus, such as extruded alumina-reinforced aluminum. MMCs have become integral to aerospace applications due to their superior strength, stiffness, and fatigue resistance, which enhance overall aircraft performance.

In aerospace, MMCs are employed in critical components like engine parts, brake systems, and drive shafts [89]. A notable example is the substitution of aluminum access doors on the F-16 aircraft with MMCs reinforced by SiC particles, which significantly improved fatigue life [90]. Titanium-based MMCs reinforced with SiC monofilaments have also been used in military applications, such as the F119 engine nozzle actuator control device on the F-16 [91]. These composites replaced heavier materials like Inconel 718 in actuator rods and stainless steel in piston rods, offering weight reduction alongside enhanced specific stiffness and fatigue resistance. Additionally, MMCs serve as alternatives to carbon/epoxy composites, which are prone to foreign object damage [92]. In addition to MMCs, the development of fiber-metal laminates (FMLs) represents a major advancement in aerospace materials [93]. FMLs, which combine metal and polymer composite laminates, create a synergistic effect, yielding superior mechanical properties compared to aluminum alloys or polymer composites alone [94]. These materials, such as GLARE (glass-reinforced aluminum) and ARALL (aramid-reinforced aluminum laminates), offer improved damage tolerance and weight reduction [95,96]. FMLs are widely used in wing structures, fuselage components, and ballistic protection. For instance, ARALL was developed for the lower wing-skin panels of the Fokker 27 aircraft and the Boeing C-17 cargo door, while GLARE is used in the cargo floor impact-resistant sections of the Boeing 777 [97,98]. The Airbus A380 extensively employs FMLs in its structure, underscoring their importance as a structural material [99]. Numerous aeronautical companies, including Aerospatiale, NASA, Bombardier, and EMBRAER, explored FML composites to replace traditional aluminum components due to their enhanced properties [100]. The continual evolution of MMCs and FMLs reflects the aerospace industry's drive to innovate and optimize materials that balance weight reduction, mechanical performance, and cost-effectiveness [101]. These advancements not only improve the durability and efficiency of aircraft but also redefine the possibilities for future aeronautical engineering.

CMCs are advanced materials that stand out for their exceptional performance at high temperatures, exceeding that of traditional superalloys [102]. Unlike monolithic ceramics, they exhibit higher fracture toughness, making them more suitable for applications requiring structural integrity [103]. In addition to these mechanical benefits, CMCs significantly reduce the overall weight of components, making them ideal for both structural and non-structural parts in aircraft engines [104]. Their ability to operate at higher temperatures and eliminate the need for cooling air through innovations such as thermal barrier coatings and air-cooled sheets allows for considerable performance improvements in aeroengines [97].

One major application of CMCs is in turbine blades, which require materials capable of withstanding extremely high temperatures [105]. C/C (carbon-carbon) composites are particularly suitable due to their ability to maintain strength at 1050 °C while being

lightweight. These characteristics allow aircraft to achieve speeds of up to Mach 10, compared to titanium-based composites that are limited to Mach 3.8. C/C composites achieve a specific tensile strength of  $160 \text{ MPa/g}\cdot\text{cm}^3$  at  $2000 \text{ }^\circ\text{C}$ , far surpassing traditional ceramics [106]. Furthermore, SiC-coated carbon-fiber composites in a carbon matrix are widely adopted in aerospace for their superior performance [107]. In recent years, projects like HIPOC (High-Performance Oxide Composite) have been initiated to develop oxide-based CMCs for hot-section applications in aircraft turbines [108]. Another critical application is in braking systems. The extreme temperatures generated during braking can reach up to  $3000 \text{ }^\circ\text{C}$ . C/C composites, when used in aircraft braking systems, offer significant weight reductions compared to traditional materials like high-strength steel or sintered metals [109]. For example, the weight of commercial aircraft braking systems can be reduced from 1100 kg to 700 kg. These materials not only improve performance and resistance but also enhance process reliability and reduce manufacturing costs [110]. CMCs also play a crucial role in the development of lightweight blisks, which combine blades and rotating disks into a single component [111]. The reduced weight of these components helps decrease axle and bearing chamber loads, resulting in broader system benefits [112]. Blisks made from three-dimensional woven fabrics, such as Tyrannoe Si-Ti-C-O composites, are densified through techniques like chemical vapor infiltration (CVI) and polymer impregnation and pyrolysis (PIP). These materials can achieve tensile strengths of up to 500 MPa at room temperature, making them well-suited for high-performance applications [113]. Exhaust nozzles are another area where CMCs excel. Companies like Boeing and GE Aviation are developing Ox/Ox (oxide–oxide) CMCs to replace titanium in subsonic jet engines [114]. These composites improve durability while avoiding the weight increase associated with higher-performance metal alloys. Notably, GE Aviation has incorporated Ox/Ox CMCs in the divergent exhaust seals of F414 engines, demonstrating their suitability for both commercial and supersonic aircraft [115]. Finally, turbine nozzle blades, which have complex geometries, benefit from advancements in CMC materials. For example, slip/hip mold casting of SiC whiskers with  $\text{Si}_3\text{N}_4$  powder has been explored for shaping these components [116]. GE Aviation tested the world's first rotating turbine blade made from a SiC matrix CMC for the low-pressure turbine of the F414 engine [117]. Such developments aim to double the use of CMCs in aero-engines, particularly by leveraging their high-temperature resistance and weight-saving advantages, which eliminate the need for cooling air.

Composite materials, particularly carbon fiber-reinforced polymers (CFRPs), have revolutionized the aerospace industry due to their exceptional mechanical properties and lightweight nature [118]. Weight is an important consideration when it comes to the design of aircraft because weight savings means saving on fuel consumption. Composite materials are lightweight and provide high strength, and so it results in a better strength-to-weight ratio compared to metallic alloys [119]. Various polymers, such as PLA, PP, and epoxy resins, have been used as matrix materials to develop composites for aerospace applications. For non-critical components like shroud panels, fans, duct fairings, spacers, and seals, fiberglass/epoxy composites have been employed. However, CFRPs dominate the practical applications in aircraft component design. CFRPs are widely used in aircraft due to their lightweight properties and ability to endure demanding conditions. For instance, the use of polymer-matrix composites in a four-seater aircraft resulted in a weight reduction of nearly 25% compared to its metal alloy counterpart [120]. Furthermore, efforts to reduce aircraft weight have led to the integration of components into single composite parts, such as the main landing gear integrated with the fuselage in the landing gear bay. This design, primarily composed of CFRP with minimal use of titanium, was manufactured using a

one-shot curing process [121]. This approach not only reduces the overall weight but also cuts recurrent assembly costs by up to 80% [122,123].

The application of advanced composites has also revolutionized commercial aviation. The Boeing 787 stands as a milestone in composite material usage, with 80% of its structure by volume comprising composites [124,125]. This includes a material composition of 50% composites, 20% aluminum, 15% titanium, 10% steel, and 5% other by weight. The carbon fiber-reinforced plastic and other composites used in its airframe enable a 20% weight reduction compared to traditional aluminum designs [126]. This lightweight construction significantly enhances fuel efficiency and performance. Boeing engineers adopted a design approach that prioritized selecting optimal materials for specific structural needs, resulting in a composite-dominated fuselage and main structure [127].

Nanocomposites are advanced materials with significant potential for aerospace applications, thanks to their unique properties that enhance safety, efficiency, and aircraft maintenance [128]. Key applications include electromagnetic interference (EMI) shielding, anti-corrosion and anti-icing coatings, and structural health monitoring (SHM). Electromagnetic interference protection is essential to ensure the proper functioning of aircraft electronic systems [129]. Polymer-based nanocomposites, combined with magnetic metallic nanoparticles, provide a lightweight and corrosion-resistant alternative to traditional metals [130,131]. For instance, PVDF/Fe<sub>3</sub>O<sub>4</sub> composites and hybrid materials like CNTs/rGO/epoxy achieve shielding effectiveness (SSE) values of up to 93.8 dB, effectively protecting electronic devices [131]. These materials integrate electrical conductivity and magnetic behavior, creating Faraday cage-like protection without adding significant weight. Corrosion protection is critical to maintaining aircraft structural integrity. Polymer-matrix nanocomposites reinforced with inorganic nanoparticles offer durable and lightweight coatings. Examples include CoFe<sub>2</sub>O<sub>4</sub>/PANI composites and graphene oxide-enhanced epoxy systems, which exhibit excellent anticorrosive properties [132]. Additionally, anti-icing nanocomposites, such as Fe<sub>3</sub>O<sub>4</sub>- or CNT/SiO<sub>2</sub>-based materials, delay ice formation and reduce adhesion, making them highly suitable for extreme polar aviation environments [133]. SHM is vital to ensure aircraft safety by detecting structural damage or failures promptly [134,135]. Piezoelectric nanocomposites, such as PZT/PDMS-based materials, are used in sensors to monitor structural integrity in real time, even at high temperatures. These materials exhibit superior piezoelectric performance, making them ideal for aerospace applications in extreme environments [136].

However, the increased adoption of composites introduces substantial challenges, particularly in managing their end-of-life phase. Unlike metals, which are efficiently recyclable through established processes, CFRPs are difficult to recycle due to their thermoset polymer matrices [137]. These matrices consist of cross-linked molecular structures that cannot be remelted or reshaped, rendering traditional recycling methods ineffective [77]. As a result, composite waste often ends up in landfills or is incinerated, practices that are increasingly unsustainable both economically and environmentally [138,139].

The end-of-life phase of an aircraft typically occurs after 25 to 30 years of service [77]. While components like engines, avionics, and landing gear are salvaged, re-certified, and resold, the airframe, which contains a significant amount of composite materials, poses a major disposal challenge [77]. Landfilling composite waste is becoming less viable due to increasing costs, diminishing landfill space, and stricter environmental regulations [140]. Additionally, some composites are classified as hazardous waste, requiring expensive treatments before disposal [138]. Incineration, another common disposal method, reduces waste volume but destroys valuable carbon fibers and generates harmful emissions [141]. For an industry striving to reduce its environmental footprint, these methods are no longer

sustainable. The need for alternative solutions is pressing, especially as the global aerospace fleet is projected to double by 2040, further amplifying the volume of composite waste.

Recycling composite materials presents an opportunity to mitigate EoL challenges while aligning with global sustainability goals [127]. The production of virgin carbon fibers is energy-intensive and costly, making the recovery of these fibers from waste an attractive solution. Recycling can help address the growing demand for carbon fibers, which are projected to face shortages in the near future, while also reducing environmental impacts and fostering a circular economy [142–144]. Composite recycling methods can be categorized into three main approaches: thermal, chemical, and mechanical.

Recognizing the urgency of the issue, leading aerospace manufacturers Airbus and Boeing have spearheaded initiatives to develop sustainable EoL solutions for composites.

Airbus has been at the forefront of composite recycling through projects like PAMELA (Process for Advanced Management of End-of-Life Aircraft) and its evolution, LIFE-PAMELA, supported by the European Commission [56]. These initiatives demonstrated that up to 85–90% of an aircraft's materials could be reused, recycled, or recovered. Metals like aluminum and titanium were relatively easy to process, but the projects also explored advanced methods for composite recovery, laying the groundwork for future advancements. Airbus's participation in the Clean Sky 2 program underscores its commitment to sustainable aviation. This public–private partnership focuses on developing greener technologies, including the integration of sustainable materials and improving the recyclability of composites in future aircraft designs. Airbus has set an ambitious target to recycle 95% of materials from retired aircraft by 2025, with particular emphasis on recovering high-value carbon fibers. The 2022 report of Airbus stated that they are able to recover more than 90% of an aircraft's weight at end-of-life through a selective dismantling process [145].

Boeing's efforts in composite recycling are equally significant. Through its leadership in the Aircraft Fleet Recycling Association, Boeing has helped establish global standards for EoL aircraft recycling [146]. AFRA's Best Management Practices (BMP) provide guidelines for dismantling and recovering materials from retired aircraft, emphasizing economic and environmental viability [59]. The ecoDemonstrator program is another cornerstone of Boeing's sustainability strategy. This initiative has recycled over 90% of materials from test aircraft, leveraging advanced recycling techniques [147]. Boeing's collaboration with ELG Carbon Fibre, a leader in carbon-fiber recycling, has resulted in the recovery of fibers through pyrolysis, which are then repurposed for use in non-structural aerospace components and other industries. Boeing is also exploring the integration of recycled fibers into manufacturing processes, creating lighter and more cost-effective components. These efforts align with Boeing's broader commitment to achieving net-zero carbon emissions and reducing resource consumption.

Beyond individual manufacturers, collaborative efforts play a crucial role in advancing composite recycling technologies. The Re-Carbon Project, funded by the European Union, focuses on developing scalable chemical and thermal recycling methods to recover high-quality carbon fibers and reintegrate them into new composites, creating a closed-loop manufacturing cycle. The UK's HiPerDiF (High-Performance Discontinuous Fibre) project explores using recycled fibers to produce high-performance materials, demonstrating that, with proper processing, recycled fibers can match or even exceed virgin fiber performance in some applications. The Composite Recycling Technology Center (CRTC) in Washington State is a notable example of innovation in recycling. This nonprofit organization collaborates with manufacturers to repurpose scrap carbon fiber into consumer products, reducing waste and promoting circular economy principles.

The future of composite materials in aerospace hinges on developing efficient and scalable recycling solutions. Airbus and Boeing's leadership, combined with collaborative

research efforts, exemplify the industry's commitment to addressing EoL challenges. Advanced recycling technologies, such as enhanced solvolysis and low-temperature pyrolysis, offer promising avenues for improving recovery rates and fiber quality.

Emerging trends, including the use of bio-based resins and thermoplastics, aim to simplify recycling processes by enabling re-melting and reshaping. Additionally, investments in artificial intelligence and machine learning could optimize recycling workflows, improving material sorting and processing efficiency.

As composite usage continues to grow, the aerospace industry must integrate sustainability principles into all stages of the lifecycle. By fostering innovation and collaboration, manufacturers can transform EoL challenges into opportunities, ensuring the long-term viability of composite materials while meeting environmental and economic goals.

### 3.1.3. Metal Wastestreams

Metal materials have been fundamental in shaping modern aircraft manufacturing, evolving alongside advancements in the aerospace industry. From the wooden airframes of early aviation in 1903 to the widespread adoption of aluminum alloys in 1927, metals have played a pivotal role due to their strength-to-weight ratios, damage tolerance, and high-temperature performance [148]. Despite the increasing use of composite materials, metals remain indispensable. This discussion investigates into the primary metal materials used in aircraft manufacturing, such as aluminum, magnesium, and titanium alloys, while also addressing recycling and sustainability practices.

Aluminum alloys have served as the cornerstone of aerospace materials for over 80 years, prominently featured in airframes, fuselages, and structural components [149,150]. Their low cost, manufacturability, and lightweight properties make them ideal for aircraft structures. Aluminum alloys are broadly categorized into cast and wrought types, with wrought alloys accounting for 80% of applications due to their superior strength and lightweight characteristics [79]. Among the aluminum alloys, the 2000 series, such as the Al-Cu-based 2024 alloy, is renowned for its damage tolerance and fatigue resistance. Enhanced versions, like the 2224-T39 alloy, exhibit higher tensile strength through refined microstructural features [44]. Meanwhile, the 7000 series, including the Al-Zn-based 7075 alloy, stands out for its exceptional strength, although advances such as the 7085 alloy have improved its fracture toughness and corrosion resistance. Al-Li alloys, like the 2199, further enhance stiffness and reduce weight, making them suitable for fuselage and wing skins, although challenges like anisotropy persist [79].

Magnesium alloys, celebrated as the lightest structural metals, offer significant weight reduction, which increases payload capacity. Despite this advantage, their mechanical properties and corrosion resistance pose challenges. To address these, alloying with elements such as aluminum, zinc, and rare-earth metals has proven effective [151]. Mg-Al alloys achieve solid-solution strengthening, while Mg-Zn alloys exhibit improved strength and ductility. Alloys with rare-earth additions, like the  $Mg_{97}Zn_1Y_2$  alloy, reach impressive yield strengths through advanced techniques such as powder metallurgy [152].

Titanium alloys have seen increasing use in aerospace applications, growing from 1% to 19% of an aircraft's operating empty weight in modern designs. Known for their high specific strength, corrosion resistance, and high-temperature performance, these alloys are categorized into alpha, beta, and alpha-beta types [148]. Alpha alloys excel at high temperatures, beta alloys offer superior formability and strength, and alpha-beta alloys provide a balance of these properties, making them widely applicable in both structural and engine components [153]. Notable examples include Ti-6Al-4V, used in compressor parts and structural elements, and Ti-10V-2Fe-3Al, employed in arrestor hook structures due to its high tensile strength.

Other metal alloys, such as stainless steel, nickel-based, and cobalt-based variants, are essential for high-temperature and high-pressure environments, particularly in engine blocks. These materials ensure durability and reliability under extreme conditions, contributing to the efficiency and performance of modern aircraft [154].

Recycling and sustainability efforts have become integral to the aerospace industry. For instance, aluminum, which constitutes 80% of a civil aircraft's weight, is extensively recycled. Programs like Bombardier's aircraft dismantling initiative recover over 1500 reusable parts per aircraft, integrating reclaimed materials back into production [155]. Innovations in recycling processes have preserved the mechanical properties of aluminum and titanium alloys, fostering circular manufacturing practices. Ongoing advancements in aerospace materials research aim to enhance alloy compositions and processing techniques. By optimizing elements such as zinc, magnesium, and copper, engineers improve mechanical properties while reducing costs and environmental impact. The integration of advanced alloys with composite materials further reflects the industry's commitment to balancing performance with sustainability.

The correct management of metal components is fundamental for effective recycling and for the consequent reduction in environmental impact, given the large amount of energy required for the production of raw materials through primary processes. In addition, modern aircraft contain a significant amount of electronic material which is subject to strict regulations that complicate its recovery. At their end-of-life, these materials are known as waste electrical and electronic equipment (WEEE).

The majority of aircraft wiring consists of conductive metals such as copper, silver, and aluminum, which come in various sizes and shapes and are coated with plastic insulation. In recent years, fiber optic cables have also been incorporated into aircraft design. Among these materials, copper remains the primary choice for electrical wiring in aviation. For example, the Boeing 787 Dreamliner contains approximately 60 miles of wiring, while the Boeing 777 has around 100 miles of cables [78].

When aircraft wiring is dismantled, recycling becomes more manageable. Larger wires are typically shredded and granulated into smaller pieces to facilitate separation of metals from plastic insulation. Methods such as gravity, electrical, and optical separation are commonly employed for this purpose. One example is the use of an eddy-current separator, which processes granulated copper wires to separate the metal from the plastic. Afterward, both materials can be repurposed for use in new aircraft through melting and reprocessing. However, recycling very thin copper wires is more challenging. In such cases, burning the plastic insulation may be the primary method for recovering the metal. The heat generated during the burning process can also be harnessed as an energy source within the industry. Depending on the wire size, complexity, and recycling methods employed, recovery rates for wires and cables can range from 50% to 90% or higher [83].

The proper management of WEEE is a complex topic. In European Union, the management of this waste is regulated by Directive 2012/19/EU [156]. The regulation attributes to the producer the responsibility for the EOL of the product, thus encouraging the development of a product that can be more easily disassembled. The directive also encourages the recovery of valuable metals. The wastestream of WEEE begins with the disposal in a collection center. Then, hazardous materials are separated from other components. The waste is ready to be mechanically processed. After shredding, other separation techniques are performed to isolate plastics (by density), ferrous and non-ferrous metals [157].

### 3.2. Recycling Technologies

Recovery technologies represent a large field filled with very different approaches to face the wastestream management. As shown in Table 1, each recycling route show

intrinsically advantages and disadvantages related to the materials processability, energy consumption and environmental impact. Actually, there is not a common framework to select one technology upon the others other than a balanced economical analysis based on regulatory framework and marketplace. Nevertheless, some general guidelines and good practices are arising across the companies.

**Table 1.** Comparative evaluation of recycling technologies.

Technology	Materials Treated	Advantages	Disadvantages
Thermal processes	<ul style="list-style-type: none"> <li>■ Polymers</li> <li>■ Polymer-based composites</li> </ul>	<ul style="list-style-type: none"> <li>■ Raw material recovery</li> <li>■ Composites reinforcement recovery</li> <li>■ No need of pre-treatments</li> <li>■ Well-established technology</li> <li>■ Affordable plants</li> </ul>	<ul style="list-style-type: none"> <li>■ Highly energy-intensive</li> <li>■ Degradation of starting materials</li> </ul>
Melting and forging	<ul style="list-style-type: none"> <li>■ Metal-based materials</li> </ul>	<ul style="list-style-type: none"> <li>■ Recovery of quasi-pure metal streams</li> </ul>	<ul style="list-style-type: none"> <li>■ Highly energy-intensive</li> <li>■ Need for pretreatments</li> </ul>
Mechanical processes and disassembling	<ul style="list-style-type: none"> <li>■ Polymers</li> <li>■ Composites</li> <li>■ Metals</li> </ul>	<ul style="list-style-type: none"> <li>■ Minimally energy-intensive</li> <li>■ Recovery of non-processed pure materials streams</li> </ul>	<ul style="list-style-type: none"> <li>■ Contamination</li> <li>■ Time-consuming</li> </ul>
Chemical processes	<ul style="list-style-type: none"> <li>■ Polymers</li> <li>■ Polymer-based composites</li> </ul>	<ul style="list-style-type: none"> <li>■ Recovery of high value materials</li> </ul>	<ul style="list-style-type: none"> <li>■ Need for pretreatments</li> <li>■ Highly energy-intensive</li> <li>■ High environment impact</li> <li>■ High cost</li> </ul>
Landfilling	<ul style="list-style-type: none"> <li>■ All materials</li> </ul>	<ul style="list-style-type: none"> <li>■ Cheap</li> <li>■ Minimally energy-intensive</li> </ul>	<ul style="list-style-type: none"> <li>■ Tremendous environmental impact</li> <li>■ Loss of raw materials</li> </ul>

### 3.2.1. Thermal Processes

Thermal recycling involves the heat-induced decomposition of polymeric matrix wastestreams with the recovery of reusable raw materials [158] and combustibles both gaseous and liquid [159]. The common methods for thermal recycling include pyrolysis, gasification, and incineration [160].

Incineration is a process that consists of completely burning waste materials and maintaining low levels of emissions, dramatically reducing the waste volume producing inert residues and heat [161]. Its use in the treatment and management of waste dates back to the 19th century and is still practiced today. Incineration is carried out at high temperatures, generally between 750 °C and 1200 °C, in an oxygen-enriched atmosphere in order to guarantee the total combustion of the waste [162], as this means that polluted flue gases can be formed and cleaned before being released into the atmosphere. The solid residue produced is a powder material classified into bottom and fly ash. Bottom ashes are solid combustion residues while fly ash is generally recovered from flue gas cleaning. Both types of ash can either be landfilled or reused, depending on their composition and processing [163]. Different kind of furnaces suitable for specific kinds of waste were developed for incineration, including rotary kilns [164], fluidized bed incinerators [165], and moving grate furnaces [166]. Rotary kilns incinerators are versatile systems mainly used for the treatment of hazardous materials composed by cylindrical furnaces that can rotate to give uniform mixing of waste [167]. Fluidized bed incinerators are cylindrical

furnaces inside which there is a bed of inert material [168] and heated air to separate fillers from resin particles for polymer-based carbon-fiber composites. In this case, the process starts by heating the air to 450–500 °C, which volatilizes the organic resin while enabling the sand to transport the non-organic materials, such as fibers and fillers, for further collection [169]. The clean fibers are separated from the gas stream using a cyclone, and the gas is then reheated to around 1000 °C in a secondary combustion chamber to fully combust any residual organic material [158]. This reheating step also allows for energy recovery in the form of heat from the polymers. The fluidized bed process offers efficient heat transfer and mixing, as well as precise temperature control, making it applicable across various industries [170]. Initially, it was used to recover glass fibers, but its scope has expanded to include carbon fibers, which have a higher economic value. Recovered carbon and glass fibers can be reused in applications such as molding compounds and veil-type products [171]. Research on the process has focused on understanding and improving the quality of recovered fibers, as reported by Yip et al. [158]. Authors reported that the key factors influencing the process are the bed temperature and fluidizing velocity, allowing for the recovery of short and randomly oriented carbon fibers. Pickering et al. [172] applied the fluidized bed process to recover fibers from various composite materials, including chopped E-glass fiber sheets and automobile body panels made from E-glass/polyester. Interestingly, the temperature of the fluidized bed was found to inversely affect fiber strength, with higher temperatures leading to reduced fiber strength. Additionally, veils fabricated using a mixture of recovered and virgin fibers exhibited reduced strength as the proportion of recovered fibers increased, highlighting the influence of fiber length, strength, and content on the final product's performance. Kennerley et al. [173] designed a test rig to recover glass fibers from polyester-based sheet-molding compounds. Their study confirmed that the temperature of the fluidized bed had a greater impact on fiber strength than fluidizing velocity, with higher temperatures weakening the fibers. Recovered glass fibers, often contaminated with fillers, required washing and treatment to improve their compatibility with the matrix [174]. These treated fibers were used to manufacture polyester dough-molding compounds, with tests revealing that while flexural and tensile strength decreased as the proportion of recovered fibers increased, stiffness remained unaffected. This outcome suggests that recovered fibers can be incorporated into composite materials without significant loss in mechanical properties, particularly at concentrations up to 50%. Moving grate furnaces are the most common system for incineration of municipal solid waste for many reasons. This technology does not require any preprocessing of waste showing a good flexibility and it can work continuously ensuring efficient treatment for different waste compositions. It involves placing the feedstock onto a moving grate, where it falls through different zones and is exposed to oxygen and burnt [87,175]. In fact, plastic waste materials are burned primarily to recover energy instead to recovery raw materials. The heat released during the combustion of organic components can be captured and transformed into other forms of energy such as electricity [118]. Nevertheless, several factors reduced the efficiency of energy recovery from composites including the high filler loading as in the case sheet-molding compounds (SMC). SMC is composed only of 35 wt.% resin, which is the only degradable organic material [176]. Additionally, some fillers act as a proper flame retardant reducing the overall energy efficiency of incineration [177] generating solid residues that are difficult to use [178].

Gasification is a thermal process used to convert organic materials into syngas, a mixture primarily composed of carbon monoxide and hydrogen. Industrially, gasification is typically run using autothermal using a sub-stoichiometric amount of oxygen in the atmosphere at temperatures ranging from 800 to 1200 °C [179]. Gasification can be used to recycle components composed of carbon-based composite materials, such as PCM [180];

this method is particularly relevant for aerospace applications, where components such as carbon-fiber-reinforced polymers (CFRPs) are extensively used [181,182]. However, gasification still faces relevant challenges such as the loss of metal from PCM components with a significant treat for the air quality [180]. Nonetheless, gasification provides an environmentally alternative to traditional incineration methods according to European environmental regulations under the Green Deal plan [183].

Alternatively to oxidizing processes, pyrolysis is performed in the absence of oxygen, inhibiting the production of combustion-related products in a temperature range up to 800 °C [184]. The process leads to the generation of three fractions, gases, liquids, and solid char, with yields varying accordingly to both feedstocks and process parameters used [185,186]. As a result, the pyrolytic process is able to create added value compared to incineration, even if it is highly energy intense [187]. The highest processing temperature and heating rate and residence time are the more relevant parameters and they can be used to tune the fraction ratio [188]. Oils can be used directly as drop-in fuel for energy purposes, or further refined to produce higher-value-added fuels [189]. The gas fraction generally contains hydrogen, small hydrocarbons, and traces of both carbon monoxide and dioxide based on the feedstock used [185,186], while solids can be used for several applications [190–195]. When the feedstock is composed of plastic wastes, polymers undergo a depolymerization process that leads to the formation of monomers or short-chain hydrocarbons [189,196]. Thermal pyrolysis is suitable for the treatment of a large number of wastes, including contaminated and mixed materials (e.g., mixed plastics). It offers an effective solution for processing EOL aircraft materials, such as common polyolefins and polyesters, without the need for cleaning or separation of materials. Moreover, pyrolysis has demonstrated potential application for recovery of polymer composite materials, such as CFRP and GFRP. A wide number of studies explored the feasibility of this method for the recovery of good-quality carbon fibers [197–199]. Many studies demonstrated properties suitable for other kinds of applications. In addition to the recovery of hydrocarbons and gases, this process allows for the recovery of carbon fibers with high mechanical properties, slightly lower than the virgin product. Furthermore, the use of appropriate process parameters guarantees the achievement of good surface properties of the fiber, allowing its reuse in field such as automotive. Given the potential of the process, which guarantees the recovery of high-added-value materials, many companies have started projects for the development of pilot plants, aiming to a large-scale development [200–203].

Alternatively to thermal pyrolysis, microwave-assisted pyrolysis have been explored even if it struggles to reach large-scale development due to intrinsic issues related to temperature control [204–207]. Nevertheless, the processing of composites represent an interesting application for such techniques considering that is not necessary the addition of any additives for boosting the microwave-induced heating [208–214]. As mentioned by Lester et al. [215], the processing of carbon-fiber composites can be easily processed with high-quality fibers that can be recovered a limited number of times. Alternatively, microwave techniques can be combined with solvent media for the recycling of complex materials such as poly(carbonate) glasses for the production of high-value monomers [216,217].

### 3.2.2. Melting and Forging

After the aircraft is scrapped, the recovered metals are mechanically treated (shredding) in order to reduce their size for better handling. When an aircraft reaches the end of its life, the recovery and recycling of materials begins with a mechanical shredding process to reduce the size of recovered metals for easier handling. After shredding, various sorting technologies, such as density separation with air streams, eddy-current separation, and

magnetic separation, are employed to segregate the materials, which are then sold to recyclers [218,219]. In some cases, flotation techniques are also utilized for additional sorting. This process is exemplified by Bartin's dismantling and shredding facilities in Châteauroux and Bourges, although other companies may adopt slightly different approaches that generally follow a similar framework [18].

The primary metals recovered from end-of-life aircraft include aluminum, alloy steel, titanium, and tungsten, with aluminum being the predominant material, especially in the fuselage and wings. Tungsten is often found in counterweights, and copper wires can also be separated. Certain dismantlers recover smaller quantities of rare and precious metals, such as those in electrical connectors, although these are often neglected due to their limited presence. Most of the recovered metals, like aluminum, are of mixed quality. The mixed quality of recovered aluminum, which often contains different alloys, limits its reuse in more demanding applications. However, since the primary production of aluminum is an energy-intensive process, the demand for it to be recycled is huge [220]. For example, EOL aircraft aluminum may contain a combination of different alloys, primarily from the 7000 and 2000 series, along with traces of other metals like steel and titanium from rivets. Additionally, composites, plastics, and textiles are frequently mixed in, especially if the aircraft's interior is not fully removed before scrapping [218]. While manual dismantling could improve material quality, it significantly increases costs, particularly in regions with high labor expenses. Thus, a trade-off exists between the costs of manual dismantling and the quality of recovered materials. To address this, advancements in automated dismantling techniques, such as small drilling robots to recover specific types of aluminum, steel, and titanium rivets, could offer a more cost-effective solution.

Recycling avionics and electronics from EOL aircraft poses additional challenges. These components can be shredded in waste electrical and electronic equipment shredders to recover rare earths and precious metals, but the quality of the recovered fragments is often suboptimal. Moreover, the recycling of emerging aluminum alloys, such as aluminum–lithium (Al–Li), aluminum–scandium (Al–Sc), and aluminum–magnesium–lithium (Al–Mg–Li), presents unresolved issues. For instance, the presence of lithium in aluminum scrap creates explosion risks during remelting, making it undesirable in recycling processes [218].

Regarding aircraft engines, these components follow a distinct recycling process due to their high-value precious metals such as gold and platinum which, when present in sufficient concentrations, are extracted from engine parts [18]. Rare earths in engine disks can be remelted and used in manufacturing new turbines. In some cases, components like turbine blades are repurposed for land-based gas turbines. After salvaging high-value components, the remaining parts are further separated to maximize reuse or recycling potential. Specialized machinery is used for these processes, with certificates of destruction issued to confirm that the parts will no longer be used in aviation [221].

The melting process is the main method for recycling of metal components from EOL aircrafts. It consists of heating selected metal scrap to form molten material, which can be cast to form new high-value-added products or secondary raw material in form of ingots or billets [221]. The melting and recycling of metal scraps from EOL aircraft represents a critical process in advancing both environmental sustainability and material efficiency. Melting can be performed at industrial scale, enabling large volumes of metal scrap to be processed efficiently. The molten material can be re-alloyed, purified, or combined with other metals to meet specific needs.

A melting process for specific aluminum alloys was patented [222]. It outlines a general method for recycling aluminum alloys. The process begins with the selection of scraps by alloy series (e.g., 2XXX or 7XXX) and their preprocessing, aimed to remove metallic contaminations, lubricants and other impurities, ensuring a purer raw material for sub-

sequent stages. Advanced technologies, such as Laser-Induced Breakdown Spectroscopy (LIBS) developed by companies like Huron Valley Steel Company, play a crucial role in accurately classifying large aircraft components. This technology enables precise differentiation of elemental content in alloys, improving the flexibility and cost-effectiveness of recycling [223].

Then, the scraps are melted in a furnace and cooled following a controlled temperature ramp. This process allows us to further purify the solid metal while impurities, such as iron and silicon, concentrated in the remaining liquid phase. The purified solid block can either be directly used or subjected to further processing. The remelting process for scrap aluminum offers significant economic and environmental advantages compared to traditional production methods, which rely on bauxite as the primary raw material and use energy-intensive electrolysis [224]. The cost savings of aluminum recycling and remelting can reach up to 90%, accompanied by considerable energy savings [225]. Furthermore, the molten aluminum obtained from scrap is generally of higher purity than electrolytic aluminum which required additional purification step in order to avoid non-metallic slags containing alkali metal ions such (i.e., sodium, calcium, and lithium) as well as alumina and carbon particles that can compromise material quality [226,227]. Once the chemical composition of the molten metal is accurately analyzed using spectrometers, it is transferred to casting furnaces to produce aluminum alloy products with various specifications. By adjusting the alloy composition ratios, products tailored for diverse applications can be created [228].

The third-generation aluminum–lithium alloys have increasingly found applications in the aviation industry. Lithium, a rare and valuable metal, adds significant economic and environmental value to recycling efforts. While aluminum–lithium alloys are broadly classified as aluminum-based materials, their recycling and smelting processes differ considerably from conventional aluminum alloy recycling due to challenges in controlling impurities such as potassium and sodium [229]. Recycling aluminum–lithium alloys can follow several routes. One method involves separating lithium as a pure metal, while another focuses on extracting lithium and converting it into lithium compounds. Alternatively, the alloys can be transformed into other grades of aluminum–lithium or smelted with salt flux to regenerate the material into its original grade. The extraction of pure lithium from aluminum–lithium alloys typically relies on techniques such as vacuum distillation, three-layer liquid electrolysis, and hierarchical solidification. With the exception of distillation, these processes often begin by converting lithium into lithium halide, which is then processed through metallurgical methods to obtain pure lithium. This closed-loop recycling approach for aviation metal materials addresses a portion of the demand for raw materials, mitigates the risk of supply-chain disruptions, reduces costs, and significantly lowers the environmental impact associated with mining and processing metals [230].

A similar approach can be performed for the recovery of nickel-based superalloys. These materials are often alloyed with critical raw materials for the European Union. This aspect significantly increases the need for recycling. The recovery of nickel superalloys starts with the determination of chemical composition of scraps, performed by a spectrometer. After the selection, scraps are recycled in a two-step method that consists of a remelting in an electric furnace followed by a purification step, performed in vacuum conditions. This process is often characterized by considerable material losses (up to 20 wt.%, in particular of alloy elements); this problem can be overcome by adding slag-forming elements such as fluorspar during the electric furnace treatment [231,232]. Another melting process for the recovery of Ni-based superalloys involves the presence of a slag with predetermined composition. The technique consists of an electro slag remelting. A non-consumable electrode is used to generate electric currents, leading to the melting of the slag. The process, fed with

superalloy scraps, develops very high temperatures that melt the Ni superalloys scraps. The presence of the slag preserves the material from oxidation and minimizes material losses. Finally, high-quality ingots are recovered. The technology is suitable for recycling Ni-based superalloys from aeronautical components [233].

A novel process for the recovery of nickel from Ni-based superalloys was proposed by Cui et al. [234]. In their research, authors used molten magnesium as extraction medium to recover nickel from superalloys scraps. The process, performed at 800 °C, exploits the preferential dissolution of nickel in magnesium, respectively, to other impurities. It results in a Ni-Mg alloy that is then subjected to vacuum distillation. The process leads to the recovery of high-purity nickel and to the reusability of magnesium (99.99% purity).

For titanium recycling, the most widely used technologies are plasma-arc melting (PAM) and vacuum-arc remelting (VAR), both carried out in strictly controlled atmospheres in order to prevent oxidation and contamination of the metal bath. These processes can be combined in order to optimize the composition of the final product. PAM process, carried out in argon atmosphere, exploits the use of a plasma torch to generate high-temperature plasma arc. The process is fed with selected titanium scraps that melt into the crucible. Since the process is not capable of removing some impurities, a secondary treatment (VAR) can be performed to refine titanium quality. VAR involves the melting of a titanium electrode in a vacuum chamber. An electric arc between electrode and molten metal causes its melting into a mold. The ingot exhibits low contaminations thanks to the vacuum environment, which is critical for reducing gaseous impurities. The combination of the processes guarantees the quality of the final product, ensuring the reuse in aerospace industry [235]. Once the material composition has been restored to the desired level, ingots and billets can be processed through forging. The technology consists of the mechanical treatment of heated ingots to shape them into the desired geometry. Since it is a thermomechanical treatment that develops very high pressures on the material, it allows us to refine the metal microstructure boosting important properties for aeronautical applications, such as tensile strength and fatigue resistance [236,237]. For what concerns titanium alloys, the process is usually carried out at temperatures higher than their  $\beta$ -transus temperature. This process favors dynamic recrystallization of the microstructure, assuring better mechanical properties to the final product [238]. Differently from titanium, aluminum can undergo forging as direct recycling method, without passing any remelting process. The technology involves the preparation of billets by hot-pressing aluminum sorted scraps, making this technology less energy-intensive than a traditional remelting. Anyway, if superior quality is required, the feedstock for forging process should be a remelted aluminum alloy [239].

### 3.2.3. Mechanical Processes

Mechanical recycling is a process used in recycling systems to recover materials through physical forces, either as a standalone method for fabric or fiber recycling or as a pre-treatment for thermomechanical, chemical, or biochemical recycling processes, as defined by ISO 5157:2023 [240]. Mechanical recycling, currently at Technology Readiness Level 9 (TRL 9), is an established technology in the market with already decades of experience [241]. This method involves the size reduction in materials through steps such as shredding, crushing, or milling, which enhances the separation of fibers from resins. Unlike thermal and chemical recycling, mechanical recycling does not generate toxic gases such as carbon monoxide or greenhouse gases such as carbon dioxide [242].

Initially, materials are cut or milled into fragments approximately 100 mm in size [118]. To facilitate transport and minimize risks, metal inserts are extracted using magnetic fields. This step is crucial as metallic components can pose fire hazards caused by metal fragments hitting machinery may ignite flammable materials like cotton [243]. Removing these

components also prevents machinery damage and ensures a gentler separation of fibers. Ferromagnetic parts are easily removed with magnets, while non-ferrous components are separated based on density using centrifugal force after fragmentation [241]. After metal removal, the material undergoes further downsizing using high-speed mills. The resulting fragments are sorted by size using hydrocyclones, sieves, and shaking screens [118]. Coarser products have a higher fiber content, while finer, powder-like fractions are richer in fillers and polymer content [79,172]. Finely ground materials can be reused as fillers or reinforcements in the manufacturing of new composites [244,245]. Although mechanical recycling has been applied to both carbon- and glass-fiber composites, research has primarily focused on fiberglass composites [246,247]. For example, Kouparitsas et al. [248] analyzed a grinding–sifting process for recovering fibers from epoxy-based carbon-, glass-, and aramid-fiber composites. The recovered fibers were combined with virgin resin matrices to create new thermoset composites. Tensile tests showed favorable performance for these samples compared to those made with virgin fibers. Bernasconi et al. [249] studied the tensile strength of polyamide 6,6 reinforced with 35% reprocessed fiberglass obtained via specimen grinding. Their results revealed that increasing the recycled fiber content led to decreased tensile strength and elastic modulus, while the strain at break increased. Similarly, Ogi et al. [250] explored composites made of ABS resin reinforced with CFRP. They found that specimens with higher concentrations of crushed CFRP exhibited increased strength, with optimal performance at a 50:50 ratio of CFRP to ABS. However, using milled CFRP fibers resulted in lower strength and modulus compared to crushed fibers. Takahashi et al. [251] evaluated continuous fiber-reinforced thermoplastic (CFRTP) pellets containing varying amounts of recycled CFRP fibers. Injection-molded panels and specimens were tested for bending, tensile, and impact properties. Panels with longitudinal fiber alignment demonstrated an increase in flexural modulus with higher fiber concentrations, while transversal panels showed consistent modulus values regardless of concentration. The optimal fiber concentration for such panels was determined to be 24%, balancing mechanical performance and manufacturability. Repeated recycling, involving four cycles of crushing and injection molding, did not significantly alter the mechanical properties of the specimens.

Despite ongoing research efforts to preserve mechanical properties, mechanical recycling is often employed as a preliminary step before thermal or chemical recycling due to its tendency to damage fibers and reduce their length. This reduction in fiber length significantly impacts the mechanical performance of the recycled composites, as the resulting discontinuous carbon fibers cannot achieve properties comparable to those of long or continuous carbon fiber composites. As an alternative to traditional shredding, Roux et al. [252] demonstrated the use of electrodynamic fragmentation to process composite materials, specifically door hinges from the aerospace industry. By precisely controlling the applied voltage, this method avoided mechanical shredding, resulting in a mechanical performance reduction of only 17% compared to the original material. Despite its promise, implementing this technique in industrial applications would require the development of a continuous-flow processing machine.

In the context of aircraft, textiles slated for recycling typically come from components such as seat upholstery, carpets, curtains, and other cabin fabrics. These materials accumulate wear and tear overtime due to high passenger turnover and the demanding conditions of flight operations [253]. Additionally, textiles from safety gear like seatbelts or life vests might be included if they meet recycling criteria. Unlike composites, textile recycling must contend with diverse chemical treatments, dyes, and finishes that can influence the recyclability of the material [243]. Processes such as sorting by material type and color are crucial to ensure consistent output quality, as certain combinations can degrade the performance

or appearance of recycled textiles [254]. Additionally, textiles often require a more intensive cleaning process, including the removal of oils, dyes, and surface treatments that are not typically encountered in composite recycling [255]. The end products, ranging from yarns and fabrics to insulation materials, rely heavily on maintaining the flexibility, dyeability, and texture of the fibers, which are central to their reuse in various industries [256].

#### 3.2.4. Chemical Processes

Chemical recycling, alongside thermal recycling, represents a key focus of ongoing research efforts [242]. It involves breaking down polymers into monomers or partially depolymerizing them into oligomers through chemical reactions in wet environment using additional reactants and solvents [257]. Primarily applied to CFRPs [258], chemical recycling aims to produce recycled carbon fibers that maintain their original mechanical properties and morphology while also reducing the energy demands of thermal methods [259]. In fact, chemical recycling typically achieves the best mechanical performance for recycled carbon fibers. The recycled fibers, fillers, and degraded organic materials can be reused in various applications. Key factors influencing the process include temperature, pressure, catalysts, and the type of solvent employed. Chemical recycling techniques generally operate at temperatures below 400 °C. Solvolysis methods are further categorized by their operating conditions: high temperature (>200 °C) and high pressure, or lower temperature (<200 °C) and low pressure [260]. Based on the solvent used, chemical recycling can be classified into solvolysis and hydrolysis [178,261]. After dissolving the polymer matrix, the recovered fibers are thoroughly washed to eliminate residual surface impurities [262]. The resulting fibers retain their original length and optimal mechanical properties.

In the solvolysis process, organic solvents are used for the chemical degradation of the polymers. The solvolysis process can be applied to both carbon fibers and glass fibers. However, the research on the application of the solvolysis process on carbon fibers is slightly more advanced than the research focused on recovering glass fibers [263]. Liu et al. [124] investigated the recovery of fibers from carbon/epoxy composites using a nitric acid bath. The optimal parameters identified were a temperature of 90 °C, an acid concentration of 8 M, and a sample-to-solution ratio of 4 g:100 mL, resulting in a minor strength loss of 1.1% for the recovered fibers when using a 6 g:100 mL ratio. Nakagawa et al. [264] applied the solvolysis process to recover carbon fibers from carbon-fiber-reinforced plastics. This involved depolymerizing the material using potassium phosphate tribasic ( $K_3PO_4$ ) and benzyl alcohol (BYA). The recovered fibers were used to fabricate recycled CFRP, which exhibited better tensile elongation and strength compared to mass-produced glass-fiber-reinforced plastics, with an equivalent tensile modulus. Xu et al. [265] employed a two-step solvolysis process to recover fibers from carbon-fiber/epoxy composites. The first step involved treatment with acetic acid, washing with acetone, and drying to increase surface area. In the second step, the material was treated in a hermetic reactor with hydrogen peroxide ( $H_2O_2$ ) and *N,N*-dimethylformamide (DMF) under varying temperatures (80–100 °C), concentrations, and durations (5–120 min). The method effectively decomposed most of the epoxy resin, revealing smooth fibers. Tensile tests demonstrated that the recovered fibers retained at least 95% of the tensile strength of virgin carbon fibers. As far as solvolysis is concerned, research has been conducted at lab scale with the focus on carbon-fiber composites, but a commercial application does not yet exist. According to Wong et al. [77] in 2017, a solvolysis pilot plant with an annual capacity of 100 tonnes of composite will be built by Vartega Carbon Fibre Recycling LLC in the United States.

The use of harmful and concentrated chemicals can lead to a significant environmental impact. To minimize the environmental problems as well as the harmfulness and toxicity of

hazardous and concentrated chemicals, much research is focused on the use of subcritical or supercritical water and alcohol as a substitute for these chemicals [242].

The hydrolysis process uses water as the solvent for the chemical degradation of polymers. Kao et al. [266] investigated how experimental parameters affect the mechanical strength of glass fibers. Fiberglass-based composite samples were immersed in sub-critical distilled water, with variables including temperature, duration, catalyst concentration, and water volume. Fibers recovered at lower temperatures over longer periods retained better mechanical properties but only preserved about 60% of their original strength. Reduced water volumes led to incomplete resin removal, leaving residues on the fibers. Liu et al. [267] supplemented the solvolysis process with additives such as phenol and potassium hydroxide (KOH) to improve decomposition efficiency in CFRP. The highest epoxy decomposition was achieved at a 1/10/100 g/g/mL ratio of KOH, phenol, and water, with recovered fibers retaining tensile strength comparable to virgin fibers. Oliveux et al. [268] applied a design of experiments approach to study the effects of process parameters on the recycling of carbon-fiber-reinforced epoxy composites. The use of KOH as a catalyst improved the resin removal rate from 79.3% to 95.3%, with recovered fibers maintaining 90–98% of their tensile strength compared to virgin fibers.

Sub- and supercritical solvents require significant energy to achieve their state due to high pressure and temperature. Okajima et al. [269] tested various solvents, including supercritical acetone, which proved optimal for rapidly degrading the matrix. Carbon fibers recovered using supercritical acetone showed no matrix residues and retained their tensile strength. Similarly, Sokoli et al. [270] used supercritical acetone to recover both glass and carbon fibers from FRPs. While glass fibers had residual matrix deposits, carbon fibers were perfectly clean, with intact mechanical properties. The authors highlighted the potential for upscaling solvolysis due to the reusability of all product streams. Das et al. [271] explored peracetic acid, formed from acetic acid and hydrogen peroxide, as an oxidative method for CFRP recycling. Recovered carbon fibers had clean surfaces and tensile strength comparable to virgin fibers. The method allows for solvent recovery with over 90% efficiency, operating at lower temperatures and pressures, resulting in reduced environmental impact. Khalil et al. [272] reviewed seventeen supercritical fluids for thermoset resin depolymerization in CFRP waste, showing that higher temperatures and pressures improve resin removal efficiency but increase the environmental footprint. Supercritical mixtures of solvents and water were found to be effective for fiber recovery with lower energy intensity, reducing environmental impact. However, the scalability of chemical recycling processes remains a significant challenge.

### 3.3. Landfill

A landfill area is a site for disposal of waste materials. According to the EU's waste hierarchy, landfilling is the least preferable option and should be limited to the necessary minimum [18]. In some cases, the recovery of EOL materials is not a viable solution. As it is the case for energy recovery, the process of sending aviation waste to landfill is not aviation specific.

Nowadays, technology has made many progresses in recycling and approximately 85% in weight of an aircraft is recycled or reused, while around 15% by weight is sent to landfill [273]. Sending waste to landfill implies costs for aircraft dismantlers; these costs change depending on each region. If bigger volumes are sent, higher costs are derived [18]. Typically, the EOL aircraft materials disposed in landfills are composite materials (e.g., carbon fibers), for which recovery methodologies have only recently been developed, hazardous materials and some components that make up the interiors of aircraft, such as insulation blankets, ceiling panels, and others. The main problem with these

components is the presence of flame retardants and additives, which leads to restrictions according to existing regulations [273,274]. In the United States, the management of these wastes falls under the U.S. Environmental Protection Agency (EPA). In particular, Land Disposal Restrictions (40 CFR Part 268) defines the guidelines to be adopted for the correct management of hazardous waste, illustrating standard treatments to which such waste must be subjected. Furthermore, it establishes limit concentration values for hazardous substances that must be respected by wastes to be sent for disposal [275,276].

In Europe, landfill management is regulated by the Landfill Directive (Directive 1999/31/EC), aimed at minimizing negative effects on human health and the environment; the directive provides strict technical requirements for the treatment of waste so that it can be disposed of in landfills, categorized into three groups depending on the materials stored: landfills for inert waste (which do not undergo significant degradation over long periods), landfills for non-hazardous waste, and landfills for hazardous waste [277]. In 2018, the amendment “Directive (EU) 2018/850” to Directive 1999/31/EC was approved with the aim of progressively limiting the use of landfills until reaching a target by 2035: reducing the quantity of waste disposed of up to a maximum of 10% of the total weight of municipal waste produced [278].

Since landfill disposal is neither a recycling nor a recovery process, it is always the last option pursued for the treatment of end-of-life materials. Despite this, the technique has been widely exploited due to the low initial investment costs compared to other recovery technologies, which require large resources for the development of the plants, and the relatively small amount of manpower required [279]. This type of disposal contributes to the contamination of the soil and surrounding waters and generates greenhouse gases [280,281]. Furthermore, it represents a loss of potentially recoverable resources in the perspective of a circular economy.

#### 4. Cost and Environmental Considerations

A lifecycle cost (LCC) analysis is critical to evaluating whether recycling retired aircraft is economically viable compared to traditional disposal methods, such as landfill and incineration. Recycling typically involves significant upfront costs, including dismantling, sorting, and processing materials, with estimates suggesting that dismantling costs alone range from USD 800 to USD 2000 per ton of aircraft weight. However, this process yields valuable materials such as aluminum, titanium, and carbon fibers. For instance, recycled aerospace-grade aluminum can generate revenues of approximately USD 1500 per ton, offsetting some of the costs. On the other hand, traditional disposal methods, like landfilling, cost between USD 50 and USD 100 per ton in regions with low landfill fees, making them initially cheaper.

Findings from Zhao et al. [44] provide further insights into the economic performance of aircraft EoL solutions. The study, based on averaged data and cases of Boeing 737–300 and 747–400 aircraft, highlights that disassembly and dismantling (D&R) processes for engines yield relatively greater economic benefits compared to the full aircraft. Aircraft are most economically recycled immediately upon reaching their disposal point, whereas long-term parking with maintenance is more cost-intensive. The study emphasizes that a higher salvage value and lower D&R costs significantly enhance economic performance. This is further supported by Net Present Value (NPV) evaluations, which validate the effectiveness of economic indicators in guiding decisions about disassembly, dismantling, or resale during the early stages of an aircraft’s EoL.

Adding to this, Liberacki et al. [282] highlight that contrary to common assumptions, aircraft EoL is not climate-neutral, and different disposal methods have varying environmental impacts. According to their analysis, recycling is the only disposal method with

significant environmental benefits. Incineration, while having negligible impacts on carbon emissions compared to the global warming potential (GWP) of the manufacturing and operational phases, is not optimal for recovering valuable materials embedded in components. Similarly, landfill disposal is environmentally negligible, providing neither major benefits nor harms. A notable example from related industries, such as electric vehicle production, demonstrates the advantages of recycling: recycling processes can reduce lifecycle greenhouse gas (GHG) emissions by up to 34%. For aircraft, this reduction in emissions during the manufacturing phase underscores the importance of selecting recycling as the preferred disposal method.

Recycling retired aircraft can cut greenhouse gas emissions by up to 70% compared to producing virgin materials. For example, carbon-fiber recycling through advanced methods, such as pyrolysis or solvolysis, saves up to 50% of the energy required for virgin carbon-fiber production. Balancing LCC and lifecycle assessment (LCA) analyses demonstrates that while traditional disposal methods may offer cost advantages in certain regions, recycling becomes increasingly viable when environmental costs, long-term economic trends, and regulatory pressures are considered. Integrating the findings from Zhao et al. and Liberaki et al., it is evident that adopting recycling as the main EoL strategy not only aligns with economic indicators but also ensures significant sustainability benefits, contributing to the circular economy of the aerospace sector.

## 5. Regulatory Prospectives

As has been indicated in the previous sections, there is currently no regulation worldwide about EoL specifically targeting aircraft. There is, however, regulation that affects aircraft EoL, such as the waste legislation, which enters into play after the dismantling process has started, when the different aircraft parts and materials become waste. There is a Regulatory Position Statement from the UK Environment Agency regarding the removal of airworthy parts from waste aircraft as well.

In the EU, the EoL Vehicles Directive is in effect, although it is focused on road vehicles. Setting related regulations would help changing the current situation, in which aircraft disassembling customers (leasing companies rather than airlines) often do not tend to include sustainability and circular economy considerations into their decision to choose a particular company to take care of their EoL aircraft. It is important to keep in mind that when designing this type of solution, the perspectives and experiences from other sectors are beneficial and useful. For example, experiences from the automotive industry as well as the maritime transportation are relevant for the implementation of specific solutions for the aviation industry.

In addition, when proposing solutions, these should be considered from the perspective of the global system (Table 2).

International aspects need to be considered, otherwise there are risks in, for instance, establishing comprehensive and strict legislation in Europe that could lead to the relocation of aircraft-disassembling and -dismantling activities to other countries where these regulations would not apply.

The inclusion of any of these regulation aspects are to be discussed in detail among all relevant stakeholders before taking definitive decisions (for instance, AFRA, GAMA, IATA, etc.). Regulations are important but are one of the many measures available. Therefore, a balanced approach should be taken, including regulatory aspects when required and to the extent which is found to be necessary and/or supporting stakeholders' work towards sustainability and circular economy.

As part of the EU Circular Economy Action Plan (adopted March 2020), there will be upcoming legislation on eco-design (but only for specific groups of products, which do not

include aircraft). Textiles, construction, and electronics are the priority under the scope of the EU. Therefore, it is recommended to consider integrating aircraft into these groups. Aircraft sector is to lead by example, translating eco-designs into the aviation business.

**Table 2.** Regulation and best practice in the matter of reuse and disposal of aircrafts.

Standard/Regulation	Mandatory/Recommended	EU, NON-EU, Internal, Other	Brief Topic Description
ISO 9001	Recommended	Internal	Quality management systems
ISO 14001	Recommended	Internal	Environmental management systems
REACH	Mandatory	EU	Registration, Evaluation, Authorization and Restriction of Chemicals
OSHA 1910	Mandatory	Non-EU	Occupational safety and health standards in the U.S.
EASA Part M	Mandatory	EU	Requirements for the continuing airworthiness management of aircraft components
EASA Part 145	Mandatory	EU	Company-level certification for maintenance and operations on aircraft components
EASA Part 21 Subpart G	Mandatory	EU	Approval of organizations for the production of aeronautical components
EASA Part 147	Mandatory	EU	Regulation of maintenance training organizations
EASA Part 66	Mandatory	EU	European aircraft maintenance license recognized across EU Member States
EASA Part T	Mandatory	EU	Airworthiness management of third-country aircraft leased short-term
EASA Part ML	Mandatory	EU	Simplified rules for maintaining non-complex aircraft
EASA Part CAMO	Mandatory	EU	Requirements for continuing airworthiness management organizations
EASA Part CAO	Mandatory	EU	Combined requirements for managing maintenance and airworthiness of non-complex aircraft
Regulation (EU) 2018/1139	Mandatory	EU	Common aviation rules and triennial environmental review
ASA-100/FAA AC00-56	Recommended	Non-EU	Voluntary accreditation program for aviation parts distributors
UK Position Statement 164	Mandatory	Non-EU	Removal of airworthy parts from waste aircraft without an environmental permit
ICAO Annex 16	Mandatory	Other	Environmental protection: noise, emissions, CO <sub>2</sub> standards, and CORSIA program
AFRA BMP	Recommended	Other	Best management practices for aircraft parts recycling and facility accreditation by the Aircraft Fleet Recycling Association
IATA BIPAD	Recommended	Other	Guidelines for sustainable aircraft decommissioning addressing economic, safety, and environmental aspects
IATA PAO: TO	Recommended	Other	Guidance for implementing paperless aircraft operations, focusing on cost-efficiency, compliance, and knowledge management.
IATA Cabin Waste Handbook	Recommended	Other	Best practices for cabin waste management, including recycling solutions and waste reduction strategies

In addition, the inclusion of aircraft in the EoL Vehicles Directive could be analyzed, in order to provide clear aviation targets for reuse, recycling, and recovery of aircraft parts and materials, and mechanisms for its monitoring. This inclusion would have to consider the evolution of materials and in aircraft manufacturing over the years, as well as the new technologies, such as electric or hydrogen-powered aircraft. It is important to note that the current End-of-Life Vehicles Directive places the responsibility on manufacturers, importers, and distributors to collect the road vehicles and provide systems for their reuse and recycling—this responds to the “polluter pays” principle, indicated in the EU Waste Framework Directive. The application of this responsibility to the aviation counterparts would have to be discussed, in order to assess which stakeholders (manufacturers, distributors, owners, etc.) should have it. The application of this Directive should always be adapted in a way that optimizes environmental benefit without incentivizing the relocation of the aircraft disassembling and dismantling activities into other countries.

Also, the European Waste Directive is to be harmonized among the different European countries. The current application leads to differences within the different EU member states, which needs to be solved in order to reach equality. This is a general recommendation to ensure the harmonization of the Directive, rather than making aircraft owners carriers of waste, which would be troublesome and which would not reflect the fact that many parts and components would re-enter the aerospace sector to be reused.

## 6. Conclusions

The recovery of raw materials from end-of-life aircraft represents a crucial issue for the sustainability of aerospace industry, considering the increase in decommissioned aircraft due to fleet modernization and regulatory changes. The present comprehensive review highlighted the pillar technological approach for each wastestream produced during in aircraft decommissioning, focusing on material recovery and environmental sustainability. Despite technological advancements, several challenges remain in optimizing aircraft recycling processes due to the highly heterogeneous composition of aircraft, economic constraints, regulatory compliance, and the mandatory standardized protocols required for aircraft dismantling operations. The proper combination of chemical, mechanical, and thermochemical routes represent the only way to properly valorize the high-tech materials, including fiber-reinforced plastics and aerospace alloy. Nevertheless, it requires the efforts of regulatory agency to push the producers towards a more sustainable end-of-life management framework. To address these challenges, collaboration among industry stakeholders, policymakers, and academia represents the only synergistic route to properly assess it, merging both sustainability-related and economic goals.

**Author Contributions:** Conceptualization, S.Z. and M.B.; validation, S.Z., G.C., C.R., A.T. and M.B.; investigation, S.Z. and G.C.; data curation S.Z. and M.B.; writing—original draft preparation, S.Z., G.C., C.R., A.T. and M.B.; writing—review and editing S.Z., G.C., C.R., A.T. and M.B.; visualization, S.Z.; supervision, C.R., A.T. and M.B., project administration, C.R., A.T. and M.B.; funding acquisition, C.R. and A.T. All authors have read and agreed to the published version of the manuscript.

**Funding:** This research received no external funding.

**Data Availability Statement:** No new data were created or analyzed in this study.

**Conflicts of Interest:** The authors declare no conflicts of interest.

## References

1. European Commission. Communication from the commission to the european parliament, the council, the european economic and social committee and the committee of the regions. In *A new Circular Economy Action Plan For a Cleaner and More Competitive Europe*; European Commission: Brussels, Belgium, 2020.
2. Fawzy, S.; Osman, A.I.; Doran, J.; Rooney, D.W. Strategies for mitigation of climate change: A review. *Environ. Chem. Lett.* **2020**, *18*, 2069–2094. [CrossRef]
3. Ghadge, A.; Wurtmann, H.; Seuring, S. Managing climate change risks in global supply chains: A review and research agenda. *Int. J. Prod. Res.* **2020**, *58*, 44–64. [CrossRef]
4. European Commission; Directorate-General for Climate Action. *Going Climate-Neutral by 2050: A Strategic Long-Term Vision for a Prosperous, Modern, Competitive and Climate-Neutral EU Economy*; Publications Office of the European Union: Luxembourg, 2019.
5. Ritchie, H. What Share of Global CO<sub>2</sub> Emissions Come from Aviation? Available online: <https://ourworldindata.org/global-aviation-emissions> (accessed on 30 October 2024).
6. KPMG. *Circularity in Flight: The Potential for Aircraft and the Circular Economy*; KPMG: Dublin, Ireland, 2024.
7. RTDS Group. New HORIZON 2020 Project SUSTAINair to Provide Flight Path for Green Deal Transition. Available online: <https://cordis.europa.eu/article/id/429554-new-horizon-2020-project-sustainair-to-provide-flight-path-for-green-deal-transition> (accessed on 30 October 2024).
8. Prentice, B.; DiNota, A.; Dulac, N.; Hayes, L.; Ferguson, I.; Holden, D.; Mishra, U.; Huang, R. *Global fleet and MRO market forecast 2024-2034*; Oliver Wyman: New York, NY, USA, 2024.
9. Zhou, J. InsightIQ: Explore How Retirement Trends Have Evolved with InsightIQ. Available online: <https://www.iba.aero/resources/articles/insightiq-explore-how-retirement-trends-have-evolved-with-insightiq/> (accessed on 30 October 2024).
10. Oliver Wyman. *Projected Size of the Global Aircraft Fleet from 2020 to 2024, with a Forecast for 2034*. Available online: <https://www.statista.com/statistics/282237/aircraft-fleet-size/> (accessed on 21 August 2025).
11. Keivanpour, S.; Kadi, D.A.; Masclé, C. End of life aircrafts recovery and green supply chain (a conceptual framework for addressing opportunities and challenges). *Manag. Res. Rev.* **2015**, *38*, 1098–1124. [CrossRef]

12. Sabaghi, M.; Cai, Y.; Mascle, C.; Baptiste, P. Recycling. Sustainability assessment of dismantling strategies for end-of-life aircraft recycling. *Resour. Conserv. Recycl.* **2015**, *102*, 163–169. [CrossRef]
13. Airbus. PAMELA-Process for Advanced Management of End-of-Life Aircraft. Available online: <https://webgate.ec.europa.eu/life/publicWebsite/project/LIFE05-ENV-F-000059/process-for-advanced-management-of-end-of-life-of-aircraft> (accessed on 21 August 2025).
14. European Commission. *Eu Research results. Aircraft Metal Recycling*; European Commission: Brussels, Belgium, 2022.
15. SUSTAINair. Available online: <https://www.sustainair.eu/> (accessed on 10 December 2024).
16. Airbus. From Aircraft to Bikes, Airbus Is Breaking away to Upcycle Carbon Waste. Available online: <https://www.airbus.com/en/newsroom/news/2021-05-from-aircraft-to-bikes-airbus-is-breaking-away-to-upcycle-carbon-waste> (accessed on 11 December 2024).
17. Boeing. Boeing, ELG Carbon Fibre Find New Life for Airplane Structure Material in Ground-Breaking Partnership. 2018. Available online: <https://boeing.mediaroom.com/2018-12-05-Boeing-ELG-Carbon-Fibre-find-new-life-for-airplane-structure-material-in-groundbreaking-partnership> (accessed on 21 August 2025).
18. The European Union Aviation Safety Agency. *Study–Assessment of the Environmental Sustainability Status in the Aviation Maintenance and Production Organisation (M&P) Domain*; The European Union Aviation Safety Agency: Cologne, Germany, 2022.
19. Mascle, C. Product design for rebirth: Application to aircraft life cycle modeling. In *Supply Chain Forum: An International Journal*; Taylor & Francis: Abingdon, UK, 2013; pp. 70–83.
20. Immarigeon, J.; Holt, R.; Koul, A.; Zhao, L.; Wallace, W.; Beddoes, J.C. Lightweight materials for aircraft applications. *Mater. Charact.* **1995**, *35*, 41–67. [CrossRef]
21. Baker, A.A. *Composite Materials for Aircraft Structures*; American Institute of Aeronautics and Astronautics: Reston, VA, USA, 2004.
22. Plan, R. *Communication from the Commission to the European Parliament, the European Council, the Council, the European Economic and Social Committee and the Committee of the Regions*; European Commission: Brussels, Belgium, 2018.
23. Hool, A.; Helbig, C.; Wierink, G. Challenges and opportunities of the European critical raw materials act. *Miner. Econ.* **2024**, *37*, 661–668. [CrossRef]
24. Carrara, S.; Bobba, S.; Blagoeva, D.; Dias, P.A.; Cavalli, A.; Georgitzikis, K.; Grohol, M.; Itul, A.; Kuzov, T.; Latunussa, C.E. *Supply Chain Analysis and Material Demand Forecast in Strategic Technologies and Sectors in the EU: A Foresight Study*; Publications Office of the European Union: Luxembourg, 2023.
25. Bobba, S.; Carrara, S.; Huisman, J.; Mathieux, F.; Pavel, C. *Critical Raw Materials for Strategic Technologies and Sectors in the EU. A Foresight Study*; Publications Office of the European Union: Luxembourg, 2020.
26. Li, M.; Lu, J. Cobalt in lithium-ion batteries. *Science* **2020**, *367*, 979–980. [CrossRef] [PubMed]
27. Kumari, A.; Sahu, S.K. A comprehensive review on recycling of critical raw materials from spent neodymium iron boron (NdFeB) magnet. *Sep. Purif. Technol.* **2023**, *317*, 123527. [CrossRef]
28. U.S. Geological Survey. *Mineral Commodity Summaries, Rare Earths*; European Commission: Brussels, Belgium, 2021.
29. Grohol, M.; Veeh, C. *Study on the Critical Raw Materials for the EU 2023*; Publications Office of the European Union: Luxembourg, 2023.
30. Breuer, U.P. *Commercial Aircraft Composite Technology*; Springer: Cham, Switzerland, 2016; Volume 115.
31. Zhang, X.; Boscolo, M.; Figueroa-Gordon, D.; Allegri, G.; Irving, P.E. Fail-safe design of integral metallic aircraft structures reinforced by bonded crack retarders. *Eng. Fract. Mech.* **2009**, *76*, 114–133. [CrossRef]
32. Khalil, Y.F. Eco-efficient lightweight carbon-fiber reinforced polymer for environmentally greener commercial aviation industry. *Sustain. Prod. Consum.* **2017**, *12*, 16–26. [CrossRef]
33. McLaughlin, J.W.; Tobin, E.; O’Higgins, R.M. An investigation of Polyether Imide (PEI) toughening of carbon fibre-reinforced Polyether Ether Ketone (PEEK) laminates. *Mater. Des.* **2021**, *212*, 110189. [CrossRef]
34. Raj, R.J.; Selvam, P.; Pughalendi, M. A review of aluminum alloys in aircraft and aerospace industry. *J. Huazhong Univ. Sci. Technol* **2021**, *1671*, 4512.
35. Singh, P.; Pungotra, H.; Kalsi, N.S. On the characteristics of titanium alloys for the aircraft applications. *Mater. Today Proc.* **2017**, *4*, 8971–8982. [CrossRef]
36. Akca, E.; Gürsel, A. A review on superalloys and IN718 nickel-based INCONEL superalloy. *Period. Eng. Nat. Sci. (PEN)* **2015**, *3*, 15–27. [CrossRef]
37. Johanning, A.; Scholz, D. *A First Step Towards the Integration of Life Cycle Assessment into Conceptual Aircraft Design*; Deutsche Gesellschaft für Luft-und Raumfahrt-Lilienthal-Oberth eV: Bonn, Germany, 2014.
38. Woidasky, J.; Klinke, C.; Jeanvré, S. Materials stock of the civilian aircraft fleet. *Recycling* **2017**, *2*, 21. [CrossRef]
39. Hellard, G. Composites in Airbus: A long story of innovations and experiences. In Proceedings of the Airbus Global Investor Forum, Seville, Spain, 21–22 September 2008.

40. Abalde-Cela, S.; Aldeanueva-Potel, P.; Mateo-Mateo, C.; Rodríguez-Lorenzo, L.; Alvarez-Puebla, R.A.; Liz-Marzán, L.M. Surface-enhanced Raman scattering biomedical applications of plasmonic colloidal particles. *J. R. Soc. Interface* **2010**, *7*, S435–S450. [CrossRef] [PubMed]
41. Boeing Commercial Airplanes. Available online: [https://en.wikipedia.org/wiki/Boeing\\_Commercial\\_Airplanes](https://en.wikipedia.org/wiki/Boeing_Commercial_Airplanes) (accessed on 22 September 2025).
42. Kesarwani, S. Polymer composites in aviation sector. *Int. J. Eng. Res* **2017**, *6*, 518–526. [CrossRef]
43. Airbus. Orders and Deliveries. Available online: <https://www.airbus.com/en/products-services/commercial-aircraft/orders-and-deliveries> (accessed on 22 September 2025).
44. Zhao, D.; Guo, Z.; Xue, J. Research on scrap recycling of retired civil aircraft. *IOP Conf. Ser. Earth Environ. Sci.* **2021**, *657*, 012062. [CrossRef]
45. Ekici, S.; Sohret, Y.; Coban, K.; Altuntas, O.; Karakoc, T.H. Sustainability metrics of a small scale turbojet engine. *Int. J. Turbo Jet-Engines* **2018**, *35*, 113–119. [CrossRef]
46. Boichenko, S.; Ivanchenko, O.; Yakovlieva, A. *Modern Trends in Technologies for air Transport Recycling and Utilization*; Politechnika Rzeszowska im. Ignacego Lukaszewicza: Rzeszów, Poland, 2017.
47. *Aluminum Times*; Mmcpublications: Brighton, UK, 2018; Volume 5, p. 40.
48. Hamama, Z. Tear-Downs and End-of-Life Solutions. Available online: <https://www.firnas-aero.com/2018/05/04/tear-downs-and-end-of-life-solutions/> (accessed on 18 November 2024).
49. Fortune Business Insights. Commercial Aircraft Disassembly, Dismantling and Recycling Market Size, Share & COVID-19 Impact Analysis, by Application (Disassembly & Dismantling, Recycling & Storage, USM, and Rotable Parts), by Aircraft Type (Narrow Body, Wide Body, and Regional Jet), and Regional Forecast, 2023–2033. Available online: <https://www.fortunebusinessinsights.com/commercial-aircraft-disassembly-dismantling-and-recycling-market-103584> (accessed on 18 November 2024).
50. Yang, C. More opportunities in retired aircraft. *Aviat. Maint. Eng.* **2018**, *324*, 15–19.
51. Wang, Y.; Zou, G.; Liu, C.; Gao, Y. Comparison of fire extinguishing performance of four halon substitutes and Halon 1301. *J. Fire Sci.* **2021**, *39*, 370–399. [CrossRef]
52. Kendig, M.; Jeanjaquet, S.; Addison, R.; Waldrop, J. Role of hexavalent chromium in the inhibition of corrosion of aluminum alloys. *Surf. Coat. Technol.* **2001**, *140*, 58–66. [CrossRef]
53. AFRA-Who We Are? Available online: <https://afraassociation.org/about-us/> (accessed on 18 November 2024).
54. Aircraft Fleet Recycling Association (AFRA). *Recycling Best Management Practice (BMP) for Management of Used Aircraft Parts and Assemblies (rev. 4.0)*; AFRA: Castle Hill, NSW, Australia, 2018.
55. Boeing. Boeing and Alenia to Support Italy's First Composite Industrial Recycling Plant. Available online: <https://boeing.mediaroom.com/2008-07-15-Boeing-and-Alenia-to-Support-Italys-First-Composite-Industrial-Recycling-Plant> (accessed on 21 August 2025).
56. Airbus, S. *Process for Advanced Management of End-of-Life of Aircraft (PAMELA)*; Airbus Academy: Champniers, France, 2008.
57. Ribeiro, J.S.; de Oliveira Gomes, J. Proposed framework for end-of-life aircraft recycling. *Procedia CIRP* **2015**, *26*, 311–316. [CrossRef]
58. Jiang, H. *Trends in Fleet and Aircraft Retirement*; The Boeing Company: Renton, WA, USA, 2015.
59. Elsayed, A.; Roetger, T.; Bann, A. Best practices and standards in aircraft end-of-life and recycling. In *Chapter Eight: Towards a Circular Economy*; International Civil Aviation Organisation: Montreal, Canada, 2019; pp. 279–284.
60. Maaß, S. Aircraft Recycling—A Literature Review. 2020. Available online: <https://repo.uni-hannover.de/handle/123456789/11639> (accessed on 21 August 2025).
61. Müller, T. Aircraft Metals Recycling-Process, Challenges and Opportunities. In Proceedings of the 7th European Aeronautics Days (Aeroday 2015), London, UK, 21 October 2015.
62. Tarmac Aerosave. Tarmac Aerosave-History. Available online: <https://www.tarmac-aerosave.aero/history> (accessed on 20 November 2024).
63. Airbus, Tarmac Aerosave and Chengdu to Launch China's First Aircraft Lifecycle Center. Available online: <https://aircraft.airbus.com/en/newsroom/press-releases/2023-04-airbus-tarmac-aerosave-and-chengdu-to-launch-chinas-first-aircraft> (accessed on 21 August 2025).
64. Summers, B. Old Airplane Tires Are Turned into... What? Available online: <https://www.cntraveler.com/stories/2016-05-27/old-airplane-tires-are-turned-into-what> (accessed on 25 November 2024).
65. Yoo, T.W.; Lee, Y.K.; Lim, S.J.; Yoon, H.G.; Kim, W.N. Effects of hybrid fillers on the electromagnetic interference shielding effectiveness of polyamide 6/ conductive filler composites. *J. Mater. Sci.* **2014**, *49*, 1701–1708. [CrossRef]
66. Harrison-Obi, C.N. Environmental impact of end of life tyre (ELT) or scrap tyre waste pollution and the need for sustainable waste tyre disposal and transformation mechanism in Nigeria. *Nnamdi Azikiwe Univ. J. Int. Law Jurisprud.* **2019**, *10*, 60–70.
67. Yakovlieva, A.; Boichenko, S.; Kale, U.; Nagy, A. Recent advances in technologies for aircraft scrap tyres recycling and utilization. *Transp. Logist.* **2018**, *18*, 41–54.

68. Malik, J.; Karpate, Y.; Datta, A.; Sharma, S.; Sharpe, B.; Sundar, M.S.; Laferriere, M.; Garg, V. *Tire Technologies and Their Impact on Heavy-Duty Vehicle Fuel Efficiency in India*; Energy and Resources Institute: New Delhi, India; International Council on Clean Transportation: Washington, DC, USA, 2016.
69. Phale, A.R. *Environmental Impact and Waste Management of Used Tyres in the RSA*; University of Johannesburg: Johannesburg, South Africa, 2005.
70. Ramos, G.; Alguacil, F.J.; López Gómez, F.A. The recycling of end-of-life tyres. *Technol. Rev.* **2011**, *47*, 273–284.
71. Kumar, S.A. Tyre Retreading by Hot Retreading Process. *Int. J. Appl. Sci. Eng.* **2016**, *4*, 61–65. [[CrossRef](#)]
72. Gaidhane, J.; Ullah, I.; Khalatkar, A. Tyre remanufacturing: A brief review. *Mater. Today Proc.* **2022**, *60*, 2257–2261. [[CrossRef](#)]
73. Walter, C.; Kempainen, M. Market Research-Tyre Recycling in Finland and Germany: Case: Humuspehtoori Ltd. Bachelor's Thesis, Tampere University of Applied Sciences, Tampere, Finland, 2009.
74. Black, S. Advanced Materials for Aircraft Interiors. Available online: <https://www.compositesworld.com/articles/advanced-materials-for-aircraft-interiors> (accessed on 25 November 2024).
75. Hyvärinen, M.; Pylkkö, M.; Kärki, T. Closed-Loop Recycling and Remanufacturing of Polymeric Aircraft Parts. *J. Compos. Sci.* **2023**, *7*, 121. [[CrossRef](#)]
76. Pierobon, M. Under Construction: Composite Materials Replace Traditional Aircraft Materials. Available online: <https://www.aviationbusinessnews.com/cabin/composite-materials-aircraft/> (accessed on 25 November 2024).
77. Wong, K.; Rudd, C.; Pickering, S.; Liu, X. Composites recycling solutions for the aviation industry. *Sci. China Technol. Sci.* **2017**, *60*, 1291–1300. [[CrossRef](#)]
78. Asmatulu, E.; Twomey, J.; Overcash, M. Evaluation of recycling efforts of aircraft companies in Wichita. *Resour. Conserv. Recycl.* **2013**, *80*, 36–45. [[CrossRef](#)]
79. Asmatulu, E.; Overcash, M.; Twomey, J. Recycling of Aircraft: State of the Art in 2011. *J. Ind. Eng.* **2013**, *2013*, 960581. [[CrossRef](#)]
80. Buggy, M.; Farragher, L.; Madden, W. Recycling of composite materials. *J. Mater. Process. Technol.* **1995**, *55*, 448–456. [[CrossRef](#)]
81. Semitekolos, D.; Terzopoulou, S.; Zecchi, S.; Marinis, D.; Farsari, E.; Amanatides, E.; Sajdak, M.; Sobek, S.; Smok, W.; Tański, T.; et al. Performance Restoration of Chemically Recycled Carbon Fibres Through Surface Modification with Sizing. *Polymers* **2025**, *17*, 33. [[CrossRef](#)] [[PubMed](#)]
82. McLauchlin, A.R.; Ghita, O.R.; Savage, L. Studies on the reprocessability of poly(ether ether ketone) (PEEK). *J. Mater. Process. Technol.* **2014**, *214*, 75–80. [[CrossRef](#)]
83. Yi, J.; Yu, B.; Du, L.; Li, C.; Hu, D. Research on the selectable disassembly strategy of mechanical parts based on the generalized CAD model. *Int. J. Adv. Manuf. Technol.* **2008**, *37*, 599–604. [[CrossRef](#)]
84. Bartoli, M.; Malucelli, G.; Tagliaferro, A. Overview on Classification of Flame-Retardant Additives for Polymeric Matrix. In *Materials and Chemistry of Flame-Retardant Polyurethanes Volume 1: A Fundamental Approach*; ACS Publications: Washington, DC, USA, 2021; pp. 59–82.
85. Gopal, P.; Kavimani, V.; Sudhagar, S. Evolution and recent advancements of composite materials in industrial applications. In *Applications of Composite Materials in Engineering*; Elsevier: Amsterdam, The Netherlands, 2025; pp. 317–334.
86. Skoczylas, J.; Samborski, S.; Kłonica, M. The application of composite materials in the aerospace industry. *J. Technol. Exploit. Mech. Eng.* **2019**, *5*, 1–6. [[CrossRef](#)]
87. Makarichi, L.; Jutidamrongphan, W.; Techato, K.-a.J.R.; Reviews, S.E. The evolution of waste-to-energy incineration: A review. *Renew. Sustain. Energy Rev.* **2018**, *91*, 812–821. [[CrossRef](#)]
88. Sharma, D.K.; Mahant, D.; Upadhyay, G. Manufacturing of metal matrix composites: A state of review. *Mater. Today Proc.* **2020**, *26*, 506–519. [[CrossRef](#)]
89. Hooker, J.; Doorbar, P. Metal matrix composites for aeroengines. *Mater. Sci. Technol.* **2000**, *16*, 725–731. [[CrossRef](#)]
90. Singerman, S.; Jackson, J.; Lynn, M. Titanium metal matrix composites for aerospace applications. *Superalloys* **1996**, *3*, 579–586.
91. Chawla, K.K.; Chawla, K.K. *Metal Matrix Composites*; Springer: Cham, Switzerland, 1998.
92. Yokozeki, T.; Kotsuka, N.; Yoshida, K.; Fujiwara, K.; Sato, T. Damage characterization and numerical modeling of titanium matrix composites subjected to low-velocity impact for landing gear application. *Adv. Compos. Mater.* **2015**, *24*, 343–358. [[CrossRef](#)]
93. Xie, M.; Zhan, L.; Ma, B.; Hui, S. Classification of fiber metal laminates (FMLs), adhesion theories and methods for improving interfacial adhesion: A review. *Thin-Walled Struct.* **2024**, *198*, 111744. [[CrossRef](#)]
94. Costa, R.D.; Sales-Contini, R.C.; Silva, F.J.; Sebbe, N.; Jesus, A.M. A critical review on fiber metal laminates (FML): From manufacturing to sustainable processing. *Metals* **2023**, *13*, 638. [[CrossRef](#)]
95. Asghar, W.; Nasir, M.; Qayyum, F.; Shah, M.; Azeem, M.; Nauman, S.; Khushnood, S. Investigation of fatigue crack growth rate in CARALL, ARALL and GLARE. *Fatigue Fract. Eng. Mater. Struct.* **2017**, *40*, 1086–1100. [[CrossRef](#)]
96. van Hengel, C.; Kortbeek, P. Arall and Glare Fml's: Three Decades of Bridging the Gap Between Theory and Operational Practice. In Proceedings of the ICAF 2009, Bridging the Gap between Theory and Operational Practice: Proceedings of the 25th Symposium of the International Committee on Aeronautical Fatigue, Rotterdam, The Netherlands, 27–29 May 2009; pp. 601–615.

97. Vlot, A. The birth of Arall (1945–1981). In *Glare: History of the Development of a New Aircraft Material*; Springer: Cham, Switzerland, 2001; pp. 17–50.
98. Vlot, A. Taward Glare, fuselages and the US (1988–1997). In *Glare: History of the Development of a New Aircraft Material*; Springer: Cham, Switzerland, 2001; pp. 85–110.
99. Edwardson, S.; French, P.; Dearden, G.; Watkins, K.; Cantwell, W. Laser forming of fibre metal laminates. *Lasers Eng.* **2005**, *15*, 233–255.
100. Romli, N.; Rejab, M.; Bachtiar, D.; Siregar, J.; Rani, M.; Harun, W.; Salleh, S.M.; Merzuki, M. The behavior of Aluminium Carbon/Epoxy fibre metal laminate under quasi-static loading. *IOP Conf. Ser. Mater. Sci. Eng.* **2017**, *257*, 012046. [[CrossRef](#)]
101. Awi, M.; Abdullah, A.S. A Review on Mechanical Properties and Response of Fibre Metal Laminate under Impact Loading (Experiment). *Evergreen* **2023**, *10*, 111–129. [[CrossRef](#)]
102. Trabandt, U.; Wulz, H.G.; Schmid, T. CMC for hot structures and control surfaces of future launchers. *Key Eng. Mater.* **1999**, *164*, 445–449.
103. Zhang, Q.M. Research on ceramic matrix composites (CMC) for aerospace applications. *Adv. Mater. Res.* **2011**, *284*, 324–329. [[CrossRef](#)]
104. Zawada, L.; Lee, S. Evaluation of four CMCs for aerospace turbine engine divergent flaps and seals. In *Proceedings of the 19th Annual Conference on Composites, Advanced Ceramics, Materials, and Structures-A*; Wiley-American Ceramic Society: Hoboken, NJ, USA, 2009; Volume 16, p. 337.
105. Dale, D.; Ruschau, A. NASA Hytec CMC Turbine Blade Durability. 2023. Available online: <https://ntrs.nasa.gov/citations/20230008139> (accessed on 21 August 2025).
106. Misra, A. Composite materials for aerospace propulsion related to air and space transportation. In *Lightweight Composite Structures in Transport*; Elsevier: Amsterdam, The Netherlands, 2016; pp. 305–327.
107. Krenkel, W. Carbon fibre reinforced silicon carbide composites (C/SiC, C/C-SiC). In *Handbook of Ceramic Composites*; Springer: Cham, Switzerland, 2005; pp. 117–148.
108. Gerenda's, M.s.; Cadoret, Y.; Wilhelmi, C.; Machry, T.; Knoche, R.; Behrendt, T.; Aumeier, T.; Denis, S.; Göring, J.; Koch, D. Improvement of oxide/oxide CMC and development of combustor and turbine components in the HiPOC program. In *Proceedings of the Turbo Expo: Power for Land, Sea, and Air*; American Society of Mechanical Engineers: Washington, DC, USA, 2011; pp. 477–490.
109. Gadow, R.; Jiménez, M. Carbon fiber-reinforced carbon composites for aircraft brakes. *Am. Ceram. Soc. Bull.* **2019**, *98*, 28–34.
110. Krenkel, W.; Renz, R. CMCs for friction applications. *Ceram. Matrix Compos.* **2008**, 385–407. [[CrossRef](#)]
111. Liu, X.; Li, L. Design, Fabrication and Testing of CMC Turbine Blisk. In *Design, Fabrication and Testing of Aeroengine Ceramic-Matrix Composite Components*; Springer: Cham, Switzerland, 2024; pp. 71–94.
112. Ohnabe, H.; Masaki, S.; Onozuka, M.; Miyahara, K.; Sasa, T. Potential application of ceramic matrix composites to aero-engine components. *Compos. Part A Appl. Sci. Manuf.* **1999**, *30*, 489–496. [[CrossRef](#)]
113. Parveez, B.; Kittur, M.; Badruddin, I.A.; Kamangar, S.; Hussien, M.; Umarfarooq, M. Scientific advancements in composite materials for aircraft applications: A review. *Polymers* **2022**, *14*, 5007. [[CrossRef](#)]
114. Keller, K.A.; Jefferson, G.; Kerans, R.J. Oxide–oxide composites. In *Ceramic Matrix Composites: Materials, Modeling and Technology*; John Wiley & Sons: Hoboken, NJ, USA, 2014; pp. 236–272. [[CrossRef](#)]
115. Wehrel, P. *Technological Level of CMC Components for Stationary Gas Turbines and Aero-Engines*; German Aerospace Center (DLR), Institute of Propulsion Technology: Cologne, Germany, 2022.
116. Kameda, T.; Sayano, A.; Amiji, N.; Ichikawa, H.; Hamada, H.; Fujita, A.; Uozumi, T. Fabrication and mechanical properties of reaction sintered silicon carbide matrix composite. In *Proceedings of the 21st Annual Conference on Composites, Advanced Ceramics, Materials, and Structures—A: Ceramic Engineering and Science Proceedings*, Cocoa Beach, FL, USA, 26 March 1997; pp. 419–426.
117. Spriet, P. CMC applications to gas turbines. In *Ceramic Matrix Composites: Materials, Modeling and Technology*; Wiley: Hoboken, NJ, USA, 2014; pp. 591–608. [[CrossRef](#)]
118. Wang, P.H.; Zimmermann, N. Composite recycling techniques: A literature review. *Juniper Online J. Mater. Sci.* **2020**, *6*, 11–17. [[CrossRef](#)]
119. Kalanchiam, M.; Chinnasamy, M. Advantages of composite materials in aircraft structures, *World Acad. Sci. Eng. Technol.* **2012**, *71*, 597–601.
120. Neelakante Gowda, G.; Varughese, B.; Arumugam, G. 14-seater civil aircraft design with an innovative composite structure. *JEC Compos. Mag* **2013**, *6*, 951–952.
121. Viscardi, M.; Arena, M.; Cerreta, P.; Iaccarino, P. Design and prototyping of a novel composite architecture for a widebody landing gear bay. *Mater. Today Proc.* **2021**, *34*, 288–292. [[CrossRef](#)]
122. Arena, M.; Chiariello, A.; Castaldo, M.; Di Palma, L. Vibration response aspects of a main landing gear composite door designed for high-speed rotorcraft. *Aerospace* **2021**, *8*, 52. [[CrossRef](#)]

123. Viscardi, M.; Arena, M.; Cerreta, P.; Iaccarino, P.; Imparato, S.I. Manufacturing and validation of a novel composite component for aircraft main landing gear bay. *J. Mater. Eng. Perform.* **2019**, *28*, 3292–3300. [CrossRef]
124. Liu, Y.; Meng, L.; Huang, Y.; Du, J. Recycling of carbon/epoxy composites. *J. Appl. Polym. Sci.* **2004**, *94*, 1912–1916. [CrossRef]
125. Bachmann, J.; Hidalgo, C.; Bricout, S. Environmental analysis of innovative sustainable composites with potential use in aviation sector—A life cycle assessment review. *Sci. China Technol. Sci.* **2017**, *60*, 1301–1317. [CrossRef]
126. Fahrenholtz, W.G.; Hilmas, G.E.; Talmy, I.G.; Zaykoski, J.A. Refractory diborides of zirconium and hafnium. *J. Am. Ceram. Soc.* **2007**, *90*, 1347–1364. [CrossRef]
127. Yakovlieva, A.; Boichenko, S.; Kale, U.; Nagy, A. Holistic approaches and advanced technologies in aviation product recycling. *Aircr. Eng. Aerosp. Technol.* **2021**, *93*, 1302–1312. [CrossRef]
128. Li, X.; Xu, W.; Sutton, M.A.; Mello, M. In situ nanoscale in-plane deformation studies of ultrathin polymeric films during tensile deformation using atomic force microscopy and digital image correlation techniques. *IEEE Trans. Nanotechnol.* **2007**, *6*, 4–12. [CrossRef]
129. Jayakrishna, K.; Kar, V.R.; Sultan, M.T.; Rajesh, M. Materials selection for aerospace components. In *Sustainable Composites for Aerospace Applications*; Elsevier: Amsterdam, The Netherlands, 2018; pp. 1–18.
130. Zhang, N.; Zhao, R.; He, D.; Ma, Y.; Qiu, J.; Jin, C.; Wang, C. Lightweight and flexible Ni-Co alloy nanoparticle-coated electrospun polymer nanofiber hybrid membranes for high-performance electromagnetic interference shielding. *J. Alloys Compd.* **2019**, *784*, 244–255. [CrossRef]
131. Tang, X.-H.; Tang, Y.; Wang, Y.; Weng, Y.-X.; Wang, M. Interfacial metallization in segregated poly (lactic acid)/poly ( $\epsilon$ -caprolactone)/multi-walled carbon nanotubes composites for enhancing electromagnetic interference shielding. *Compos. Part A Appl. Sci. Manuf.* **2020**, *139*, 106116. [CrossRef]
132. Peng, T.; Xiao, R.; Rong, Z.; Liu, H.; Hu, Q.; Wang, S.; Li, X.; Zhang, J. Polymer nanocomposite-based coatings for corrosion protection. *Chem.-Asian J.* **2020**, *15*, 3915–3941. [CrossRef]
133. Zhang, G.; Zhang, Q.; Cheng, T.; Zhan, X.; Chen, F. Polyols-infused slippery surfaces based on magnetic Fe<sub>3</sub>O<sub>4</sub>-functionalized polymer hybrids for enhanced multifunctional anti-icing and deicing properties. *Langmuir* **2018**, *34*, 4052–4058. [CrossRef]
134. Hou, Y.; Choy, K.L. Durable and robust PVDF-HFP/SiO<sub>2</sub>/CNTs nanocomposites for anti-icing application: Water repellency, icing delay, and ice adhesion. *Prog. Org. Coat.* **2022**, *163*, 106637. [CrossRef]
135. Rocha, H.; Semprinoschnig, C.; Nunes, J.P. Sensors for process and structural health monitoring of aerospace composites: A review. *Eng. Struct.* **2021**, *237*, 112231. [CrossRef]
136. Qing, X.; Li, W.; Wang, Y.; Sun, H. Piezoelectric transducer-based structural health monitoring for aircraft applications. *Sensors* **2019**, *19*, 545. [CrossRef] [PubMed]
137. Marx, W.J.; Mavris, D.N.; Schrage, D.P. Cost/time analysis for theoretical aircraft production. *J. Aircr.* **1998**, *35*, 637–646. [CrossRef]
138. Guilvezan, G.; Carberry, B. Composite recycling and disposal; an environmental R&D issue. *Boeing Environ. Technotes* **2003**, *8*, 4.
139. Koblen, I.; Talpaš, L.; Jurčák, J. Selected aspects of aviation equipment disposal issue. *Review* **2012**, *102*, 1–145.
140. Witik, R.A.; Teuscher, R.; Michaud, V.; Ludwig, C.; Månson, J.-A.E. Carbon fibre reinforced composite waste: An environmental assessment of recycling, energy recovery and landfilling. *Compos. Part A Appl. Sci. Manuf.* **2013**, *49*, 89–99. [CrossRef]
141. Li, X.; Bai, R.; McKechnie, J. Environmental and financial performance of mechanical recycling of carbon fibre reinforced polymers and comparison with conventional disposal routes. *J. Clean. Prod.* **2016**, *127*, 451–460. [CrossRef]
142. Balaga, U.K.; Gunes, A.; Ozdemir, T.; Blackwell, C.; Davis, M.; Sauerbrunn, S.; Fuessel, L.; Deitzel, J.M.; Heider, D. Optimization of the Recycling Process for Aligned Short Carbon Fiber TuFF Composites. *Recycling* **2025**, *10*, 55. [CrossRef]
143. Ozdemir, T.; Deitzel, J.M.; Crane, R.; Yarlagadda, S.; Blackwell, C.; Davis, M.; Emmerich, R.; Heider, D. Carbon fiber composites recycling technology enabled by the TuFF technology. *Recycling* **2024**, *9*, 11. [CrossRef]
144. Lahive, C.W.; Dempsey, S.H.; Reiber, S.E.; Pal, A.; Stevenson, K.R.; Michener, W.E.; Alt, H.M.; Ramirez, K.J.; Rognerud, E.G.; Lincoln, C.L. Acetolysis for epoxy-amine carbon fibre-reinforced polymer recycling. *Nature* **2025**, *642*, 605–612. [CrossRef]
145. Airbus. Airbus Annual Financial Statement. 2022. Available online: <https://www.airbus.com/en/investors/annual-reports> (accessed on 25 September 2025).
146. Hitchcock, R. A panel discussion with the AFRA. In Proceedings of the AFRA Annual Conference, Las Vegas, NV, USA, 26–28 June 2016.
147. Aerosave, T. Available online: <http://www.tarmacaerosave.aero/index.php?lang=en> (accessed on 29 November 2024).
148. Zhang, X.; Chen, Y.; Hu, J. Recent advances in the development of aerospace materials. *Prog. Aerosp. Sci.* **2018**, *97*, 22–34. [CrossRef]
149. Dursun, T.; Soutis, C. Recent developments in advanced aircraft aluminium alloys. *Mater. Des. (1980–2015)* **2014**, *56*, 862–871. [CrossRef]
150. Starke, E.A., Jr.; Staley, J.T. Application of modern aluminum alloys to aircraft. *Prog. Aerosp. Sci.* **1996**, *32*, 131–172. [CrossRef]
151. Chen, Y.; Xu, Z.; Smith, C.; Sankar, J. Recent advances on the development of magnesium alloys for biodegradable implants. *Acta Biomater.* **2014**, *10*, 4561–4573. [CrossRef] [PubMed]

152. Czerwinski, F. Controlling the ignition and flammability of magnesium for aerospace applications. *Corros. Sci.* **2014**, *86*, 1–16. [[CrossRef](#)]
153. Veiga, C.; Davim, J.P.; Loureiro, A. Properties and applications of titanium alloys: A brief review. *Rev. Adv. Mater. Sci.* **2012**, *32*, 133–148.
154. Davis, J. *Aluminum and Aluminum Alloys*; ASM International: Novelty, OH, USA, 1993.
155. Modarress, B.; Ansari, A.; Ansari, A. Environmental degradation and the implementation of the circular economy in commercial aviation. *Sustain. J. Rec.* **2020**, *13*, 178–184. [[CrossRef](#)]
156. Directive, E.C. Directive 2012/19/EU of the European Parliament and of the Council of 4 July 2012 on waste electrical and electronic equipment (WEEE) (recast) Text with EEA relevance. *Off. J. Eur. Union L* **2012**, *197*, 38–71.
157. Cui, J.; Forsberg, E. Mechanical recycling of waste electric and electronic equipment: A review. *J. Hazard. Mater.* **2003**, *99*, 243–263. [[CrossRef](#)]
158. Yip, H.; Pickering, S.; Rudd, C. Characterisation of carbon fibres recycled from scrap composites using fluidised bed process. *Plast. Rubber Compos.* **2002**, *31*, 278–282. [[CrossRef](#)]
159. Hasan, M.; Haque, R.; Jahirul, M.; Rasul, M. Pyrolysis of plastic waste for sustainable energy Recovery: Technological advancements and environmental impacts. *Energy Convers. Manag.* **2025**, *326*, 119511. [[CrossRef](#)]
160. Roychand, R.; Zafar, M.A.; Jacob, M.; Ngo, T. A Comprehensive Review on the Thermochemical Treatment of Plastic Waste to Produce High Value Products for Different Applications. *Mater. Circ. Econ.* **2025**, *7*, 1–33. [[CrossRef](#)]
161. Mazhandu, Z.; Muzenda, E.; Belaid, M.; Mamvura, T.; Nhubu, T. Incineration as a potential solution to Africa’s plastic waste challenges: A narrative review. In Proceedings of the International Conference on Energy, Environment and Storage of Energy, Online, 19–21 November 2020; pp. 1–11.
162. Buekens, A. *Incineration Technologies*; Springer Science & Business Media: Berlin/Heidelberg Germany, 2013.
163. Manžuch, Z.; Akelytė, R.; Camboni, M.; Carlander, D.; García, R.P.; Kriščiūnaitė, G.; Baun, A.; Kaegi, R. *Study on the Product Lifecycles, Waste Recycling and the Circular Economy for Nanomaterials*; European Chemicals Agency: Helsinki, Finland, 2021.
164. Bojanovský, J.; Máša, V.; Hudák, I.; Skryja, P.; Hopjan, J. Rotary Kiln, a Unit on the Border of the Process and Energy Industry—Current State and Perspectives. *Sustainability* **2022**, *14*, 13903. [[CrossRef](#)]
165. Van Caneghem, J.; Brems, A.; Lievens, P.; Block, C.; Billen, P.; Vermeulen, I.; Dewil, R.; Baeyens, J.; Vandecasteele, C. Fluidized bed waste incinerators: Design, operational and environmental issues. *Prog. Energy Combust. Sci.* **2012**, *38*, 551–582. [[CrossRef](#)]
166. Heidari, M.; Garnaik, P.P.; Dutta, A. The valorization of plastic via thermal means: Industrial scale combustion methods. *Plast. Energy* **2019**, 295–312.
167. Jiang, X.; Li, Y.; Yan, J. Hazardous waste incineration in a rotary kiln: A review. *Waste Dispos. Sustain. Energy* **2019**, *1*, 3–37. [[CrossRef](#)]
168. Franke, H.-J.; Shimizu, T.; Nishio, A.; Nishikawa, H.; Inagaki, M.; Ibashi, W. Improvement of carbon burn-up during fluidized bed incineration of plastic by using porous bed materials. *Energy Fuels* **1999**, *13*, 773–777. [[CrossRef](#)]
169. Pickering, S.; Kelly, R.; Kennerley, J.; Rudd, C.; Fenwick, N. A fluidised-bed process for the recovery of glass fibres from scrap thermoset composites. *Compos. Sci. Technol.* **2000**, *60*, 509–523. [[CrossRef](#)]
170. Saxena, S.C.; Jotshi, C.K. Fluidized-bed incineration of waste materials. *Prog. Energy Combust. Sci.* **1994**, *20*, 281–324. [[CrossRef](#)]
171. Marsh, G. Reclaiming value from post-use carbon composite. *Reinf. Plast.* **2008**, *52*, 36–39. [[CrossRef](#)]
172. Pickering, S.J. Recycling technologies for thermoset composite materials—Current status. *Compos. Part A Appl. Sci. Manuf.* **2006**, *37*, 1206–1215. [[CrossRef](#)]
173. Kennerley, J.; Kelly, R.; Fenwick, N.; Pickering, S.; Rudd, C. The characterisation and reuse of glass fibres recycled from scrap composites by the action of a fluidised bed process. *Compos. Part A Appl. Sci. Manuf.* **1998**, *29*, 839–845. [[CrossRef](#)]
174. Bartoli, M.; Giorcelli, M.; Tagliaferro, A. Morphology and Mechanical Properties of Epoxy/Synthetic Fiber Composites. In *Handbook of Epoxy/Fiber Composites*; Springer Nature: Singapore, 2022; pp. 229–251.
175. Grosso, M.; Motta, A.; Rigamonti, L.J.W.M. Efficiency of energy recovery from waste incineration, in the light of the new Waste Framework Directive. *Waste Manag.* **2010**, *30*, 1238–1243. [[CrossRef](#)]
176. Derosa, R.; Telfeyan, E.; Mayes, J. Current state of recycling sheet molding compounds and related materials. *J. Thermoplast. Compos. Mater.* **2005**, *18*, 219–240. [[CrossRef](#)]
177. Besco, S.; Brisotto, M.; Gianoncelli, A.; Depero, L.E.; Bontempi, E.; Lorenzetti, A.; Modesti, M. Processing and properties of polypropylene-based composites containing inertized fly ash from municipal solid waste incineration. *J. Appl. Polym. Sci.* **2013**, *130*, 4157–4164. [[CrossRef](#)]
178. Asmatulu, E.; Twomey, J.; Overcash, M. Recycling of fiber-reinforced composites and direct structural composite recycling concept. *J. Compos. Mater.* **2014**, *48*, 593–608. [[CrossRef](#)]
179. Shahabuddin, M.; Alam, M.T.; Krishna, B.B.; Bhaskar, T.; Perkins, G. A review on the production of renewable aviation fuels from the gasification of biomass and residual wastes. *Bioresour. Technol.* **2020**, *312*, 123596. [[CrossRef](#)]

180. Nistratov, A.V.; Klimenko, N.N.; Pustynnikov, I.V.; Vu, L.K. Thermal regeneration and reuse of carbon and glass fibers from waste composites. *Emerg Sci J* **2022**, *6*, 967–984. [CrossRef]
181. Yang, Y.; Boom, R.; Irion, B.; Van Heerden, D.-J.; Kuiper, P.; De Wit, H. Recycling of composite materials. *Chem. Eng. Process. Process Intensif.* **2012**, *51*, 53–68. [CrossRef]
182. Ateeq, M. A review on recycling technique and remanufacturing of the carbon fiber from the carbon fiber polymer composite: Processing, challenges, and state-of-arts. *Compos. Part C Open Access* **2023**, *12*, 100412. [CrossRef]
183. Fetting, C. The European green deal. *ESDN Rep.* **2020**, *2*, 53.
184. Maqsood, T.; Dai, J.; Zhang, Y.; Guang, M.; Li, B. Pyrolysis of plastic species: A review of resources and products. *J. Anal. Appl. Pyrolysis* **2021**, *159*, 105295. [CrossRef]
185. Sharuddin, S.D.A.; Abnisa, F.; Daud, W.M.A.W.; Aroua, M.K. A review on pyrolysis of plastic wastes. *Energy Convers. Manag.* **2016**, *115*, 308–326. [CrossRef]
186. Qureshi, M.S.; Oasmaa, A.; Pihkola, H.; Deviatkin, I.; Tenhunen, A.; Mannila, J.; Minkkinen, H.; Pohjakallio, M.; Laine-Ylijoki, J. Pyrolysis of plastic waste: Opportunities and challenges. *J. Anal. Appl. Pyrolysis* **2020**, *152*, 104804. [CrossRef]
187. Wróblewska-Krepsztul, J.; Rydzkowski, T. Pyrolysis and incineration in polymer waste management system. *J. Mech. Energy Eng.* **2019**, *3*, 337–342. [CrossRef]
188. Dai, L.; Zhou, N.; Lv, Y.; Cheng, Y.; Wang, Y.; Liu, Y.; Cobb, K.; Chen, P.; Lei, H.; Ruan, R. Pyrolysis technology for plastic waste recycling: A state-of-the-art review. *Prog. Energy Combust. Sci.* **2022**, *93*, 101021. [CrossRef]
189. Eze, W.U.; Umunakwe, R.; Obasi, H.C.; Ugbaja, M.I.; Uche, C.C.; Madufor, I.C. Plastics waste management: A review of pyrolysis technology. *Clean Technol. Recycl.* **2021**, *1*, 50–69. [CrossRef]
190. Torsello, D.; Bartoli, M.; Giorcelli, M.; Rovere, M.; Arrigo, R.; Malucelli, G.; Tagliaferro, A.; Ghigo, G. High frequency electromagnetic shielding by biochar-based composites. *Nanomaterials* **2021**, *11*, 2383. [CrossRef]
191. Torsello, D.; Ghigo, G.; Giorcelli, M.; Bartoli, M.; Rovere, M.; Tagliaferro, A. Tuning the microwave electromagnetic properties of biochar-based composites by annealing. *Carbon Trends* **2021**, *4*, 100062. [CrossRef]
192. Animalì, L.; Corrado, S.; Mitillo, N.; Tuccimei, P.; Bartoli, M.; Mattei, M.; Giorcelli, M. Characterization and evaluation of commercial biochar for surface water purification. *Sustain. Horiz.* **2025**, *15*, 100145. [CrossRef]
193. Bartoli, M.; Giorcelli, M.; Jagdale, P.; Rovere, M.; Tagliaferro, A. A review of non-soil biochar applications. *Materials* **2020**, *13*, 261. [CrossRef] [PubMed]
194. Bartoli, M.; Giorcelli, M.; Tagliaferro, A. A Comprehensive Overview on Biochar-Based Materials for Catalytic Applications. *Catalysts* **2023**, *13*, 1336. [CrossRef]
195. Bartoli, M.; Troiano, M.; Giudicianni, P.; Amato, D.; Giorcelli, M.; Solimene, R.; Tagliaferro, A. Effect of heating rate and feedstock nature on electrical conductivity of biochar and biochar-based composites. *Appl. Energy Combust. Sci.* **2022**, *12*, 100089. [CrossRef]
196. Bartoli, M.; Rosi, L.; Frediani, F.; Undri, A.; Frediani, P. Depolymerization of polystyrene at reduced pressure through a microwave assisted pyrolysis. *J. Anal. Appl. Pyrolysis* **2015**, *113*, 281–287. [CrossRef]
197. Thamizh Selvan, R.; Vishakh Raja, P.; Mangal, P.; Mohan, N.; Bhowmik, S. Recycling technology of epoxy glass fiber and epoxy carbon fiber composites used in aerospace vehicles. *J. Compos. Mater.* **2021**, *55*, 3281–3292. [CrossRef]
198. Torres-Herrador, F.; Eschenbacher, A.; Coheur, J.; Blondeau, J.; Magin, T.E.; Van Geem, K.M. Decomposition of carbon/phenolic composites for aerospace heatshields: Detailed speciation of phenolic resin pyrolysis products. *Aerosp. Sci. Technol.* **2021**, *119*, 107079. [CrossRef]
199. Fernández, A.; Lopes, C.S.; González, C.; López, F.A. *Characterization of Carbon Fibers Recovered by Pyrolysis of Cured Prepregs and Their Reuse in New Composites*; InTech Rijeka: Rijeka, Croatia, 2018; Volume 7.
200. Ma, C.; Sánchez-Rodríguez, D.; Kamo, T. A comprehensive study on the oxidative pyrolysis of epoxy resin from fiber/epoxy composites: Product characteristics and kinetics. *J. Hazard. Mater.* **2021**, *412*, 125329. [CrossRef]
201. Abdou, T.R.; Junior, A.B.; Espinosa, D.C.R.; Tenório, J. Recycling of polymeric composites from industrial waste by pyrolysis: Deep evaluation for carbon fibers reuse. *Waste Manag.* **2021**, *120*, 1–9. [CrossRef]
202. Guo, L.; Xu, L.; Ren, Y.; Shen, Z.; Fu, R.; Xiao, H.; Liu, J. Research on a two-step pyrolysis-oxidation process of carbon fiber-reinforced epoxy resin-based composites and analysis of product properties. *J. Environ. Chem. Eng.* **2022**, *10*, 107510. [CrossRef]
203. Li, H.; Englund, K. Recycling of carbon fiber-reinforced thermoplastic composite wastes from the aerospace industry. *J. Compos. Mater.* **2017**, *51*, 1265–1273. [CrossRef]
204. Aishwarya, K.; Sindhu, N. Microwave assisted pyrolysis of plastic waste. *Procedia Technol.* **2016**, *25*, 990–997. [CrossRef]
205. Miandad, R.; Barakat, M.; Aburiazaiza, A.S.; Rehan, M.; Nizami, A. Catalytic pyrolysis of plastic waste: A review. *Process. Saf. Environ. Prot.* **2016**, *102*, 822–838. [CrossRef]
206. Bartoli, M.; Frediani, M.; Briens, C.; Berruti, F.; Rosi, L. An Overview of Temperature Issues in Microwave-Assisted Pyrolysis. *Processes* **2019**, *7*, 658. [CrossRef]
207. Tyrebirth. Available online: <https://www.tyrebirth.com/it/> (accessed on 2 March 2021).

208. Giorcelli, M.; Das, O.; Sas, G.; Försth, M.; Bartoli, M. A review of bio-oil production through microwave-assisted pyrolysis. *Processes* **2021**, *9*, 561. [CrossRef]
209. Bartoli, M.; Rosi, L.; Frediani, P.; Frediani, M. Bio-oils from microwave assisted pyrolysis of kraft lignin operating at reduced residual pressure. *Fuel* **2020**, *278*, 118175. [CrossRef]
210. Bartoli, M.; Rosi, L.; Giovannelli, A.; Frediani, P.; Frediani, M. Bio-oil from residues of short rotation coppice of poplar using a microwave assisted pyrolysis. *J. Anal. Appl. Pyrolysis* **2016**, *119*, 224–232. [CrossRef]
211. Bartoli, M.; Rosi, L.; Giovannelli, A.; Frediani, P.; Frediani, M. Pyrolysis of  $\alpha$ -cellulose using a multimode microwave oven. *J. Anal. Appl. Pyrolysis* **2016**, *120*, 284–296. [CrossRef]
212. Bartoli, M.; Rosi, L.; Giovannelli, A.; Frediani, P.; Frediani, M. Production of bio-oils and bio-char from *Arundo donax* through microwave assisted pyrolysis in a multimode batch reactor. *J. Anal. Appl. Pyrolysis* **2016**, *122*, 479–489. [CrossRef]
213. Bartoli, M.; Rosi, L.; Giovannelli, A.; Frediani, P.; Frediani, M. Characterization of bio-oil and bio-char produced by low-temperature microwave-assisted pyrolysis of olive pruning residue using various absorbers. *Waste Manag. Res.* **2020**, *38*, 213–225. [CrossRef]
214. Bartoli, M.; Rosi, L.; Giovannelli, A.; Frediani, P.; Passaponti, M.; Frediani, M. Microwave assisted pyrolysis of crop residues from *Vitis vinifera*. *J. Anal. Appl. Pyrolysis* **2018**, *130*, 249–255. [CrossRef]
215. Lester, E.; Kingman, S.; Wong, K.H.; Rudd, C.; Pickering, S.; Hilal, N. Microwave heating as a means for carbon fibre recovery from polymer composites: A technical feasibility study. *Mater. Res. Bull.* **2004**, *39*, 1549–1556. [CrossRef]
216. Rosi, L.; Bartoli, M.; Undri, A.; Frediani, M.; Frediani, P. Synthesis of dianols or BPA through catalytic hydrolysis/glycolysis of waste polycarbonates using a microwave heating. *J. Mol. Catal. A Chem.* **2015**, *408*, 278–286. [CrossRef]
217. Nikje, M.M.A.; Askarzadeh, M. Controllable microwave-assisted polycarbonate waste chemical recycling. *Prog. Rubber Plast. Recycl. Technol.* **2013**, *29*, 169–176. [CrossRef]
218. Das, S.K.; Kaufman, J.G. Recycling aluminum aerospace alloys. *Adv. Mater. Process.* **2008**, *166*, 34.
219. Shaffer, C. Aircraft Keep Working Even After Retirement. Available online: <https://www.thermofisher.com/blog/metals/aircraft-keep-working-even-after-retirement/> (accessed on 30 October 2024).
220. Padamata, S.K.; Yasinskiy, A.; Polyakov, P. A review of secondary aluminum production and its byproducts. *JOM* **2021**, *73*, 2603–2614. [CrossRef]
221. Capuzzi, S.; Timelli, G. Preparation and melting of scrap in aluminum recycling: A review. *Metals* **2018**, *8*, 249. [CrossRef]
222. Verdier, J.F.; Butruille, J.R.; Leroy, M.; Valax, D. Process for Recycling Aluminum Alloy Scrap Coming from the Aeronautical Industry. U.S. Patent 8,202,347 B2, 19 June 2012.
223. Gesing, A.; Wolanski, R. Recycling light metals from end-of-life vehicle. *JOM* **2001**, *53*, 21–23. [CrossRef]
224. Das, S.K.; Green, J.; Kaufman, J. Aluminum recycling: Economic and environmental benefits. *Light Met. Age* **2010**, *68*, 42.
225. Ogilvie, S. *A Review of: The Environmental Impact of Recycling*; Report LR; Warren Spring Laboratory: Stevenage, UK, 1993.
226. Raabe, D.; Ponge, D.; Uggowitzer, P.J.; Roscher, M.; Paolantonio, M.; Liu, C.; Antrekowitsch, H.; Kozeschnik, E.; Seidmann, D.; Gault, B. Making sustainable aluminum by recycling scrap: The science of “dirty” alloys. *Prog. Mater. Sci.* **2022**, *128*, 100947. [CrossRef]
227. Gaustad, G.; Olivetti, E.; Kirchain, R. Improving aluminum recycling: A survey of sorting and impurity removal technologies. *Resour. Conserv. Recycl.* **2012**, *58*, 79–87. [CrossRef]
228. Green, J.A. *Aluminum Recycling and Processing for Energy Conservation and Sustainability*; ASM International: Novelty, OH, USA, 2007.
229. Shi, L.; Peng, Z.; Ning, P.; Sun, X.; Li, K.; Zhang, H.; Qu, T. Clean and Efficient Recovery of Lithium from Al-Li Alloys via Vacuum Fractional Condensation. *Separations* **2023**, *10*, 374. [CrossRef]
230. Eckelman, M.J.; Ciacci, L.; Kavlak, G.; Nuss, P.; Reck, B.K.; Graedel, T. Life cycle carbon benefits of aerospace alloy recycling. *J. Clean. Prod.* **2014**, *80*, 38–45. [CrossRef]
231. Srivastava, R.R.; Kim, M.-s.; Lee, J.-c.; Jha, M.K.; Kim, B.-S. Resource recycling of superalloys and hydrometallurgical challenges. *J. Mater. Sci.* **2014**, *49*, 4671–4686. [CrossRef]
232. Kollová, A.; Pauerová, K. Superalloys-characterization, usage and recycling. *Manuf. Technol.* **2022**, *22*, 550–557. [CrossRef]
233. VV, S.P.; Rao, A.S.; Prakash, U.; Rao, V.R.; Rao, P.K.; Gupta, K.M. Recycling of superalloy scrap through electro slag remelting. *ISIJ Int.* **1996**, *36*, 1459–1464. [CrossRef]
234. Cui, F.; Wang, G.; Yu, D.; Gan, X.; Tian, Q.; Guo, X. Towards “zero waste” extraction of nickel from scrap nickel-based superalloy using magnesium. *J. Clean. Prod.* **2020**, *262*, 121275. [CrossRef]
235. Takeda, O.; Okabe, T.H. Current status of titanium recycling and related technologies. *JOM* **2019**, *71*, 1981–1990. [CrossRef]
236. Rath, M.G.; Niles, A.J. An overview of forging processes with their defects. *Int. J. Sci. Res. Publ.* **2014**, *4*, 1–7.
237. Suomalainen, E.; Celikel, A.; Vénuat, P. *Aircraft Metals Recycling: Process, Challenges and Opportunities*; ENVISA and Birtin Recycling Group: Paris, France, 2017.

238. Zhao, Q.; Sun, Q.; Xin, S.; Chen, Y.; Wu, C.; Wang, H.; Xu, J.; Wan, M.; Zeng, W.; Zhao, Y.J.M.S.; et al. High-strength titanium alloys for aerospace engineering applications: A review on melting-forging process. *Mater. Sci. Eng. A* **2022**, *845*, 143260. [[CrossRef](#)]
239. Ahmad, A.; Lajis, M.; Yusuf, N.; Wagiman, A. Hot press forging as the direct recycling technique of aluminium—A review. *ARPJ. Eng. Appl. Sci.* **2016**, *11*, 2258–2265.
240. *ISO 5157:2023*; Textiles—Environmental Aspects. International Organization for Standardization: Geneva, Switzerland, 2023.
241. Duhoux, T.; Maes, E.; Hirschnitz-Garbers, M.; Peeters, K.; Asscherickx, L.; Christis, M.; Stubbe, B.; Colignon, P.; Hinzmann, M.; Sachdeva, A. *Study on the Technical, Regulatory, Economic and Environmental Effectiveness of Textile Fibres Recycling*; European Commission: Brussels, Belgium, 2021; Volume 24.
242. Butenegro, J.A.; Bahrami, M.; Abenojar, J.; Martínez, M.Á. Recent progress in carbon fiber reinforced polymers recycling: A review of recycling methods and reuse of carbon fibers. *Materials* **2021**, *14*, 6401. [[CrossRef](#)] [[PubMed](#)]
243. Huygens, D.; Foschi, J.; Caro, D.; Caldeira, C.; Faraca, G.; Foster, G.; Solis, M.; Marschinski, R.; Napolano, L.; Fruergaard Astrup, T. *Techno-Scientific Assessment of the Management Options for Used and Waste Textiles in the European Union*; Joint Research Centre (Seville site): Sevilla, Spain, 2023.
244. Ribeiro, M.; Meira-Castro, A.C.; Silva, F.; Santos, J.; Meixedo, J.P.; Fiúza, A.; Dinis, M.; Alvim, M.R. Re-use assessment of thermoset composite wastes as aggregate and filler replacement for concrete-polymer composite materials: A case study regarding GFRP pultrusion wastes. *Resour. Conserv. Recycl.* **2015**, *104*, 417–426. [[CrossRef](#)]
245. Palmer, J.A.T. *Mechanical Recycling of Automotive Composites for Use as Reinforcement in Thermoset Composites*; University of Exeter (United Kingdom): Exeter, UK, 2009.
246. Job, S. Recycling glass fibre reinforced composites—history and progress. *Reinf. Plast.* **2013**, *57*, 19–23. [[CrossRef](#)]
247. Ward, C.; Potter, K. Understanding composites design and manufacturing for minimisation of scrap generation: The first steps to efficient material use. In Proceedings of the SECIO 08, SAMPE Europe International Conference, Paris, France, 6–7 October 2008; pp. 543–548.
248. Kouparitsas, C.; Kartalis, C.; Varelidis, P.; Tsenoglou, C.; Papaspyrides, C. Recycling of the fibrous fraction of reinforced thermoset composites. *Polym. Compos.* **2002**, *23*, 682–689. [[CrossRef](#)]
249. Bernasconi, A.; Rossin, D.; Armani, C. Analysis of the effect of mechanical recycling upon tensile strength of a short glass fibre reinforced polyamide 6,6. *Eng. Fract. Mech.* **2007**, *74*, 627–641. [[CrossRef](#)]
250. Ogi, K.; Nishikawa, T.; Okano, Y.; Taketa, I. Mechanical properties of ABS resin reinforced with recycled CFRP. *Adv. Compos. Mater.* **2007**, *16*, 181–194. [[CrossRef](#)]
251. Takahashi, J.; Matsutsuka, N.; Okazumi, T.; Uzawa, K.; Ohsawa, I.; Yamaguchi, K.; Kitano, A. Mechanical properties of recycled CFRP by injection molding method. In Proceedings of the ICCM-16, Japan Society for Composite Materials, Kyoto, Japan, 8 July 2007.
252. Roux, M.; Eguémann, N.; Dransfeld, C.; Thiébaud, F.; Perreux, D. Thermoplastic carbon fibre-reinforced polymer recycling with electro-dynamical fragmentation: From cradle to cradle. *J. Thermoplast. Compos. Mater.* **2017**, *30*, 381–403. [[CrossRef](#)]
253. Aly, N.M. A review on utilization of textile composites in transportation towards sustainability. *IOP Conf. Ser. Mater. Sci. Eng.* **2017**, *254*, 042002. [[CrossRef](#)]
254. Juanga-Labayen, J.P.; Labayen, I.V.; Yuan, Q. A review on textile recycling practices and challenges. *Textiles* **2022**, *2*, 174–188. [[CrossRef](#)]
255. Baloyi, R.B.; Gbadeyan, O.J.; Sithole, B.; Chuniilall, V. Recent advances in recycling technologies for waste textile fabrics: A review. *Text. Res. J.* **2024**, *94*, 508–529. [[CrossRef](#)]
256. Sandberg, E.; Pal, R. Exploring supply chain capabilities in textile-to-textile recycling—A European interview study. *Clean. Logist. Supply Chain* **2024**, *11*, 100152. [[CrossRef](#)]
257. Krauklis, A.E.; Karl, C.W.; Gagani, A.I.; Jørgensen, J.K. Composite material recycling technology—State-of-the-art and sustainable development for the 2020s. *J. Compos. Sci.* **2021**, *5*, 28. [[CrossRef](#)]
258. Oliveux, G.; Dandy, L.O.; Leeke, G.A. Current status of recycling of fibre reinforced polymers: Review of technologies, reuse and resulting properties. *Prog. Mater. Sci.* **2015**, *72*, 61–99. [[CrossRef](#)]
259. Jiang, J.; Deng, G.; Chen, X.; Gao, X.; Guo, Q.; Xu, C.; Zhou, L. On the successful chemical recycling of carbon fiber/epoxy resin composites under the mild condition. *Compos. Sci. Technol.* **2017**, *151*, 243–251. [[CrossRef](#)]
260. Borjan, D.; Knez, Ž.; Knez, M. Recycling of carbon fiber-reinforced composites—Difficulties and future perspectives. *Materials* **2021**, *14*, 4191. [[CrossRef](#)]
261. Pimenta, S.; Pinho, S.T. Recycling carbon fibre reinforced polymers for structural applications: Technology review and market outlook. *Waste Manag.* **2011**, *31*, 378–392. [[CrossRef](#)]
262. Jody, B.J.; Pomykala, J.A.; Daniels, E.J.; Greminger, J.L. A process to recover carbon fibers from polymer-matrix composites in end-of-life vehicles. *JOM* **2004**, *56*, 43–47. [[CrossRef](#)]
263. Rybicka, J.; Tiwari, A.; Leeke, G.A. Technology readiness level assessment of composites recycling technologies. *J. Clean. Prod.* **2016**, *112*, 1001–1012. [[CrossRef](#)]

264. Nakagawa, M.; Shibata, K.; Kuriya, H. Characterization of CFRP using recovered carbon fibers from waste CFRP. In Proceedings of the Second International Symposium on Fiber Recycling, the Fiber Recycling, Chengdu, China, 11–14 October 2009.
265. Xu, P.; Li, J.; Ding, J. Chemical recycling of carbon fibre/epoxy composites in a mixed solution of peroxide hydrogen and N, N-dimethylformamide. *Compos. Sci. Technol.* **2013**, *82*, 54–59. [CrossRef]
266. Kao, C.; Ghita, O.; Hallam, K.; Heard, P.; Evans, K. Mechanical studies of single glass fibres recycled from hydrolysis process using sub-critical water. *Compos. Part A Appl. Sci. Manuf.* **2012**, *43*, 398–406. [CrossRef]
267. Liu, Y.; Liu, J.; Jiang, Z.; Tang, T. Chemical recycling of carbon fibre reinforced epoxy resin composites in subcritical water: Synergistic effect of phenol and KOH on the decomposition efficiency. *Polym. Degrad. Stab.* **2012**, *97*, 214–220. [CrossRef]
268. Oliveux, G.; Bailleul, J.-L.; La Salle, E.L.G.; Lefèvre, N.; Biotteau, G. Recycling of glass fibre reinforced composites using subcritical hydrolysis: Reaction mechanisms and kinetics, influence of the chemical structure of the resin. *Polym. Degrad. Stab.* **2013**, *98*, 785–800. [CrossRef]
269. Okajima, I.; Watanabe, K.; Haramiishi, S.; Nakamura, M.; Shimamura, Y.; Sako, T. Recycling of carbon fiber reinforced plastic containing amine-cured epoxy resin using supercritical and subcritical fluids. *J. Supercrit. Fluids* **2017**, *119*, 44–51. [CrossRef]
270. Sokoli, H.U.; Beauson, J.; Simonsen, M.E.; Fraisse, A.; Brøndsted, P.; Søgaard, E.G. Optimized process for recovery of glass-and carbon fibers with retained mechanical properties by means of near-and supercritical fluids. *J. Supercrit. Fluids* **2017**, *124*, 80–89. [CrossRef]
271. Das, M.; Chacko, R.; Varughese, S. An efficient method of recycling of CFRP waste using peracetic acid. *ACS Sustain. Chem. Eng.* **2018**, *6*, 1564–1571. [CrossRef]
272. Khalil, Y. Sustainability assessment of solvolysis using supercritical fluids for carbon fiber reinforced polymers waste management. *Sustain. Prod. Consum.* **2019**, *17*, 74–84. [CrossRef]
273. Abdelghafar Elsayed, T.R.A.B. *Best Practices and Standards in Aircraft End-of-Life and Recycling*; International Civil Aviation Organisation: Montreal, QC, Canada, 2019. Available online: [https://www.icao.int/environmental-protection/Documents/EnvironmentalReports/2019/ENVReport2019\\_pg279-284.pdf](https://www.icao.int/environmental-protection/Documents/EnvironmentalReports/2019/ENVReport2019_pg279-284.pdf) (accessed on 27 September 2024).
274. Amy Bann, T.B.T. Paul McElroy. In *Airplane and Carbon Fiber Recycling*; Boeing: Arlington, VA, USA, 2020.
275. 40 CFR Part 268-Land Disposal Restrictions. 1986. Available online: <https://www.ecfr.gov/current/title-40/chapter-I/subchapter-I/part-268> (accessed on 21 August 2025).
276. Giulvezan, G.; Carberry, B. *Composite Recycling and Disposal—An Environmental R&D Issue*; Boeing: Arlington, VA, USA, 2003.
277. Council of the European Union. Council Directive 1999/31/EC of 26 April 1999 on the Landfill of Waste. 1999. Available online: <https://eur-lex.europa.eu/eli/dir/1999/31/oj/eng> (accessed on 21 August 2025).
278. European Parliament and Council of the European Union. Directive (EU) 2018/850 of the European Parliament and of the Council of 30 May 2018 Amending Directive 1999/31/EC on the Landfill of Waste (Text with EEA Relevance). 2018. Available online: <https://eur-lex.europa.eu/eli/dir/2018/850/oj/eng> (accessed on 21 August 2025).
279. Nanda, S.; Berruti, F. Municipal solid waste management and landfilling technologies: A review. *Environ. Chem. Lett.* **2021**, *19*, 1433–1456. [CrossRef]
280. Iravanian, A.; Ravari, S.O. Types of contamination in landfills and effects on the environment: A review study. *IOP Conf. Ser. Earth Environ. Sci.* **2020**, *614*, 012083. [CrossRef]
281. Lou, X.; Nair, J. The impact of landfilling and composting on greenhouse gas emissions—A review. *Bioresour. Technol.* **2009**, *100*, 3792–3798. [CrossRef]
282. Liberacki, A.; Trincone, B.; Duca, G.; Aldieri, L.; Vinci, C.P.; Carlucci, F. The Environmental Life Cycle Costs (ELCC) of Urban Air Mobility (UAM) as an input for sustainable urban mobility. *J. Clean. Prod.* **2023**, *389*, 136009. [CrossRef]

**Disclaimer/Publisher’s Note:** The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.